

Article

Application Potential of *Trichoderma* in the Degradation of Phenolic Acid-Modified Chitosan

Maria Swiontek Brzezinska ^{1,*}, Beata Kaczmarek-Szczepańska ^{2,*}, Grażyna B. Dąbrowska ³,
Marta Michalska-Sionkowska ¹, Katarzyna Dembińska ¹, Agnieszka Richert ³, Marcela Pejchalová ⁴,
Sweta Binod Kumar ¹ and Agnieszka Kalwasińska ¹

- ¹ Department of Environmental Microbiology and Biotechnology, Faculty of Biological and Veterinary Sciences, Nicolaus Copernicus University in Torun, Lwowska 1, 87-100 Torun, Poland; mms@umk.pl (M.M.-S.); katarzynadembinska6@gmail.com (K.D.); sweta14789@gmail.com (S.B.K.); kala@umk.pl (A.K.)
- ² Department of Biomaterials and Cosmetics Chemistry, Faculty of Chemistry, Nicolaus Copernicus University in Torun, Gagarina 7, 87-100 Torun, Poland
- ³ Department of Genetics, Faculty of Biological and Veterinary Sciences, Nicolaus Copernicus University in Torun, Lwowska 1, 87-100 Torun, Poland; browsk@umk.pl (G.B.D.); a.richert@umk.pl (A.R.)
- ⁴ Department of Biological and Biochemical Sciences, Faculty of Chemical Technology, University of Pardubice, Sudentska 573, 53210 Pardubice, Czech Republic; marcela.pejchalova@upce.cz
- * Correspondence: swiontek@umk.pl (M.S.B.); beata.kaczmarek@umk.pl (B.K.-S.)

Abstract: The aim of the study was to determine the potential use of fungi of the genus *Trichoderma* for the degradation of phenolic acid-modified chitosan in compost. At the same time, the enzymatic activity in the compost was checked after the application of a preparation containing a suspension of the fungi *Trichoderma* (spores concentration 10⁵/mL). The *Trichoderma* strains were characterized by high lipase and aminopeptidase activity, chitinase, and β -1,3-glucanases. *T. atroviride* TN1 and *T. citrinoviride* TN3 metabolized the modified chitosan films best. Biodegradation of modified chitosan films by native microorganisms in the compost was significantly less effective than after the application of a formulation composed of *Trichoderma* TN1 and TN3. Bioaugmentation with a *Trichoderma* preparation had a significant effect on the activity of all enzymes in the compost. The highest oxygen consumption in the presence of chitosan with tannic acid film was found after the application of the consortium of these strains (861 mg O₂/kg after 21 days of incubation). Similarly, chitosan with gallic acid and chitosan with ferulic acid were found after the application of the consortium of these strains (849 mg O₂/kg and 725 mg O₂/kg after 21 days of incubation). The use of the *Trichoderma* consortium significantly increased the chitinase activity. The application of *Trichoderma* also offers many possibilities in sustainable agriculture. *Trichoderma* can not only degrade chitosan films, but also protect plants against fungal pathogens by synthesizing chitinases and β -1,3 glucanases with antifungal properties.

Keywords: chitosan; *Trichoderma*; biodegradation



Citation: Swiontek Brzezinska, M.; Kaczmarek-Szczepańska, B.; Dąbrowska, G.B.; Michalska-Sionkowska, M.; Dembińska, K.; Richert, A.; Pejchalová, M.; Kumar, S.B.; Kalwasińska, A. Application Potential of *Trichoderma* in the Degradation of Phenolic Acid-Modified Chitosan. *Foods* **2023**, *12*, 3669. <https://doi.org/10.3390/foods12193669>

Academic Editor: Sílvia Petronilho

Received: 5 September 2023

Revised: 30 September 2023

Accepted: 3 October 2023

Published: 5 October 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Plastics are used in many areas such as packaging, construction materials, and hygiene products due to their chemical resistance. Unfortunately, they are not susceptible to microbial degradation, which makes them a serious environmental pollutant. For this reason, interest in biodegradable polymers has increased [1]. Chitosan obtained in the deacetylation process of chitin [2] has antimicrobial and fungicidal properties and can therefore be applied as a natural biocide in medicine, food production, and agriculture. The biocidal properties of chitosan result from its ability to degrade the cell wall and membrane, bind metal ions, and combine with DNA [3].

Chitosan-based films in particular can be used in the food packaging industry. They are modified just as often with various biocidal substances, e.g., tannic acid [4]. Phenolic

substances are synthesized by plants as a variety of secondary metabolites (phytochemicals) known to be involved in defense mechanisms and, over the past few years, some of these molecules have been recognized to have health benefits, including antimicrobial properties [5]. They are capable of forming strong hydrogen bonds with polymers and thus, they are good cross-linkers for proteins and polysaccharides [6]. The presence of phenolic acids in chitosan film increases its stability for food packaging applications. Despite their use, the film polymers should be biodegradable [7,8]. Polymer degradation is a complex process involving physical, chemical, and biological factors [9]. Undoubtedly, microorganisms producing hydrolytic enzymes contribute to their biodegradation [8,10–12]. Fungi, for example, *Pseudozyma japonica* Y7-09 and *Trichoderma viride* 99, degraded polycaprolactone (PCL) [13,14], *Clitocybe* sp. and *Laccaria laccata* degraded polylactide (PLA) and polyethylene terephthalate (PET) [9], and *Aspergillus* degraded polyethylene (PE) [15]. Vivi et al. [16] reported that polycaprolactone (PCL) and polyvinyl chloride (PVC) were degraded by *Chaetomium globosum* ATCC 16021. A sample of each polymer was placed in a Petri dish with complete agar and a second one on the incomplete medium. A spare sample was kept as a control inside an envelope in the dark. Individual samples of polymers (PCL and PVC) were immersed in 25 mL mix suspension with a concentration of 10^6 spores/mL for 15 s. The samples were analyzed by means of morphological and color changes, mass loss, optical microscopy (OM), and scanning electron microscopy (SEM) after 28 days of culturing. After the incubation period, visual observations of the PCL films showed many micropores and cracks, pigmentation, surface erosion and hyphal adhesion on the sample surfaces, and a mass loss of up to 75%. Also, *Cladosporium* sp., *Mucor* sp., *Penicillium caseicola*, *Penicillium citrinium*, and *Rhizopus* sp. degraded chitosan-gellan and polylysine-gellan fibers [17]. Degradation of phenolic acid-modified chitosan film can be a problem, as native microorganisms are unable to degrade the polymers. For this reason, it is so important to introduce additional microorganisms to aid in the degradation of the chitosan film. In recent years, microbial formulations have been increasingly developed to accelerate polymers' biodegradation. In the case of chitosan films, it is worthwhile to select chitinolytic microorganisms with multifarious enzymes which are capable of degrading chitin and its derivatives. Therefore, it is suitable to use the fungi of the genus *Trichoderma*, which are already used in agriculture and known for their chitinolytic properties [18]. *Trichoderma* spp. belong to the Ascomycota, which are the most numerous species of fungi in almost all temperate and tropical soils. They are characterized by rapid growth, abundant sporulation, and the production of several hydrolytic enzymes [11,19].

Our previous reports in the literature indicated the possibility of the practical use of fungi like *Trichoderma* in accelerating the biodegradation of polymeric materials [9,11]. The research conducted by Znajewska et al. [14] has shown that *T. viride* accelerated the degradation of polycaprolactone in soil. Moreover, *T. viride* also showed growth on polymer materials including PE, PCL, PET, PLA, and PHB in in vitro studies [20]. Dąbrowska et al. [11] reported that the *T. viride* strain GZ1 produced hydrophobin proteins in contact with PLA and PET, producing a hydrophobin film that enabled the mycelium to adhere to the surface of the polymer.

Food packaging produced on an industrial scale from materials that are difficult to degrade represents a serious environmental problem. They take many years to decompose. An alternative to current packaging materials could be chitosan films modified with gallic, ferulic, and tannic acids. These materials can be degraded in the environment by native microorganisms. However, not all native microorganisms are able to degrade chitosan films due to their biocidal properties. In order to accelerate biodegradation, a microbiological preparation based on *Trichoderma* has been developed to support their decomposition. Fungi of the *Trichoderma* genus are known especially for the production of antifungal enzymes, which may be an additional feature when applied to the environment.

2. Experiments

2.1. Isolation and Molecular Identification of Fungal Strains

Saprophytic fungi isolated from oak wood were used in this study. The culture of the fungus stored in microbiological solid potato dextrose agar (Difco, Franklin Lakes, NJ, USA) was transferred to the same medium and incubated at 23 °C for 5 days.

Mycelia fragments were homogenized in liquid nitrogen for molecular identification. The genomic DNA from mycelia was extracted using the Plant & Fungi DNA Purification Kit (EURx, Gdansk, Poland) according to the manufacturer's protocol. The quality and quantity of the isolated DNA were checked spectrophotometrically (Nanodrop) and electrophoretically by separation in a 1% agarose gel with ethidium bromide (BioRad, Hamburg, Germany). The isolated DNA served as a template for the PCR reaction which was run under the following conditions: The amplification reaction used a primer with the sequences (5'-CTTGGTCATTTAGAGGAAGTA-3' and 5'-TCCTCCGCTTATTGATATGC-3'), named ITS1_f and ITS2, respectively. The genomic region including internal transcribed regions ITS2 (the region between 5.8S rRNA and 28S rRNA genes) and ITS1 (the region between 18S rRNA and 5.8 rRNA genes) was amplified [21,22]. The amplified PCR products were sequenced using the Sanger method (Genomed, Warsaw, Poland). The obtained sequences were compared with those contained in GenBank NCBI (<https://blast.ncbi.nlm.nih.gov/Blast.cgi> (accessed on 3 October 2022)) and MycoBank Polyphasic Identifications Database (<http://www.mycobank.org> (accessed on 3 October 2022)).

2.2. Chitosan Films Preparation

Phenolic acids (tannic acid, ferulic acid, and gallic acid) used for chitosan film preparation were acquired from Sigma Aldrich (Saint Louis, MO, USA). Phenolic acids were selected based on our previous research, where those compounds were used as chitosan crosslinkers [23]. Raw compounds such as chitosan and all phenolic acids were dissolved in 0.1 M acetic acid as a solvent to obtain a solution at 1% concentration. Phenolic acids were added to the chitosan (1/10 *w/w*%) and mixed on a magnetic stirrer. Mixtures were put on the plastic holder (40 mL per 10 × 10 cm) and left for solvent evaporation in room conditions. This resulted in obtaining thin dry films.

2.3. Enzymatic Characteristics of *Trichoderma*

The study included the determination of hydrolytic enzymes involved in the degradation of organic matter: lipase, aminopeptidase, α , and β -glucosidase. For this purpose, a liquid medium containing (g/L) sucrose 10 and yeast extract 3 was inoculated with fungal spores (10^5 /mL) and incubated for 4 days at 25 °C. The culture was then centrifuged (10 min, $10,000 \times g$) and the supernatant was collected for the determination of the enzyme activity. Subsequently, 2 mL of each supernatant was added to its corresponding substrate (0.2 mL): 4-Methylumbelliferyl butyrate for lipase activity, L-Leucine-7-amido-4-methylcoumarin hydrochloride for aminopeptidase activity, 4-methylumbelliferyl α -D-glucoside, and 4-methylumbelliferyl β -D-glucoside for α and β -glucosidase activity. The final concentration of substrates in the sample was 50 μ mol/mL. Incubation was carried out in a thermoblock at 40 °C for one hour. After incubation, the amount of MUF and MCA released was measured using a Hitachi F—2500 spectrophotometer [24–26].

Excitation/emission wavelengths were centered on 318/445 nm for methylumbelliferyl (MUF) and 345/425 for amido-4-methylcoumarinhydrochloride (MCA). The unit of activity (U) of enzymes was taken as μ mol of MUF/MCA released per hour.

Trichoderma is known for its antifungal activity, therefore the activity of chitinase and β -1,3-glucanase (enzymes having antifungal properties) were also determined. For this purpose, a liquid medium containing (g/L) sucrose 5, yeast extract 1, and colloidal chitin 10 was inoculated with a suspension of fungal spores (10^5 /mL) and incubated at 25 °C for 4 days. After incubation, the culture was centrifuged (10 min, 10 rpm) and the activity of chitinase and β -1,3-glucanase was determined from the supernatant.

For the measurement of chitinase activity, the procedure mentioned in the above paragraph was used, taking methylumbelliferyl-N-acetyl- β -D-glucosaminide as the substrate [25]. The β -1,3-glucanase activity was determined according to Wu et al. [27] by the spectrophotometric method. In brief, 500 μ L of supernatant was mixed with 500 μ L of laminarin 0.5% (*v/w*) in 100 mM sodium acetate buffer (pH 5.5). The reaction was allowed to proceed at 50 °C for 60 min after which it was terminated by heating for 5 min at 100 °C. Thereafter, 2 mL of dinitrosalicylate (DNS) 1% (*v/w*) was added to the reaction and the mixture was boiled for 10 min. After cooling the samples, the sugar concentration was measured with a spectrophotometer at 540 nm. The β -1,3-glucanase activity was expressed as μ mol of glucose per hour.

2.4. Biological Activity of *Trichoderma* in the Presence of Chitosan Films

The biological activity of *Trichoderma* in the presence of the test films was determined using the respirometric method with the OxiTop Control system (WTW, Wroclaw, Poland) according to the modified method of Swiontek Brzezinska et al. [28]. Into the OxiTop measuring dishes, 100 mL of sterile medium containing (g/L) sucrose 5, yeast extract 0.5, and fragments (2 cm \times 2 cm) of the test films (total mass 1 g) were placed and inoculated with 0.1 mL of *Trichoderma* suspension (spores concentration 10^5 /mL). The quivers with CO₂ absorbent (0.4 g NaOH) were placed in the measuring dishes and the measuring heads were screwed on. Incubation was carried out at 26 °C for 14 days. The control sample contained a polymer-free medium inoculated with the same amount of fungal suspension. The biological activity was expressed as mg of O₂/L of culture.

2.5. Fourier Transform Infrared Spectroscopy—Attenuated Total Reflectance (FTIR–ATR)

FTIR–ATR analysis was made for each kind of chitosan film modified by phenolic acids. Films before and after degradation were placed under the diamond ATR crystal and scanned with 4 cm^{−1} resolution in the range of 4000–600 cm^{−1} using Nicolet iS10 spectrometer (Thermo Fisher Scientific Inc., Waltham, MA, USA). Each registered spectrum was obtained by averaging 64 scans. Spectra were recorded and graphs were prepared in the Excel program. Only the CTS/GA and CTS/TA films were selected for testing as the other films were broken and were not suitable for further analysis.

2.6. Mechanical Properties

The mechanical testing was carried out using a testing machine (Shimadzu EZ-Test EZ-SX, Kyoto, Japan). Samples were inserted between two handles and stretched (5 mm/min). Young's Modulus was calculated from the slope of the stress–strain curve in the linear region with the use of the Trapezium X Texture program. The thickness of the samples was measured using a thickness gauge (Sylvac, Yverdon-les-Bains, Switzerland). Each measurement was carried out in ten repetitions [6].

2.7. Scanning Electron Microscopy (SEM)

The morphology of the samples was studied using Scanning Electron Microscope (SEM) (LEO Electron Microscopy, Thornwood, NY, USA). The films were covered with gold before the observation. Scanning electron microscope images were made with a magnification of 1000 \times .

2.8. Biodegradation of Chitosan Films in the Compost after Application of *Trichoderma* Strains

The biodegradation of the chitosan films in the compost after the application of *Trichoderma* strains was determined using the OxiTop system [29] according to the modified procedure described previously. For this purpose, 100 g of compost was placed in the jar of the OxiTop system, mixed with chitosan film fragments (total mass, 1 g, 2 cm \times 2 cm), and inoculated with a 1 mL fungal culture (10^9 CFU/mL). Incubation was carried out at 26 °C for 21 days.

The study was carried out in variants: variant 1—biodegradation of chitosan films by native compost microorganisms; variant 2—biodegradation of chitosan film after application of *T. atroviride* TN1; variant 3—biodegradation of chitosan film after application *T. citrinoviride* TN3; variant 4—biodegradation of chitosan film after application of consortium composed of TN1 and TN3. The control sample contained compost without chitosan films and without supplementation with a fungal culture. The susceptibility to biodegradation of chitosan films was determined based on oxygen consumption and expressed as mgO₂/kg compost. The physicochemical parameters of the compost are shown in Table 1. The pH of the compost was measured by the potentiometric method using a glass electrode in 1 M KCl. The Tiurin procedure was used to assess total organic carbon (TOC), while total nitrogen (TN) was determined by the Kjeldahl method [30]. Soil humidity was measured with a tensionometer T1-q-30. P₂O₅, K₂O, Mg, N-NO₃, and NNH₄ were determined according to the following standards: PN-ISO 10390:1997, PN-R-04022:1996, PN-R-04022:1996/Az1:2002, PN-R-04020:1994/Az1:2004, and PN-R-04028:1997 [31–35]. Biological oxygen consumption (BOD) at 20 °C for 5 days was measured using the OxiTop measurement system [36]. Hydrolase activity was checked using fluorescein diacetate (Sigma-Aldrich) by following Adam & Duncan’s [37] method, with a small modification. Microbial abundance was tested using the Koch plate method. Compost samples, after a series of tenfold dilutions, were transferred to nutrient agar (for bacteria), potato glucose agar (for molds), and actinomycetes agar (for actinomycetes).

Table 1. Physicochemical properties of the compost. Values are expressed as mean ± SD (*n* = 3).

Parameters	Values
pH	7.5
humidity	200 mbar/hPa
TOC (g/kg)	351
TN (g/kg)	27
N-NH ₄ (mg/kg)	2.72
N-NO ₃ (mg/kg)	29.0
P ₂ O ₅ (mg/100 g)	26.2
Mg (mg/100 g)	7.1
K ₂ O (mg/100 g)	27.5
BOD ₅ (mgO ₂ /kg)	80
Hydrolase activity (mg/kg)	14
Heterotrophic bacteria numbers (CFU/g)	45 × 10 ⁵
Actinomycete numbers (CFU/g)	39 × 10 ⁴
Mold numbers (CFU/g)	23 × 10 ³

2.9. Effect of Application of *Trichoderma* on Hydrolytic Enzymes Activity in Compost

Compost samples without chitosan films (control), compost samples containing chitosan films without fungal supplementation, and compost samples with chitosan films after bioaugmentation with a *Trichoderma* preparation were used for the study. To determine the enzymatic activity, 10 g of compost was ten-fold diluted using saline (0.9% NaCl) and shaken for 20 min. The activities of aminopeptidase, lipase, chitinase, α, and β-glucosidase were determined in the diluted samples as described previously (point 2.3).

2.10. Statistical Analysis

The statistical analyses of studies in 3.2, 3.3, and 3.8 point were conducted using Past v. 3.08 [38], with three replicates for each type of data. For all datasets, we calculated summary statistics (mean and standard deviation), performed a normality test (Shapiro–Wilk test), and assessed homogeneity of variance (Levene’s test). One-way ANOVA was employed to examine differences in enzyme activity and BOD between sample groups with different *Trichoderma* strains. Tukey’s pairwise test was applied for post hoc comparisons.

The statistical analysis of the rest of the study was performed using commercial software (SigmaPlot 14.0, Systat Software, San Jose, CA, USA). The Shapiro–Wilk test

was used to assess the normal distribution of the data. All the results were calculated as means \pm standard deviations (SD) and statistically analyzed using one-way analysis of variance (one-way ANOVA). Multiple comparisons versus the control group between means were performed using the Bonferroni *t*-test with the statistical significance set at $p < 0.05$.

3. Results and Discussion

3.1. Molecular Identification of *Trichoderma*

Conventional methods for the identification of *Trichoderma* spp. using cultural and morphological methods might provide erroneous results [39]. A better approach is to use molecular phylogenetic characteristics in combination with conventional methods [40]. One of the molecular methods used to identify fungi is rDNA sequencing [41–43] identification which has made it possible to identify fungi belonging to the species of *Trichoderma atroviride* and *Trichoderma citrinoviride*. The resulting sequences designated TN1–3 have been deposited with GeneBank NCBI under accession numbers (TN1—ID OP586643.1; TN2—ID OP586653.1 and TN3—ID: OP586652.1). A comparison of the TN1 sequence with the sequences available from MycoBase showed homologies to *T. atroviride* and *T. citrinoviride*. The TN1 sequence showed homology to *T. atroviride* (NBRC 101776) with 99.82% sequence similarity, TN2 was 99.83% homologous to *T. atroviride* (FMR12650), and TN3 sequence showed 100% similarity to *T. citrinoviride* (DAOM 172792). Identification of fungi is often problematic and it is not always possible to identify them by species [43]. There are various molecular characterization techniques to confirm *Trichoderma* isolates, such as amplification and sequence analysis of the internal transcribed spacer gene ITS 1 and 2 and the translation elongation factor 1-alpha (*tef1*) encoding gene and BLAST interface in TrichoKEY and TrichoBLAST (<https://trichokey.com/index.php/trichoblast> (accessed on 3 October 2022) [39]. Dendrogram prepared using nucleotide sequences of the ITS region of the 18S rRNA gene and using Clustal W showed in Figure S1.

3.2. Enzymatic Activity of *Trichoderma* Strains

The results of enzymatic activities of three different *Trichoderma* cultures designated as TN1, TN2, and TN3 are presented in Table 2.

Table 2. Enzymatic activity of *Trichoderma* strains. Values are expressed as mean \pm SD ($n = 3$). Different letters in the same line indicate statistically significant differences with $p < 0.05$.

Enzymes Activity (U/h)	<i>Trichoderma atroviride</i> TN1	<i>Trichoderma atroviride</i> TN2	<i>Trichoderma citrinoviride</i> TN3
chitinase	0.82 \pm 0.03 ^a	0.4 \pm 0.03 ^c	0.70 \pm 0.04 ^b
β —1,3—glucanase	1.63 \pm 0.02 ^a	0.7 \pm 0.02 ^b	1.9 \pm 0.01 ^a
lipase	2.23 \pm 0.01 ^a	0.51 \pm 0.20 ^c	1.99 \pm 0.06 ^b
α -glucosidase	0.08 \pm 0.01 ^a	0.06 \pm 0.01 ^b	0.08 \pm 0.04 ^a
β -glucosidase	0.05 \pm 0.01 ^b	0.02 \pm 0.01 ^c	0.09 \pm 0.02 ^a
aminopeptidase	1.7 \pm 0.02 ^b	1.9 \pm 0.01 ^a	1.8 \pm 0.01 ^a

Strain *T. atroviride* TN1 and *T. citrinoviride* TN3 appeared to be the most enzymatically active. All the *Trichoderma* strains were characterized by the highest lipase and aminopeptidase activity. These enzymes are important in the degradation of organic matter, which can be deposited in significant quantities in the environment. All the tested isolates produced chitinases and β -1,3-glucanases, which are known for their fungicidal properties. By producing fungicidal chitinases, *Trichoderma* strains are used for plant protection.

Also, some secondary metabolites and hydrolytic enzymes excreted by *Trichoderma* have been shown to be involved in inhibiting the growth of pathogenic microorganisms and stimulating plant growth [44]. Cherkupally et al. [45] studied the *Trichoderma* genus for activity on amylases, cellulases, peptidases, pectinases, and chitinases. They reported that *T. harzianum*, *T. pseudokoningii*, *T. atroviride*, *T. viride*, *T. virens*, and *T. koningii* had high

chitinolytic activity. Similarly, Xia et al. [46] found that *T. viride* showed high chitinase activity. Win et al. [47] isolated *Trichoderma asperellum*, which presented antifungal activity against four species of phytopathogenic fungi from the *Fusarium* genus. In addition, *Trichoderma asperellum* has been shown to secrete mycolytic enzymes (chitinase and β -1,3-glucanase). The number of chitinase genes showed great variation in fungal genomes, ranging from a single gene in *Schizosaccharomyces pombe* to 36 genes in *T. virens* [48].

Trichoderma have the ability to detoxify pesticides and herbicides [49]. This is certainly due to the processing of substances by extracellular and intracellular enzymes. According to Abdenaceur et al. [50], *Trichoderma* isolates obtained in the ecosystem niche of olives showed high potential for plant growth promoting biomolecule production. According to Wang et al. [51], *Trichoderma lentiforme* ACCC30425 showed the highest lipase production capacity at high pH. According to Qian et al. [52], the filamentous fungus *Trichoderma reesei* is one of the best-known cellulolytic organisms and the significant producer of cellulases for industrial applications. In addition, aspartic protease P6281 secreted by *Trichoderma harzianum* is important in mycoparasitism on phytopathogenic fungi [53].

3.3. Respirometric Activity of *Trichoderma* in the Presence of Modified Chitosan Films

The tested *Trichoderma* strains degraded chitosan films at different levels (Table 3).

Table 3. Biological oxygen demand of *Trichoderma* strains in the presence of chitosan films modified by phenolic acids.

Materials	<i>Trichoderma atroviride</i> TN1	<i>Trichoderma atroviride</i> TN2	<i>Trichoderma citrinoviride</i> TN3
CTS	* 137 ± 2.2 ^a	89 ± 3.3 ^a	110 ± 2.5 ^a
CTS/TA	210 ± 3.1 ^b	120 ± 3.4 ^b	178 ± 3.2 ^b
CTS/GA	104 ± 4.0 ^a	98 ± 1.3 ^a	117 ± 3.3 ^a
CTS/FA	257 ± 4.2 ^c	130 ± 3.2 ^b	220 ± 4.1 ^c

* Biological activity was expressed in mg O₂/L after 8 days of incubation. Values are expressed as mean ± SD (*n* = 3). Different letters in the columns indicate statistically significant differences with *p* < 0.05).

T. atroviride TN1 and *T. citrinoviride* TN3 metabolized the tested films best. At the same time, a statistically significant influence of phenolic acids incorporated into chitosan on the biological activity of *Trichoderma* was observed. CTS/FA films were best used by *Trichoderma* (BOD 130–257 mg O₂/L after 8 days). In turn, CTS/GA films were less prone to biodegradation (BOD 98–117 mg O₂/L after 8 days).

Chitosan has many intrinsic characteristics including biocompatibility and biodegradability [54]. Furthermore, it shows antimicrobial, antitumor, and antioxidant properties [55]. Inhibition of fungal and bacterial growth depends on the molecular weight of chitosan and its functional groups. Smaller oligomeric chitosan molecules can easily penetrate the cell membrane and inhibit RNA transcription to prevent cell growth [56].

Our previous research [4] showed that chitosan film modified with tannic acid was difficult to degrade by microorganisms. However, there is no doubt that there might be some microorganisms in the environment capable of utilizing chitosan as a source of carbon. Ohkawa et al. [17] studied the degradation of chitosan–gellan (CGF) by seven species of soil filamentous fungi. Biodegradation processes were observed under the microscope and it was revealed that only *P. caseicolum* on the CGF grew along with the breakdown of the fiber matrices. In the biochemical oxygen demand (BOD) test, the degradation of CGF by *A. oryzae* was the highest at 59% among the seven species of tested fungi. *Penicillium caseicolum* and *P. citrinum* also degraded the CGF at the level of 41% and 10%, respectively. Babae et al. [57] examined the biodegradation of chitosan nanoparticles (CNPs) films using *T. versicolor*. According to these authors, the chitosan films underwent a fast degradation process during storage within the first 30 days and complete degradation after 50–60 days.

3.4. Fourier Transform Infrared Spectroscopy—Attenuated Total Reflectance (FTIR–ATR)

The degradation of chitosan films modified by phenolic acids was observed in all studied conditions (Figure 1A), however, it was not controlled by the type of phenolic acid added to chitosan. The degradation peak in the range of $3600\text{--}2700\text{ cm}^{-1}$ was observed from amine and hydroxyl groups. A peak was not observed after the degradation. Similarly, a peak at 1025 cm^{-1} from COH and CH_2OH groups was observed before degradation and was not noticed after the treatment with fungi. It suggested that the degradation process broke C–N and C–O bonds. Peaks at 2055 and 1835 cm^{-1} were present after degradation. It proved that the number of C=C and C=O groups had increased. The characteristic peaks of chitosan films modified by tannic acid are shown in Figure 1B. Similar observations were also found for CTS/GA acid films (Figure 1C).

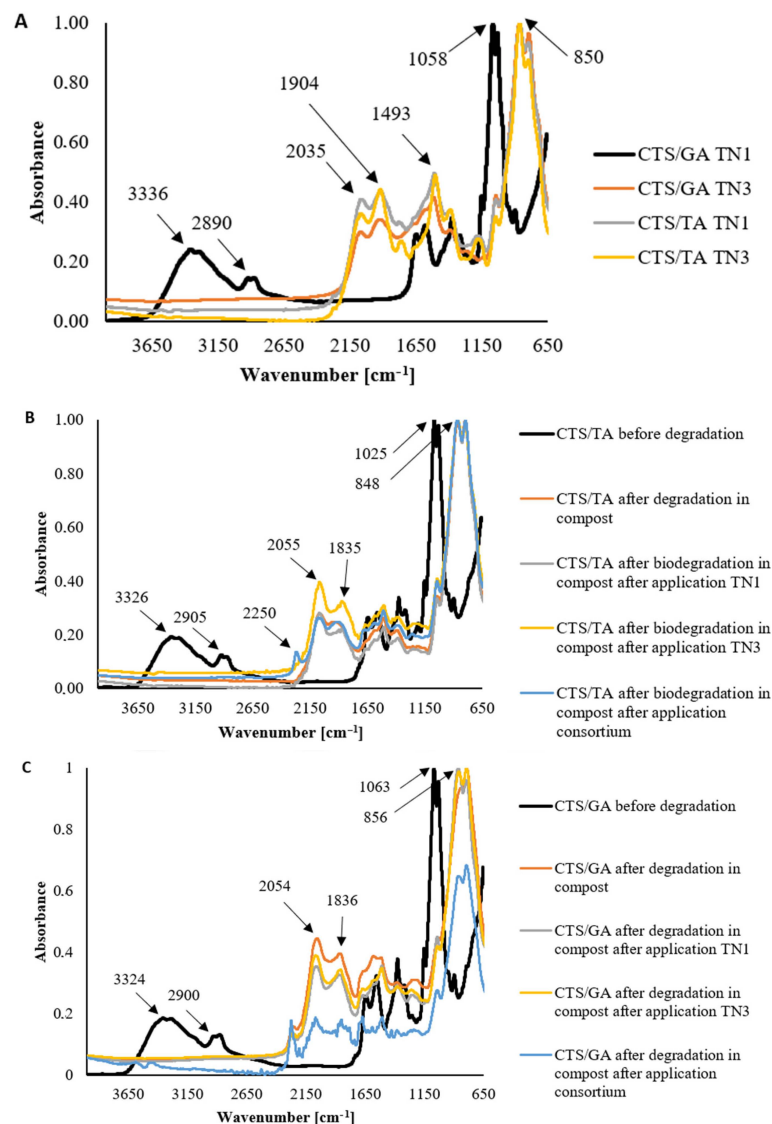


Figure 1. The FTIR–ATR spectra of (A) chitosan film modified by gallic acid (CTS/GA) and tannic acid (CTS/TA) after degradation of *Trichoderma* strains (TN1 and TN3); chitosan film modified by tannic acid (B) and gallic acid (C) before and after degradation in compost after application *Trichoderma* strains (TN1 and TN3).

Through previous studies, it has been shown that chitosan can be modified by phenolic acids addition. The FTIR spectra of chitosan-based materials with ferulic acid, gallic acid, and tannic acid were published before by Kaczmarek-Szczepańska et al. [21]. Significant

changes in the localization and the presence of characteristic groups on the spectra were not observed. It was assumed that covalent bonds between chitosan and phenolic acids are not formed, and the cross-linking process is based on the hydrogen bond formation between hydrophilic groups.

Stoleru et al. [58] tested the biodegradation of poly(lactic acid)/chitosan by *Phanerochaete chrysosporium*, a white rot fungus. The degradation was followed by infrared spectroscopy (FTIR). Notable structural changes resulted from the fungal biodegradation of PLA/chitosan-based samples which showed the onset of hydrolytic or fungal degradation. Biodegradation by the fungi increased the crystallinity of the samples, which means that degradation occurs primarily in amorphous regions. It should be noted that chitosan in the initial days of incubation may act as an antimicrobial agent and the fungi tested may be less active in degrading chitosan films. Stoleru et al. [58] reported that changes in structure are less pronounced for polylactide/chitosan composite than for uncoated polylactide which undergoes important changes after a short incubation period. Therefore, after degradation in the presence of *P. chrysosporium*, due to hydrolytic cleavage of polylactide backbone and chitosan deacetylation, both components of the layered composites exhibited structural changes. Our previous research [4] showed that bacteria isolated from chitosan films modified by tannic acid accelerated the degradation of the materials. Before the degradation, films based on chitosan and tannic acid in a ratio of 80/20 had a big peak at 1289 cm^{-1} from the C-O-C group, which corresponded to the backbone of the chitosan polymeric chain. It decreased after biodegradation. This may be due to the fact that the bond is broken by the action of microorganisms.

3.5. Mechanical Properties

All tested samples after the degradation process showed greater thickness than before (Table 4).

Table 4. The thickness of films based on chitosan (CTS) with tannic acid (TA), ferulic acid (FA), and gallic acid (GA) before and after degradation (significantly different $p < 0.05$ from control: ^a vs. CTS, ^b vs. CTS/TA, ^c vs. CTS/GA).

Sample	Thickness [mm]	Sample	Thickness [mm]
CTS	0.090 ± 0.009	CTS/TA after degradation in compost	1.073 ± 0.011 ^{a,b}
CTS/TA	0.131 ± 0.008 ^a	CTS/TA after degradation in compost after application TN1	1.038 ± 0.017 ^{a,b}
CTS/FA	0.100 ± 0.010	CTS/TA after degradation in compost after application TN3	1.098 ± 0.010 ^{a,b}
CTS/GA	0.080 ± 0.006	CTS/TA after degradation in compost after application consortium	1.671 ± 0.013 ^{a,b}
		CTS/GA after degradation in compost	1.011 ± 0.008 ^c
		CTS/GA after degradation in compost after application TN1	1.045 ± 0.014 ^c
		CTS/GA after degradation in compost after application TN3	1.024 ± 0.009 ^c
		CTS/GA after degradation in compost after application consortium	1.781 ± 0.018 ^c

As a result of degradation, the film shrinks, thereby allowing the increase in thickness to be observed. Mechanical parameters such as Young Modulus, maximum tensile strength, and elongation at break were determined (Figure 2).

It was noticed that the highest value of Young Modulus and maximum tensile strength were noticed for the material composed of chitosan and ferulic acid (Figure 2). Mathew & Abraham [59] showed that the incorporation of ferulic acid to starch/chitosan films enhances the tensile strength. In terms of gallic acid incorporated into chitosan/gelatin, the chitosan-based films modified by gallic acid showed higher Emod and σ_{max} values than the films without phenolic acids. Similar results were obtained by Rui et al. [60] where gallic acid addition resulted in the increase in mechanical properties of the fabricated films. No significant differences in the elongation at break values were observed between the studied samples. Qin et al. [61] observed that the addition of tannic acid to chitosan results

in an increase in tensile strength as well as the Young Modulus. Also, Sun et al. [62] documented that the presence of gallic acid results in a significant increase in the tensile strength of the studied chitosan/gallic acid films. No statistically significant differences in the elongation at break values were observed between the studied samples. Similar results were obtained by Rivero et al. [63] where the elongation at break did not significantly change after the addition of phenolic acids.

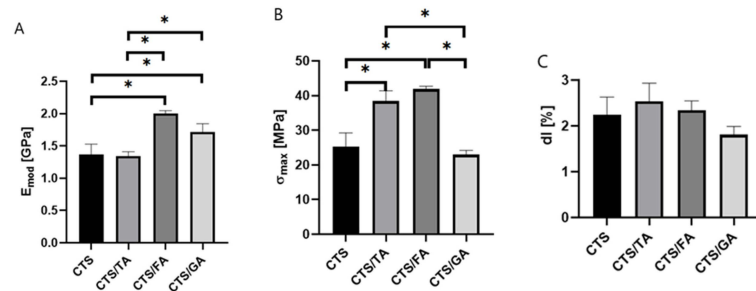


Figure 2. The Young Modulus (A), maximum tensile strength (B), and elongation at break (C) of films based on chitosan (CTS) with tannic acid (TA), ferulic acid (FA), and gallic acid (GA) (* significantly different $p < 0.05$).

3.6. Scanning Electron Microscopy (SEM)

The images of CTS/TA and CTS/GA before degradation showed the smooth surface of films without any scratches or structures (Figure 3).

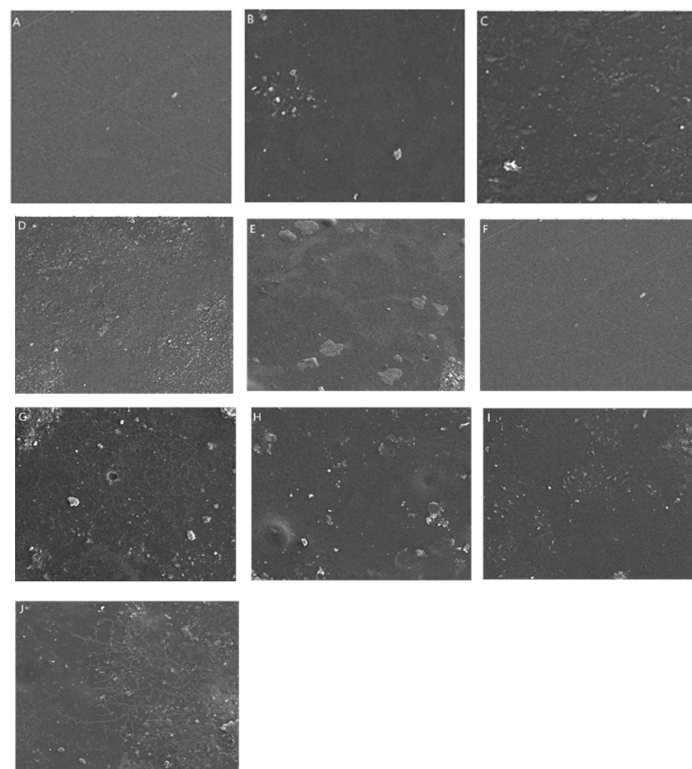


Figure 3. The SEM images (1000 \times) of (A) CTS/TA before degradation; (B) CTS/TA after degradation in compost; (C) CTS/TA after biodegradation in compost after application of TN1; (D) CTS/TA after biodegradation in compost after application of TN3; (E) CTS/TA after biodegradation in compost after application of consortium; (F) CTS/GA before degradation; (G) CTS/GA after degradation in compost; (H) CTS/GA after biodegradation in compost after application of TN1; (I) CTS/GA after biodegradation in compost after application of TN3; (J) CTS/GA after biodegradation in compost after application of consortium.

It can be observed that after degradation in the compost, the soil grains are present on the surface of both types of films. For images after biodegradation in the compost after application, the *Trichoderma* application allowed us to observe the presence of fungi-like structures that adhere to the materials' surface. It suggests that the biodegradation process includes the adhesion of fungi to the CTS/TA and CTS/GA surface, both TN1 and TN3 types. Similar structures were observed by Poorna Chandrika et al. [64] on SEM images of chitosan-PEG blended films using *Trichoderma* and by Cheng et al. [65] on carvacrol/sodium alginate films.

3.7. Biodegradation of Chitosan Films in the Compost after Application of *Trichoderma*

The biodegradation of the chitosan film modified by phenolic acids after application of *Trichoderma* is shown in Figure 4.

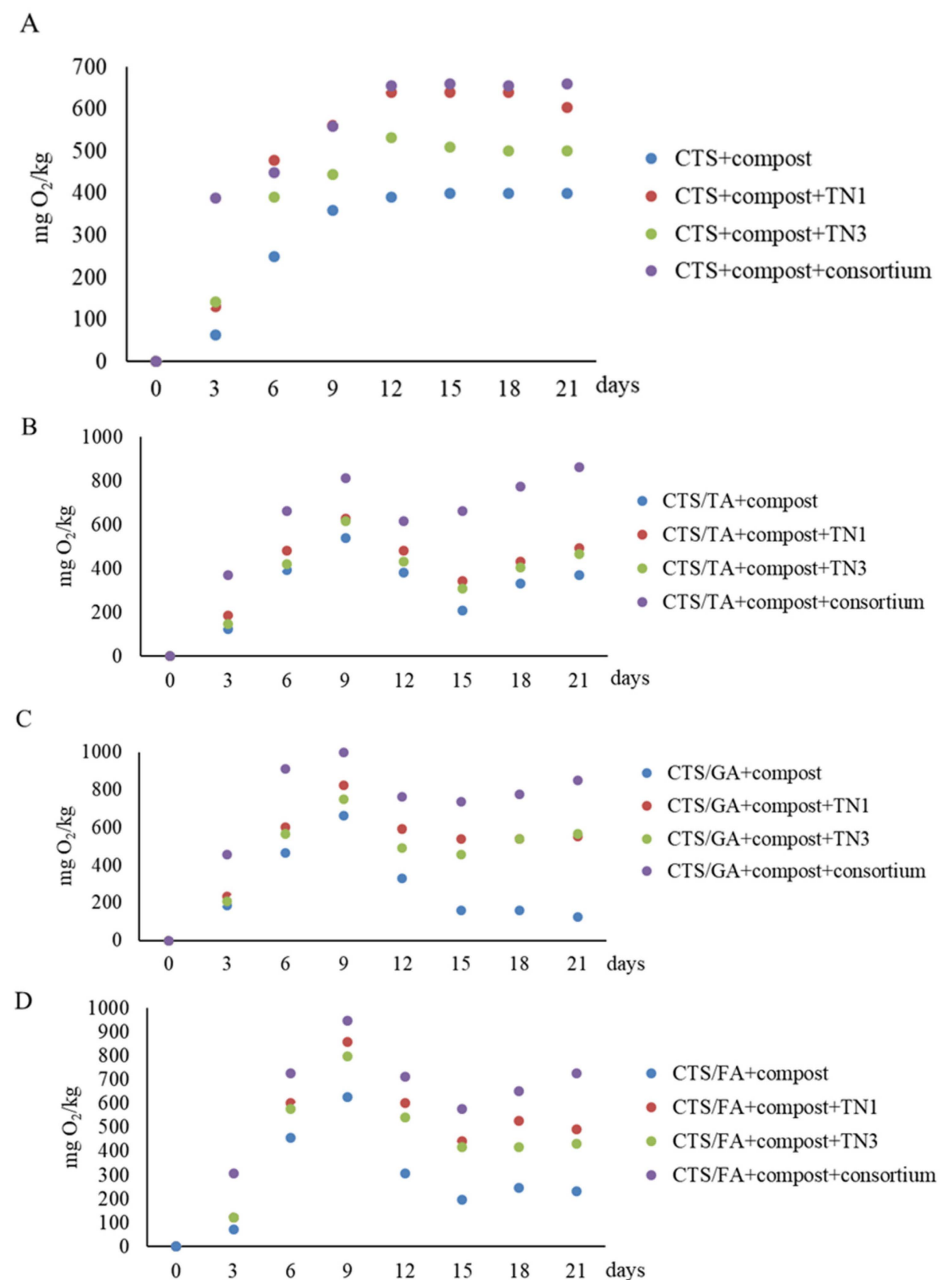


Figure 4. The biodegradation of chitosan film modified by phenolic acids after application of *Trichoderma* strains (TN1 and TN3): chitosan (A), chitosan modified tannic acid (B), chitosan modified gallic acid (C), and chitosan modified ferulic acid (D).

Overall, the oxygen consumption by microorganisms in the presence of chitosan films modified by phenolic acids was significantly dependent on the type of phenolic acids used, the fungal culture, and the interaction of the two factors (Table 5).

Table 5. Two-way ANOVA results on the influence of phenolic compounds, fungal strain/consortium (experiment variant), and their interaction on biological oxygen demand (BOD 21) in compost.

	Sum of Squares	df	Mean Square	F	<i>p</i> -Value
Phenolic substance	4.48×10^4	3	1.49×10^4	1.25×10^3	3.32×10^{-33}
Variant	1.46×10^6	3	4.88×10^5	4.08×10^4	2.24×10^{-57}
Interaction	2.46×10^5	9	2.74×10^4	2.29×10^3	2.55×10^{-42}
Within	3.83×10^2	32	1.20×10^1		
Total	1.76×10^6	47			

The application of *T. atroviride* TN1 and *T. citrinoviride* TN3 similarly influenced the degradation of the CTS/TA film. The respiratory activity after 21 days of incubation was 492 mgO₂/kg and 468 mgO₂/kg. However, the highest oxygen consumption in the presence of CTS/TA film was found after the application of the consortium of these strains (861 mg O₂/kg after 21 days of incubation). Similarly, chitosan with gallic acid (CTS/GA) was least degraded by the native microorganisms of the compost (Figure 4B). The application of *T. atroviride* TN1 and *T. citrinoviride* TN3 similarly influenced the degradation of the CTS/GA film. The respiratory activity was 553 mgO₂/kg and 566 mgO₂/kg, respectively, after 21 days of incubation. However, the highest oxygen consumption in the presence of CTS/GA was found after the application of the consortium of these strains (849 mgO₂/kg after 21 days of incubation). Similar relationships were observed after the introduction of chitosan with ferulic acid (CTS/FA) into the compost after the application of the *Trichoderma* consortium (Figure 4C). The films before and after degradation in Oxi-Top are shown in Figure 5.

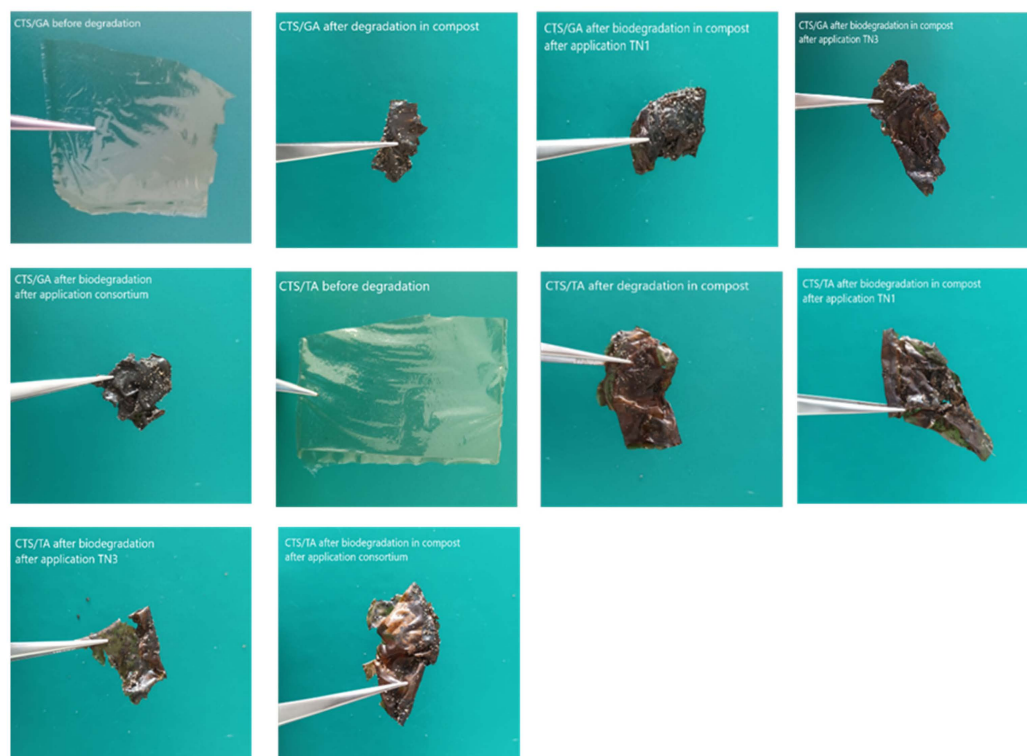


Figure 5. The films before and after degradation in OxiTop.

Composting is a significant method of waste management, including polymer films. Altun et al. [66] used controlled composting reactors to study the biodegradation of chitosan films. Microbial diversity was also determined by PCR-denaturing gradient gel electrophoresis (DGGE). The dominant taxonomic groups of microorganisms in composting reactors at the phylum level were Ascomycota and Proteobacteria. Carbon dioxide emissions data showed a high degradation rate of chitosan in reactors inoculated with microorganisms, which were capable of producing chitosanase. The control reactor contained only chitosan films (no microbial inoculum). In comparison, the group I microorganisms (*Bacillus circulans*, *Bacillus licheniformis*, *Streptomyces roseolus*, *Streptomyces zaomycticus*, *Penicillium islandicum*, and *Penicillium chrysogenum*) increased the biodegradation rate. On the other hand, the group II inoculant (*Mycoplana dimorpha*, *Fennellia flavipes*, and *Chaetomium globosum*) reduced the efficiency of chitosan biodegradation. In the biodegradation of chitosan, the appropriate selection of microbial strains for inoculation is important, especially strains producing chitinases of different subclasses. Kaczmarek-Szczepańska et al. [4] reported that the bacteria isolated from the soil degraded the chitosan films modified by tannic acid (50CTS/50TA) better than the bacteria isolated from the compost. Their study also showed that consortia of bacteria (*Acinetobacter calcoaceticus* GTA2, *Bacillus mycoides* GTA7, *Pseudomonas arsenicoxydans* GTA8, and *Pseudomonas laurylsulfatorans* GTA9) added to soil had a positive effect on the biodegradation of the 50CTS/50TA. Similarly, consortia of bacteria (*Pseudomonas hunanensis* KTA1 and *Pseudomonas psychrophila* KTA3) added to the compost accelerated the degradation of chitosan films modified by tannic acid (50CTS/50TA).

Our study showed that *T. atroviride* metabolized chitosan-based materials, but the process was relatively slow. The chitosan films used for this study were modified with phenolic acids, which had antimicrobial properties. Therefore, it can be speculated that the degradation of such materials might start with the adaptation of microorganisms to the polymers and the production of enzymes such as chitosanase. Znajewska et al. [14] reported that *T. viride* DAR5, *T. viride* 3333, and *T. viride* 154 accelerated polycaprolactone (PCL) degradation in the soil. The greatest degree of polymer degradation expressed in terms of mass loss was shown by *T. viride* 3333 (complete disintegration of the PCL film). The other two strains degraded PCL to a lesser extent (PCL mass loss of 27.85% and 11.58%, respectively). These results were obtained after 6 months of PCL storage in the soil. On the other hand, the studies by Dąbrowska et al. [11] showed that *T. viride* GZ1 is capable of producing hydrolytic enzymes degraded polylactide and polyethylene terephthalate, producing hydrophobin in the first stage of biodegradation.

The introduction of engineered consortia of microorganisms into the environment often has a positive effect not only on the biodegradation processes of organic matter but also improves soil quality and favorably influences plant development. For example, the addition of suitable microorganism-based boosters compensates for stress and reduced plant growth caused by weeds, drought, heavy metals, salt, and other adverse environmental conditions [67].

3.8. Effect of Application of *Trichoderma* on Hydrolytic Enzymes Activity in Compost

Extracellular enzymes secreted by microorganisms into the compost significantly affect the degradation of organic matter. The introduction of the *Trichoderma* preparation into the compost further enriched the compost with enzymes capable of degrading macromolecular compounds (Table 6).

Lipase and aminopeptidase were found to be the most active. The greatest changes in enzyme activity were found for chitinases. These enzymes showed the highest activities after the introduction into the compost chitosan films with ferulic acid. The application of the *Trichoderma* consortium significantly increased the activity of chitinases in the compost. In contrast, the activity of glucosidases in the compost was the lowest even after the introduction of chitosan films and *Trichoderma*.

Table 6. Effect of chitosan film modified by phenolic acids on changes in soil hydrolytic enzyme activity after *Trichoderma* strains bioaugmentation.

Variants	Enzyme Activity (U/h)				
	Chit.	Lip.	α -Gluc.	β -Gluc	Amino.
Compost	4.4 ± 0.14 ^a	19.4 ± 0.1 ^a	4.2 ± 0.13 ^a	4.2 ± 0.03 ^a	8.2 ± 0.05 ^a
CTS/TA + compost	3.1 ± 0.03 ^b	15.6 ± 0.01 ^b	4.5 ± 0.01 ^a	4.5 ± 0.01 ^a	6.8 ± 0.05 ^b
CTS/TA + compost + TN1	5.8 ± 0.07 ^c	16.8 ± 0.10 ^b	4.5 ± 0.01 ^a	4.3 ± 0.03 ^a	9.2 ± 0.06 ^c
CTS/TA + compost + TN3	5.3 ± 0.06 ^c	17.9 ± 0.07 ^b	4.4 ± 0.01 ^a	3.9 ± 0.03 ^a	9.6 ± 0.02 ^c
CTS + compost + TN1 + TN3	5.8 ± 0.21 ^c	34.2 ± 0.31 ^c	4.6 ± 0.41 ^a	4.2 ± 0.02 ^a	9.4 ± 0.06 ^c
CTS/GA + compost	4.0 ± 0.18 ^a	7.0 ± 0.05 ^b	3.6 ± 0.01 ^a	4.1 ± 0.01 ^a	1.3 ± 0.03 ^b
CTS/GA + compost + TN1	5.5 ± 0.01 ^a	13.2 ± 0.12 ^c	3.7 ± 0.01 ^a	4.2 ± 0.02 ^a	5.8 ± 0.01 ^c
CTS/GA + compost + TN3	6.6 ± 0.03 ^b	13.4 ± 0.01 ^c	3.0 ± 0.01 ^a	4.3 ± 0.02 ^a	6.2 ± 0.01 ^c
CTS/GA + compost + TN1 + TN3	11.2 ± 0.12 ^c	13.6 ± 0.01 ^c	3.0 ± 0.01 ^a	3.9 ± 0.01 ^a	5.4 ± 0.05 ^c
CTS/FA + compost	3.9 ± 0.28 ^a	19.9 ± 0.08 ^a	4.7 ± 0.01 ^a	4.2 ± 0.08 ^a	3.7 ± 0.02 ^b
CTS/FA + compost + TN1	25 ± 0.11 ^b	14.0 ± 0.04 ^b	4.8 ± 0.01 ^b	4.4 ± 0.01 ^a	7.4 ± 0.03 ^c
CTS/FA + compost + TN3	28.3 ± 0.28 ^b	23.3 ± 0.01 ^b	4.6 ± 0.03 ^b	4.9 ± 0.01 ^a	6.5 ± 0.03 ^c
CTS/FA + compost + N1 + TN3	38.5 ± 0.57 ^c	25.1 ± 0.01 ^b	4.3 ± 0.02 ^b	4.6 ± 0.01 ^a	6.1 ± 0.06 ^c

Values are expressed as mean ± SD ($n = 3$). Chit—chitinase, Lip—lipase, α -gluc— α -glucosidase, β -gluc— β -glucosidase, and Amino—aminopeptidase. Different letters in the column indicate statistically significant differences at $p < 0.05$ according to the HDS Tukey's test.

The introduction of materials with antimicrobial properties into the environment often affects the production of extracellular enzymes by microorganisms. And our results also showed that for most enzymes, inhibition of activity was observed after the introduction of chitosan films with ferulic, tannic, and gallic acids. Further, the addition of the *Trichoderma* consortium to the compost improved enzyme synthesis, especially chitinase, lipase, and aminopeptidase. Klose et al. [68] fumigated toxic compounds including methyl bromide, propargyl bromide, chloropicrin, and sandy soil, and then checked the activity of acid phosphatase, arylsulfatase, β -glucosidase, and dehydrogenase. Their tests showed that arylsulfatase (62%), dehydrogenase (35%), acid phosphatase (22%), and β -glucosidase (6%) activities decreased within 90 days after fumigation. Su et al. [69] studied enzyme activity in arsenic-contaminated soils. After inoculation of *Trichoderma asperellum* SM-12F1 into contaminated soil, they observed β -glucosidase (155%), chitinase (211%), and phosphatase (108%) activities in SM soils, while significantly decreased β -glucosidase (81%), phosphatase (54%), aminopeptidase (60%), and catalase (67%) activities in soils. Such a result demonstrates the positive effects of bioaugmentation, which is increasingly practiced. Inoculation of *Trichoderma* into the environment can improve enzymatic activity in the rhizosphere of plants. Yedidia et al. [70] reported that cucumber roots inoculated with *Trichoderma harzianum* T-203 showed higher chitinase, β -1,3-glucanase, cellulase, and peroxidase activities up to 72 h after inoculation compared to roots without *Trichoderma*. Soil enzyme activity is sensitive to environmental changes and has been proposed as an indicator of soil quality due to its relationship with soil biology [71] and rapid responses to changes in management and soil environment [72,73]. Therefore, the introduction of biocidal materials into the environment is associated with the inhibition of enzyme activity. Inoculation with microorganisms with high enzymatic activity can improve soil quality as well as soil enzyme activity.

4. Conclusions

Chitosan is known primarily for its antifungal properties. Chitosan-based liquid preparations have been developed for plant protection. Chitosan films are also used in medicine as a dressing material. The introduction of biocidal phenolic acids into chitosan film makes it possible to use it as food packaging to protect against the growth of both bacteria and fungi. The potential of modified chitosan films may be seen in the protection of fruits and vegetables. Such foil can protect them against the development of fungi. However, packaging materials should be degradable in the environment. Studies have shown that chitosan modified with phenolic acid is less readily degraded by native microorganisms. Only after the application of *Trichoderma* does the degradation of chitosan films occur more effectively. At the same time, studies have shown a beneficial effect of the use of *Trichoderma*

on the enzymatic activity of compost. Chitinases, the activity of which increased after the introduction of the preparation, can control the development of phytopathogens.

Supplementary Materials: The following supporting information can be downloaded at: <https://www.mdpi.com/article/10.3390/foods12193669/s1>, Figure S1: Dendrogram prepared using nucleotide sequences of the ITS region of the 18S rRNA gene and using Clustal W (<https://www.genome.jp/tools-bin/clustalw>, accessed on 3 October 2022). Sequences from NCBI's GeneBank were used to analysis: (Acc. no. OP586652.1) *T. citrinoviride*, (OP586653.1) *T. atroviride* G, (OP586643.1), *T. atroviride* isolate Fb1, (AY380909.1) *T. viride* strain ATCC 28038, (X93978.1) *T. viride* strain ATCC 18652, (AF279395.1) *T. citrinoviride* strain ATCC 90178, (JQ745264.1) *T. atroviride* strain ATCC 20476, (AF278796.1) *T. atroviride* strain ATCC 36042, (AF127152.1) *T. atroviride* ATCC 28036, (DQ315445.1) *Trichoderma trixiae* strain ATCC 32630, (NG_059411.1) *Trichoderma koningii* ATCC 64262, (DQ315434.1) *Trichoderma paraviridescens* strain ATCC 20898, (AF127154.1) *Trichoderma reesei* QM6a ATCC 13631, (AF127145.1) *T. viride* strain Tr48 ATCC 5242, (AY625068.1) *Trichoderma harzianum* strain NRRL 13019.

Author Contributions: M.S.B.: Conceptualization, methodology, investigation, project administration, supervision, and writing—original draft. G.B.D.: Investigation and writing—original draft. B.K.-S.: Writing—original draft, investigation, and data curation. M.M.-S.: Investigation. K.D.: Writing—review and editing. A.R.: Writing—original draft. M.P.: Writing—review and editing, and data curation. S.B.K.: Writing—review and editing. A.K.: Writing—review and editing, and data curation. All authors have read and agreed to the published version of the manuscript.

Funding: This research was supported by funds provided by Nicolaus Copernicus University (Torun, Poland) to maintain research potential and the Excellence Initiative Research University competition for scientific groups—BIODEGRADABLE PACKAGING materials research group no. 4101.00000085 IDUB/Research Group.

Data Availability Statement: The data used to support the findings of this study can be made available by the corresponding author upon request.

Conflicts of Interest: The funders had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript; or in the decision to publish the results.

References

1. Vroman, I.; Tighzert, L. Biodegradable Polymers. *Materials* **2009**, *2*, 307–344. [[CrossRef](#)]
2. Priyadarshi, R.; Rhim, J.W. Chitosan-based biodegradable functional films for food packaging applications. *Innov. Food Sci. Emerg. Technol.* **2020**, *62*, 102346. [[CrossRef](#)]
3. Wang, W.; Xue, C.; Mao, X. Chitosan: Structural modification, biological activity and application. *Int. J. Biol. Macromol.* **2020**, *164*, 4532–4546. [[CrossRef](#)] [[PubMed](#)]
4. Kaczmarek-Szczepańska, B.; Michalska-Sionkowska, M.; Mazur, O.; Świątczak, J.; Swiontek Brzezinska, M. The role of microorganisms in biodegradation of chitosan/tannic acid materials. *Int. J. Biol. Macromol.* **2021**, *184*, 584–592. [[CrossRef](#)] [[PubMed](#)]
5. Borges, A.; Ferreira, C.; Saavedra, M.J.; Simões, M. Antibacterial activity and mode of action of ferulic and gallic acids against pathogenic bacteria. *Microb. Drug Resist.* **2013**, *19*, 256–265. [[CrossRef](#)]
6. Kaczmarek-Szczepańska, B.; Wekwejt, M.; Mazur, O.; Zasada, L.; Pałubicka, A.; Olewnik-Kruszkowska, E. The physicochemical and antibacterial properties of chitosan-based materials modified with phenolic acids irradiated by UVC light. *Int. J. Mol. Sci.* **2021**, *22*, 6472. [[CrossRef](#)]
7. Richert, A.; Olewnik-Kruszkowska, E.; Dąbrowska, G.B.; Dąbrowski, H.P. The Role of Birch Tar in Changing the Physicochemical and Biocidal Properties of Polylactide-Based Films. *Int. J. Mol. Sci.* **2022**, *23*, 268. [[CrossRef](#)]
8. Richert, A.; Kalwasińska, A.; Jankiewicz, U.; Swiontek Brzezinska, M. Effect of birch tar embedded in polylactide on its biodegradation. *Int. J. Biol. Macromol.* **2023**, *239*, 124226. [[CrossRef](#)]
9. Janczak, K.; Dąbrowska, G.B.; Raszewska-Kaczor, A.; Kaczor, D.; Hryniewicz, K.; Richert, A. Biodegradation of the plastics PLA and PET in cultivated soil with the participation of microorganisms and plants. *Int. Biodeterior. Biodegrad.* **2020**, *155*, 1050. [[CrossRef](#)]
10. Richert, A.; Dąbrowska, G.B. Bacterial biofilm on PLA films and methods of its identification. *Ecol. Quest.* **2020**, *31*, 31–38. [[CrossRef](#)]
11. Dąbrowska, G.B.; Garstecka, Z.; Olewnik-Kruszkowska, E.; Szczepańska, G.; Ostrowski, M.; Mierek-Adamska, A. Comparative study of structural changes of polylactide and poly(ethylene terephthalate) in the presence of *Trichoderma viride*. *Int. J. Mol. Sci.* **2021**, *22*, 3491. [[CrossRef](#)] [[PubMed](#)]

12. Richert, A.; Dąbrowska, G.B. Enzymatic degradation and biofilm formation during biodegradation of polylactide and polycaprolactone polymers in various environments. *Int. J. Biol. Macromol.* **2021**, *176*, 226–232. [[CrossRef](#)] [[PubMed](#)]
13. Abdel-Motaal, F.F.; El-Sayed, M.A.; El-Zayat, S.A.; Ito, S.I. Biodegradation of poly (-caprolactone) (PCL) film and foam plastic by *Pseudozyma japonica* sp. nov., a novel cutinolytic ustilaginomycetous yeast species. *3 Biotech* **2014**, *4*, 507–512. [[CrossRef](#)] [[PubMed](#)]
14. Znajewska, Z.; Dąbrowska, G.B.; Hryniewicz, K.; Janczak, K. Biodegradation of polycaprolactone by *Trichoderma viride* fungi. *Chem. Ind.* **2018**, *97*, 1676–1679. [[CrossRef](#)]
15. Kannahi, M.; Thamizhmarai, T. Biodegradation of plastic by *Aspergillus* sp. *Int. J. Trend Sci. Res. Dev.* **2018**, *2*, 683–690. [[CrossRef](#)]
16. Vivi, V.K.; Martins-Franchetti, S.M.; Attili-Angelis, D. Biodegradation of PCL and PVC: *Chaetomium globosum* (ATCC 16021) activity. *Folia Microbiol.* **2019**, *64*, 1–7. [[CrossRef](#)] [[PubMed](#)]
17. Ohkawa, K.; Yamada, M.; Nishida, A.; Nishi, N.; Yamamoto, H. Biodegradation of chitosan-gellan and poly (L-lysine)-gellan polyion complex fibers by pure cultures of soil filamentous fungi. *J. Polym. Environ.* **2000**, *8*, 59–66. [[CrossRef](#)]
18. Znajewska, Z.; Dąbrowska, G.B.; Narbutt, O. *Trichoderma viride* stains stimulating the growth and development of winter rapeseed (*Brassica napus* L.). *Prog. Plant Prot.* **2018**, *58*, 264–269. [[CrossRef](#)]
19. Harman, G.E.; Howell, C.R.; Viterbo, A.; Chet, I.; Lorito, M. *Trichoderma* species—Opportunistic, avirulent plant symbionts. *Nat. Rev. Microbiol.* **2004**, *2*, 43–56. [[CrossRef](#)]
20. Janczak, K.; Dąbrowska, G.; Znajewska, Z.; Hryniewicz, K. Searching for the fungi capable to grow on polymeric materials. *Przemysł Chem.* **2014**, *93*, 1206–1209. [[CrossRef](#)]
21. Kaczmarek-Szczepańska, B.; Polkowska, I.; Paździor-Czapula, K.; Nowicka, B.; Gierszewska, M.; Michalska-Sionkowska, M.; Otrocka-Domagala, I. Chitosan/Phenolic Compounds Scaffolds for Connective Tissue Regeneration. *J. Funct. Biomater.* **2023**, *14*, 69. [[CrossRef](#)] [[PubMed](#)]
22. Vancov, T.; Keen, B. Amplification of soil fungal community DNA using the ITS86F and ITS4 primers. *FEMS Microbiol. Lett.* **2009**, *296*, 91–96. [[CrossRef](#)] [[PubMed](#)]
23. Raja, H.A.; Miller, A.N.; Pearce, C.J.; Oberlies, N.H. Fungal identification using molecular tools: A primer from the natural products research community. *J. Nat. Prod.* **2017**, *80*, 756–770. [[CrossRef](#)] [[PubMed](#)]
24. Hoppe, H.G. Significance of exoenzymatic activities in the ecology of brackish water: Measurements by means of methylumbelliferyl-substrates. *Mar. Ecol. Prog. Ser.* **1983**, *11*, 299–308. [[CrossRef](#)]
25. Freeman, C.; Liska, G.; Ostle, N.J.; Jones, S.E.; Lock, M.A. The use of fluorogenic substrates for measuring enzyme activity in peatlands. *Plant Soil* **1995**, *175*, 147–152. [[CrossRef](#)]
26. Niemi, R.M.; Vepsäläinen, M. Stability of the fluorogenic enzyme substrates and pH optima of enzyme activities in different Finnish soils. *J. Microbiol. Methods* **2005**, *60*, 195–205. [[CrossRef](#)] [[PubMed](#)]
27. Wu, Q.; Dou, X.; Wang, Q.; Guan, Z.; Cai, Y.; Liao, X. Isolation of β -1,3-Glucanase-Producing Microorganisms from *Poria cocos* Cultivation Soil via Molecular Biology. *Molecules* **2018**, *23*, 1555. [[CrossRef](#)]
28. Swiontek Brzezinska, M.; Jankiewicz, U.; Walczak, M. Biodegradation of chitinous substances and chitinase production by the soil actinomycete *Streptomyces rimosus*. *Int. Biodeterior. Biodegrad.* **2013**, *84*, 104–110. [[CrossRef](#)]
29. Swiontek Brzezinska, M.; Richert, A.; Kalwasińska, A.; Świątczak, J.; Deja-Sikora, E.; Walczak, M.; Michalska-Sionkowska, M.; Piekarska, K.; Kaczmarek-Szczepańska, B. Microbial degradation of polyhydroxybutarate with embedded polyhexamethylene guanidine derivatives. *Int. J. Biol. Macromol.* **2021**, *187*, 309–318. [[CrossRef](#)]
30. Bednarek, R.; Dziadowiec, H.; Pokojka, U.; Prusinkiewicz, Z. *Badania Ekologiczno-Gleboznawcze*; Wydawnictwo Naukowe PWN: Warszawa, Poland, 2004; ISBN 83-01-14216-2.
31. *PN-ISO 14235*; Determination of Organic Carbon Content by Oxidation With Dichromate (VI) in Sulphuric Acid Medium. Polish Committee for Standardisation: Warsaw, Poland, 2003. (In Polish)
32. *PN-R-04022*; Chemical and Agricultural Analysis of Soil—Determination of Available Potassium in Mineral Soils. Polish Committee for Standardisation: Warsaw, Poland, 1996. (In Polish)
33. *PN-R-04028*; Soil Chemical and Agricultural Analysis, Sampling and Determination of Nitrogen and Ammonium Ions in Mineral Soils. Polish Committee for Standardisation: Warsaw, Poland, 1997. (In Polish)
34. *PN-R-04022:1996/Az1*; Soil Chemical and Agricultural Analysis -Determination of Available Potassium in Mineral Soils. Polish Committee for Standardisation: Warsaw, Poland, 2002. (In Polish)
35. *PN-R-04020:1994/Az1*; Chemical and Agricultural Analysis of Soil—Determination of Available Magnesium Content. Polish Committee for Standardisation: Warsaw, Poland, 2004. (In Polish)
36. Platen, H.; Wirtz, A. The measurement of respiration activity soil with a respirometric method (measuring system Oxi Top Control). In *WTW/OxiTopR/Appliance*; Fachbereich KMUB, Umwelt-und Hygienetechnik und Zentrum f.r Umwelttechnologie: Giessen, Germany, 1999.
37. Adam, G.; Duncan, H. Development of a sensitive and rapid method for the measurement of total microbial activity using fluorescein diacetate (FDA) in a range of soils. *Soil Biol. Biochem.* **2001**, *33*, 943–951. [[CrossRef](#)]
38. Hammer, Ā.; Harper, D.A.T.; Ryan, P.D. PAST: Paleontological Statistics Software Package for Education and Data Analysis. *Palaeontol. Electron.* **2001**, *4*, 9.
39. Savitha, M.J.; Sriram, S. Morphological and molecular identification of *Trichoderma* isolates with biocontrol potential against *Phytophthora* blight in red pepper. *Pest Manag. Hortic. Ecosyst.* **2015**, *21*, 194–202.

40. Soesanto, L.; Sri-Utami, D.; Rahayuniati, R.F. Morphological characteristics of four *Trichoderma* isolates and two endophytic *Fusarium* isolates. *Can. J. Sci. Ind. Res.* **2011**, *2*, 294–306.
41. Choi, I.-Y.; Hong, S.-B.; Yadav, M.C. Molecular and morphological characterization of green mold, *Trichoderma* spp. isolated from oyster mushrooms. *Mycobiology* **2003**, *31*, 74–80. [[CrossRef](#)]
42. Narayan, K.; Kotasthane, A. Genetic relatedness among *Trichoderma* isolates inhibiting a pathogenic fungi *Rhizoctonia solani*. *J. Biotechnol.* **2006**, *5*, 580–584.
43. Lücking, R.; Aime, M.C.; Robbertse, B.; Miller, A.N.; Ariyawansa, H.A.; Aoki, T.; Cardinali, G.; Crous, P.W.; Druzhinina, I.S.; Geiser, D.M.; et al. Unambiguous identification of fungi: Where do we stand and how accurate and precise is fungal DNA barcoding? *IMA Fungus* **2020**, *11*, 14. [[CrossRef](#)] [[PubMed](#)]
44. Contreras-Cornejo, H.A.; López-Bucio, J.S.; Méndez-Bravo, A.; Macías-Rodríguez, L.; Ramos-Vega, M.; Guevara-García, A.A.; López-Bucio, J. Mitogen-Activated Protein Kinase 6 and Ethylene and Auxin Signaling Pathways Are Involved in Arabidopsis Root-System Architecture Alterations by *Trichoderma atroviride*. *Mol. Plant Microbe Interact.* **2015**, *28*, 701–710. [[CrossRef](#)]
45. Cherkupally, R.; Amballa, H.; Bhoomi, N.R. In vitro screening for enzymatic activity of *Trichoderma* species for biocontrol potential. *Ann. Plant Sci.* **2017**, *6*, 1784–1789. [[CrossRef](#)]
46. Xia, W.; Liu, P.; Liu, J. Advance in chitosan hydrolysis by non-specific cellulases. *Bioresour. Technol.* **2008**, *99*, 6751–6762. [[CrossRef](#)]
47. Win, T.T.; Bo, B.; Malec, P.; Khan, S.; Fu, P. Newly isolated strain of *Trichoderma asperellum* from disease suppressive soil is a potential bio-control agent to suppress *Fusarium* soil borne fungal phytopathogens. *J. Plant Pathol.* **2021**, *103*, 549–561. [[CrossRef](#)]
48. Gruber, S.; Seidl-Seiboth, V. Self versus non-self: Fungal cell wall degradation in *Trichoderma*. *Microbiology* **2021**, *158*, 26–34. [[CrossRef](#)] [[PubMed](#)]
49. Vázquez, M.B.; Barrera, V.; Bianchinotti, V. Molecular identification of three isolates of *Trichoderma harzianum* isolated from agricultural soils in Argentina, and their abilities to detoxify in vitro metsulfuron methyl. *Botany* **2015**, *93*, 793–800. [[CrossRef](#)]
50. Abdenaceur, R.; Farida, B.T.; Mourad, D.; Rima, H.; Zahia, O.; Fatma, S.H. Effective biofertilizer *Trichoderma* spp. isolates with enzymatic activity and metabolites enhancing plant growth. *Int. Microbiol.* **2022**, *25*, 817–829. [[CrossRef](#)]
51. Wang, Y.; Ma, R.; Li, S.; Gong, M.; Yao, B.; Bai, Y.; Gu, J. An alkaline and surfactant-tolerant lipase from *Trichoderma lentiforme* ACCC30425 with high application potential in the detergent industry. *AMB Express* **2018**, *8*, 95. [[CrossRef](#)] [[PubMed](#)]
52. Qian, Y.; Zhong, L.; Sun, Y.; Sun, N.; Zhang, L.; Liu, W.; Zhong, Y. Enhancement of cellulase production in *Trichoderma reesei* via disruption of multiple protease genes identified by comparative secretomics. *Front. Microbiol.* **2019**, *10*, 2784. [[CrossRef](#)]
53. Deng, J.J.; Huang, W.Q.; Li, Z.W.; Lu, D.L.; Zhang, Y.; Luo, X.C. Biocontrol activity of recombinant aspartic protease from *Trichoderma harzianum* against pathogenic fungi. *Enzym. Microb. Technol.* **2018**, *112*, 35–42. [[CrossRef](#)] [[PubMed](#)]
54. Aranaz, I.; Mengibar, M.; Harris, R.; Panos, I.; Miralles, B.; Acosta, N.; Gemma, G.; Heras, A. Functional characterization of chitin and chitosan. *Curr. Chem. Biol.* **2009**, *3*, 203–230. [[CrossRef](#)]
55. Islam, S.; Bhuiyan, M.R.; Islam, M.N. Chitin and chitosan: Structure, properties and applications in biomedical engineering. *J. Polym. Environ.* **2017**, *25*, 854–866. [[CrossRef](#)]
56. Klaykruyat, B.; Siralertmukul, K.; Srikulkit, K. Chemical modification of chitosan with cationic hyperbranched dendritic polyamidoamine and its antimicrobial activity on cotton fabric. *Carbohydr. Polym.* **2010**, *80*, 197–207. [[CrossRef](#)]
57. Babae, M.; Garavand, F.; Rehman, A.; Jafarazadeh, S.; Amini, E.; Cacciotti, I. Biodegradability, physical, mechanical and antimicrobial attributes of starch nanocomposites containing chitosan nanoparticles. *Int. J. Biol. Macromol.* **2022**, *195*, 49–58. [[CrossRef](#)]
58. Stoleru, E.; Hitruc, E.G.; Vasile, C.; Oprică, L. Biodegradation of poly (lactic acid)/chitosan stratified composites in presence of the *Phanerochaete chrysosporium* fungus. *Polym. Degrad. Stab.* **2017**, *143*, 118–129. [[CrossRef](#)]
59. Mathew, S.; Abraham, T.E. Characterisation of ferulic acid incorporated starch–chitosan blend films. *Food Hydrocoll.* **2008**, *22*, 826–835. [[CrossRef](#)]
60. Rui, L.; Xie, M.; Hu, B.; Zhou, L.; Yin, D.; Zeng, X. A comparative study on chitosan/gelatin composite films with conjugated or incorporated gallic acid. *Carbohydr. Polym.* **2017**, *173*, 473–481. [[CrossRef](#)]
61. Qin, Z.; Huang, Y.; Xiao, S.; Zhang, H.; Lu, Y.; Xu, K. Preparation and characterization of high mechanical strength chitosan/oxidized tannic acid composite film with Schiff base and hydrogen bond crosslinking. *Int. J. Mol. Sci.* **2022**, *23*, 9284. [[CrossRef](#)] [[PubMed](#)]
62. Sun, X.; Wang, Z.; Kadouh, H.; Zhou, K. The antimicrobial, mechanical, physical and structural properties of chitosan–gallic acid films. *LWT-Food Sci. Technol.* **2014**, *57*, 83–89. [[CrossRef](#)]
63. Rivero, S.; Garcia, M.A.; Pinotti, A. Physical and chemical treatments on chitosan matrix to modify film properties and kinetics of biodegradation. *J. Mater. Phys. Chem.* **2013**, *1*, 51–57.
64. Poorna Chandrika, K.S.V.; Prasad, R.D.; Godbole, V. Development of chitosan-PEG blended films using *Trichoderma*: Enhancement of antimicrobial activity and seed quality. *Int. J. Biol. Macromol.* **2019**, *126*, 282–290. [[CrossRef](#)] [[PubMed](#)]
65. Cheng, M.; Wang, J.; Zhang, R.; Kong, R.; Lu, W.; Wang, X. Characterization and application of the microencapsulated carvacrol/sodium alginate films as food packaging materials. *Int. J. Biol. Macromol.* **2019**, *141*, 259–267. [[CrossRef](#)]
66. Altun, E.; Çelik, E.; Ersan, H.Y. Tailoring the microbial community for improving the biodegradation of chitosan films in composting environment. *J. Polym. Environ.* **2020**, *28*, 1548–1559. [[CrossRef](#)]
67. Ahmad, R.; Jilan, G.; Arshad, M.; Zahir, Z.A.; Khalid, A. Bio-conversion of organic wastes for their recycling in agriculture: An overview of perspectives and prospects. *Ann. Microbiol.* **2007**, *57*, 471–479. [[CrossRef](#)]

68. Klose, S.; Acosta-Martínez, V.; Ajwa, H.A. Microbial community composition and enzyme activities in a sandy loam soil after fumigation with methyl bromide or alternative biocides. *Soil Biol. Biochem.* **2006**, *38*, 1243–1254. [[CrossRef](#)]
69. Su, S.; Zeng, X.; Bai, L.; Williams, P.N.; Wang, Y.; Zhang, L.; Wu, C. Inoculating chlamydospores of *Trichoderma asperellum* SM-12F1 changes arsenic availability and enzyme activity in soils and improves water spinach growth. *Chemosphere* **2017**, *175*, 497–504. [[CrossRef](#)] [[PubMed](#)]
70. Yedidia, I.; Benhamou, N.; Kapulnik, Y.; Chet, I. Induction and accumulation of PR proteins activity during early stages of root colonization by the mycoparasite *Trichoderma harzianum* strain T-203. *Plant Physiol. Biochem.* **2000**, *38*, 863–873. [[CrossRef](#)]
71. Henry, H.A. Reprint of “Soil extracellular enzyme dynamics in a changing climate”. *Soil Biol. Biochem.* **2013**, *56*, 53–59. [[CrossRef](#)]
72. García-Ruiz, R.; Ochoa, V.; Vinegla, B.; Hinojosa, M.B.; Pena-Santiago, R.; Liébanas, G.; Linares, J.C.; Carreira, J.A. Soil enzymes, nematode community and selected physico-chemical properties as soil quality indicators in organic and conventional olive oil farming: Influence of seasonality and site features. *Appl. Soil Ecol.* **2009**, *41*, 305–314. [[CrossRef](#)]
73. Burke, D.J.; Weintraub, M.N.; Hewins, C.R.; Kalisz, S. Relationship between soil enzyme activities, nutrient cycling and soil fungal communities in a northern hardwood forest. *Soil Biol. Biochem.* **2011**, *43*, 795–803. [[CrossRef](#)]

Disclaimer/Publisher’s Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.