

CHEMISTRY

Much more to explore with an oxidation state of nearly four: Pr valence instability in intermetallic m -Pr₂Co₃Ge₅

Trent M. Kyrk¹, Ellis R. Kennedy², Jorge Galeano-Cabral^{3,4}, Gregory T. McCandless¹, Mary C. Scott^{2,5,6}, Ryan E. Baumbach^{4,7}, Julia Y. Chan^{1*}

For some intermetallic compounds containing lanthanides, structural transitions can result in intermediate electronic states between trivalency and tetravalency; however, this is rarely observed for praseodymium compounds. The dominant trivalency of praseodymium limits potential discoveries of emergent quantum states in itinerant $4f^1$ systems accessible using Pr⁴⁺-based compounds. Here, we use in situ powder x-ray diffraction and in situ electron energy-loss spectroscopy (EELS) to identify an intermetallic example of a dominantly Pr⁴⁺ state in the polymorphic system Pr₂Co₃Ge₅. The structure-valence transition from a nearly full Pr⁴⁺ electronic state to a typical Pr³⁺ state shows the potential of Pr-based intermetallic compounds to host valence-unstable states and provides an opportunity to discover previously unknown quantum phenomena. In addition, this work emphasizes the need for complementary techniques like EELS when evaluating the magnetic and electronic properties of Pr intermetallic systems to reveal details easily overlooked when relying on bulk magnetic measurements alone.

INTRODUCTION

Crystalline structure plays a key role in controlling thermal decomposition in batteries, improving catalyst efficiency, and the development of quantum materials due to its explicit relationship with electronic structure and chemical behavior. In the latter group, electron-electron interactions result in the formation of strongly correlated electronic states that can be linked to emergent quantum phenomena depending on the presence of specific structural elements (1). For example, in combination with strong electron interactions, nonsymmorphic symmetry elements give rise to topological electronic states (2, 3) and geometrically frustrated lattices to magnetic spin-liquid behavior (4–6), both of which find applications in spintronic and quantum computing (7).

Often, materials obtain their strongly correlated nature from the presence of lanthanide elements with $4f$ electrons at the limit between local moment and itinerant behavior (8–12). Valence instabilities in lanthanide compounds can have substantial impacts on crystal structure and physical properties (13–16). Targeting systems with structural phase transformations can provide an exciting path forward for strongly correlated materials, specifically in identifying valence-unstable states in dominantly trivalent lanthanides like Pr with the opportunity to access technologically relevant quantum states (17–20). Still, Pr compounds are typically trivalent, with only a small number of dominantly tetravalent Pr-containing oxides and fluorides reported (21). Critically, there are no examples of dominantly tetravalent intermetallic compounds leaving much more to explore regarding the impact of Pr⁴⁺

ions on their magnetic properties. Given the link between structural and valence transitions, one avenue for identifying an intermetallic system capable of hosting tetravalent Pr is to target structure types where instabilities in electronic structure and valence are already present.

A particularly deep reservoir for studies of interesting electronic states are compounds with the formula A₂M₃X₅ (A = lanthanide, actinide, Y, Sc; M = transition metal; X = main group metal) where various examples exhibit quantum critical points, unstable valence states, superconductivity, topological semimetallic states, charge density waves, and other phenomena (22). These compounds crystallize in eight known structure types and can be considered polyanionic three-dimensional frameworks of transition and main group metals that are most commonly filled with lanthanide or actinide cations (23). Polymorphism and structural phase transformations between the U₂Co₃Si₅ (*Ibam*) (24), Lu₂Co₃Si₅ (*C2/c* or the nonstandard equivalent *I2/c*) (25), and Sc₂Fe₃Si₅ (*P4/mnc*) (26) structure types have opened avenues of investigation as the formation of metastable structures often leads to emergent physical properties (27–30).

Intrigued by the unstable electronic states and polymorphism in the group 9 germanides (31–35), we recently showed that large single crystals of both m -Pr₂Co₃Ge₅ (Lu₂Co₃Si₅ type, *I2/c*) (36) and o -Pr₂Co₃Ge₅ (U₂Co₃Si₅ type, *Ibam*) (37) can be stabilized at room temperature. In this work, we reveal a second-order structural phase transition between two polymorphs of Pr₂Co₃Ge₅ through complementary in situ powder x-ray diffraction (PXRD) and in situ electron energy-loss spectroscopy (EELS). We demonstrate a relationship between the structural phase transformation and a change in Pr valence from Pr^{3.80(5)+} to Pr^{3.00(5)+}, the first of its kind for an intermetallic compound. We discuss the hallmarks of valence changes and delocalization evident in the Pr and Co electron energy-loss spectra and show how the anisotropic magnetic properties are affected with this change in structure and valence. This work demonstrates how minor changes in crystal structure can be indicative of substantial reconfigurations in electronic and magnetic interactions leading to unexplored and exciting avenues for quantum materials investigations.

¹Department of Chemistry and Biochemistry, Baylor University, Waco, TX 76706, USA. ²Department of Materials Science and Engineering, University of California, Berkeley, Berkeley, CA 94720, USA. ³FAMU-FSU College of Engineering, Department of Mechanical Engineering, Florida State University, Tallahassee, FL 32310, USA. ⁴National High Magnetic Field Laboratory, Florida State University, Tallahassee, FL 32310, USA. ⁵Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA. ⁶National Center for Electron Microscopy, Molecular Foundry, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA. ⁷Department of Physics, Florida State University, Tallahassee, FL 32310, USA.

*Corresponding author. Email: julia_chan@baylor.edu

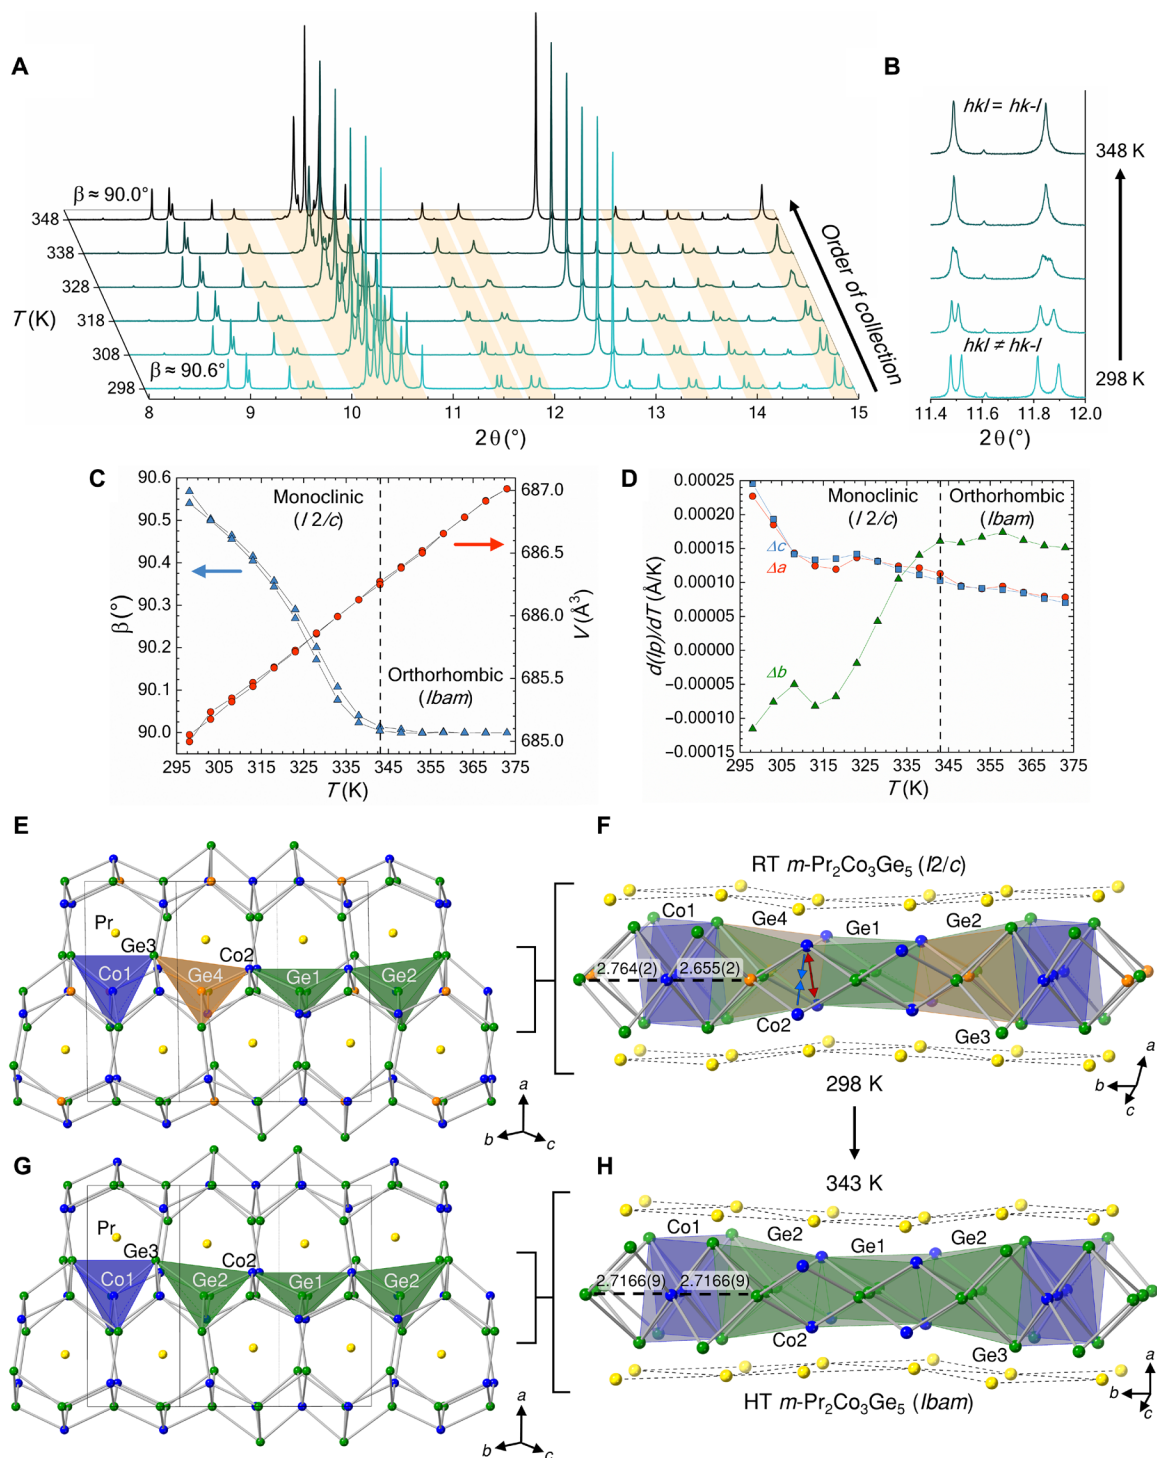


Fig. 1. In situ x-ray diffraction and crystal structure of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$. (A and B) Temperature-dependent x-ray diffraction of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ ($\lambda = 0.458977$ Å) highlighting the structural phase transformation from $I2/c$ to $Ibam$. The change in angle β as related to the change in volume and the change in lattice parameters (lp) are given in (C) and (D), respectively. Dashed lines indicate the conclusion of the second-order structural phase transformation. Crystal structure of room-temperature (E and F) and 343-K (G and H) $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ obtained from synchrotron PXRD where Pr, Co, and Ge are represented with yellow, blue, and green/orange spheres, respectively. Select Co-Ge distances (Å) are shown to illustrate the distortion of the basal atoms of the tetrahedral slab along the crystallographic b direction. Red and blue arrows indicate the separation and contraction of the Co2 dimerization, respectively.

RESULTS

Figure 1A shows the temperature-dependent PXRD patterns from 298 to 348 K taken for m -Pr₂Co₃Ge₅. The convergence of the hkl and $hk-l$ reflections (Fig. 1B) demonstrates that the structure of m -Pr₂Co₃Ge₅ undergoes a second-order structural phase transformation from the space group $I2/c$ (Lu₂Co₃Si₅ structure type) to $Ibam$ (U₂Co₃Si₅ structure type). The β angle, the angle between the a and c lattice directions, of m -Pr₂Co₃Ge₅ begins converging homogeneously toward 90° immediately upon heating from room temperature indicating the beginning of the structural phase transformation and concludes at approximately 343 K. The high-temperature diffraction pattern of m -Pr₂Co₃Ge₅ matches exceedingly well with the room-temperature powder diffraction pattern of o -Pr₂Co₃Ge₅. For comparison, Rietveld refinements of synchrotron PXRD for room-temperature m -Pr₂Co₃Ge₅ and o -Pr₂Co₃Ge₅ are shown in fig. S1, and atomic position and bond distance tables for all structures are provided in tables S1 and S2. Figure 1C shows that while the β angle converges to 90° upon heating, the volume increases linearly with temperature giving no clear indication of a valence change. The first derivative of the change in lattice parameters of m -Pr₂Co₃Ge₅ (Fig. 1D) shows nonlinear change in the b lattice direction in contrast to the a and c directions corresponding with a transformation to the orthorhombic structure type. The length of the b axis is directly related to the β angle of m -Pr₂Co₃Ge₅. As the β angle approaches 90° across the phase transition, the b axis must elongate to compensate for the change since the volume of the Pr₂Co₃Ge₅ unit cell of changes minimally as a function of temperature.

The structural differences of room-temperature and high-temperature m -Pr₂Co₃Ge are shown in Fig. 1 (E to H). Notably, the five coordinate Co2 atoms that were dimerized along the c direction at room temperature undergo the largest change in bond distance within the framework, expanding from $d_{\text{Co2-Co2}} = 3.464(2)$ Å to $d_{\text{Co2-Co2}} = 3.5838(7)$ Å at 343 K. The distortion of the [Co₃Ge₅] framework across the phase transition leads to an increase in Pr local environment symmetry from C_1 to C_3 as the Pr-Ge_{2/4} and Pr-Co₂ distances undergo contractions ranging from $\Delta_{\text{Pr-Ge4}} = -0.029(1)$ Å to $\Delta_{\text{Pr-Ge2}} = -0.019(1)$ Å and elongations ranging from $\Delta_{\text{Pr-Ge2}} = 0.010(1)$ Å to $\Delta_{\text{Pr-Ge4}} = 0.028(1)$ Å. With the existence of a structural phase transformation confirmed in m -Pr₂Co₃Ge₅, temperature-dependent EEL spectra were obtained to determine the structure-valence relationship of the two polymorphs.

In situ EELS collects quantitative information regarding the 4f electronic states of the lanthanide without the influence of sample contributions like thickness and compositional inhomogeneities. Monochromated EELS data were acquired during in situ heating of m -Pr₂Co₃Ge₅ within the TEAM I S/TEM from room temperature to 333 K with an energy resolution of 0.25 eV. The final state of the Pr and Co edges after heating (shown in black in Fig. 2, C and D, respectively) were compared to a sample produced in the room-temperature orthorhombic phase (shown in black in Fig. 2, A and B, respectively) to confirm that the sample had been fully transformed in situ under vacuum. A description of the room-temperature EELS for each polymorph can be found in the Supplementary Materials. During the heating process, the Pr M_{4,5} and Co L_{2,3} edges representing the excitation of core electrons to the partially filled higher energy 4f and 3d orbitals, respectively, were recorded at two intermediate temperature steps.

Upon heating, several changes are observed in the Pr EEL spectra. A lower-energy satellite edge emerged on the Pr M₄ edge of m -Pr₂Co₃Ge₅ (see arrow in Fig. 2A), indicating a change in Pr valence from a dominantly Pr⁴⁺ state to a dominantly Pr³⁺ state most likely

due to an increase in electron filling of the 4f orbitals and reconfiguration of the Pr 4f electronic states. In addition, the edge onset, defined as 10% the peak maxima, increases from 925.02 to 925.65 eV, indicating that the ionization energy required for an electron to transition from the core level to the 4f valence band is greater at 333 K. We also observe an increase in both the M₅:M₄ edge height ratio and a decrease in total integrated area (see Supplementary Materials) upon heating. The reduction in unoccupied 4f states indicated by the decrease in integrated area implies a greater filling of the 4f orbitals in the high-temperature state of m -Pr₂Co₃Ge₅. Multiple linear least squares (MLLS) fits (see Methods) of room-temperature m -Pr₂Co₃Ge₅ reveals a valence state of Pr^{3.80(5)+} compared to Pr^{3.00(5)+} in room-temperature o -Pr₂Co₃Ge₅. At 333 K, the MLLS fits of m -Pr₂Co₃Ge₅ yield a valence of Pr^{3.16(5)+}, in good agreement with the in situ PXRD, which indicate a β angle slightly greater than 90°. It is important to note that the MLLS method relies on the precision of the reference spectra and does not account for differences in coordination environment or data collection methods. While the exact values of the Pr oxidation state may differ from the determined values, the change from tetravalent to trivalent with heating is clear.

The maxima of the Co L_{2,3} edges in m -Pr₂Co₃Ge₅, shown with dotted lines in Fig. 2D, shift to lower energy upon heating while the edge onsets remain relatively constant or shift slightly higher in energy. The L₃:L₂ edge height ratio remains constant across the phase transition. Given the alteration to the Co interatomic distances during the phase transition, it is not unexpected that we observe corresponding energy shifts in the Co L_{2,3} edge maxima and smaller peaks in the edge tails. Specifically, we observe a broader energy-loss range for electron transitions in the room-temperature m -Pr₂Co₃Ge₅ Co spectra compared to those measured at 333 K, indicating an increased diversity in energy transition pathways and, consequently, a greater variety of potentially unoccupied final 3d states.

EEL spectra of Pr valence transitions in cobalt containing oxides indicate nearly identical modifications of Pr M_{4,5} edges as reported here; however, large changes in the Co L_{2,3} edges were not observed despite O K edge modifications indicating alterations to the Co oxidation state (38). Ultimately, in situ EELS conclusively demonstrates that the observed variations in the electronic states of Co and Pr are inherent to the structural differences of the Pr₂Co₃Ge₅ polymorphs.

While we would expect a reduction in effective magnetic moment, magnetic saturation moment, and magnetic entropy associated with the nearly tetravalent Pr state of m -Pr₂Co₃Ge₅ when compared to the room-temperature stabilized o -Pr₂Co₃Ge₅, magnetic and transport measurements of both polymorphs indicate that this is not the case. The temperature-dependent magnetic susceptibility is shown in Fig. 3 and fig. S5 and are summarized in table S3. The differences in the magnetic ordering of the two polymorphs is most visible with applied fields of $H = 0.05$ T parallel to the a crystallographic direction, where two ordering events, $T_{\text{sp}} = 30.8$ K and $T_{\text{M}} = 3.4$ K, are visible for o -Pr₂Co₃Ge₅ that shift to higher temperatures, $T_{\text{sp}} = 35.3$ K and $T_{\text{M}} = 10$ K, for m -Pr₂Co₃Ge₅ (Fig. 3A).

The inverse susceptibility data indicates a linear Curie-Weiss dependence. Both polymorphs have an effective magnetic moment $\mu_{\text{eff}} \sim 4.0 \mu_{\text{B}}/\text{Pr}$, elevated from the calculated value of a Pr³⁺ ion, $\mu_{\text{calc}} = 3.58 \mu_{\text{B}}/\text{Pr}^{3+}$, implying a Co contribution to the magnetic moment. Weiss constants for o -Pr₂Co₃Ge₅ and m -Pr₂Co₃Ge₅, summarized in table S3, are consistent from $H = 0.05$ to 0.5 T and indicate dominant antiferromagnetic interactions along the a direction and dominant ferromagnetic interactions along the c direction. The

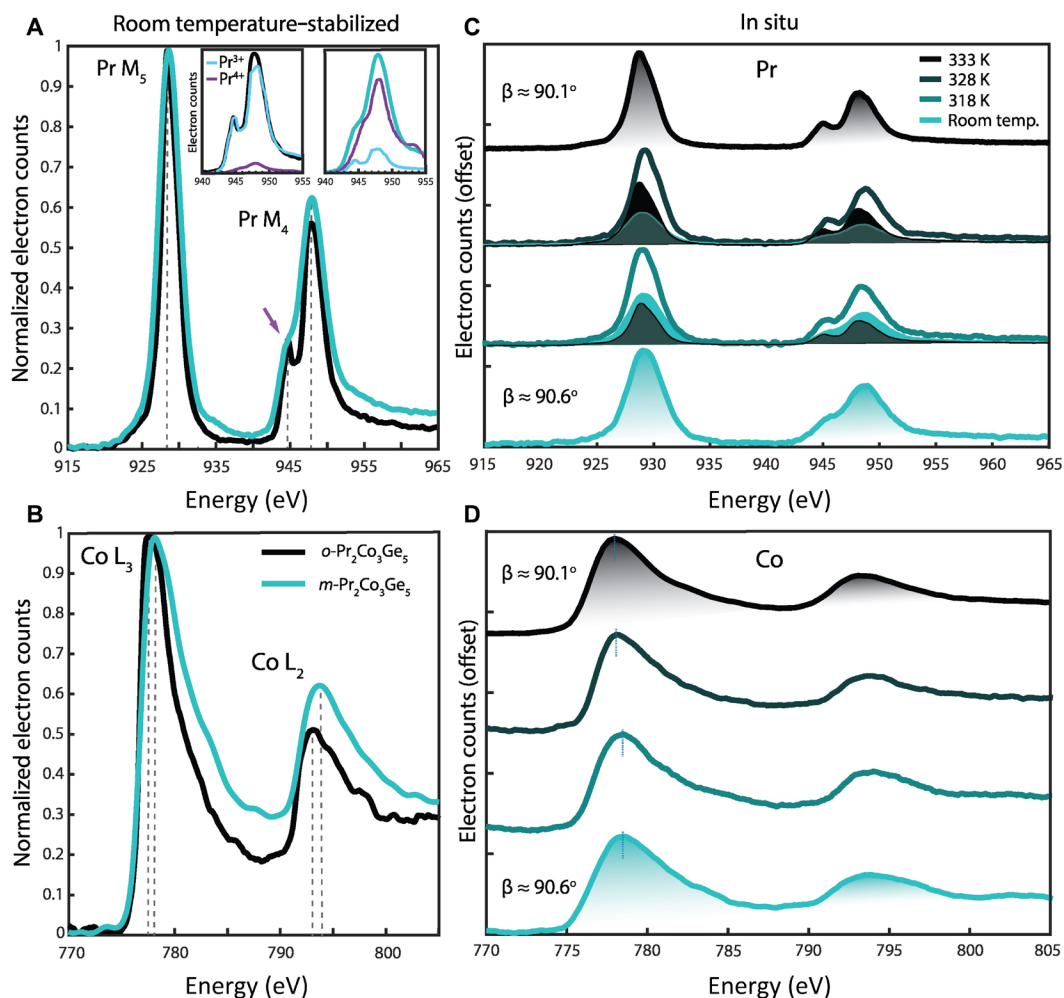


Fig. 2. Room-temperature and in situ EEL spectra of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$. Core-loss EELS of the Pr $M_{4,5}$ (A) and Co $L_{2,3}$ edges (B) for room-temperature $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ (blue) and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ (black). Dashed lines indicate the peak maxima, highlighting differences in the distribution of density of states between the two structures. Pr valency was determined by fitting reference $M_{4,5}$ spectra for Pr^{3+} and Pr^{4+} (see Methods) to the acquired data, as shown in the inset of (A). The M_4 edge feature at 945 eV (marked with an arrow) is a signature of Pr^{3+} . This feature increases in prominence when the sample undergoes transformation. Temperature-dependent EEL spectra across the structural phase transformation are shown in (C and D). The Pr $M_{4,5}$ edges correspond to $4f$ orbital occupancy and the Co $L_{2,3}$ edges to $3d$ occupancy. The shading in (C) shows the linear fit contributions of the initial and final structures' $M_{4,5}$ edges to the spectra of the intermediate structures, indicating a gradual transition in Pr valency with structural transformation. The total integrated area of the spectra taken at room temperature and 333 K are shaded beneath their respective curves. Data were normalized on the basis of the M_5 or L_3 edge maxima.

potential for Co magnetic contribution prevents an unambiguous quantification of Pr moment between the two polymorphs through bulk magnetic measurement and will require magnetic structure determination (e.g., using neutron scattering). However, the magnetic contribution of Co can be estimated using the oxidation states determined from EELS (see Methods), resulting in $\mu_{\text{calc}} = 2.32 \mu_{\text{B}}/\text{Co}$ for $\text{Pr}^{3.80(5)+}$ in $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $\mu_{\text{calc}} = 1.35 \mu_{\text{B}}/\text{Co}$ for $\text{Pr}^{3.00(5)+}$ in $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$. On the basis of these calculations, the Co contribution to the magnetic moment is decreased in $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$, countering the increased Pr magnetic contribution from the trivalent oxidation state.

From field-dependent magnetization applied along the a direction at 20 K (Fig. 3, B and C, and figs. S6 and S7), $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ attains a saturation moment of $\mu_{\text{sat}} = 1.36 \mu_{\text{B}}/\text{F.U.}$ and $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ a value of $\mu_{\text{sat}} = 1.66 \mu_{\text{B}}/\text{F.U.}$, far below the expected saturation moment for

Pr^{3+} ($\mu_{\text{sat}} = 6.40 \mu_{\text{B}}/\text{F.U.}$) or Pr^{4+} ($\mu_{\text{sat}} = 4.28 \mu_{\text{B}}/\text{F.U.}$) assuming no Co contribution. When measured along the c direction at 1.8 K (figs. S6 and S7), the magnetic saturation is higher, $\mu_{\text{sat}} = 3.66$ and $2.60 \mu_{\text{B}}/\text{F.U.}$ for $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$, respectively, but this is still less than half the expected value based on the oxidation states determined from EELS. In both cases, it is likely that the reduced magnetic saturation value can be attributed to crystal electric field splitting of the full J multiplets; however, additional measurements such as inelastic neutron scattering are needed to understand the crystal electric field splitting. The monoclinic polymorph exhibits multiple metamagnetic transitions at fields less than 0.7 T applied along the a direction while the orthorhombic polymorph does not. In addition, $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ saturates more rapidly up to 0.7 T than $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$, attaining magnetizations of 0.60 and 0.30 T, respectively. Similar behavior is observed with magnetic field applied

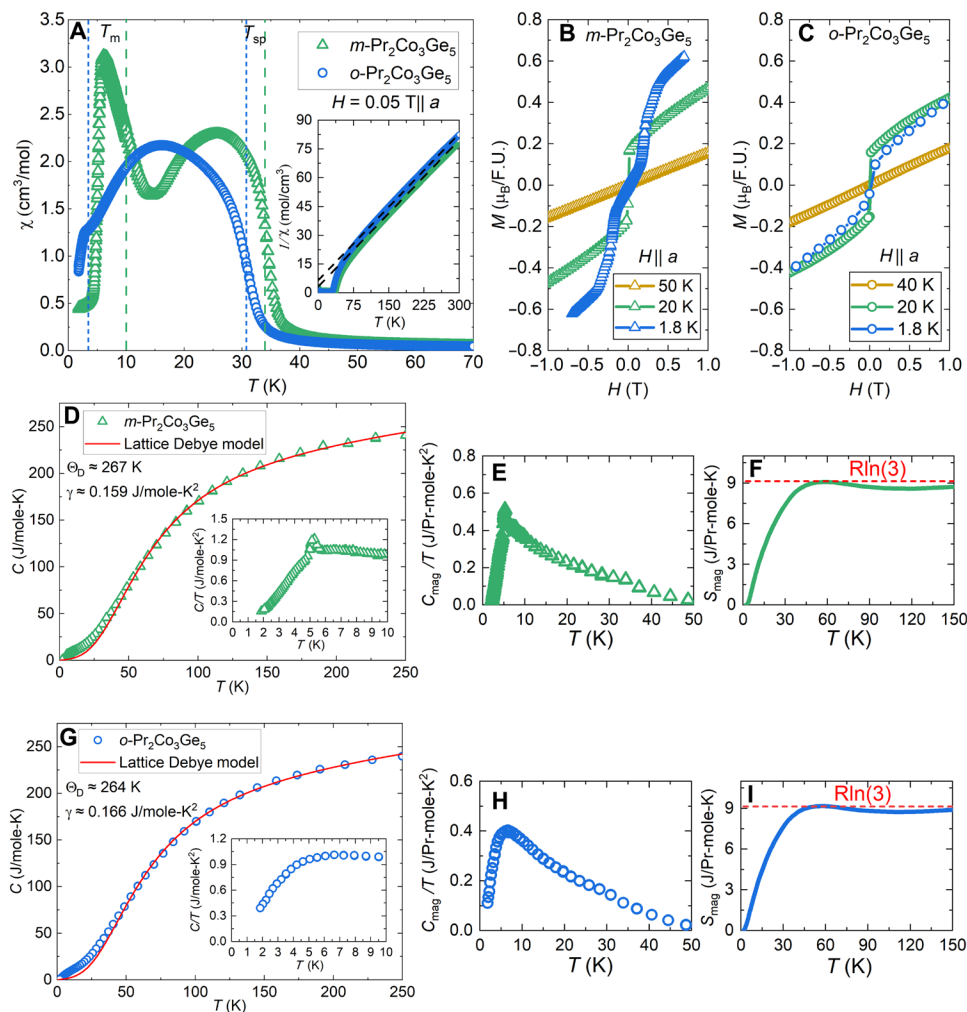


Fig. 3. Magnetic and transport properties of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$. (A) Zoomed temperature-dependent magnetic susceptibility of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ at $H = 0.05 \text{ T} \parallel a$. The inset shows the inverse magnetic susceptibility and Curie-Weiss fit for the entire temperature range. (B and C) Zoomed field-dependent magnetization with $H \parallel a$ per formula unit of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ (triangles) and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ (circles) at $T = 1.8, 20, \text{ and } 40, \text{ or } 50 \text{ K}$ (blue, green, and yellow, respectively). Magnetic data for $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ were obtained from prior work (37). (D and G) Temperature-dependent heat capacity with a Lattice Debye fit for $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$, respectively. The insets show the low-temperature behavior of the heat capacity. (E and H) Magnetic contribution to the heat capacity. (F and I) Temperature-dependent magnetic entropy.

along the c -direction, where the monoclinic polymorph is more responsive to weak magnetic fields.

The heat capacity data of the two polymorphs is shown in Fig. 3, D and G. Above 50 K, the two polymorphs are indistinguishable, which is expected given that the similarities between the lattices are likely to produce similar phonon behaviors. The broad magnetic contributions below 50 K in both polymorphs are expected from the ferromagnetic ordering observed in susceptibility measurements and show that the initial ordering for both polymorphs is not abrupt, possibly because of magnetic frustration. The distinct lambda feature at 5 K in $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ (Fig. 3D, inset, and E) is absent in $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ (Fig. 3, G, inset, and H) and corresponds to the prominent spin reorientation observed at 10 K in temperature-dependent magnetic susceptibility measurements. To obtain the magnetic contribution to the specific heat and the magnetic entropy of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$, we fit the heat capacity to a lattice-Debye model (Methods)

and subtracted it from the measured heat capacities of each polymorph (Fig. 3, F and I, respectively). For both polymorphs, the experimental magnetic entropy is reduced from a theoretical value of either $R\ln(9)$ for Pr^{3+} or $R\ln(6)$ for Pr^{4+} each attaining a value of $R\ln(3)$ at 50 K. This is consistent with the effects of crystal field splitting but may be difficult to interpret because of the presence of Co magnetism. The Sommerfeld coefficients are approximately $\gamma = 0.159 \text{ J/mol}\cdot\text{K}^2$ for $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $\gamma = 0.166 \text{ J/mol}\cdot\text{K}^2$ for $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ indicating a moderately correlated system that, when considered with the broad curvature in electrical resistivity measurements observed in prior work (36, 37), could suggest Kondo lattice behavior.

DISCUSSION

The large change in Pr valence is notable given the unit cell volume of room-temperature $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ sees a contraction of only

$\Delta V = -0.52(1) \text{ \AA}^3$ when compared to the high-temperature transformed $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$. In addition, neither the Pr-Ge, nor the Pr-Co interatomic distances undergo substantial contraction to accommodate the smaller atomic radii of the Pr^{4+} dominant state in room-temperature $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ relative to the Pr^{3+} state at 343 K. However, lattice volume contraction does not always directly correlate with the degree of valence transition (39). Upon heating, Pr transforms from an 8-coordinate system in $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ to a 12-coordinate system in $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$, which could motivate a change in interaction of the Pr $4f$ and conduction electrons. The effects of local point group symmetry on the valence behavior of Pr are well known, where loss of cubic symmetry typically generates a singlet ground state and lack of strong Kondo interactions unless a low-lying singlet state can form (40–43). The increase in point symmetry from $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ to $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ could tune the crystal electric field of Pr from a quasi-doublet state to a singlet state that, given strong enough hybridization with neighboring p and d electrons, could motivate a transition from an intermediate valent state like what has been described for Pr-based skutterudites (44) to a fully trivalent state. The largely reduced saturation magnetic moments and experimental magnetic entropies for both polymorphs suggest strong crystal electric field splitting of the Pr J multiplets. However, in this case, larger differences between the two polymorphs' experimental magnetic entropies and Sommerfeld coefficients would be expected, as these metrics are strongly tied to the crystal field splitting schemes. It is possible that the Co contribution to the magnetic moment is adding additional complexity to the interpretation of ΔS_{mag} and γ .

The loss of Co dimerization across the structural phase transformation of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ suggests that the structural dimorphism could be motivated by an electronic instability due to an unfilled transition metal valence shell, as previously shown for many binary intermetallic compounds (45). To account for this lack of electrons, transition metal–transition metal (M–M) bonding occurs, effectively reducing the required electron count from $18 e^-/M$ to some $18-n e^-/M$, where n is the number of electron pairs formed via M–M bonding. While more complex bonding analysis is required to fully grasp the influence of Co–Co bonding on the oxidation state of Pr in $\text{Pr}_2\text{Co}_3\text{Ge}_5$, it would not be an isolated case. On the basis of spectral and structural evidence, however, the behavior of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ is distinct from these previous observations in that both the lanthanide and transition metal become more oxidized without marked changes in bond lengths or unit cell size. The lack of electron transfer between the lanthanide and transition metals, as observed in other systems like CeRhGe (46), suggests that the Ge atoms are withdrawing electrons. The determination of electron transfer and bonding in lanthanide–transition metal–germanides is a complex issue that is still under investigation due to the similar electronegativities of group 8 to 10 transition metals and Ge (47). Still, Ge has been determined to participate in strong polar-covalent interactions with alkali metals and La (48). It is possible that the strong lanthanide–transition metal interactions exhibited in the $4d$ transition metal lanthanide germanide systems (49, 50) departs from what is observed for $\text{Pr}_2\text{Co}_3\text{Ge}_5$ because of the lower electronegativities of the $3d$ transition metals. While the role of the transition metal and tetrel elements in the formation of tetravalent Pr are not presently clear, we can broadly state that further investigations should be focused toward $3d$ transition metal germanides that likely have electronic instabilities, i.e., structural phase transformations. Naturally, this demonstrates the importance of future temperature-dependent spectroscopic and structural investigations in the $A_2M_3X_5$

family of compounds, but other tetragonal to monoclinic deformations have been found in systems of the ThCr_2Si_2 (51), BaNiSn_3 (52), and CaBe_2Ge_2 structure types (53) which may also host Pr intermediate valence behavior.

While a combination of computational and inelastic scattering experiments would be required to fully elucidate the mechanism responsible for the nearly Pr^{4+} valence state in $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$, it is most likely that a combination of changing symmetry and $4f$ hybridization across the structural phase transformation are responsible. Tangentially, lattice vibrations could also be playing a role in the structural phase transformation of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$. The configuration of bonds within the constraints of the $18-n$ rule can undergo rearrangement due to electron-phonon interactions as illustrated by the temperature-dependent phase transformation of IrIn_3 (54). The presence of charge density waves in compounds isostructural to $\text{Pr}_2\text{Co}_3\text{Ge}_5$ seems to suggest a complicated interplay between valence, vibrational, and electronic states.

We have shown a marked hidden valence change in a Pr-based intermetallic compound linked to a monoclinic to orthorhombic second-order phase transformation in $\text{Pr}_2\text{Co}_3\text{Ge}_5$. The nature of the Pr valence state in $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ was confirmed through in situ PXRD and in situ EELS across the structural phase transformation of $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$. While the origin of the Pr valence transition is not clear on the basis of bulk heat capacity and magnetic measurements, its implications for understanding the duality between local/itinerant $4f$ states and the moderately correlated nature of $\text{Pr}_2\text{Co}_3\text{Ge}_5$ make it a promising platform for future investigations of Pr-based mixed valent intermetallic compounds. Given the ubiquity of the $\text{U}_2\text{Co}_3\text{Si}_5$ structure type, many more examples of structural phase transformations might be found in the $A_2M_3X_5$ system. Developing our understanding of the relationship between valence and structure in Pr-based intermetallic compounds enables design of strongly correlated materials capable of accessing presently un-found quantum states based on magnetic lanthanides and actinides with unstable valences.

METHODS

Synthesis

$o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ and $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$ were synthesized using the flux growth method, where Sn was the low-melting metal flux and elements were weighed out in the stoichiometric ratio of 3 Pr:2 Co:7 Ge:50 Sn. The reactants were transferred into an alumina Canfield crucible set (55) and sealed in a fused silica tube with $\sim 1/3$ -atm argon gas. For $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$, the ampoule was placed in a furnace set to 300°C , raised to 1175°C at a rate of $150^\circ\text{C}/\text{hour}$, and dwelled for 6 hours, whereas for $m\text{-Pr}_2\text{Co}_3\text{Ge}_5$, the ampoule was raised to 1175°C at a slower rate of $100^\circ\text{C}/\text{hour}$ and dwelled for longer (24 hours). In both cases, the samples were cooled to 815°C at a rate of $3^\circ\text{C}/\text{hour}$ before being removed, inverted, and centrifuged at 815°C to separate excess Sn from the large (1 to 5 mm in length) polyhedral crystals. The remaining Sn flux was etched using 1:1 HCl:H₂O, with a yield of approximately 80%. Almost all reactions produced members of the $\text{Pr}_{n+1}\text{Co}_n\text{Ge}_{3n+1}$ homologous series (56) as a side product, but this phase was easily removed because of its plate like morphology and size (~ 2 mm by ~ 2 mm). In addition, trace amounts of PrCoGe_3 are evident in high-resolution PXRD.

While the synthetic conditions presented above are different for each polymorph, the formation of $o\text{-Pr}_2\text{Co}_3\text{Ge}_5$ is challenging. We

initially attempted to reproduce *o*-Pr₂Co₃Ge₅ by varying the duration of the high-temperature dwell step ranging from 4 to 48 hours but obtained only the monoclinic polymorph. From here, we investigated the possibility that *o*-Pr₂Co₃Ge₅ was a metastable high-temperature polymorph. Reheating and annealing of *m*-Pr₂Co₃Ge₅ sealed in an evacuated quartz ampoule followed by quenching in either ice water, icy brine, or liquid nitrogen were also unsuccessful in stabilizing *o*-Pr₂Co₃Ge₅, but this could be due to the reduced rate of heat transfer caused by the quartz ampoule. We then moved to altering the postsynthetic conditions directly from the final dwell temperature of 815°C including varying the centrifugation speed, precooling the centrifuge with dry ice, and inverting the reaction ampoule directly into liquid nitrogen but were unsuccessful in obtaining the orthorhombic polymorph. While some reactions have been successful in synthesizing *o*-Pr₂Co₃Ge₅, *m*-Pr₂Co₃Ge₅ is the more common product.

Powder x-ray diffraction

High-resolution in situ PXRD data ($\lambda = 0.458977 \text{ \AA}$) were collected in the 2θ range from 0.5° to 28° on a ground single crystal of *m*-Pr₂Co₃Ge₅ at the 11-BM beamline at the Advanced Photon Source of Argonne National Laboratory. TOPAS was used to perform a sequential Rietveld refinement, identifying *m*-Pr₂Co₃Ge₅ as the dominant phase with PrCoGe₃ (less than 1 wt %) and Sn (less than 4 wt %) as impurity phases. The PrCoGe₃ and residual Sn from flux growth most likely originate from excess flux that remained on the surface of the crystal after acid etching. For in situ experiments, samples were placed in Kapton capillaries and heated using a hot gas blower in 5-K increments from 298 to 373 K and back. For each measurement, the sample was held for 30 min at temperature before diffraction data were collected to ensure the sample was at equilibrium.

Anisotropic susceptibility and transport measurements

Magnetic properties measurements were performed on oriented single crystals of *m*-Pr₂Co₃Ge₅ and *o*-Pr₂Co₃Ge₅ using a Quantum Design VSM magnetic property measurement system. For *m*-Pr₂Co₃Ge₅, all anisotropic measurements were performed with crystal oriented relative to the *I*-centered monoclinic unit cell to allow direct comparison between the two polymorphs. The magnetization measurements were performed at constant temperatures of $T = 1.8, 10, 20, 30, 40,$ and 50 K for *o*-Pr₂Co₃Ge₅ and $T = 1.8 \text{ K}$ under applied magnetic fields (H) from -7 to 7 T . For the zero field-cooled and field-cooled magnetic susceptibility measurements, the sample was cooled down to 1.8 K with no applied field before heating to 300 K and cooling back down to 1.8 K with an applied field of $H = 0.2 \text{ T}$. In both cases, single crystals were mounted such that the magnetic fields were parallel to *a*, *b*, and *c* axes. Heat capacity (C) was measured from 1.8 to 250 K using a Quantum Design physical property measurement system.

The magnetic contribution of Co can be estimated using Eq. 1

$$\mu_{\text{eff}}^2 = n_{\text{Pr}}(\mu_{\text{calc}})^2 + n_{\text{Co}}(\mu_{\text{calc}})^2 \quad (1)$$

where μ_{eff} is the effective magnetic moment per formula unit determined from Curie-Weiss fit of the inverse magnetic susceptibility (Fig. 3A, inset), μ_{calc} is the calculated Pr or Co contribution based on valences determined from EELS, n_{Pr} is the number of moles of Pr per formula unit, and n_{Co} is the number of moles of Co per formula unit. For *m*-Pr₂Co₃Ge₅ with $\mu_{\text{eff}} = 5.58 \mu_{\text{B}}/\text{F.U.}$ ($H = 0.05 \text{ T} \parallel a$) and

$\mu_{\text{calc}} = 2.74 \mu_{\text{B}}/\text{Pr}$ for a valence of $\text{Pr}^{3.80(5)+}$, then the expected Co contribution to the effective magnetic moment is $\mu_{\text{calc}} = 2.32 \mu_{\text{B}}/\text{Co}$. Following the same procedure for Pr^{3+} in *o*-Pr₂Co₃Ge₅, we obtain a Co contribution of $\mu_{\text{calc}} = 1.35 \mu_{\text{B}}/\text{Co}$.

The heat capacity was fit to a lattice-Debye model shown in Eq. 2

$$C = \gamma T + C_{\text{D}} \left(\frac{T}{\theta_{\text{D}}} \right)^3 \int_0^{\theta_{\text{D}}/T} \frac{x^4 e^x}{(e^x - 1)^2} dx \quad (2)$$

where $x = \hbar\omega/\kappa_{\text{B}}T$, ω is the Debye frequency, θ_{D} is the Debye temperature, and C_{D} is a constant containing numbers of oscillators and degrees of freedom. To obtain the magnetic contribution to the specific heat and the magnetic entropy, these fits were subtracted from the measured heat capacities of each polymorph.

Energy-dispersive x-ray spectroscopy

Elemental maps were collected in a FEI ThemIS operated at 300 kV with a Super-X energy-dispersive x-ray spectroscopy (EDS) detector. The energy resolution of the system is 140 eV. The composition of *m*-Pr₂Co₃Ge₅ was measured as 17.9-at % (at %) Pr, 35.2-at % Co, and 46.9-at % Ge (Pr₂Co_{3.9}Ge_{5.2}). The composition of *o*-Pr₂Co₃Ge₅ was measured as 17.8-at % Pr, 31.5-at % Co, and 50.7-at % Ge (Pr₂Co_{3.5}Ge_{5.7}). EDS maps were acquired over 5 min from bulk regions of the sample with drift correction enabled. No other elements, including Sn, which is used during flux synthesis, were detected in quantities above their fit errors.

Electron energy-loss spectroscopy

The TEAM I, an aberration-corrected transmission electron microscope, was used to collect dual EELS spectral images in probe-corrected scanning transmission electron microscopy mode that include the zero-loss peak and either the L_{2,3} edges ($2p \rightarrow 3d$) of Co or the M_{4,5} edges ($3d \rightarrow 4f$) of Pr. The following acquisition parameters were used: a 17-mrad convergence angle, 400-mm camera length, 90-meV dispersion, and 2.5-mm energy filtering slit. Core-loss EELS was collected from a 40-nm-thick region of an electron-transparent lamella of *m*-Pr₂Co₃Ge₅. The lamella was tilted off zone axis to avoid orientation-specific channeling effects.

The room-temperature orthorhombic and monoclinic Pr M_{4,5} edges were fit using MLLS to determine the Pr oxidation state. MLLS fits were performed using spectra obtained from Pr₂O₃ and BaPrO₃ as references for Pr³⁺ and Pr⁴⁺, respectively (57, 58). Fitting the edges indicates that the orthorhombic sample is 90 to 100% Pr³⁺ and 0 to 10% Pr⁴⁺ (95% \pm 5% Pr³⁺). As for the monoclinic sample, the valence states are 75 to 85% Pr⁴⁺ and 15 to 25% Pr³⁺ (20% \pm 5% Pr³⁺). The MLLS fits require a trade-off between fitting the fine features and fitting the general edge shapes. The fine features were weighted more heavily, particularly those visible in the M₄ edge, in determination of oxidation state because of the broadening issues that would influence peak shapes and the dependency of location on the energy axis on crystal structure.

Using a Gatan model 652 double-tilt heating holder, the temperature of the lamella was raised from room temperature (approximately 297 K) until changes in the Pr were first observed. This occurred around 318 K. The temperature was held for 2 min, and then EELS images from both the Co L_{2,3} and Pr M_{4,5} energy regimes were collected. The temperature was then raised to 328 K, and spectral images were collected again following the same procedure. Last, the holder temperature was raised to 333 K, held at that temperature for 2 min,

and then allowed to cool back to room temperature before EELS was performed. There is an estimated 5-K systematic error in the temperature control of the heating holder within this temperature range.

Supplementary Materials

This PDF file includes:

Supplementary Text

Figs. S1 to S7

Tables S1 to S3

References

REFERENCES AND NOTES

- Y.-F. Yang, An emerging global picture of heavy fermion physics. *J. Phys. Condens. Matter* **35**, 103002 (2022).
- S. E. Grefe, H.-H. Lai, S. Paschen, Q. Si, Weyl-Kondo semimetals in nonsymmorphic systems. *Phys. Rev. B* **101**, 075138 (2020).
- L. Chen, C. Setty, H. Hu, M. G. Vergniory, S. E. Grefe, L. Fischer, X. Yan, G. Eguchi, A. Prokofiev, S. Paschen, J. Cano, Q. Si, Topological semimetal driven by strong correlations and crystalline symmetry. *Nat. Phys.* **18**, 1341–1346 (2022).
- W. Wittczak-Krempa, G. Chen, Y. B. Kim, L. Balents, Correlated quantum phenomena in the strong spin-orbit regime. *Annu. Rev. Condens. Matter Phys.* **5**, 57–82 (2014).
- H. Zhao, J. Zhang, M. Lyu, S. Bachus, Y. Tokiwa, P. Gegenwart, S. Zhang, J. Cheng, Y.-F. Yang, G. Chen, Y. Isikawa, Q. Si, F. Steglich, P. Sun, Quantum-critical phase from frustrated magnetism in a strongly correlated metal. *Nat. Phys.* **15**, 1261–1266 (2019).
- M. Kavai, J. Friedman, K. Sherman, M. Gong, I. Giannakis, S. Hajinazar, H. Hu, S. E. Grefe, J. Leshen, Q. Yang, S. Nakatsuji, A. N. Kolmogorov, Q. Si, M. Lawler, P. Aynajian, Inhomogeneous Kondo-Lattice in geometrically frustrated Pr₂IrO₇. *Nat. Commun.* **12**, 1377 (2021).
- F. Giustino, J. H. Lee, F. Trier, M. Bibes, S. M. Winter, R. Valenti, Y.-W. Son, L. Taillefer, C. Heil, A. I. Figueroa, B. Plaçais, Q. Wu, O. V. Yazyev, E. P. A. M. Bakkers, J. Nygård, P. Forn-Díaz, S. De Franceschi, J. W. McIver, L. E. F. F. Torres, T. Low, A. Kumar, R. Galceran, S. O. Valenzuela, M. V. Costache, A. Manchon, E.-A. Kim, G. R. Schleder, A. Fazio, S. Roche, The 2021 quantum materials roadmap. *J. Phys. Mater.* **3**, 042006 (2020).
- H. Q. Yuan, F. M. Grosche, M. Deppe, C. Geibel, G. Sparr, F. Steglich, Observation of two distinct superconducting phases in CeCu₂Si₂. *Science* **302**, 2104–2107 (2003).
- R. T. Macaluso, S. Nakatsuji, K. Kuga, E. L. Thomas, Y. Machida, Y. Maeno, Z. Fisk, J. Y. Chan, Crystal structure and physical properties of polymorphs of LnAlB₄ (Ln = Yb, Lu). *Chem. Mater.* **19**, 1918–1922 (2007).
- P. S. Riseborough, J. M. Lawrence, Mixed valent metals. *Rep. Prog. Phys.* **79**, 084501 (2016).
- K. Kuga, Y. Matsumoto, M. Okawa, S. Suzuki, T. Tomita, K. Sone, Y. Shimura, T. Sakakibara, D. Nishio-Hamane, Y. Karaki, Y. Takata, M. Matsunami, R. Eguchi, M. Taguchi, A. Chainani, S. Shin, K. Tamasaku, Y. Nishino, M. Yabashi, T. Ishikawa, S. Nakatsuji, Quantum valence criticality in a correlated metal. *Sci. Adv.* **4**, eaao3547 (2018).
- L. Prochaska, X. Li, D. C. MacFarland, A. M. Andrews, M. Bonta, E. F. Bianco, S. Yazdi, W. Schrenk, H. Detz, A. Limbeck, Q. Si, E. Ringe, G. Strasser, J. Kono, S. Paschen, Singular charge fluctuations at a magnetic quantum critical point. *Science* **367**, 285–288 (2020).
- A. Jayaraman, V. Narayanamurti, E. Bucher, R. G. Maines, Continuous and discontinuous semiconductor-metal transition in samarium monochalcogenides under pressure. *Phys. Rev. Lett.* **25**, 1430–1433 (1970).
- I. Jarrige, H. Yamaoka, J. P. Rueff, J. F. Lin, M. Taguchi, N. Hiraoka, H. Ishii, K. D. Tsuei, K. Imura, T. Matsumura, A. Ochiai, H. S. Suzuki, A. Kotani, Unified understanding of the valence transition in the rare-earth monochalcogenides under pressure. *Phys. Rev. B* **87**, 115107 (2013).
- Y.-F. Liao, B. Tegomo Chiogo, T. Clause, T. Mazet, K.-D. Tsuei, D. Malterre, A. Chainani, Dual kondo effect charge ordering and zero thermal expansion in a correlated intermetallic. *Commun. Mater.* **3**, 23 (2022).
- M. Ye, M. J. G. von Westarp, S.-M. Souliou, M. Peters, R. Möller, K. Kliemt, M. Merz, R. Heid, C. Krellner, M. Le Tacon, Strong electron-phonon coupling and enhanced phonon Grüneisen parameters in valence-fluctuating metal EuPd₂Si₂. *Phys. Rev. B* **107**, 195111 (2023).
- S.-H. Jang, R. Sano, Y. Kato, Y. Motome, Antiferromagnetic Kitaev interaction in *f*-electron based honeycomb magnets. *Phys. Rev. B* **99**, 241106 (2019).
- V. Chaturvedi, S. Ghosh, D. Gautreau, W. M. Postiglione, J. E. Dewey, P. Quarterman, P. P. Balakrishnan, B. J. Kirby, H. Zhou, H. Cheng, A. Huon, T. Charlton, M. R. Fitzsimmons, C. Korostynski, A. Jacobson, L. Figari, J. G. Barriocanal, T. Birol, K. A. Mkhoyan, C. Leighton, Room-temperature valence transition in a strain-tuned perovskite oxide. *Nat. Commun.* **13**, 7774 (2022).
- A. Ramanathan, J. Kaplan, D.-C. Sergentou, J. A. Branson, M. Ozerov, A. I. Kolesnikov, S. G. Minasian, J. Autschbach, J. W. Freeland, Z. Jiang, M. Mourigal, H. S. La Pierre, Chemical design of electronic and magnetic energy scales of tetravalent praseodymium materials. *Nat. Commun.* **14**, 3134 (2023).
- A. Ramanathan, E. D. Walter, M. Mourigal, H. S. La Pierre, Increased crystal field drives intermediate coupling and minimizes decoherence in tetravalent praseodymium qubits. *J. Am. Chem. Soc.* **145**, 17603–17612 (2023).
- T. P. Gomba, A. Ramanathan, N. T. Rice, H. S. La Pierre, The chemical and physical properties of tetravalent lanthanides: Pr, Nd, Tb, and Dy. *Dalton Trans.* **49**, 15945–15987 (2020).
- K. W. Brown, M. A. Plata, M. E. Raines, J. Y. Chan, Structural and Physical Properties of R₂M₃X₅ Compounds, in *Handbook on the Physics and Chemistry of Rare Earth Elements*, J.-C. G. Bünzli, S. M. Kauzlarich, Eds. (Elsevier, 2023), vol. 64, chap. 330, pp. 1–92.
- D. E. Bugaris, C. D. Malliakas, S. L. Bud'ko, N. P. Calta, D. Y. Chung, M. G. Kanatzidis, Flux crystal growth of the RE₂Ru₃Ge₅ (RE = La, Ce, Nd, Gd, Tb) series and their magnetic and metamagnetic transitions. *Inorg. Chem.* **56**, 14584–14595 (2017).
- L. G. Aksel'rud, Y. P. Yarmolyuk, E. I. Gladyshevskij, Kristallicheskaya structure soedineniya U₂Co₃Si₅. *Kristallografiya* **22**, 861 (1977).
- B. Chabot, E. Parthé, Dy₂Co₃Si₅, Lu₂Co₃Si₅, Y₂Co₃Si₅ and Sc₂Co₃Si₅ with a monoclinic Structural deformation variant of the orthorhombic U₂Co₃Si₅ structure type. *J. Less-Common Met.* **106**, 53–59 (1985).
- O. I. Bodak, B. Y. Kotur, V. I. Yarovets, E. I. Gladyshevskii, Kristallicheskaya struktura soedinenij Sc₂Fe₃Si₅ i Dy₂Fe₃Si₅. *Kristallografiya* **22**, 385–388 (1977).
- D. E. Bugaris, C. D. Malliakas, F. Han, N. P. Calta, M. Sturza, M. J. Krogstad, R. Osborn, S. Rosenkranz, J. P. C. Ruff, G. Trimarchi, S. L. Bud'ko, M. Balasubramanian, D. Y. Chung, M. G. Kanatzidis, Charge density wave in the new polymorphs of RE₂Ru₃Ge₅ (RE = Pr, Sm, Dy). *J. Am. Chem. Soc.* **139**, 4130–4143 (2017).
- C. N. Kuo, C. J. Hsu, C. W. Tseng, W. T. Chen, S. Y. Lin, W. Z. Liu, Y. K. Kuo, C. S. Lue, Charge density wave like behavior with magnetic ordering in orthorhombic Sm₂Ru₃Ge₅. *Phys. Rev. B* **101**, 155140 (2020).
- R. Sokkalingam, G. Lingannan, M. Sundaramoorthy, C. S. Lue, C. N. Kuo, B. Joseph, S. Arumugam, Evidence of structural modulations induced by a charge density wave transition in orthorhombic Sm₂Ru₃Ge₅. *Solid State Commun.* **372**, 115293 (2023).
- Z. Li, X. Chen, X. Liu, Z. Yu, N. Su, Z. Liu, W. Xia, J. Jiao, C. Zhou, L. Zhang, Z. Dong, X. Wang, N. Yu, Z. Zou, J. Ma, J. Cheng, Z. Zhong, Y. Guo, Suppressed charge-density-wave, robust ferromagnetism and lifshitz transition in Sm₂Ru₃Ge₅ crystal under high pressure. *J. Alloys Compd.* **937**, 168337 (2023).
- Z. Hossain, H. Ohmoto, K. Umeo, F. Iga, T. Suzuki, T. Takabatake, N. Takamoto, K. Kindo, Antiferromagnetic kondo-lattice systems Ce₂Rh₃Ge₅ and Ce₂Ir₃Ge₅ with moderate heavy-fermion behavior. *Phys. Rev. B* **60**, 10383–10387 (1999).
- S. Layek, V. K. Anand, Z. Hossain, Valence fluctuation in Ce₂Co₃Ge₅ and crystal field effect in Pr₂Co₃Ge₅. *J. Magn. Magn. Mater.* **321**, 3447–3452 (2020).
- S. Ramakrishnan, A. Schönleber, T. Rekis, N. van Well, L. Noohinejad, S. van Smaalen, M. Tolkiehn, C. Paulmann, B. Bag, A. Thamizhavel, D. Pal, S. Ramakrishnan, Unusual charge density wave transition and absence of magnetic ordering in Er₂Ir₃Si₅. *Phys. Rev. B* **101**, 060101 (2020).
- S. Ramakrishnan, A. Schönleber, J.-K. Bao, T. Rekis, S. R. Kotla, A. M. Schaller, S. van Smaalen, L. Noohinejad, M. Tolkiehn, C. Paulmann, N. S. Sangeetha, D. Pal, A. Thamizhavel, S. Ramakrishnan, Modulated crystal structure of the atypical charge density wave state of single-crystal Lu₂Ir₃Si₅. *Phys. Rev. B* **104**, 054116 (2021).
- S. Ramakrishnan, J. Bao, C. Eisele, B. Patra, M. Nohara, B. Bag, L. Noohinejad, M. Tolkiehn, C. Paulmann, A. M. Schaller, T. Rekis, S. R. Kotla, A. Schönleber, A. Thamizhavel, B. Singh, S. Ramakrishnan, S. van Smaalen, Coupling between charge density wave ordering and magnetism in Ho₂Ir₃Si₅. *Chem. Mater.* **35**, 1980–1990 (2023).
- T. M. Kyrk, J. P. Scheifers, K. Thanabalasingam, G. T. McCandless, D. P. Young, J. Y. Chan, It runs in the BaAl₄ family: relating the structure and properties of middle child Ln₂Co₃Ge₅ (Ln = Pr, Nd, and Sm) to its siblings LnCo₂Ge₂ and LnCoGe₃. *Inorg. Chem.* **60**, 15343–15350 (2021).
- T. M. Kyrk, J. Galeano-Cabral, E. R. Kennedy, K. Wei, G. T. McCandless, M. C. Scott, R. E. Baumbach, J. Y. Chan, Anisotropic magnetic and transport properties of orthorhombic o-Pr₂Co₃Ge₅. *J. Phys. Mater.* **5**, 044007 (2022).
- A. Gulec, D. Phelan, C. Leighton, R. F. Klie, Simultaneous first-order valence and oxygen vacancy order/disorder transitions in (Pr_{0.85}Y_{0.15})_{0.7}Ca_{0.3}CoO_{3-δ} via analytical transmission electron microscopy. *ACS Nano* **10**, 938–947 (2016).
- P. Weidner, K. Keulzer, R. Löhe, B. Roden, J. Röhlér, B. Wittershagen, D. Wohlleben, High temperature susceptibility, valence and volume anomaly of some Ce-compounds. *J. Magn. Magn. Mater.* **47–48**, 75–78 (1985).
- R. M. White, P. Fulde, Excitonic mass enhancement in praseodymium. *Phys. Rev. Lett.* **47**, 1540–1542 (1981).
- V. K. Anand, Z. Hossain, C. Geibel, Magnetic order in Pr₂Pd₃Ge₅ and possible heavy-fermion behavior in Pr₂Rh₃Ge₅. *Phys. Rev. B* **77**, 184407 (2008).
- T. A. Sayles, R. E. Baumbach, W. M. Yuhasz, M. B. Maple, Ł. Bochenek, R. Wawryk, T. Cichorek, A. Pietraszko, Z. Henkie, P.-C. Ho, Superconductivity and crystalline electric field effects in the filled skutterudite PrRu₄Si₁₂. *Phys. Rev. B* **82**, 104513 (2010).
- A. Sakai, S. Nakatsuji, Kondo effects and multipolar order in the cubic PrTr₂Al₂₀ (Tr=Ti, V). *J. Phys. Soc. Jpn.* **80**, 063701 (2011).

44. J. Otsuki, H. Kusunose, Y. Kuramoto, Theory of crystalline electric field and Kondo effect in Pr kutterudites. *J. Physical Soc. Jpn.* **74**, 200–208 (2005).
45. V. J. Yannello, D. C. Fredrickson, Generality of the 18-n rule: Intermetallic structural chemistry explained through isolobal analogies to transition metal complexes. *Inorg. Chem.* **54**, 11385–11398 (2015).
46. V. Svitylyk, W. Hermes, B. Chevalier, S. F. Matar, E. Gaudin, D. Voßwinkel, D. Chernyshov, R.-D. Hoffmann, R. Pöttgen, Change of the cerium valence with temperature – Structure and chemical bonding of HT-CeRhGe. *Solid State Sci.* **21**, 6–10 (2013).
47. D. Zhang, A. O. Olynyk, A. Mar, Three Rh-rich ternary germanides in the Ce–Rh–Ge system. *J. Solid State Chem.* **304**, 122585 (2021).
48. R. Freccero, P. Solokha, S. De Negri, A. Saccone, Y. Grin, F. R. Wagner, Polar-covalent bonding beyond the zintl picture in intermetallic rare-earth germanides. *Chemistry* **25**, 6600–6612 (2019).
49. R. Freccero, S. De Negri, G. Rogl, G. Binder, H. Michor, P. F. Rogl, A. Saccone, P. Solokha, La₂Pd₃Ge₅ and Nd₂Pd₃Ge₅ compounds: Chemical bonding and physical properties. *Inorg. Chem.* **60**, 3345–3354 (2021).
50. R. Freccero, L. C. J. Pereira, P. Solokha, S. De Negri, Flux growth, crystal structure, and chemical bonding of Yb₂PdGe₃, an AlB₂ superstructure within the rare-earth series. *Inorg. Chem.* **62**, 1988–1999 (2023).
51. Y. Lai, K. Wei, G. Chappell, J. Diaz, T. Siegrist, P. J. W. Moll, D. Graf, R. E. Baumbach, Tuning the structural and antiferromagnetic phase transitions in UCr₂Si₂: Hydrostatic pressure and chemical substitution. *Phys. Rev. Mater.* **4**, 075003 (2020).
52. U. Subbarao, S. C. Peter, Crystal growth and properties of YbCuGa₃: First monoclinic system in the RETX₃ family. *Cryst. Growth Des.* **13**, 953–959 (2013).
53. A. Imre, A. Hellmann, A. Mewis, LaPt₂Ge₂ und EuPt₂Ge₂ – Neubestimmung der Kristallstrukturen. *Z. Anorg. Allg. Chem.* **632**, 2217–2221 (2006).
54. A. Lim, D. C. Fredrickson, Entropic control of bonding, guided by chemical pressure: Phase transitions and 18-*n*+*m* isomerism of IrIn₃. *Inorg. Chem.* **62**, 10833–10846 (2023).
55. P. Canfield, T. Kong, U. Kaluarachchi, N. H. Jo, Use of Frit-disc crucibles for routine and exploratory solution growth of single crystalline samples. *Philos. Mag.* **96**, 84–92 (2016).
56. T. M. Kyrk, M. Bravo, G. T. McCandless, S. H. Lapidus, J. Y. Chan, Investigating the A_{n+1}B_nX_{3n+1} homologous series: A new platform for studying magnetic praseodymium based intermetallics. *ACS Omega* **7**, 19048–19057 (2022).
57. J. Herrero-Martin, J. L. Garcia-Muñoz, S. Valencia, C. Frontera, J. Blasco, A. J. Barón-González, G. Subías, R. Abruñán, F. Radu, E. Dudzik, R. Feyerherm, Valence change of praseodymium in Pr_{0.5}Ca_{0.5}CoO₃ investigated by X-ray absorption spectroscopy. *Phys. Rev. B* **84**, 115131 (2011).
58. Q. Lu, G. Vardar, M. Jansen, S. R. Bishop, I. Waluyo, H. L. Tuller, B. Yildiz, Surface defect chemistry and electronic structure of Pr_{0.1}Ce_{0.9}O_{2-δ} revealed in operando. *Chem. Mater.* **30**, 2600–2606 (2018).
59. P. Solokha, R. Freccero, S. De Negri, D. M. Proserpio, A. Saccone, The R₂Pd₃Ge₅ (R = La–Nd, Sm) Germanides: Synthesis, crystal structure and symmetry reduction. *Struct. Chem.* **27**, 1693–1701 (2016).
60. B. Chabot, E. Parthé, Ce₂Co₃Si₅ and R₂Ni₃Si₅ (R = Ce, Dy, Y) with the orthorhombic U₂Co₃Si₅-type structure and the structural relationship with the tetragonal Sc₂Fe₃Si₅-type structure. *J. Less-Common Met.* **97**, 285–290 (1984).
61. B. Chevalier, T. Roisnel, J. Etourneau, Magnetic structure of U₂(Ru_{0.65}Rh_{0.35})₃Si₅ silicide. *J. Magn. Magn. Mater.* **134**, 88–94 (1994).
62. T. Kawai, H. Muranaka, T. Endo, N. Duc Dung, Y. Doi, S. Ikeda, T. D. Matsuda, Y. Haga, H. Harima, R. Settai, Y. Ōnuki, Split fermi surface properties of LaTGe₃ (T: Transition Metal) and PrCoGe₃ with the non-centrosymmetric crystal structure. *J. Phys. Soc. Jpn.* **77**, 064717 (2008).
63. A. Szytula, J. Leciejewicz, H. Bińczycka, Crystal and magnetic structures of PrCo₂Ge₂ and HoCo₂Ge₂. *Phys. Stat. Sol. A* **58**, 67–70 (1980).
64. M. Rahm, R. Hoffmann, N. W. Ashcroft, Atomic and ionic radii of elements 1–96. *Chem. A Eur. J.* **22**, 14625–14632 (2016).
65. H. Fukuoka, K. Baba, M. Yoshikawa, F. Ohtsu, S. Yamanaka, High-pressure synthesis and structures of lanthanide germanides of LnGe₅ (Ln=Ce, Pr, Nd, and Sm) isotopic with LaGe₅. *J. Solid State Chem.* **182**, 2024–2029 (2009).
66. H. Fukuoka, M. Yoshikawa, K. Baba, S. Yamanaka, Preparation and structures of lanthanoid germanides, PrGe_{3.36}, NdGe_{3.25}, and TmGe₃ with double square Ge-Mesh structures. *Bull. Chem. Soc. Jpn.* **83**, 323–327 (2010).
67. J. Liu, V. Smetana, K. A. G. Jr, G. J. Miller, V. K. Pecharsky, The crystal structure and magnetic properties of Pr₁₁₇Co_{56.7}Ge₁₁₂. *J. Appl. Phys.* **113**, 17E120 (2013).
68. S. Skanthakumar, J. W. Lynn, C. Mazumdar, R. Nagarajan, L. C. Gupta, Magnetic phase transitions in R₂Ni₃Si₅. *Physica B* **241–243**, 693–695 (1997).
69. A. Gil, M. Kolenda, S. Baran, B. Penc, M. Hofmann, A. Szytula, Neutron diffraction studies of R₂Co₃Si₅ (R = Tb, Dy) and Tb₂Ir₃Si₅ compounds. *Physica B Condens. Matter* **276–278**, 742–743 (2000).
70. L. Durivault, F. Bourée, B. Chevalier, G. André, J. Etourneau, Magnetic ordering in the ternary germanide Ce₂Ni₃Ge₅ as studied by neutron powder diffraction. *J. Magn. Magn. Mater.* **246**, 366–374 (2002).
71. V. K. Anand, D. T. Adroja, C. Ritter, D. Das, H. S. Nair, A. Bhattacharyya, L. Liborio, S. Sturniolo, F. L. Pratt, D. Le, G. Andre, H. Luetkens, A. D. Hillier, Z. Hossain, Magnetic structure and crystal field states of Pr₂Pd₃Ge₅: μ SR and neutron scattering investigations. *Phys. Rev. B* **107**, 104412 (2023).
72. N. N. Efremova, Praseodymium valence state in PrFe₁₀Mo₂, PrNi₅, and PrNi₄M intermetallic compounds (M = Cu, Al, Ga). *Phys. Solid State* **47**, 424–428 (2005).

Acknowledgments: We are grateful to S. Lapidus for helpful suggestions and conversation. **Funding:** J.Y.C. and T.M.K. acknowledge support from the Welch Foundation under award no. AA-2056-20220101 and the U.S. Department of Energy (DOE), Office of Science, Basic Energy Sciences, under award no. DE-SC0022854. This material is based on work supported by the U.S. DOE, Office of Science, Office of Workforce Development for Teachers and Scientists, Office of Science Graduate Student Research (SCGSR) program. The SCGSR program is administered by the Oak Ridge Institute for Science and Education for the DOE under contract no. DE-SC0014664. This research used resources of the Advanced Photon Source; a U.S. DOE Office of Science user facility operated for the DOE Office of Science by Argonne National Laboratory under contract no. DE-AC02-06CH11357. M.C.S. was supported by National Science Foundation STROBE grant DMR-1548924. Work at the Molecular Foundry is supported by the Office of Science, Office of Basic Energy Sciences, of the U.S. DOE under contract no. DE-AC02-05CH11231. R.E.B. was supported by the National Science Foundation through NSF DMR-1904361. The National High Magnetic Field Laboratory is supported by the National Science Foundation through NSF DMR-1644779 and the State of Florida. **Author contributions:** T.M.K. synthesized *m*-Pr₂Co₃Ge₅ and *o*-Pr₂Co₃Ge₅ and collected and analyzed the PXRD data. G.T.M. assisted in the interpretation of the crystallography. E.R.K. collected and analyzed the EEL spectra. J.G.-C. collected and analyzed the magnetic and transport data. T.M.K. and J.Y.C. conceived the study. J.Y.C., R.E.B., and M.C.S. are the principal investigators. **Competing interests:** The authors declare that they have no competing interests. **Data and materials availability:** All data needed to evaluate the conclusions in this paper are present in the paper and/or the Supplementary Materials.

Submitted 9 October 2023
Accepted 27 December 2023
Published 26 January 2024
10.1126/sciadv.adl2818