

Bioactive elements manipulate bone regeneration

Long Bai^{1,2,3,#}, Peiran Song^{1,3,#}, Jiacan Su^{1,2,3,*}

Key Words:

bioactive elements; biomaterials; bone organoid; bone regeneration; controllable release

From the Contents

Introduction	248
The Process of Bone Regeneration	249
The Role of Bioactive Elements in Bone Regeneration	251
Challenges and Perspectives	262

ABSTRACT

While bone tissue is known for its inherent regenerative abilities, various pathological conditions and trauma can disrupt its meticulously regulated processes of bone formation and resorption. Bone tissue engineering aims to replicate the extracellular matrix of bone tissue as well as the sophisticated biochemical mechanisms crucial for effective regeneration. Traditionally, the field has relied on external agents like growth factors and pharmaceuticals to modulate these processes. Although efficacious in certain scenarios, this strategy is compromised by limitations such as safety issues and the transient nature of the compound release and half-life. Conversely, bioactive elements such as zinc (Zn), magnesium (Mg) and silicon (Si), have garnered increasing interest for their therapeutic benefits, superior stability, and reduced biotic risks. Moreover, these elements are often incorporated into biomaterials that function as multifaceted bioactive components, facilitating bone regeneration via release on-demand. By elucidating the mechanistic roles and therapeutic efficacy of the bioactive elements, this review aims to establish bioactive elements as a robust and clinically viable strategy for advanced bone regeneration.

*Corresponding author:

Jiacan Su,
drsujacan@163.com.

#Author equally.

<http://doi.org/10.12336/biomatertransl.2023.04.005>

How to cite this article:

Bai, L.; Song, P.; Su, J. Bioactive elements manipulate bone regeneration. *Biomater Transl.* 2023, 4(4), 248-269.

Introduction

Bone is a complex and hierarchical organ, the remodelling of which depends on specific macro- and micro-environments. The primary function of bone tissue is to provide mechanical stability to the body and protect major organs. Additionally, bone tissue exhibits high metabolic turnover, aiding in maintaining ionic balance within the body.¹⁻³ Diseases or traumatic injuries can impair bone function, making it crucial to restore lost functionality swiftly and efficiently. Autografts and allografts remain the benchmark in tissue engineering, yet their clinical utility is curtailed by supply constraints and the risk of disease transmission.⁴⁻⁶ In light of this, there is an urgent need to develop alternative bone substitutes through bone tissue engineering, which could offer functionalities similar to natural grafts while avoiding associated issues.

For successful bone regeneration, it is vital that bone substitutes mimic the highly ordered steps of bone regeneration to a maximum extent. Bone

repair is a dynamic biological process evolving over time, mainly involving post-operative bleeding, clot formation, inflammatory response, angiogenesis, and new bone formation.⁷ The regulation at each stage impacts subsequent biological events and ultimately determines the pace and quality of bone regeneration. The primary focus has been on integrating growth factors into bone tissue scaffolds or implants.⁸⁻¹⁰ Growth factors like insulin-like growth factors can activate cellular signalling cascades in stem cells surrounding bone lesions, thereby inducing proactive repair, including the angiogenesis process crucial for tissue regeneration.^{11, 12} However, the use of these growth factors presents significant drawbacks, including instability, immunogenicity, and high costs.¹³⁻¹⁵ Recently, many small molecules such as peptides have attracted researchers' attention. Yet, controlling their proper release in the defect area and their low half-life once implanted in the defect area are major barriers to their clinical translation.¹⁶⁻¹⁸



Biomaterials contain bioactive elements for bone repair

In contrast, employing bioactive elements is an appealing option, given their known therapeutic effects, higher stability, and lower risks compared to using biomolecules. The therapeutic elements released from biomaterials can regulate tissue regeneration steps in a manner akin to bioactive molecules. In recent years, researchers have been exploring the role of multiple bioactive elements in bone regeneration. Evidence suggests that elements, such as calcium (Ca),¹⁹ cobalt (Co),²⁰ copper (Cu),²¹ fluoride (F),²² lithium (Li),²³ magnesium (Mg),²⁴ silicon (Si),²⁵ silver (Ag),²⁶ strontium (Sr),²⁷ zinc (Zn),²⁸ can induce osteoprogenitor cell differentiation through growth factor signalling pathways or stimulate other processes supporting bone tissue growth.

Overall, this review meticulously delineates the impact of bioactive elements during various stages of bone regeneration, elucidating their mechanisms in osteoimmunomodulation, orchestrating neuroregulation, stimulating angiogenesis, and promoting osteogenesis (Figure 1). The comprehensive analysis of these bioactive ions not only furnishes a robust theoretical scaffold for ensuing basic research but also unveils novel therapeutic vistas and design principles for clinicians and materials scientists. Especially in the milieu of confronting the limitations inherent to natural grafts and growth factors, the exploration of bioactive elements emerges as a cost-effective, low-risk, and viable avenue for bone regeneration.

Periodic Table of the Elements

■ Osteoimmunomodulation
■ Neuroregulation
■ Angiogenesis
■ Osteogenesis

1 IA H Hydrogen 1.008	2 IIA He Helium 4.002602																	18 VIIIA Ar Argon 39.948
3 Li Lithium 6.94	4 Be Beryllium 9.0121831																	10 Ne Neon 20.1797
11 Na Sodium 22.98976928	12 Mg Magnesium 24.304																	18 Ar Argon 39.948
19 K Potassium 39.0983	20 Ca Calcium 40.078	21 Sc Scandium 44.955912	22 Ti Titanium 47.88	23 V Vanadium 50.9415	24 Cr Chromium 51.9961	25 Mn Manganese 54.938044	26 Fe Iron 55.845	27 Co Cobalt 58.933194	28 Ni Nickel 58.6934	29 Cu Copper 63.546	30 Zn Zinc 65.38	31 Ga Gallium 69.723	32 Ge Germanium 72.630	33 As Arsenic 74.921595	34 Se Selenium 78.9718	35 Br Bromine 79.904	36 Kr Krypton 83.798	
37 Rb Rubidium 85.4678	38 Sr Strontium 87.62	39 Y Yttrium 88.90584	40 Zr Zirconium 91.224	41 Nb Niobium 92.90638	42 Mo Molybdenum 95.94	43 Tc Technetium (98)	44 Ru Ruthenium 101.07	45 Rh Rhodium 102.90550	46 Pd Palladium 106.42	47 Ag Silver 107.8682	48 Cd Cadmium 112.414	49 In Indium 114.818	50 Sn Tin 118.710	51 Sb Antimony 121.760	52 Te Tellurium 127.603	53 I Iodine 126.90447	54 Xe Xenon 131.29	
55 Cs Caesium 132.90545196	56 Ba Barium 137.327	57-71 Lanthanoids	72 Hf Hafnium 178.49	73 Ta Tantalum 180.94788	74 W Tungsten 183.84	75 Re Rhenium 186.207	76 Os Osmium 190.23	77 Ir Iridium 192.222	78 Pt Platinum 195.084	79 Au Gold 196.966569	80 Hg Mercury 200.592	81 Tl Thallium 204.38	82 Pb Lead 207.2	83 Bi Bismuth 208.98040	84 Po Polonium (209)	85 At Astatine (210)	86 Rn Radon (222)	
87 Fr Francium (223)	88 Ra Radium (226)	89-103 Actinoids	104 Rf Rutherfordium (261)	105 Db Dubnium (268)	106 Sg Seaborgium (266)	107 Bh Bohrium (270)	108 Hs Hassium (285)	109 Mt Meitnerium (276)	110 Ds Darmstadtium (281)	111 Rg Roentgenium (282)	112 Cn Copernicium (285)	113 Nh Nihonium (284)	114 Fl Flerovium (289)	115 Mc Moscovium (288)	116 Lv Livermorium (293)	117 Ts Tennessine (294)	118 Og Oganesson (294)	
89 Ac Actinium (227)	90 Th Thorium 232.0377	91 Pa Protactinium 231.03688	92 U Uranium 238.02891	93 Np Neptunium (237)	94 Pu Plutonium (244)	95 Am Americium (243)	96 Cm Curium (247)	97 Bk Berkelium (247)	98 Cf Californium (251)	99 Es Einsteinium (252)	100 Fm Fermium (257)	101 Md Mendelevium (258)	102 No Nobelium (259)	103 Lr Lawrencium (260)				

Figure 1. The role of bioactive elements in bone regeneration. Created with BioRender.com.

The Process of Bone Regeneration

Bone regeneration unfolds through a meticulously orchestrated cascade of biological processes: osteoimmunomodulation, neuroregulation, angiogenesis, and bone formation (Figure 2). Initially, osteoimmunomodulation, mediated by macrophage polarisation, establishes a favourable inflammatory landscape.²⁹ Concurrently, neuroregulation or skeletal interoception, steers physiological responses essential for bone healing.²⁸ Advancing, angiogenesis, directed by endothelial progenitor and mature cells, forms new vasculature, delivering crucial resources to the regenerative callus.³⁰ Lastly, osteogenesis, led by cellular entities like osteoblasts and mesenchymal stem cells (MSCs), governs the synthesis and remodelling of bone tissue.³¹

Osteoimmunomodulation

Osteoimmunomodulation represents a pivotal nexus where the realms of immunology and bone biology converge, under the auspices of bone biomaterials, to orchestrate a harmonious response between bone formation and resorption, thereby augmenting the bone repair capacity.^{19, 32-34} The crucible of this interplay lies in the role of immune cells, notably macrophages, whose interactions with bone cells and biomaterials significantly shape the trajectory and efficacy of bone repair endeavors.³⁵⁻³⁷ Macrophages, serving as the quintessential effector cells in immune responses to implants, are indispensable for promoting osteogenic functionality. The tapestry of immune-bone interplay is further enriched by the polarisation dynamics of macrophages into M1 and M2 subtypes, mediating pro-inflammatory and anti-

1 Organoid Research Center, Institute of Translational Medicine, Shanghai University, Shanghai, China; 2 Department of Orthopedics, Xinhua Hospital Affiliated to Shanghai Jiao Tong University School of Medicine, Shanghai, China; 3 National Center for Translational Medicine (Shanghai) SHU Branch, Shanghai University, Shanghai, China

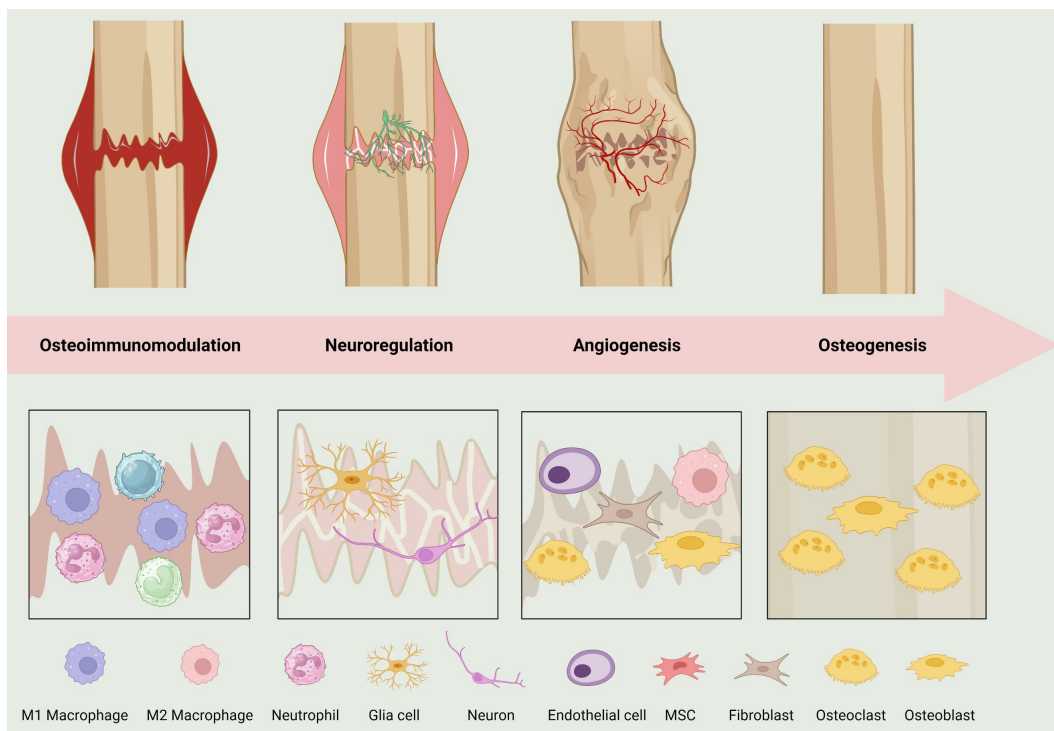


Figure 2. The process of bone regeneration. Created with BioRender.com. MSC: mesenchymal stem cell.

inflammatory responses respectively, which are integral for bone repair across diverse stages.³⁸ While M2 macrophages are emblematic for promoting bone tissue regeneration, the spotlight is gradually shifting towards unraveling the critical role of M1 macrophages in osteoimmunomodulation, particularly during the early inflammatory stages where they enhance the recruitment and commitment of angiogenic and osteogenic precursors.³⁹ Recent scholarly endeavors have also unveiled the central role of exosomes, secreted by macrophages, in mediating osteoimmunomodulation. These exosomes, upon internalisation by pivotal cells engaged in *de novo* bone formation such as endothelial cells and osteoblasts, significantly intervene in osseointegration, thereby opening new frontiers in understanding and leveraging macrophage-mediated immune modulation for enhanced bone repair.⁴⁰ In summation, osteoimmunomodulation, through the lens of macrophage-mediated interactions, unveils a complex yet rich array of mechanisms and interactions that not only deepen the comprehension of bone repair processes but also propel the development of novel therapeutic strategies and bone biomaterials.

Neuroregulation

Neuroregulation, a crucial mechanism orchestrated by the nervous system, governs the physiological and biochemical responses across various systems, organs, and cells in the body.⁴¹ This regulation is facilitated through the release of chemical substances, impacting an array of biological processes. In the realm of bone repair, neuroregulation, either known as skeletal interoception, emerges as a pivotal player in fostering the regeneration of bone tissues. It holds a significant

sway in maintaining the equilibrium of bone mass. Moreover, an assortment of neural factors, including neurotrophic growth factors, neuropeptides, and prostaglandin E2 (PGE2), are known to exercise a substantial influence over the growth, regeneration, and repair processes of bone tissues.⁴² Neuroregulation manoeuvres the balance of bone remodelling through diverse mechanisms, such as the activation of TrkA signalling pathway in osteoblastic cells, modulation of Wnt signalling pathway, and regulation of PGE2 production and secretion, thereby propelling the process of bone rebuilding. The promising horizon of skeletal interoception in bone repair is further bolstered by the supplementary use of PGE2, which, by modulating the proliferation and differentiation of stem cells, and promoting bone regeneration, augments the processes of bone repair and regeneration.⁴³⁻⁴⁶ Hence, the domain of neuroregulation not only unveils a profound understanding of the intricate interplay between neural and bone tissues but also heralds a promising avenue for advancements in bone repair methodologies, thereby contributing significantly to the broader spectrum of regenerative medicine.

Angiogenesis

Angiogenesis, the formation of new blood vessels from pre-existing vessels, is a cornerstone of bone repair, serving as the conduit for essential resources to the regenerative callus, a temporary tissue formed during bone healing. This process is orchestrated by endothelial progenitor cells and mature endothelial cells through recruitment, proliferation, differentiation, and reconstruction, facilitating the sprouting of microvessels from existing blood vessels.^{47, 48} The newly formed vasculature is indispensable for delivering oxygen

Biomaterials contain bioactive elements for bone repair

and nutrients to the metabolically active regenerating callus and facilitating the migration of inflammatory cells, as well as cartilage and bone precursor cells to the injury site, thereby providing a conducive environment for bone regeneration. The vitality of angiogenesis is underscored during fracture healing where the creation of new blood vessels is pivotal for supplying the requisite oxygen and nutrients to the evolving bone tissue. A sluggish or partial vascularisation process could hamper the supply of these essential resources to the bone defect area, which may lead to cell death, thus, emphasizing the need for prompt and robust angiogenesis during the bone regeneration. Notably, the angiogenic process is driven by various growth factors such as fibroblast growth factor, platelet-derived growth factor, and transforming growth factor- β (TGF- β), which invoke the proliferation, migration, differentiation, and vascularisation of endothelial cells and/or endothelial progenitor cells.^{49,50} The intricate biochemical and physical interplay between angiogenesis and bone repair processes elucidates a complex yet harmonious orchestration of events that are crucial for effective bone regeneration.

Osteogenesis

Osteogenesis is the pivotal process of bone tissue formation and remodelling, orchestrated chiefly by several cellular entities including osteoblasts, bone marrow-derived mesenchymal stem cells (BMSCs), osteoclasts, and osteocytes.⁵¹ Osteoblasts are the primary architects of bone formation. They migrate to the site of bone repair, especially at the implant-bone tissue interface during implant osseointegration, and govern the synthesis, secretion, and mineralisation of the extracellular matrix (ECM). Their activity is markedly enhanced by the expression of growth factors such as bone morphogenetic protein-2 (BMP-2) and TGF- β , which facilitate the formation and mineralisation of bone tissue.^{52,53} BMSCs, residing within the bone structure, BMSCs hold the potential to differentiate into osteoblasts, a transformation triggered by signals such as the release of TGF- β 1 from neighboring osteoclasts. This differentiation is a critical step towards the formation of new bone tissue, setting the stage for further maturation and mineralisation processes.^{54,55} Osteoclasts are principally involved in bone resorption, a process vital for the subsequent bone formation by osteoblasts. The resorption pits created by osteoclasts serve as the sites for new bone formation, where osteoblasts deposit the new bone material. Moreover, the resorption process also releases factors that, in turn, activate osteoblast proliferation, maturation, and differentiation, establishing a coordinated homeostatic mechanism integral for bone remodelling.⁵⁶ Osteocytes, originating from osteoblasts that become entrapped within the mineralized matrix, osteocytes play a crucial role in bone maintenance and remodelling. They are instrumental in attracting osteoclasts to implant sites, thereby facilitating the process of bone remodelling. In the process of bone regeneration, the orchestrated interplay of these cellular entities is indispensable.^{57,58} Through a deeper understanding of the cellular and molecular mechanisms underlying osteogenesis, novel therapeutic strategies and biomaterials can be developed, potentially advancing orthopedic and dental applications.

The Role of Bioactive Elements in Bone Regeneration

The role of bioactive elements in osteoimmunomodulation

Ag

Chen et al.⁵⁹ developed a titanium dioxide (TiO₂) nanotube loaded with Ag nanoparticles (Ag@TiO₂-NTs) that releases ultra-low amounts of Ag ions to improve immunoregulation and enhance bone repair. The study demonstrated that Ag@TiO₂-NTs, releasing ultra-low-dose Ag ions, effectively induced M2 macrophage polarisation and promoted a favourable osteoimmune environment by modulating phosphatidylinositol 3-kinase (PI3K)/protein kinase B (Akt), glucose transporter 1, and autophagy *in vitro*. *In vivo*, Ag@TiO₂-NTs enhanced bone formation, reduced inflammation, and promoted osteoimmune microenvironment compared to TiO₂-NTs and polished Ti surfaces.

Boron

Boron (B) has been demonstrated to amplify pro-inflammatory conditions by facilitating lymphocyte proliferation and enhancing nitric oxide and pro-inflammatory cytokine secretion in lipopolysaccharide-activated macrophages from B-exposed mice.⁶⁰ The precise molecular pathways involved are yet to be elucidated. Contrarily, B ions emanating from a calcium silicate layer on titanium surfaces have been found to downregulate pro-inflammatory cytokines and upregulate anti-inflammatory ones, potentially via attenuating the activation of the myeloid differentiation primary response 88-nuclear factor- κ B (NF- κ B) pathway.⁶¹

Ca

Ca, an essential mineral, plays a pivotal role in various physiological processes, including bone mineralisation, muscle contraction, and signal transduction in human body. Bioceramic degradation generated Ca ions, which triggered the Wnt/ β -catenin signalling pathway through calcium-sensing receptor (CaSR).⁶² Blocking CaSR activity decreased the inflow of macrophage-promoting Ca ions, hindered Wnt/ β -catenin signalling and the production of M2-like macrophages, and attenuated the MSC mineralisation promoted by the supernatants when they were treated with a CaSR antagonist. It implies that the Ca ions in bioceramics are dependent on CaSR-mediated Wnt/ β -catenin activation for macrophage M2 polarisation and novo bone production. The Wnt/ β -catenin pathway has been shown to be an important mediator of M2 polarisation in macrophages. During phage M2 polarisation, β -catenin is activated and transported to the nucleus, where it binds to the transcription factor T-cell factor/lymphoid enhancer factor family, triggering transcription of downstream target genes. As a major inhibitor of the Wnt/ β -catenin signal axis, glycogen synthase kinase (GSK)3 β can enhance the ubiquitination and degradation of β -catenin, diminish its protein stability, and limit its nuclear entrance in this pathway. By increasing the phosphorylation of downstream GSK3, phosphorylated AKT suppresses its function. It's worth mentioning that Ca can play a role in Wnt/ β -catenin signalling by boosting the phosphorylation of GSK3.¹⁹ Extracellular Ca

influx may positively control the Wnt/ β -catenin signalling pathway by increasing GSK3 phosphorylation, because GSK3 is a negative regulator of Wnt/ β -catenin. As a result, increased intracellular Ca stimulated the PI3K/AKT signalling pathway and caused AKT phosphorylation, which was followed by decreased downstream activity GSK3 due to its higher phosphorylation, resulting in increased β -catenin translocation.⁶³

Cu

Cu, a crucial micronutrient, functions as a cofactor in enzymes related to respiration, oxygen transport, and antioxidant defence. Cu ions can trigger oxidative damage, potentially leading to DNA damage and low-density lipoprotein peroxidation.^{64, 65} For instance, some research demonstrates the ability of Cu ions to catalyse the production of hydroxyl radicals via the Haber-Weiss reaction.⁶⁶ Therefore, Cu ion levels in the intra and extracellular are tightly regulated to minimise these effects. Wilson's disease, characterised by Cu accumulation, highlights the oxidative potential of Cu, which can cause organ damage and chronic inflammation.⁶⁷ Recent studies have produced varied results regarding the influence of Cu ions on macrophages. Some studies indicate that lower Cu concentrations promote anti-inflammatory markers, while higher concentrations induce pro-inflammatory markers. Huang et al.⁶⁸ showed that when macrophages were cultured on titanium plates containing 0.2 and 2 mM Cu ions, the pro-inflammatory markers of the cells increased in a concentration-dependent manner, and the anti-inflammatory factors (arginine, interleukin (IL)-4, IL-6) decreased in a concentration-dependent manner. Additionally, the incorporation of Cu into biomaterials has yielded conflicting findings. Wang et al.⁶⁹ investigated the inflammatory response of stainless-steel biomaterials containing nano-Cu. When it was implanted in mice, the secretion of inflammatory factors was significantly increased at the early stage, but was significantly reduced after 2 weeks.⁶⁹ Further research is essential to understand the factors governing Cu's impact on macrophage polarisation.

F

F is an essential trace element, which can be an effective osteoimmunomodulatory agent. Wu et al.⁷⁰ have shown that macrophages can be greatly influenced by F-mediated osteoimmunomodulation. F can stimulate macrophages to produce a bone immune environment conducive to osteogenesis and angiogenesis. In their research, 2.4 and 24 μ M sodium F can promote osteogenesis by increasing polyamine production in macrophages.^{70, 71} And macrophages stimulated by F showed an inhibited inflammatory response. Fluorine can promote the expression of inhibitor of κ B- α to inhibit the expression of pro-inflammatory genes such as tumour necrosis factor- α and IL-6. *In vivo*, fluorine also can influence other immune cells such as T cells and mast cells to create an immune environment suitable for bone regeneration.⁷²

Gadolinium

Gadolinium (Gd) is a rare earth element. Zhao et al.⁷³ developed

multifunctional scaffolds composed of gadolinium phosphate (GdPO_4), chitosan, and ferroferric oxide (Fe_3O_4) with a precise 100 nm pore size, and three-dimensional network of macropores. These scaffolds, embellished with hydrated GdPO_4 nanorods in a c-axis orientation on macropore walls, were crafted for addressing breast cancer bone metastases.⁷³ The structured architecture and macropores facilitated cell adhesion and new bone tissue formation. Gd ions released from the GdPO_4 /chitosan/ Fe_3O_4 scaffolds initiated M2 macrophage polarisation, and led to a significant upsurge in anti-inflammatory cytokines as indicated by CD206 expression. Moreover, the GdPO_4 /chitosan/ Fe_3O_4 and GdPO_4 /chitosan scaffolds markedly stimulated new blood vessel development, and supported osteogenesis through enhanced vascularisation.

Hafnium

Seweryn et al.⁷⁴ investigated the immunomodulatory effects of hafnium (Hf) oxide (HfO_2) by analysing macrophage M1/M2 polarisation utilizing reverse transcription quantitative polymerase chain reaction. Following 4 hours of lipopolysaccharide stimulation, an increase in anti-inflammatory IL-10 expression was observed in lipopolysaccharide-treated macrophages cultured on HfO_2 . The data underline the potential immunomodulatory capacity of HfO_2 , and herald promising application in bone regeneration.

Li

Bartnikowski et al.⁷⁵ investigated the effect on bone by mixing Li carbonate with the biomaterial polymer polycaprolactone to achieve sustained release of Li. Experimental results showed that the released Li significantly polarised macrophages towards an immunomodulatory M2 phenotype, reduced pro-inflammatory M1 phase, and inhibited osteoclast activity, demonstrating an effective targeted tissue engineering system with the potential for further innovative ion release.

Mg

Mg is crucial for cellular metabolism, activating over 300 enzymes involved in the metabolism of carbohydrates, nucleic acids, and proteins.⁷⁶ It is also vital for the structural and functional integrity of cellular organelles.⁷⁷ In immunology, Mg modulates white blood cell functions, such as phagocytosis and lymphocyte production, and exhibits anti-inflammatory properties.⁷⁸ Mg deficiency has been linked to heightened inflammatory responses, including the activation of white blood cells and macrophages, increased cytokine release, and excess free radical production.⁷⁹ Qiao et al.⁸⁰ found that Mg ions induce a distinct cytokine profile, characterised by elevated levels of C-C motif chemokine ligand-5, IL-8, and IL-1ra, and a decrease in IL-1. This profile suggests that Mg ions facilitate monocyte recruitment and maturation into macrophages, while concurrently inhibiting pro-inflammatory cytokines like IL-1 through the up-regulation of IL-1ra, thus contributing to bone formation.

Si

Si ions, emanating from silica-based materials, have been shown to suppress pro-inflammatory cytokines and M1

Biomaterials contain bioactive elements for bone repair

markers through the Wnt5a/Ca²⁺ signalling pathway, thereby promoting osteogenesis by enhancing mineralisation and alkaline phosphatase (ALP) activity in BMSCs.^{81,82} Similarly, Si ions from titanium nanotube arrays also modulate the immune response by decreasing M1 markers and elevating anti-inflammatory markers like IL-10 and CD206.⁸³ Moreover, Si ions derived from various titanium-based materials have demonstrated an ability to inhibit pro-inflammatory cytokine secretion, such as tumour necrosis factor- α , IL-1 β , and IL-6, *in vitro*, likely via the attenuation of NF- κ B activation.^{84,85}

Sr

Sr exhibits a notable potential in modulating macrophage polarisation, crucial for immune response in bone regeneration. Zhao et al.⁸⁶ demonstrated that a Sr-Zn-phosphorus (P) coating on Ti substrates could preferentially steer macrophages toward the M2 phenotype by activating hypoxia-inducible factor-1 (HIF-1) signalling through the release of Sr ions and Zn ions, thereby bolstering bone integration in rat femur with titanium implants. Concurrently, Yu et al.⁸⁷ delineated that Sr ions doped nanorods array expedited the phenotypic transition of macrophages to M2, consequently amplifying osteogenic cytokine and growth factors (TGF- β 1 and BMP-2) expressions. Furthermore, the study elucidated that STSr₇ (Sr-doped Ti coated with sodium titanate, prepared via ion exchange at 100°C for 24 hours in 1000 mM 10 mL Sr(CH₃COO)₂ solution) outperformed *in vivo* in terms of osseointegration, releasing a higher concentration of Sr ions compared to STSr₄ (prepared under similar conditions but with 10 mM 10 mL Sr(CH₃COO)₂ solution). This enhanced Sr ions ion release from STSr₇ demonstrated a more consistent and effective stimulation of macrophage transition to M2, establishing a conducive environment for bone regeneration.

Zn

Zn, a pivotal element in human physiology, partakes in diverse cellular responses, profoundly influencing immune function,

cell division, and skeletal morphogenesis. As an essential trace element, it is indispensable for specific key enzymes and transcription factors, which is integral to immune responsiveness. Optimal Zn levels mitigate inflammatory cytokine secretion by macrophages, enhance anti-inflammatory cytokine expression, and maintain an anti-inflammatory milieu. Zhao et al.⁸⁸ demonstrated that Zn ions, derived from Zn-coated materials, modulate macrophage polarisation, inducing anti-inflammatory and osteoblastic cytokine secretion, thereby augmenting osteogenic differentiation potential of BMSCs. According to another study, Zn ions proficiently modulate activated macrophage polarisation towards the M2 phenotype, exerting an anti-inflammatory effect.⁸⁹ The release of Zn ions from Zn-doped tricalcium phosphate (TCP) has been noted to amplify tartrate-resistant acid phosphatase and ALP activity in human BMSCs, and regulate the formation of multi-nucleated giant cells and RAW264.7 macrophage activity.⁹⁰

In summary, bioactive elements such as Zn, F, Mg, Ca, Gd, Hf, and Sr play critical roles in osteoimmunomodulation, contributing to bone regeneration (Figure 3). Zn ions aid in anti-inflammatory cytokine expression and osteogenic differentiation of bone marrow stem cells. F ions influence macrophages to create an osteogenic and angiogenic bone immune environment. Mg ions modulate monocyte recruitment and activation, impacting cytokine profiles favourable for bone healing. Ca ions, primarily through CaSR-mediated Wnt/ β -catenin signalling, promote macrophage M2 polarisation and subsequent bone formation. Gd ions in scaffolds initiate M2 macrophage polarisation and enhance vascularisation. HfO₂ shows promise in immunomodulation, particularly in increasing anti-inflammatory IL-10 expression. Sr ions in coatings and nanorods induce M2 macrophage polarisation, consequently amplifying osteogenic cytokines and growth factors, fostering bone integration and regeneration. These elements not only modulate immune responses but also activate signalling pathways crucial for bone tissue engineering and regeneration.

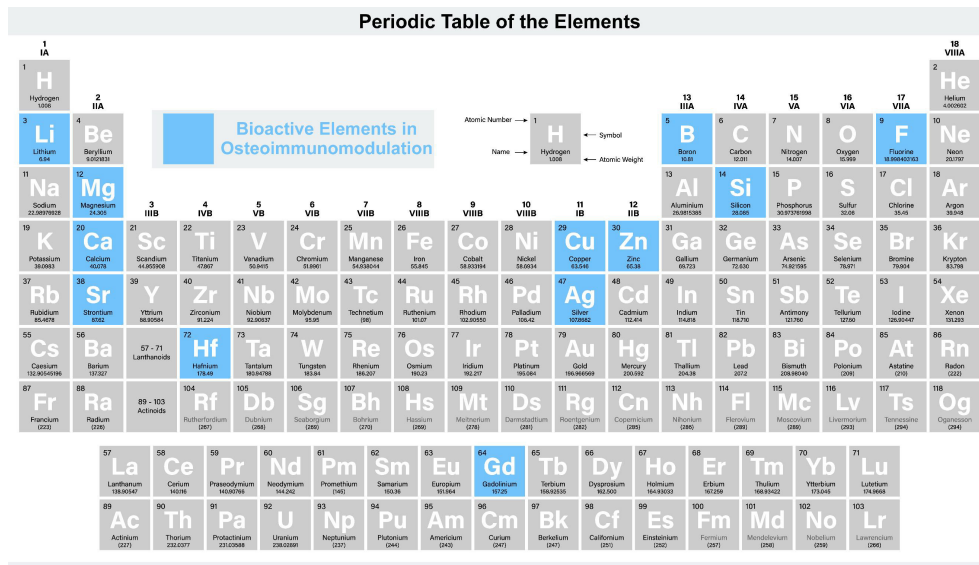


Figure 3. The role of bioactive elements in osteoimmunomodulation. Created with BioRender.com.

The role of bioactive elements in neuroregulation

Cu

In the neuroregulation of bone regeneration, Cu can act as an intracellular signalling molecule, binding with neurons to promote new bone formation, and affecting the process of bone repair. Cu can also regulate the excitability of neurons, having a significant neural regulation role in bone regeneration. Moreover, as one of the components of biodegradable metal implant, Cu can promote bone regeneration. The specific mechanisms and modes of action require further research to elucidate.²⁸

A novel biohybrid biodegradable hydrogel (gelatin methacrylate, GelMA) that incorporates copper ion-modified germanium-phosphorus (GeP) nanosheets. These nanosheets exhibit properties that promote neuro-vascular regeneration and possess antibacterial activity. The modification of GeP nanosheets with copper ions improves their stability and enables sustained release of bioactive ions. The integrated hydrogel demonstrates a significant enhancement in the osteogenic differentiation of BMSCs, facilitates angiogenesis in human umbilical vein endothelial cells (HUVECs), and upregulates neural differentiation-related proteins in neural stem cells. *In vitro* studies with injectable electroactive GelMA/GeP@Cu biohybrid hydrogel scaffolds show enhanced nerve differentiation and axon regeneration. These findings suggest that GelMA/GeP@Cu has great potential as a valuable biomaterial for neuro-vascularised bone regeneration and infection prevention in the field of bone tissue engineering.⁹¹

Mg

Mg ions can promote bone regeneration by stimulating the release of PGE2 through the activation of bone marrow macrophages. In the early stage of fracture healing (1st week), Mg ions can significantly increase the concentration of PGE2 in bone and serum, simultaneously activating sensory nerves, thereby stimulating PGE2 receptor-4 receptors. This induces the phosphorylation of cAMP-response element binding protein and upregulation of 5-hydroxytryptamine receptor 2C in the hypothalamus, ultimately downregulating sympathetic nerve activity related to bone repair. Under the influence of the medullary macrophage-sympathetic neuron-osteoblast neural circuit, this process promotes bone formation.²⁸

A photosensitive conductive hydrogel by incorporating Mg-modified black phosphorus (BP@Mg) into GelMA. The combined effect of conductive nanosheets and bioactive ions released from BP@Mg enhances the migration and secretion of Schwann cells, which directly promote innervated bone regeneration through the secretion of nerve growth factor and brain-derived neurotrophic factor. In an infected skull defect model, the GelMA-BP@Mg hydrogel demonstrates effective antibacterial activity and enhances the regeneration of bone and calcitonin gene-related polypeptide- α (CGRP) nerve fibres. This phototherapy conductive hydrogel offers a novel approach to repairing infected bone defects, utilizing skeletal-associated innervation as a therapeutic strategy.⁹² Zhang et al.⁹³ implanted a pure Mg pin into the intact distal femur of rats. This led to a notable increase in neuronal CGRP levels in the

peripheral cortex of the femur and the ipsilateral dorsal root ganglia. CGRP promotes the activation of adenosine 3,5-cyclic monophosphate-responsive element binding protein 1 and SP7 (osterix) through calcitonin receptor-like receptor and receptor activity modifying protein 1. Consequently, this enhances the osteogenic differentiation of stem cells.⁹³

Zn

Zn ions can promote the neural regulation of bone repair through modulating anti-inflammatory pathways. Specifically, under the influence of Zn, sensory nerve endings secrete PGE2, which can activate the PGE2 receptor-4 signalling in CGRP⁺ sensory nerve endings, becoming an intraneural sensory signal, and thereby activating sensory nerves. This activation, through the mutual regulation with the central nervous system, realizes the positive regulation function in bone repair. Additionally, research has indicated that under the influence of Zn ions, sensory nerve endings can also release CGRP, which can promote the proliferation and differentiation of osteoblasts, thereby better facilitating the process of bone repair.²⁸

Briefly, bioactive elements such as Cu, Mg, and Zn play critical roles in neuroregulation and contribute to bone regeneration (Figure 4). Mg ions stimulate bone repair by increasing PGE2 levels through bone marrow macrophage activation, influencing the neural circuit encompassing medullary macrophages, sympathetic neurons, and osteoblasts, thereby enhancing bone formation. Zn ions enhance neuroregulation via anti-inflammatory pathways, facilitating sensory nerve activation and osteoblast function. Cu ions, an intracellular signalling agent in bone neuroregulation, binds with neurons to bolster new bone formation and modulate neuronal excitability. Its role in biodegradable metal implants suggests potential in bone regeneration, though detailed mechanisms warrant further investigation.

The role of bioactive elements in angiogenesis

Ag

Ag has a long history for the use of antibiotics, which is a classic implant material. In recent years, scientists have discovered that Ag is a functional promoter of bone regeneration. According to Jeanmonod et al.'s study,⁹⁴ Ag acetate can promote angiogenesis. They implanted Ag acetate-coated Dacron vascular grafts into the dorsal skinfold chamber in mice, and discovered that functional capillaries were more dense than uncoated grafts. Meanwhile, Ag acetate coating could stimulate the ingrowth of new microvessels into Dacron vascular grafts. Most importantly, due to the dacron Ag graft controlling the release of Ag ions, the concentration of Ag ions wouldn't be too high to damage the normal cells. Therefore, Ag acetate-coated Dacron vascular grafts do not induce a severe inflammatory response.^{94,95} Ag nanoparticles (AgNPs) also have the function of promoting angiogenesis. Kang et al.⁹⁶ found that AgNPs induced tube formation on growth factor-reduced matrix glue, produced reactive oxygen species and released angiogenic factors vascular endothelial growth factor and nitric oxide via SVEC4-10 endothelial cells. Therefore, both Ag ions and nanoparticles can promote angiogenesis.⁹⁶

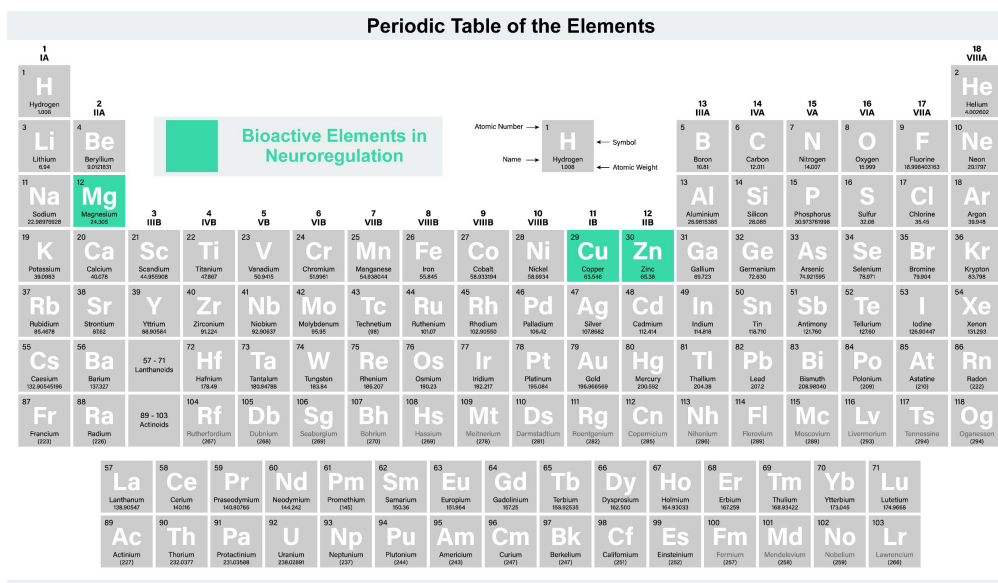


Figure 4. The role of bioactive elements in neuroregulation. Created with BioRender.com.

B

B, like the previously discussed ions, also exhibits a beneficial effect on angiogenesis, although the specific mechanisms remain less explored. B is often integrated into ceramic biomaterials, such as B-doped bioactive glass scaffolds. Different concentrations of B in these scaffolds have been tested, with lower doses (up to 925 μM) demonstrating enhanced angiogenic effects compared to higher doses (around 3700 μM).⁹⁷ A similar study showed that lower B concentrations enhanced endothelial cell proliferation and tubule formation.⁹⁸ A *in vivo* study with B-containing bioactive glass demonstrated increased angiogenic gene expression patterns and vascular density.⁹⁹ B has also been incorporated into composites of polymers and ceramics, Xia et al.⁹⁷ studied the effects of polycaprolactone containing B-bioactive glass at different levels (0, 10, 20, 30 and 40 wt%) on angiogenesis, showing that optimal angiogenic effects were achieved at specific concentrations (30 wt%), while higher concentrations (40 wt%) proved cytotoxic to cells. Additionally, when combined with other ions, B has shown synergistic effects on vascular endothelial growth factor (VEGF) secretion. Chen et al.¹⁰⁰ studied the effects of B-based glass and Cu-Zn doped B-based glass on human fibroblast cell lines. The results showed that VEGF secretion was increased in both cells, but the latter was more obvious.¹⁰⁰

Cu

Cu is one of the most important elements in humans, which is the third most prevalent mineral present in the body. Copper is mainly found in the body as Cu²⁺ and Cu⁺, and they are involved in a number of important biological reactions. Cu has an effect of promoting angiogenesis. Kong et al.²¹ found that Cu²⁺ can positively affect the expression of angiogenic growth factors in HUVECs and human dermal fibroblasts. VEGF is one of the most important mediators of angiogenesis during the proliferation phase. Angiogenin (ANG) is a ribonuclease which is a strong stimulator of angiogenesis and

interacts with endothelial cells. Cu²⁺ can not only promote the expression of VEGF, but also regulate the transcription of angiopoietin and influence the localization of ANG to enhance its function. Meanwhile, copper has a big effect on matrix metalloproteinases (MMPs), which can regulate the activity of VEGF and other growth factors and promote cell proliferation in angiogenesis.¹⁰¹ Researches have shown that low concentrations of Cu can stimulate the activity of MMPs, while high concentrations of copper can increase the expression of MMPs in fibroblasts. Therefore, Cu ions are important to angiogenesis in bone formation.¹⁰²

Cerium

Xiang et al.¹⁰³ modified a tissue engineering bone scaffold with cerium (Ce) oxide nanoparticles and evaluated the impact of Ce oxide nanoparticles on the growth and paracrine activity of MSCs on the scaffold surface. Ce oxide nanoparticles have the potential to increase MSC proliferation while also inhibiting apoptosis. Finally, large levels of the angiogenic factor VEGF were found. As a result of the improved paracrine of VEGF, endothelial progenitor cell proliferation, differentiation, and tube forming ability may be enhanced.

Co

Because of its ability to stabilise HIF-1 and hence activate VEGF, Co ions have been utilised to accelerate vascularisation.¹⁰⁴ The addition of Co ions to silk fibroin/F/calcium phosphide (CaP) may aid adipose-derived stem cells in the formation of tube-like structures.¹⁰⁵ However, because collagen type 1 matrix deposition was reduced, cell proliferation and endothelial network formation were inhibited. Chai et al.²⁰ found that preconditioning human periosteum-derived mesenchymal stem cell-seeded tissue engineered constructs with a fine-tuned solution containing Co increased VEGF secretion and improved human periosteum-derived mesenchymal stem cell development and endothelial network formation.

F

F has been shown to augment angiogenesis in a dose-dependent manner, demonstrating synergistic regulation of osteogenesis and angiogenesis by modulating the expression of key factors such as BMP-2, oncostatin M (OSM), spermine/spermidine synthase, insulin-like growth factor-1, and VEGF. Wu et al.²² observed that active angiogenesis was consistently present in F-treated groups, and attributed this to VEGF expression under varying F treatments. Further, F was found to stimulate insulin-like growth factor-1 production, a critical factor in endothelial cell migration and tubular formation.¹⁰⁶ Given the dose-dependent variations in its impact, F exerts multifaceted effects on osteogenesis, osteoclastogenesis, and angiogenesis.⁷¹

Iron

Shi et al.¹⁰⁷ studied the effect of Fe³⁺ release on the angiogenic response of bone grafts. As a controlled ferric agent, iron (Fe)-doped octacalcium phosphate was produced. The affinity, survival, proliferation, and angiogenic differentiation of HUVECs were all greatly improved by Fe-doped octacalcium phosphate. The scaffold promoted endothelial cell adhesion and spreading, as well as angiogenesis, as evidenced by the development of additional blood vessels and increased expression of particular markers. Fe³⁺ can boost HIF-1 α and VEGF levels, as well as nitric oxide secretion and endothelial nitric oxide synthase synthesis, all of which influence endothelial cell activity and angiogenesis.

Li

Li-incorporated bioactive glass ceramic has been shown to enhance the pro-angiogenic capabilities of HUVECs both *in vitro* and *in vivo*.²³ This enhancement is mediated through the induction of miR-130a in BMSC-derived exosomes, leading to phosphatase and tensin homolog deleted on chromosome ten (PTEN) downregulation and AKT pathway activation. The resultant cellular activities include increased endothelial cell proliferation, migration, tube formation, and increased expression of pro-angiogenic genes.

Mg

Mg ions improved the proliferation, migration, and osteogenic differentiation of BMSCs, as well as having evident impacts on angiogenesis, by selectively activating the mitogen-activated protein kinase/extracellular signal-regulated kinase pathway. Directly promoting the migration of ECs and up-regulating the production of VEGF in BMSCs increase angiogenesis.¹⁰⁸ The sensory nerve-endothelial cell interaction mediated by Mg through the CGRP-focal adhesion kinase-VEGF signalling pathway enhanced the repair of critical size bone defects.¹⁰⁹ Lai et al.⁴⁵ have developed a new bioactive porous scaffold using low temperature rapid prototyping technology, comprising of poly (lactide-co-glycolide), TCP, and Mg. By incorporating Mg into the scaffold, they observed that it not only provided a favourable template for vessel infiltration but also stimulated neo-angiogenesis. This ultimately led to new bone formation and remodelling in challenging bone defects, specifically those associated with steroid-induced osteonecrosis.⁴⁵

Sr

Sr can play a great effect on bone regeneration, including immune response, angiogenesis and new bone formation. Previous studies have shown that Sr-containing materials have the ability to promote angiogenesis. Yan et al.²⁷ have found that appropriate doses of Sr ions (0.2–1 mM) can enhance the secretion of VEGFA and ANG-1 in HUVECs and BMSCs co-culture systems, which has the potential to create an angiogenic microenvironment at an early stage. Sr not only promotes angiogenesis by stimulating osteoblasts to secrete angiogenic cytokines,¹¹⁰ but also significantly promotes early angiogenesis by regulating macrophage phenotype. Zhao et al.¹¹¹ have found that the monodispersed Sr-containing bioactive glasses microspheres could stimulate macrophages to exhibit a tendency towards the M2 phenotype and express high levels of platelet-derived growth factor-BB *in vitro*. What is the most important is that this access can play a big role in the early vascularisation, which is different from the way of osteoblasts.¹¹¹

Si

Si is one of the essential trace elements in human body, which is necessary in the development and growth of bone and connective tissue.¹¹² Studies have shown that Si ions can stimulate angiogenesis. Li and Chang¹¹³ found that the 0.7–1.8 $\mu\text{g}/\text{mL}$ Si ions provided by 1/64 and 1/256 diluted Ca silicate extracts stimulated the proliferation of HUVECs and upregulate the expression of pro-angiogenic factors (VEGF and basic fibroblast growth factor). Their receptors activate the expression of endothelial nitric oxide synthase and increase the expression of nitric oxide in HUVECs.¹¹³ Zhai et al.¹¹⁴ have shown that akermanite ceramics, which is a suitable source of Si ions, can promote angiogenesis. It can release and keep the suitable Si ions to induce angiogenesis by increasing gene expression of pro-angiogenic cytokine receptors and upregulating downstream signalling, such as nitric oxide synthase and nitric oxide.¹¹⁴ Their experiment successfully demonstrated that akermanite ceramics were the first silicone-containing ceramics capable of inducing angiogenesis during bone regeneration. Mao et al.¹¹⁵ have found that Sr and Si ions had synergistic effects on osteogenesis, osteoclast formation and angiogenesis. They use the SMS bioceramics, which has Sr and Si ionic compositions, to study the influence of angiogenesis. And they had made the conclusion that SMS bioceramics can enhance osteogenic differentiation and expression of preferred angiogenic factors in BMSC from ovariectomized rats, rebalance the osteoprotegerin/receptor activator of nuclear factor- κ B ligand (RANKL) ratio in BMSC from ovariectomized rats at early stage, and inhibit RANKL-induced osteoclast formation at late stage. The effect of Si ions on promoting osteogenesis and Sr ions on enhancing angiogenesis and inhibiting osteoclast formation can be well combined by SMC.¹¹⁵

Ytterbium

Tang et al.¹¹⁶ used lyophilization and mineralisation techniques to successfully create magnetic Y-doped hydroxyapatite/chitosan nanohybrid scaffolds with ytterbium (Yb) dopants as

Biomaterials contain bioactive elements for bone repair

well as magnetic SrFe₁₂O₁₉ nanoplates. Yb ions from magnetic Y-doped hydroxyapatite/chitosan nanohybrid scaffolds only reached a maximum concentration of 0.30 μM, according to *in vitro* tests. The osteogenic and angiogenic properties of the magnetic Y-doped hydroxyapatite/chitosan nanohybrid scaffolds were remarkably improved by the Yb dopants and magnetic SrFe₁₂O₁₉ nanoplates. For one thing, the bioactive components promoted the migration of endothelial cells, the up-regulation of angiogenic protein VEGFA expression, and macrophage polarisation toward M2 phenotype, leading to the rapid development of blood vessels in bone defects. *In vivo* bone mineralisation was made possible by the sufficient nutrients and oxygen that the newly created blood vessels provided. For another, by activating the BMP-2/Smad pathway in the scaffolds, both the Yb dopants and magnetic SrFe₁₂O₁₉ nanoplates enhanced osteogenic differentiation of rat BMSCs and *in vivo* bone tissue regeneration, suggesting a beneficial influence in the entire osteogenic process. The majority of bone abnormalities were filled with newly created bone tissues 12 weeks after surgery. In order to speed up the repair of bone defects, Yb dopants and magnetic SrFe₁₂O₁₉ nanoplates would be expected.

Zn

The influence of Zn on angiogenesis is primarily regulated via the Zn-sensing receptor/G protein-coupled receptor 39.¹¹⁷ Within a concentration range of 20–60 μM, Zn enhances human coronary artery endothelial cell viability, proliferation, and angiogenic marker expression.¹¹⁸ Biomaterials such as 5% Zn-Bioglass®-incorporated calcium phosphate cement have been shown to upregulate VEGF and induce tubule formation in endothelial cells.¹¹⁹ Likewise, polycaprolactone matrices with zinc oxide (ZnO) nanoparticles promote cell proliferation and elevate VEGF and fibroblast growth factor expression, with the nanoparticles also catalysing reactive oxygen species generation via hydrogen peroxide (H₂O₂), a ZnO byproduct.¹²⁰ Elevated ZnO concentrations, however,

inhibit angiogenesis due to excessive reactive oxygen species production. The angiogenic potential of Zn varies with the biomaterial's morphological properties, such as nanoparticle configuration.¹²¹ Anti-angiogenic aspects of Zn are also being explored for cancer therapeutics by inhibiting tumour vasculature.¹²² When combined with Si, Zn can activate the p38 pathway, contributing to bone regeneration and angiogenesis via cytokine expression.¹²³ Further investigations are warranted to comprehensively understand angiogenic roles and underlying mechanisms of Zn.

In summary, various bioactive elements such as Mg, Sr, Si, and Ag play pivotal roles in promoting angiogenesis, which is instrumental for bone regeneration (Figure 5). Ag, historically recognised for its antibiosis, now stands out as a bone regeneration stimulant, with Ag acetate-coated grafts showing enhanced microvessel ingrowth without inducing inflammation. B, integrated into ceramic biomaterials, demonstrates angiogenic effects at specific concentrations. Cu, vital for angiogenesis, influences angiogenic growth factor expression in key cellular components. Co ions, by stabilising HIF-1, expedite new vessel formation. Ce oxide nanoparticles on scaffolds enhance MSC proliferation, subsequently promoting VEGF secretion. Fe³⁺ boosts angiogenesis by modulating endothelial cell activity. F, in a dose-dependent manner, orchestrates angiogenesis through osteogenesis and angiogenic factor regulation. Li-incorporated bioactive glass ceramic shows enhanced angiogenic potential both *in vivo* and *in vitro*. Mg ions, channelling through the mitogen-activated protein kinase/extracellular signal-regulated kinase pathway, have a positive impact on angiogenesis. Sr, through VEGF and ANG-1 modulation, plays a significant role in early vascularisation. Si ions stimulate angiogenesis via BMP-2/Smad pathway activation. Yb dopants in scaffolds combined with magnetic particles promote angiogenesis and bone tissue regeneration. Lastly, Zn mediates its angiogenic effects through specific cellular interactions, with its potential varying based on the morphology of the biomaterial.

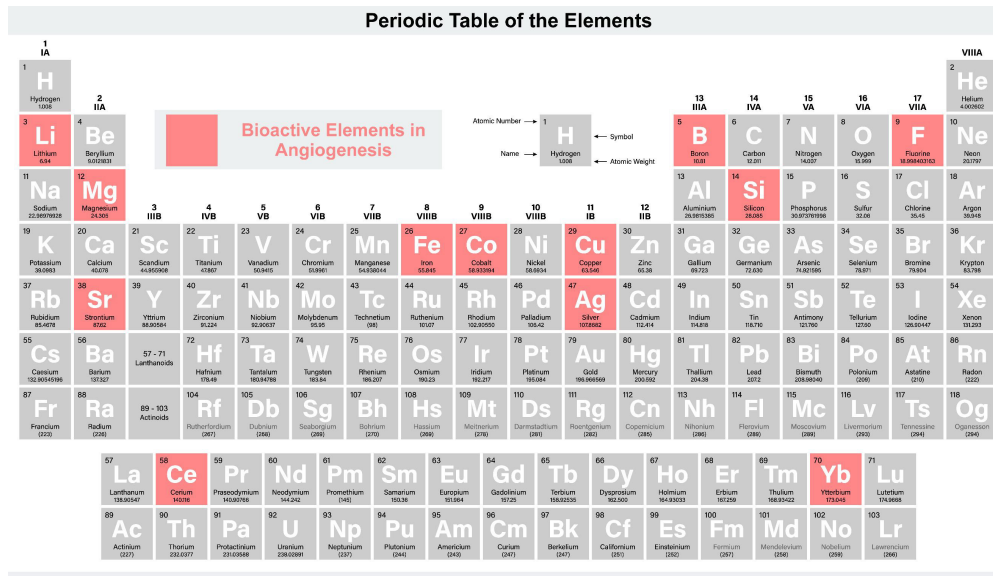


Figure 5. The role of bioactive elements in angiogenesis. Created with BioRender.com.

The role of bioactive elements in osteogenesis

Ag

Ag could not only promote angiogenesis, but also promote new bone formation. It has been reported that AgNPs can promote osteogenic lineage induction and actin aggregation in new bone formation. These promotions can only be found in AgNPs, not silver nitrate (AgNO_3). These promotions about AgNPs are achieved by stimulating the physiological activity of new bone-forming cells. AgNPs have been shown to promote mineralisation in MC3T3-E1 osteoblasts through microRNA-mediated upregulation of bone morphogenetic genes. Two studies revealed that, aside from the elevated expression of osteogenesis-critical bone morphogenetic proteins, the most significant transcriptional change was a decrease in osteoclast markers.^{124, 125} AgNPs also foster keratinocyte proliferation, fibroblast differentiation, and MSC osteogenic differentiation *in vitro*.¹²⁶ While the underlying mechanisms remain unidentified, these activities collectively contribute to new bone cell proliferation and differentiation, thereby facilitating new bone formation.

B

B, an essential trace element, plays a pivotal role in various biological processes, notably bone growth and maintenance.¹²⁷ Its supplementation has been linked to enhanced bone strength and microstructure.¹²⁸ Mechanistically, B fosters osteogenesis via the activation of the Wnt/ β -catenin pathway, particularly through the up-regulation of the transcription factor transcription factor 7-like 2.¹²⁹ This suggests its potential in bone regeneration therapies. Experimentally, B ions, when released from B nitride nanotubes, have been observed to induce osteogenesis, evidenced by enhanced protein adsorption, MSC attachment, and upregulation of osteogenic markers.¹³⁰ Furthermore, B-doped bioactive-glass scaffolds, have displayed promising osteogenic outcomes,¹³¹ amplifying cell adhesion, differentiation markers, and mineralisation. Specifically, B-enriched bioactive glass scaffolds activated the Wnt/ β -catenin pathway, influencing osteoblastic differentiation.¹³² However, while the role of Setd7 in B-mediated osteoblast differentiation has been identified, additional studies are required to uncover other potential contributing factors.

Ca

Doping Ca ions can notably accelerate adhesion, proliferation, and mineralisation of osteoblasts.¹³³ Ca, one of the ions that form the bone matrix, affect cells and living systems in several ways. The calcium phosphates in bone tissues cause bone formation and maturation through calcification.¹³⁴ Ca ions also influence bone repair via cellular communication. Ca causes bone tissue regeneration by accelerating mature bone cells and inducing bone growth precursor cells through the creation of nitric oxide.^{135, 136} Ca ions also activate the extracellular signal-regulated kinase1/2 pathway,¹³⁷ which stimulates osteoblastic bone production, and the PI3K/Akt pathways,¹³⁸ which prolongs the lifespan of osteoblasts. Ca ions also control the production and resorption activities of osteoclasts. Integrin β 1 and vinculin proteins are important factors of focal adhesion complexes that prove effective on the adhesion, proliferation,

and differentiation of BMSCs. Ca ions show helpful to the high expression of integrin β 1 and vinculin proteins. Hence Ca ions increase the protein expression and support cell adherence. The incorporation of Ca accelerates the proliferation of stem cells and the early differentiation of osteoblasts in the cell. The expression of the related proteins like osteopontin (OPN),¹³⁹ Runx2 and ALP would verify the conclusion. As a secretory phosphorylated glycoprotein, OPN adheres to HA via its distinct binding domain during osteogenesis and holds the formation of osteoid nodules *in vivo*, which directly influence the construction of the three-dimensional structure of newly formed bone.¹⁴⁰ The introduction of Ca ions suggests the abundant expression of OPN protein and supports the osteogenic differentiation of BMSCs.

Ce

Ce-doped mesoporous bioactive glass nanoparticles used as vectors for local administration of Ce have shown to stimulate the expression of pro-osteogenic genes in Saos-2 cells, as well as the development and calcification of a primitive osseous ECM. Westhauser et al.¹⁴¹ studied the impact of the ionic dissolution products of mesoporous bioactive glass nanoparticle on cellular osteogenic differentiation and their ability to form and mature a primitive osseous ECM. In the presence of Ce-doped mesoporous bioactive glass nanoparticles, the development and calcification of a primitive osseous ECM was greatly enhanced in a positive concentration-dependent manner, as evidenced by an increased presence of collagen and increased ECM calcification.

Co

Co-TCP increased the vitality of BMSCs.¹⁰⁴ *In vitro*, 2% Co-TCP increased ALP activity, matrix mineralisation, and osteogenic gene expression in BMSCs. Excessive Co doping, on the other hand, reduced TCP-induced osteogenesis. Additionally, Co^{2+} can inhibit the osteogenic differentiation of MSCs by mimicking hypoxia. Hsu et al.¹⁴² have shown that hypoxia caused by Co^{2+} activation of HIF impairing osteogenic differentiation, as evidenced by reduced ALP activity and expression of osteogenic markers core-binding factor alpha(1) (*Cbfa1*) and osteopontin. There are also some studies have shown that hypoxia caused by release of Co^{2+} can enhance the osteogenic potential of MSC after having a certain pretreatment.¹⁴³ The specific influence mechanism of Co needs to be studied in the future.

Cu

Cu can play a big role in bone metabolism, and severe Cu deficiency can lead to bone abnormalities, such as decreased bone strength. Cu can enhance the osteogenic differentiation of MSCs. The early studies on the effect of Cu on MSCs in postmenopausal women showed that Cu ions reduced osteoblast proliferation, increased differentiation by 2 folds, and, particularly, increased calcium deposition. Cu ions can enhance cell activity and proliferation and enhance the expression of bone specific protein.⁹⁵ Burghardt et al.¹⁴⁴ produced a composite material that deposited copper on a titanium alloy. The proliferation of MSC was stimulated by 0.1

Biomaterials contain bioactive elements for bone repair

mM Cu ions, ALP activity was increased, and mineralisation was increased 144. And other studies found an increase in the osteogenic gene expression of collagen type 1, ALP, OPN and Runx2 from rat BMSCs cultured with Cu-containing calcium phosphate cement.^{145,146}

F

F-containing biomaterials have been shown to have osteogenic properties, which are usually used as implant coating. F-containing biomaterials also can stimulate the proliferation and differentiation of osteoblasts *in vitro* and even promote bone formation of osteoblasts *in vivo*.¹⁴⁷ Chen et al.¹⁴⁸ have shown that the coating consisting of F can improve the activity of adhesion, proliferation and differentiation of osteoblasts, and has a good biocompatibility. Meanwhile, F can enhance bone-associated glycoprotein synthesis in BMSCs, leading to increased mineral deposition. But excessive F intake over a long period of time can eventually lead to damage to bone structure. Optimal osteogenic differentiation is achieved with F ion concentrations of 50 and 500 μM ⁷² and osteoblast mineralisation to be between 0.01 to 10 μM .¹⁴⁹ Thus, the physiological impact of F on skeletal tissue is dose-dependent in the local environment.

Fe

The addition of Fe ions ($\text{Fe}^{3+}/\text{Fe}^{2+}$) to calcium phosphate cement can speed up osteoblast proliferation. Doping Fe into bone cement boosted MC3T3-E1 cell proliferation and migration while also increasing their ALP activity and expression of osteogenic-related genes. The expression of HIF- α increased after cells were grown with Fe-dicalcium phosphate dihydrate scaffold extract, enhancing cell chemokine receptor activation and promoting cell migration.¹⁵⁰

Gallium

Gallium (Ga) is used in medicine mainly in antibacterial and cancer treatments. Ga nitrate is a drug that speeds up bone absorption. Short-term Ga therapy can effectively reduce bone turnover *in vivo* and increase bone calcium in patients with bone calcification to treat cancer-related hypercalcaemia.⁹⁵ According to Strazic Geljic et al.¹⁵¹, bone cement containing Ga can significantly inhibit the expression of osteoclast- and osteoblast-associated genes. And they found that TCP/phosphate-based scaffolds with single Ga promoted cell proliferation and significantly inhibited osteogenic differentiation and osteoclast activity *in vitro*. For the current literature, Ga has a range of promising qualities for future applications in tissue engineering.

Gd

The Gd dopants in the scaffolds triggered the signalling pathway (Wnt/ β -catenin,¹⁵² Smad/Runx2,¹⁵³ Akt/GSK3 β ¹⁵⁴), enabling BMSCs to proliferate and differentiate into osteoblasts.

Hf

HfO₂ was found to encourage pre-osteoblasts while impairing the viability of pre-osteoclasts.⁷⁴ HfO₂ stimulates the expression of OPN, Runx2, and TGF- β in osteoblasts

on the mRNA and protein levels. Meanwhile, the major regulators of osteoclast differentiation: c-Fos, MMP-9, PU.1, receptor activator of nuclear factor- κ B, and tartrate-resistant acid phosphatase, are expressed less when HfO₂ is present. HfO₂ stimulates pre-osteoclast death while simultaneously protecting pre-osteoblast from apoptosis by increasing the expression of the Bcl-2 transcript. Thus, a technique to stop the overactivity of osteoclasts during bone repair was raised. Moreover, HfO₂ protects pre-osteoblasts from apoptosis not only by activating specific genes relevant to osteogenesis but also by inducing the production of miR-17-5p and miR-7a-5p, two essential regulators of osteoblast proliferative activity and apoptosis. While miR-16 inhibits MSC production of important osteogenic markers and calcium mineral deposition during osteogenic differentiation, miR-21-5p is a well-known osteogenesis activator. Hopefully, HfO₂ may be used as a bioactive agent to modify and activate osteogenesis when administered to implantable metallic materials.

Lanthanum

Lanthanum (La)-substituted MgAl layered double hydroxide scaffolds activate the Wnt/ β -catenin pathway, thereby promoting BMSC proliferation and osteogenic differentiation due to the release of La ions. This activation leads to the upregulation of ALP, Runx2, collagen type 1, and OCN gene expressions. Additionally, the scaffolds act to obstruct the NF- κ B signalling pathway, significantly diminishing RANKL-induced osteoclastogenesis.¹⁵⁵

Li

Li increases bone regeneration via blocking GSK3 and thereby activating the β -catenin signalling pathway.¹⁵⁶ The release of Li ions stimulated the adhesion and proliferation of BMSCs more effectively. Furthermore, Li doped mesoporous silica nanospheres may improve BMSC ALP activity as well as the expression of osteogenesis-related genes (OPN, ALP, Runx2, and OCN).¹⁵⁷ Mo et al.¹⁵⁸ investigated how low concentration Li stimulation caused BMSCs to proliferate and differentiate into osteoblasts. They also discovered that adding 500 μM of Li to the canonical Wnt signalling pathway and osteogenesis differentiation in BMSCs reversed the inhibitory effect of 10 μM of XAV-939.¹⁵⁹ Huang et al.¹⁶⁰ found the RANKL/osteoprotegerin signalling axis was also involved in these effects.

Mg

Mg ions, via the PI3K/Akt signalling pathway, can influence the expression of bone-related genes such as Runx2, ALP, OCN, and OPN.¹⁶¹ *In vitro*, an appropriate concentration of Mg ions can greatly enhance pre-osteoblast proliferation and differentiation, as well as the up-regulation of osteogenic genes, and *in vivo*, significant new bone formation.²⁴

Manganese

Manganese ion (Mn^{2+}) has been shown to enhance the expression of osteogenic genes described in osteoblasts by increasing ALP activity, collagen type 1, OCN, BMP, and soluble intercellular adhesion molecule-1. Mn-doped implants have

been shown to stimulate cell proliferation, cell differentiation and biological activity, they are promising materials for bone tissue regeneration.¹⁶² Additionally, the release of Mn^{2+} from bioactive glass caused hMSCs differentiation through a bone route and subsequent mineralisation, according to the findings.¹⁶³ Mn^{2+} had a concentration-dependent effect on cell activities, and a lower Mn^{2+} concentration could encourage BMSCs to differentiate into osteoblasts. Wu et al.¹⁶⁴ discovered that Mn^{2+} concentrations below 7.17 g/L stimulated the proliferation of BMSCs and increased the expression of osteogenesis-related genes.

Rubidium

Rb, recognised as a crucial trace element in the human body, is known for its low toxicity.¹⁶⁵ Research indicates that biomaterials infused with rubidium significantly advance osteoblastic differentiation, particularly in the middle and late stages, and also enhance osteogenic capacities. A pivotal attribute of rubidium is its remarkable antibacterial properties, establishing it as an effective agent for enhancing biomaterials.^{166, 167} Tan et al.¹⁶⁸ have developed glass-ceramics infused with varying levels of Rb. Within the glass matrix, hydroxyapatite crystals are formed. The incorporation of rubidium enhances the formation and growth of these crystals. These rubidium-enriched glass-ceramics demonstrate superior bending strength compared to their rubidium-free counterparts. Crucially, the presence of rubidium fosters the proliferation and adhesion of human hBMSCs and increases ALP activity. Exhibiting robust mechanical properties, exceptional bioactivity, and biocompatibility, these rubidium-modified glass-ceramics hold promise for applications in bone regeneration.¹⁶⁸

Scandium (Sc)

$ScCl_3$ promotes osteogenesis and inhibits adipogenesis in the Wnt/ β -catenin signalling pathway when used at the optimal concentration.¹⁶⁹ Moreover, $ScCl_3$ can enhance bone remodelling by improving osteogenic differentiation in lineage commitment of rBMSCs.

Si

Si is an essential element for the development and growth of bone and connective tissue. *In vivo*, water-soluble forms of Si, chiefly as orthosilicic acid [OSA, $Si(OH)_4$]. It can accelerate bone mineralisation by affecting collagen and inhibits bone resorption in postmenopausal women.¹⁷⁰ And it can also play an important effect on stimulation of osteoblasts and bone formation and inhibition of osteoclast formation and bone resorption. A study has shown that OSA stimulated osteoblast differentiation at a physiological concentration of 20 μ M.¹⁷¹ Dong et al.¹⁷² have found that OSA could promote the osteogenic differentiation of rat BMSCs through the BMP-2/Smad1/5/Runx2 signalling pathway to participate in the induction of collagen type 1 and osteocalcin synthesis. Zhou et al.¹⁷³ have found that OSA could accelerate bone formation in human osteoblast-like cells through the PI3K-Akt-mammalian target of rapamycin pathway. Zhou et al.¹⁷⁴ have shown that OSA and $Si(OH)_4$ could stimulate osteoblast differentiation *in vitro* through upregulating miR-146a to antagonize NF- κ B

activation. OSA can also play an effect on osteoclast. A study has shown that OSA inhibits RANKL-induced osteoclastogenesis by promoting the expression of miR-130b, which can counteract the negative effect of oophorectomy on miR-130b expression in rats.¹⁷⁵ miR-130b plays a role in cell proliferation, differentiation, apoptosis, tumour progression and metastasis, and serves as a biomarker for recurrence and prognosis. You et al.¹⁷⁶ have shown that the expression of miR-130b increased with the application of OSA. *In vitro*, the overexpression or inhibition of miR-130b significantly promoted or inhibited the osteogenic differentiation of osteoblasts under the application of OSA.¹⁷⁶ And as the scaffold material, dicalcium silicate is a good choice used as containing bioactive coating materials for prosthetic bone implant. It can induce the deposition of carbonised hydroxyapatite at the material-tissue interface, form a strong binding with bone tissue, inhibit the formation of osteoclast, promote the proliferation and differentiation of human osteoblasts and the expression of bone-related genes.¹⁷⁷

Sr

The addition of Sr in biomaterials reduced the capacity to generate apatite, but it also encouraged cell division, proliferation, differentiation into osteoblasts, and mineralisation of the ECM.¹⁷⁸ Li et al.¹⁷⁹ verified the influence of Sr^{2+} on MSC osteogenic differentiation. Sr^{2+} stimulated noncanonical Wnt signalling to regulate the production and distribution of the PAR complex, hence regulating cell division, and the increased cell population contributed to enhanced osteogenic differentiation. Meanwhile, Sr^{2+} release increased the expression of genes involved in hMSC osteogenic development; early indicators (Runx2, collagen type 1) were proportionate to the amount of Sr^{2+} released, and late markers (ALP, OCN) were higher.¹⁸⁰ To some extent, Sr^{2+} could prevent osteoclastogenesis on its own. Sr^{2+} decreased osteoclast activity more than recombinant human BMP-2.¹⁸¹ By inhibiting the RANKL-activated p38 signalling and NF- κ B signalling pathways, Sr-substituted sub-micron bioactive glass with the combined action of substituted sub-micron bioactive glass extract and Sr^{2+} demonstrated the most inhibitory effect on osteoclast differentiation.¹⁸²

Vanadium

Vanadium (V), a ubiquitous trace element in both plants and animals, has intriguing biological effects.¹⁸³ Found in a variety of oxidation states, from -1 to +5, certain forms like V III, IV, and V are noted for their insulin and growth factor mimicking properties at therapeutic levels. Notably, V compounds influence bone metabolism due to their primary storage in bone tissue.¹⁸³ Recent studies have unveiled that a complex of V (IV) with ascorbic acid can promote osteoblast differentiation and mineralisation in a lab setting, underscoring its potential in bone formation.¹⁸⁴ The amount of collagen type 1 produced in osteoblasts was found to be directly correlated with the dose of the V compound.

Zn

Zn is integral to bone development and is found in calcification sites such as osteons and calcified cartilage. Its levels in bone tissue rise with increasing mineralisation. Zn promotes

Biomaterials contain bioactive elements for bone repair

osteoblast proliferation and elevates ALP activity within a narrow dose range (1–50 μM).¹⁸⁵ Beyond this range, osteogenic activity diminishes. Kwun et al.¹⁸⁶ reported that Zn-deficient media reduced ALP activity, matrix-related gene expression, and mineralised matrix deposition in MC3T3-E1 cells. Zn also safeguards osteoblasts from apoptosis and enhances their spreading, attachment, and chemotaxis. Furthermore, Zn is crucial for osteoclastogenesis. Reduced numbers of osteoclasts were observed in the distal femur growth plates of Zn-deficient rats.^{186, 187} Zn exhibits a dose-response effect on osteoclast formation and activity, and at certain concentrations, can induce osteoclast apoptosis.^{188, 189} A study by O'Connor et al.¹⁹⁰ showed that Zn deficiency in Turkey poults and Sprague-Dawley rats led to reduced growth, bone shortening, and diminished ALP activity. The rats developed osteopenia, characterised by significant reductions in cancellous bone, osteoblast surface area, and osteoclast numbers.¹⁹⁰ Thus, the multifaceted roles of Zn in bone metabolism warrant further investigation.

Tantalum

Due to its exceptional osteogenic activity, corrosion resistance, and antibacterial adhesion, biomedical tantalum (Ta) has attracted considerable attention as a promising implantable material for bone repair. Hu et al.¹⁹¹ developed Ta/polyetheretherketone composites by blending Ta nanoparticles with polyetheretherketone for load-bearing bone repair applications. The incorporation of Ta nanoparticles in Ta/polyetheretherketone composites resulted in favourable surface roughness, hydrophilicity, and surface energy, thereby enhancing the osteoconductivity of fibrous electrospun polylactic acid (PLA) membranes used in guided bone regeneration.¹⁹¹ A Ta coating was applied to electrospun PLA membranes through the deposition of sputtered Ta ions around the PLA fibres. This Ta-PLA coating greatly enhanced the attachment, proliferation, and differentiation of preosteoblasts on the membranes. *In vivo* studies demonstrated that within 6 weeks, a majority of calvarial defects treated with Ta-PLA membranes were completely covered with newly formed bone, while the defects treated with bare PLA membranes showed

minimal bone coverage.¹⁹² In recent years, porous Ta has been extensively investigated for its regulatory effects on BMSCs. It plays a crucial role in regulating the proliferation, migration, and differentiation of BMSCs, making it a widely used material for bone defect repair.¹⁹³⁻¹⁹⁵

P

P is a vital element in the human body, comprising approximately 1% of total body weight as a constituent of bones.¹⁹⁶ Culturing human tonsil-derived MSCs in osteogenic medium containing incremental concentrations of P (a mixture of Na₂HPO₄ and NaH₂PO₄) for 14 days increased their ability to undergo osteogenic differentiation.¹⁹⁷ Black phosphorus exhibits the capability to regulate oxidation and degradation, resulting in the non-toxic byproduct PO₄³⁻. This PO₄³⁻ acts as a mineralisation resource, promoting in the formation of calcium phosphate (CaP) deposits that facilitate bone repair.^{198, 199} Introduction of graphene oxide nanosheets enhances initial cell attachment and wraps around black phosphorus, enabling continuous release of PO₄³⁻. This stimulation of cell osteogenesis promotes the formation of new bone.²⁰⁰ Numerous studies have demonstrated that P-rich materials can stimulate mineralisation and promote bone regeneration.²⁰¹

Bioactive elements, ranging from trace metals to rare earths, play a foundational role in bone metabolism and regeneration (Figure 6). Elements like Ag, Cu, and Zn actively influence osteogenesis, angiogenesis, and osteoblast proliferation. Ga and Si, traditionally known for antibacterial and bone mineralisation effects respectively, showcase potential in bone turnover and osteoclast modulation. Mn, F, and Co, though dose-dependent, exhibit promising osteogenic differentiation impacts. Li, Mg, and Ca ions enhance bone cell proliferation, differentiation, and overall bone tissue regeneration. Rarer elements like Rb, Sr, Sc, La, Ce, Gd, and Hf, when doped in biomaterials, activate specific pathways fostering bone cell proliferation, differentiation, and osteogenic gene expression. These elements, in synergy, offer avenues for innovative bone regeneration therapies.

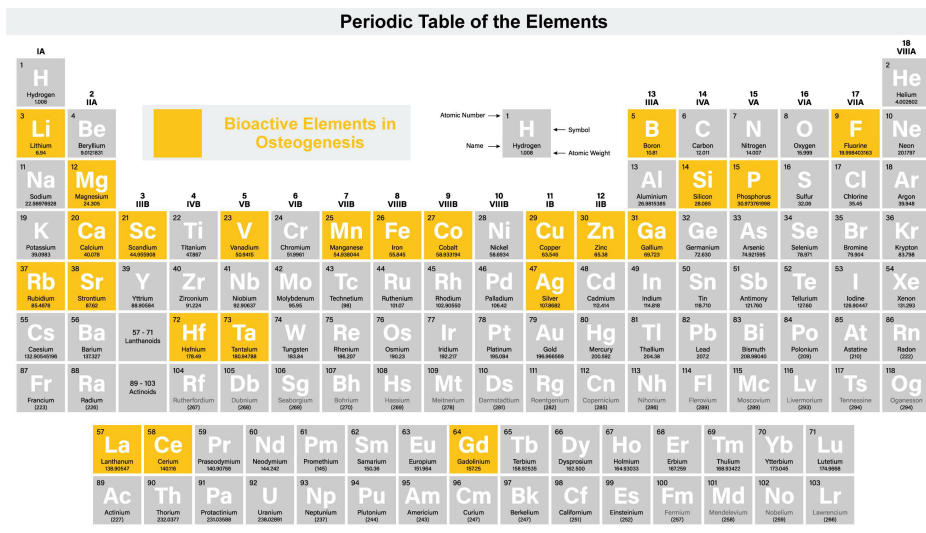


Figure 6. The role of bioactive elements in osteogenesis. Created with BioRender.com.

Challenges and Perspectives

This review comprehensively explores the role and mechanisms of bioactive elements such as Zn, Mg, and Si in bone regeneration. Initially, the review underlines the complex biological attributes and regeneration process of bone tissue, involving multiple stages like osteoimmunomodulation, neuroregulation, angiogenesis, and osteogenesis. Traditional bone regeneration strategies, although effective, are fraught with limitations such as stability, immunogenicity, and cost-effectiveness, often relying on growth factors and pharmaceuticals. Bioactive elements not only offer therapeutic efficacy but also superior stability and reduced biotic risks. These elements are frequently integrated into biomaterials, serving as multifaceted bioactive components that facilitate bone regeneration through controllable release mechanisms. In summary, this review establishes bioactive elements as a robust and clinically viable strategy for advanced bone regeneration, contributing to the advancement of bone tissue engineering.

The exploration of diverse elements in bone regeneration reveals promising prospects, showcasing a preference for employing a mixture of multiple elements in contemporary research endeavors. The myriad combinations, encompassing considerations of concentration and proportion among other parameters, necessitate rigorous experimental validations and iterative optimisations, thereby representing a time and resource-intensive endeavor. The integration of machine learning (ML) emerges as a potential solution to mitigate this impasse. ML, representing a facet of artificial intelligence, flourishes owing to its ability to evolve through data comprehension over time. It holds the promise to significantly expedite the screening and optimisation of elemental combinations for therapeutic efficacy, adeptly understanding the high-dimensional parameter space, and pinpointing potent combinations with minimal empirical trials.

Transitioning to the emerging realm of organoids, it unveils a fertile domain for clinical translational research, albeit the field of bone organoids remains nascent, with its construction strategies yet to reach maturation. The architectural complexities of bone organoids frequently necessitate the incorporation of a spectrum of growth factors to stimulate stem cell differentiation, yet the prohibitive cost of these factors presents a substantial impediment. The prospective benefits of bioactive elements in bone organoid construction herald a paradigm shift. The venture into multi-element incorporation could outline an economical and efficacious avenue, harboring the potential to revolutionize the bone organoid research paradigm. The envisaged synergistic interactions among these bioactive elements could not merely mimic the complex biochemical cues indispensable for bone development but also potentially unveil novel mechanisms underpinning bone regeneration, thereby augmenting the therapeutic and scientific horizons in bone tissue engineering and regenerative medicine.

Author contributions

JCS conceived the idea, LB handled the design, writing, and revision of the paper, and PR Song contributed to the writing and revision of this work. All authors approved the final version of the manuscript.

Financial support

This work was financially supported by National Natural Science Foundation of China (Nos. 82230071, 82172098), and Laboratory Animal Research Project of Shanghai Committee of Science and Technology (No. 23141900600).

Acknowledgement

None.

Conflicts of interest statement

There are no conflicts of interest.

Editor note: Jiacan Su is an Editorial Board member of *Biomaterials Translational*. He was blinded from reviewing or making decisions on the manuscript. The article was subject to the journal's standard procedures, with peer review handled independently of this Editorial Board member and his research group.

Open access statement

This is an open access journal, and articles are distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License, which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.

1. Koushik, T. M.; Miller, C. M.; Antunes, E. Bone tissue engineering scaffolds: function of multi-material hierarchically structured scaffolds. *Adv Healthc Mater.* **2023**, *12*, e2202766.
2. Stahl, A.; Yang, Y. P. Regenerative approaches for the treatment of large bone defects. *Tissue Eng Part B Rev.* **2021**, *27*, 539-547.
3. Fernandes, T. A. P.; Gonçalves, L. M. L.; Brito, J. A. A. Relationships between bone turnover and energy metabolism. *J Diabetes Res.* **2017**, *2017*, 9021314.
4. Yuan, J.; Maturavongsadit, P.; Metavarayuth, K.; Luckanagul, J. A.; Wang, Q. Enhanced bone defect repair by polymeric substitute fillers of multiarm polyethylene glycol-crosslinked hyaluronic acid hydrogels. *Macromol Biosci.* **2019**, *19*, e1900021.
5. Gyulay, K. K.; Karázi, P.; Rédei, M.; Sólymos, P.; Schandl, K.; Lacza, Z.; Horváthy, D. B. Evaluation of serum albumin-coated bone allograft for bone regeneration: a seven-year follow-up study of 26 cases. *Int J Mol Sci.* **2023**, *24*, 9232.
6. Ferraz, M. P. Bone grafts in dental medicine: an overview of autografts, allografts and synthetic materials. *Materials (Basel).* **2023**, *16*, 4117.
7. Bai, L.; Du, Z.; Du, J.; Yao, W.; Zhang, J.; Weng, Z.; Liu, S.; Zhao, Y.; Liu, Y.; Zhang, X.; Huang, X.; Yao, X.; Crawford, R.; Hang, R.; Huang, D.; Tang, B.; Xiao, Y. A multifaceted coating on titanium dictates osteoimmunomodulation and osteo/angio-genesis towards ameliorative osseointegration. *Biomaterials.* **2018**, *162*, 154-169.
8. Bosch-Ruá, È.; Díez-Tercero, L.; Buitrago, J. O.; Castro, E.; Pérez, R. A. Angiogenic and immunomodulation role of ions for initial stages of bone tissue regeneration. *Acta Biomater.* **2023**, *166*, 14-41.
9. Janmohammadi, M.; Nazemi, Z.; Salehi, A. O. M.; Seyfoori, A.; John, J. V.; Nourbakhsh, M. S.; Akbari, M. Cellulose-based composite scaffolds for bone tissue engineering and localized drug delivery. *Bioact Mater.* **2023**, *20*, 137-163.
10. Wu, J.; Cheng, X.; Wu, J.; Chen, J.; Pei, X. The development of magnesium-based biomaterials in bone tissue engineering: A review. *J Biomed Mater Res B Appl Biomater.* **2023**. doi: 10.1002/jbm.b.35326.
11. Wang, H.; Yu, R.; Wang, M.; Wang, S.; Ouyang, X.; Yan, Z.; Chen, S.; Wang, W.; Wu, F.; Fan, C. Insulin-like growth factor binding protein 4 loaded electrospun membrane ameliorating tendon injury by promoting retention of IGF-1. *J Control Release.* **2023**, *356*, 162-174.
12. Youssef, A.; Aboalola, D.; Han, V. K. The roles of insulin-like growth factors in mesenchymal stem cell niche. *Stem Cells Int.* **2017**, *2017*, 9453108.

Biomaterials contain bioactive elements for bone repair

13. Singh, S. K. Impact of product-related factors on immunogenicity of biotherapeutics. *J Pharm Sci.* **2011**, *100*, 354-387.
14. Jiskoot, W.; Randolph, T. W.; Volkin, D. B.; Middaugh, C. R.; Schöneich, C.; Winter, G.; Friess, W.; Crommelin, D. J.; Carpenter, J. F. Protein instability and immunogenicity: roadblocks to clinical application of injectable protein delivery systems for sustained release. *J Pharm Sci.* **2012**, *101*, 946-954.
15. Mitchell, A. C.; Briquez, P. S.; Hubbell, J. A.; Cochran, J. R. Engineering growth factors for regenerative medicine applications. *Acta Biomater.* **2016**, *30*, 1-12.
16. Apostolopoulos, V.; Bojarska, J.; Chai, T. T.; Elnagdy, S.; Kaczmarek, K.; Matsoukas, J.; New, R.; Parang, K.; Lopez, O. P.; Parhiz, H.; Perera, C. O.; Pickholz, M.; Remko, M.; Saviano, M.; Skwarczynski, M.; Tang, Y.; Wolf, W. M.; Yoshiya, T.; Zabrocki, J.; Zielenkiewicz, P.; AlKhazindar, M.; Barriga, V.; Kelaidonis, K.; Sarasia, E. M.; Toth, I. A global review on short peptides: frontiers and perspectives. *Molecules.* **2021**, *26*, 430.
17. Hamley, I. W. Small bioactive peptides for biomaterials design and therapeutics. *Chem Rev.* **2017**, *117*, 14015-14041.
18. Zou, P.; Chen, W. T.; Sun, T.; Gao, Y.; Li, L. L.; Wang, H. Recent advances: peptides and self-assembled peptide-nanosystems for antimicrobial therapy and diagnosis. *Biomater Sci.* **2020**, *8*, 4975-4996.
19. Chen, Z.; Klein, T.; Murray, R. Z.; Crawford, R.; Chang, J.; Wu, C.; Xiao, Y. Osteoimmunomodulation for the development of advanced bone biomaterials. *Mater Today.* **2016**, *19*, 304-321.
20. Chai, Y. C.; Mendes, L. F.; van Gastel, N.; Carmeliet, G.; Luyten, F. P. Fine-tuning pro-angiogenic effects of cobalt for simultaneous enhancement of vascular endothelial growth factor secretion and implant neovascularization. *Acta Biomater.* **2018**, *72*, 447-460.
21. Kong, N.; Lin, K.; Li, H.; Chang, J. Synergy effects of copper and silicon ions on stimulation of vascularization by copper-doped calcium silicate. *J Mater Chem B.* **2014**, *2*, 1100-1110.
22. De la Fuente, B.; Vázquez, M.; Rocha, R. A.; Devesa, V.; Vélez, D. Effects of sodium fluoride on immune response in murine macrophages. *Toxicol In Vitro.* **2016**, *34*, 81-87.
23. Liu, L.; Liu, Y.; Feng, C.; Chang, J.; Fu, R.; Wu, T.; Yu, F.; Wang, X.; Xia, L.; Wu, C.; Fang, B. Lithium-containing biomaterials stimulate bone marrow stromal cell-derived exosomal miR-130a secretion to promote angiogenesis. *Biomaterials.* **2019**, *192*, 523-536.
24. Shen, J.; Chen, B.; Zhai, X.; Qiao, W.; Wu, S.; Liu, X.; Zhao, Y.; Ruan, C.; Pan, H.; Chu, P. K.; Cheung, K. M. C.; Yeung, K. W. K. Stepwise 3D-spatio-temporal magnesium cationic niche: nanocomposite scaffold mediated microenvironment for modulating intramembranous ossification. *Bioact Mater.* **2021**, *6*, 503-519.
25. Bai, L.; Wu, R.; Wang, Y.; Wang, X.; Zhang, X.; Huang, X.; Qin, L.; Hang, R.; Zhao, L.; Tang, B. Osteogenic and angiogenic activities of silicon-incorporated TiO₂ nanotube arrays. *J Mater Chem B.* **2016**, *4*, 5548-5559.
26. Bai, L.; Hang, R.; Gao, A.; Zhang, X.; Huang, X.; Wang, Y.; Tang, B.; Zhao, L.; Chu, P. K. Nanostructured titanium-silver coatings with good antibacterial activity and cytocompatibility fabricated by one-step magnetron sputtering. *Appl Surf Sci.* **2015**, *355*, 32-44.
27. Yan, R.; Li, J.; Wu, Q.; Zhang, X.; Hu, L.; Deng, Y.; Jiang, R.; Wen, J.; Jiang, X. Trace element-augmented titanium implant with targeted angiogenesis and enhanced osseointegration in osteoporotic rats. *Front Chem.* **2022**, *10*, 839062.
28. Qiao, W.; Pan, D.; Zheng, Y.; Wu, S.; Liu, X.; Chen, Z.; Wan, M.; Feng, S.; Cheung, K. M. C.; Yeung, K. W. K.; Cao, X. Divalent metal cations stimulate skeleton interoception for new bone formation in mouse injury models. *Nat Commun.* **2022**, *13*, 535.
29. Bai, L.; Liu, Y.; Du, Z.; Weng, Z.; Yao, W.; Zhang, X.; Huang, X.; Yao, X.; Crawford, R.; Hang, R.; Huang, D.; Tang, B.; Xiao, Y. Differential effect of hydroxyapatite nano-particle versus nano-rod decorated titanium micro-surface on osseointegration. *Acta Biomater.* **2018**, *76*, 344-358.
30. Bai, L.; Chen, P.; Zhao, Y.; Hang, R.; Yao, X.; Tang, B.; Liu, C.; Xiao, Y.; Hang, R. A micro/nano-biomimetic coating on titanium orchestrates osteo/angio-genesis and osteoimmunomodulation for advanced osseointegration. *Biomaterials.* **2021**, *278*, 121162.
31. Kusumbe, A. P.; Ramasamy, S. K.; Adams, R. H. Coupling of angiogenesis and osteogenesis by a specific vessel subtype in bone. *Nature.* **2014**, *507*, 323-328.
32. Xie, Y.; Hu, C.; Feng, Y.; Li, D.; Ai, T.; Huang, Y.; Chen, X.; Huang, L.; Tan, J. Osteoimmunomodulatory effects of biomaterial modification strategies on macrophage polarization and bone regeneration. *Regen Biomater.* **2020**, *7*, 233-245.
33. Zhong, Z.; Wu, X.; Wang, Y.; Li, M.; Li, Y.; Liu, X.; Zhang, X.; Lan, Z.; Wang, J.; Du, Y.; Zhang, S. Zn/Sr dual ions-collagen co-assembly hydroxyapatite enhances bone regeneration through procedural osteoimmunomodulation and osteogenesis. *Bioact Mater.* **2022**, *10*, 195-206.
34. Wang, Y.; Wang, J.; Gao, R.; Liu, X.; Feng, Z.; Zhang, C.; Huang, P.; Dong, A.; Kong, D.; Wang, W. Biomimetic glycopeptide hydrogel coated PCL/nHA scaffold for enhanced cranial bone regeneration via macrophage M2 polarization-induced osteo-immunomodulation. *Biomaterials.* **2022**, *285*, 121538.
35. Schlundt, C.; Fischer, H.; Bucher, C. H.; Rendenbach, C.; Duda, G. N.; Schmidt-Bleek, K. The multifaceted roles of macrophages in bone regeneration: A story of polarization, activation and time. *Acta Biomater.* **2021**, *133*, 46-57.
36. Bai, X.; Liu, W.; Xu, L.; Ye, Q.; Zhou, H.; Berg, C.; Yuan, H.; Li, J.; Xia, W. Sequential macrophage transition facilitates endogenous bone regeneration induced by Zn-doped porous microcrystalline bioactive glass. *J Mater Chem B.* **2021**, *9*, 2885-2898.
37. Lee, J.; Byun, H.; Madhurakkat Perikamana, S. K.; Lee, S.; Shin, H. Current advances in immunomodulatory biomaterials for bone regeneration. *Adv Healthc Mater.* **2019**, *8*, e1801106.
38. Wang, Y.; Lin, Q.; Zhang, H.; Wang, S.; Cui, J.; Hu, Y.; Liu, J.; Li, M.; Zhang, K.; Zhou, F.; Jing, Y.; Geng, Z.; Su, J. M2 macrophage-derived exosomes promote diabetic fracture healing by acting as an immunomodulator. *Bioact Mater.* **2023**, *28*, 273-283.
39. Kushioka, J.; Chow, S. K.; Toya, M.; Tsubosaka, M.; Shen, H.; Gao, Q.; Li, X.; Zhang, N.; Goodman, S. B. Bone regeneration in inflammation with aging and cell-based immunomodulatory therapy. *Inflamm Regen.* **2023**, *43*, 29.
40. Xiang, X.; Pathak, J. L.; Wu, W.; Li, J.; Huang, W.; Wu, Q.; Xin, M.; Wu, Y.; Huang, Y.; Ge, L.; Zeng, S. Human serum-derived exosomes modulate macrophage inflammation to promote VCAM1-mediated angiogenesis and bone regeneration. *J Cell Mol Med.* **2023**, *27*, 1131-1143.
41. Lv, X.; Gao, F.; Cao, X. Skeletal interoception in bone homeostasis and pain. *Cell Metab.* **2022**, *34*, 1914-1931.
42. Tao, R.; Mi, B.; Hu, Y.; Lin, S.; Xiong, Y.; Lu, X.; Panayi, A. C.; Li, G.; Liu, G. Hallmarks of peripheral nerve function in bone regeneration. *Bone Res.* **2023**, *11*, 6.
43. Li, L.; Li, A.; Zhu, L.; Gan, L.; Zuo, L. Roxadustat promotes osteoblast differentiation and prevents estrogen deficiency-induced bone loss by

- stabilizing HIF-1 α and activating the Wnt/ β -catenin signaling pathway. *J Orthop Surg Res.* **2022**, *17*, 286.
44. Nencini, S.; Ringuet, M.; Kim, D. H.; Chen, Y. J.; Greenhill, C.; Ivanusic, J. J. Mechanisms of nerve growth factor signaling in bone nociceptors and in an animal model of inflammatory bone pain. *Mol Pain.* **2017**, *13*, 1744806917697011.
 45. Lai, Y.; Li, Y.; Cao, H.; Long, J.; Wang, X.; Li, L.; Li, C.; Jia, Q.; Teng, B.; Tang, T.; Peng, J.; Eglin, D.; Alini, M.; Grijpma, D. W.; Richards, G.; Qin, L. Osteogenic magnesium incorporated into PLGA/TCP porous scaffold by 3D printing for repairing challenging bone defect. *Biomaterials.* **2019**, *197*, 207-219.
 46. Yan, Y.; Wang, L.; Ge, L.; Pathak, J. L. Osteocyte-mediated translation of mechanical stimuli to cellular signaling and its role in bone and non-bone-related clinical complications. *Curr Osteoporos Rep.* **2020**, *18*, 67-80.
 47. Testa, U.; Castelli, G.; Pelosi, E. Role of endothelial progenitor cells in vascular development, homeostatic maintenance of blood vessels and in injury-mediated reparative response. *Stem Cell Investig.* **2020**, *7*, 7.
 48. Zhang, Y.; Zhang, Y. Y.; Pan, Z. W.; Li, Q. Q.; Sun, L. H.; Li, X.; Gong, M. Y.; Yang, X. W.; Wang, Y. Y.; Li, H. D.; Xuan, L. N.; Shao, Y. C.; Li, M. M.; Zhang, M. Y.; Yu, Q.; Li, Z.; Zhang, X. F.; Liu, D. H.; Zhu, Y. M.; Tan, Z. Y.; Zhang, Y. Y.; Liu, Y. Q.; Zhang, Y.; Jiao, L.; Yang, B. F. GDF11 promotes wound healing in diabetic mice via stimulating HIF-1 α -VEGF/SDF-1 α -mediated endothelial progenitor cell mobilization and neovascularization. *Acta Pharmacol Sin.* **2023**, *44*, 999-1013.
 49. Akatsu, Y.; Takahashi, N.; Yoshimatsu, Y.; Kimuro, S.; Muramatsu, T.; Katsura, A.; Maishi, N.; Suzuki, H. I.; Inazawa, J.; Hida, K.; Miyazono, K.; Watabe, T. Fibroblast growth factor signals regulate transforming growth factor- β -induced endothelial-to-myofibroblast transition of tumor endothelial cells via Elk1. *Mol Oncol.* **2019**, *13*, 1706-1724.
 50. Wang, Y.; Li, J. Current progress in growth factors and extracellular vesicles in tendon healing. *Int Wound J.* **2023**, *20*, 3871-3883.
 51. Miron, R. J.; Bosshardt, D. D. OsteoMacs: Key players around bone biomaterials. *Biomaterials.* **2016**, *82*, 1-19.
 52. Zhang, Q.; Liu, Y.; Li, J.; Wang, J.; Liu, C. Recapitulation of growth factor-enriched microenvironment via BMP receptor activating hydrogel. *Bioact Mater.* **2023**, *20*, 638-650.
 53. Rahman, M. S.; Akhtar, N.; Jamil, H. M.; Banik, R. S.; Asaduzzaman, S. M. TGF- β /BMP signaling and other molecular events: regulation of osteoblastogenesis and bone formation. *Bone Res.* **2015**, *3*, 15005.
 54. Hao, Z.; Ren, L.; Zhang, Z.; Yang, Z.; Wu, S.; Liu, G.; Cheng, B.; Wu, J.; Xia, J. A multifunctional neuromodulation platform utilizing Schwann cell-derived exosomes orchestrates bone microenvironment via immunomodulation, angiogenesis and osteogenesis. *Bioact Mater.* **2023**, *23*, 206-222.
 55. Hu, K.; Shang, Z.; Yang, X.; Zhang, Y.; Cao, L. Macrophage polarization and the regulation of bone immunity in bone homeostasis. *J Inflamm Res.* **2023**, *16*, 3563-3580.
 56. Veis, D. J.; O'Brien, C. A. Osteoclasts, Master Sculptors of Bone. *Annu Rev Pathol.* **2023**, *18*, 257-281.
 57. Yang, N.; Liu, Y. The role of the immune microenvironment in bone regeneration. *Int J Med Sci.* **2021**, *18*, 3697-3707.
 58. Cao, W.; Helder, M. N.; Bravenboer, N.; Wu, G.; Jin, J.; Ten Bruggenkate, C. M.; Klein-Nulend, J.; Schulten, E. Is there a governing role of osteocytes in bone tissue regeneration? *Curr Osteoporos Rep.* **2020**, *18*, 541-550.
 59. Chen, Y.; Guan, M.; Ren, R.; Gao, C.; Cheng, H.; Li, Y.; Gao, B.; Wei, Y.; Fu, J.; Sun, J.; Xiong, W. Improved immunoregulation of ultra-low-dose silver nanoparticle-loaded TiO(2) nanotubes via M2 macrophage polarization by regulating GLUT1 and autophagy. *Int J Nanomedicine.* **2020**, *15*, 2011-2026.
 60. Routray, I.; Ali, S. Boron induces lymphocyte proliferation and modulates the priming effects of lipopolysaccharide on macrophages. *PLoS One.* **2016**, *11*, e0150607.
 61. Lu, X.; Li, K.; Xie, Y.; Qi, S.; Shen, Q.; Yu, J.; Huang, L.; Zheng, X. Improved osteogenesis of boron incorporated calcium silicate coatings via immunomodulatory effects. *J Biomed Mater Res A.* **2019**, *107*, 12-24.
 62. Zhang, J.; Wu, Q.; Yin, C.; Jia, X.; Zhao, Z.; Zhang, X.; Yuan, G.; Hu, H.; Zhao, Q. Sustained calcium ion release from bioceramics promotes CaSR-mediated M2 macrophage polarization for osteoinduction. *J Leukoc Biol.* **2021**, *110*, 485-496.
 63. Yang, Y.; Ye, Y. C.; Chen, Y.; Zhao, J. L.; Gao, C. C.; Han, H.; Liu, W. C.; Qin, H. Y. Crosstalk between hepatic tumor cells and macrophages via Wnt/ β -catenin signaling promotes M2-like macrophage polarization and reinforces tumor malignant behaviors. *Cell Death Dis.* **2018**, *9*, 793.
 64. Balsano, C.; Porcu, C.; Sideri, S. Is copper a new target to counteract the progression of chronic diseases? *Metallomics.* **2018**, *10*, 1712-1722.
 65. Gaetke, L. M.; Chow-Johnson, H. S.; Chow, C. K. Copper: toxicological relevance and mechanisms. *Arch Toxicol.* **2014**, *88*, 1929-1938.
 66. Wu, P.; Dong, J.; Cheng, N.; Yang, R.; Han, Y.; Han, Y. Inflammatory cytokines expression in Wilson's disease. *Neurol Sci.* **2019**, *40*, 1059-1066.
 67. Chen, J.; Jiang, Y.; Shi, H.; Peng, Y.; Fan, X.; Li, C. The molecular mechanisms of copper metabolism and its roles in human diseases. *Pflugers Arch.* **2020**, *472*, 1415-1429.
 68. Huang, Q.; Li, X.; Elkhooly, T. A.; Liu, X.; Zhang, R.; Wu, H.; Feng, Q.; Liu, Y. The Cu-containing TiO(2) coatings with modulatory effects on macrophage polarization and bactericidal capacity prepared by micro-arc oxidation on titanium substrates. *Colloids Surf B Biointerfaces.* **2018**, *170*, 242-250.
 69. Wang, L.; Ren, L.; Tang, T.; Dai, K.; Yang, K.; Hao, Y. A novel nano-copper-bearing stainless steel with reduced Cu(2+) release only inducing transient foreign body reaction via affecting the activity of NF- κ B and Caspase 3. *Int J Nanomedicine.* **2015**, *10*, 6725-6739.
 70. Wu, S.; Xia, B.; Mai, S.; Feng, Z.; Wang, X.; Liu, Y.; Liu, R.; Li, Z.; Xiao, Y.; Chen, Z.; Chen, Z. Sodium fluoride under dose range of 2.4-24 μ M, a promising osteoimmunomodulatory agent for vascularized bone formation. *ACS Biomater Sci Eng.* **2019**, *5*, 817-830.
 71. Lee, M. J.; Chen, Y.; Huang, Y. P.; Hsu, Y. C.; Chiang, L. H.; Chen, T. Y.; Wang, G. J. Exogenous polyamines promote osteogenic differentiation by reciprocally regulating osteogenic and adipogenic gene expression. *J Cell Biochem.* **2013**, *114*, 2718-2728.
 72. Lee, M.; Arikawa, K.; Nagahama, F. Micromolar levels of sodium fluoride promote osteoblast differentiation through Runx2 signaling. *Biol Trace Elem Res.* **2017**, *178*, 283-291.
 73. Zhao, P. P.; Ge, Y. W.; Liu, X. L.; Ke, Q. F.; Zhang, J. W.; Zhu, Z. A.; Guo, Y. P. Ordered arrangement of hydrated GdPO4 nanorods in magnetic chitosan matrix promotes tumor photothermal therapy and bone regeneration against breast cancer bone metastases. *Chem Eng J.* **2020**, *381*, 122694.
 74. Seweryn, A.; Alicka, M.; Fal, A.; Kornicka-Garbowska, K.; Lawniczak-Jablonska, K.; Ozga, M.; Kuzmiuk, P.; Godlewski, M.; Marycz, K. Hafnium (IV) oxide obtained by atomic layer deposition (ALD) technology promotes early osteogenesis via activation of Runx2-OPN-mir21A axis while inhibits osteoclasts activity. *J Nanobiotechnology.* **2020**, *18*, 132.
 75. Bartnikowski, M.; Moon, H. J.; Ivanovski, S. Release of lithium from

- 3D printed polycaprolactone scaffolds regulates macrophage and osteoclast response. *Biomed Mater.* **2018**, *13*, 065003.
76. Fiorentini, D.; Cappadone, C.; Farruggia, G.; Prata, C. Magnesium: biochemistry, nutrition, detection, and social impact of diseases linked to its deficiency. *Nutrients.* **2021**, *13*, 1136.
 77. Wolf, F. I.; Cittadini, A. Chemistry and biochemistry of magnesium. *Mol Aspects Med.* **2003**, *24*, 3-9.
 78. Nielsen, F. H. Magnesium deficiency and increased inflammation: current perspectives. *J Inflamm Res.* **2018**, *11*, 25-34.
 79. Van Orden, R.; Eggett, D. L.; Franz, K. B. Influence of graded magnesium deficiencies on white blood cell counts and lymphocyte subpopulations in rats. *Magnes Res.* **2006**, *19*, 93-101.
 80. Qiao, W.; Wong, K. H. M.; Shen, J.; Wang, W.; Wu, J.; Li, J.; Lin, Z.; Chen, Z.; Matinlinna, J. P.; Zheng, Y.; Wu, S.; Liu, X.; Lai, K. P.; Chen, Z.; Lam, Y. W.; Cheung, K. M. C.; Yeung, K. W. K. TRPM7 kinase-mediated immunomodulation in macrophage plays a central role in magnesium ion-induced bone regeneration. *Nat Commun.* **2021**, *12*, 2885.
 81. Chen, Z.; Han, S.; Shi, M.; Liu, G.; Chen, Z.; Chang, J.; Wu, C.; Xiao, Y. Immunomodulatory effects of mesoporous silica nanoparticles on osteogenesis: From nanoimmunotoxicity to nanoimmunotherapy. *Appl Mater Today.* **2018**, *10*, 184-193.
 82. Huang, Y.; Wu, C.; Zhang, X.; Chang, J.; Dai, K. Regulation of immune response by bioactive ions released from silicate bioceramics for bone regeneration. *Acta Biomater.* **2018**, *66*, 81-92.
 83. Bai, L.; Liu, Y.; Zhang, X.; Huang, X.; Yao, X.; Hang, R.; Tang, B.; Xiao, Y. Favorable manipulation of macrophage/endothelial cell functionality and their cross-talk on silicon-doped titania nanotube arrays. *Nanoscale.* **2019**, *11*, 5920-5931.
 84. Rithidech, K. N.; Reungpatthanaphong, P.; Tungjai, M.; Jangiam, W.; Honikel, L.; Whorton, E. B. Persistent depletion of plasma gelsolin (pGSN) after exposure of mice to heavy silicon ions. *Life Sci Space Res (Amst).* **2018**, *17*, 83-90.
 85. Brown, D. M.; Beswick, P. H.; Donaldson, K. Induction of nuclear translocation of NF-kappaB in epithelial cells by respirable mineral fibres. *J Pathol.* **1999**, *189*, 258-264.
 86. Zhao, D. W.; Liu, C.; Zuo, K. Q.; Su, P.; Li, L. B.; Xiao, G. Y.; Cheng, L. Strontium-zinc phosphate chemical conversion coating improves the osseointegration of titanium implants by regulating macrophage polarization. *Chem Eng J.* **2021**, *408*, 127362.
 87. Yu, D.; Guo, S.; Yu, M.; Liu, W.; Li, X.; Chen, D.; Li, B.; Guo, Z.; Han, Y. Immunomodulation and osseointegration activities of Na(2)TiO(3) nanorods-arrayed coatings doped with different Sr content. *Bioact Mater.* **2022**, *10*, 323-334.
 88. Zhao, D. W.; Zuo, K. Q.; Wang, K.; Sun, Z. Y.; Lu, Y. P.; Cheng, L.; Xiao, G. Y.; Liu, C. Interleukin-4 assisted calcium-strontium-zinc-phosphate coating induces controllable macrophage polarization and promotes osseointegration on titanium implant. *Mater Sci Eng C Mater Biol Appl.* **2021**, *118*, 111512.
 89. Russell, K. C.; Phinney, D. G.; Lacey, M. R.; Barrilleaux, B. L.; Meyertholen, K. E.; O'Connor, K. C. In vitro high-capacity assay to quantify the clonal heterogeneity in trilineage potential of mesenchymal stem cells reveals a complex hierarchy of lineage commitment. *Stem Cells.* **2010**, *28*, 788-798.
 90. Luo, X.; Barbieri, D.; Davison, N.; Yan, Y.; de Bruijn, J. D.; Yuan, H. Zinc in calcium phosphate mediates bone induction: in vitro and in vivo model. *Acta Biomater.* **2014**, *10*, 477-485.
 91. Xu, Y.; Xu, C.; Yang, K.; Ma, L.; Li, G.; Shi, Y.; Feng, X.; Tan, L.; Duan, D.; Luo, Z.; Yang, C. Copper ion-modified germanium phosphorus nanosheets integrated with an electroactive and biodegradable hydrogel for neuro-vascularized bone regeneration. *Adv Healthc Mater.* **2023**, *12*, e2301151.
 92. Jing, X.; Xu, C.; Su, W.; Ding, Q.; Ye, B.; Su, Y.; Yu, K.; Zeng, L.; Yang, X.; Qu, Y.; Chen, K.; Sun, T.; Luo, Z.; Guo, X. Photosensitive and conductive hydrogel induced innervated bone regeneration for infected bone defect repair. *Adv Healthc Mater.* **2023**, *12*, e2201349.
 93. Zhang, Y.; Xu, J.; Ruan, Y. C.; Yu, M. K.; O'Laughlin, M.; Wise, H.; Chen, D.; Tian, L.; Shi, D.; Wang, J.; Chen, S.; Feng, J. Q.; Chow, D. H.; Xie, X.; Zheng, L.; Huang, L.; Huang, S.; Leung, K.; Lu, N.; Zhao, L.; Li, H.; Zhao, D.; Guo, X.; Chan, K.; Witte, F.; Chan, H. C.; Zheng, Y.; Qin, L. Implant-derived magnesium induces local neuronal production of CGRP to improve bone-fracture healing in rats. *Nat Med.* **2016**, *22*, 1160-1169.
 94. Jeanmonod, P.; Laschke, M. W.; Gola, N.; von Heesen, M.; Glanemann, M.; Dold, S.; Menger, M. D.; Moussavian, M. R. Silver acetate coating promotes early vascularization of Dacron vascular grafts without inducing host tissue inflammation. *J Vasc Surg.* **2013**, *58*, 1637-1643.
 95. Glenske, K.; Donkiewicz, P.; Köwitsch, A.; Milosevic-Oljaca, N.; Rider, P.; Rofall, S.; Franke, J.; Jung, O.; Smeets, R.; Schnettler, R.; Wenisch, S.; Barbeck, M. Applications of metals for bone regeneration. *Int J Mol Sci.* **2018**, *19*, 826.
 96. Kang, K.; Lim, D. H.; Choi, I. H.; Kang, T.; Lee, K.; Moon, E. Y.; Yang, Y.; Lee, M. S.; Lim, J. S. Vascular tube formation and angiogenesis induced by polyvinylpyrrolidone-coated silver nanoparticles. *Toxicol Lett.* **2011**, *205*, 227-234.
 97. Xia, L.; Ma, W.; Zhou, Y.; Gui, Z.; Yao, A.; Wang, D.; Takemura, A.; Uemura, M.; Lin, K.; Xu, Y. Stimulatory effects of boron containing bioactive glass on osteogenesis and angiogenesis of polycaprolactone: in vitro study. *Biomed Res Int.* **2019**, *2019*, 8961409.
 98. Haro Durand, L. A.; Góngora, A.; Porto López, J. M.; Boccaccini, A. R.; Zago, M. P.; Baldi, A.; Gorustovich, A. In vitro endothelial cell response to ionic dissolution products from boron-doped bioactive glass in the SiO(2)-CaO-P(2)O(5)-Na(2)O system. *J Mater Chem B.* **2014**, *2*, 7620-7630.
 99. Li, K.; Lu, X.; Liu, S.; Wu, X.; Xie, Y.; Zheng, X. Boron-incorporated micro/nano-topographical calcium silicate coating dictates osteo/angiogenesis and inflammatory response toward enhanced osseointegration. *Biol Trace Elem Res.* **2021**, *199*, 3801-3816.
 100. Chen, S.; Yang, Q.; Brow, R. K.; Liu, K.; Brow, K. A.; Ma, Y.; Shi, H. In vitro stimulation of vascular endothelial growth factor by borate-based glass fibers under dynamic flow conditions. *Mater Sci Eng C Mater Biol Appl.* **2017**, *73*, 447-455.
 101. Jacobs, A.; Renaudin, G.; Forestier, C.; Nedelec, J. M.; Descamps, S. Biological properties of copper-doped biomaterials for orthopedic applications: A review of antibacterial, angiogenic and osteogenic aspects. *Acta Biomater.* **2020**, *117*, 21-39.
 102. Wang, Y.; Zhang, W.; Yao, Q. Copper-based biomaterials for bone and cartilage tissue engineering. *J Orthop Translat.* **2021**, *29*, 60-71.
 103. Xiang, J.; Li, J.; He, J.; Tang, X.; Dou, C.; Cao, Z.; Yu, B.; Zhao, C.; Kang, F.; Yang, L.; Dong, S.; Yang, X. Cerium oxide nanoparticle modified scaffold interface enhances vascularization of bone grafts by activating calcium channel of mesenchymal stem cells. *ACS Appl Mater Interfaces.* **2016**, *8*, 4489-4499.
 104. Zheng, Y.; Yang, Y.; Deng, Y. Dual therapeutic cobalt-incorporated bioceramics accelerate bone tissue regeneration. *Mater Sci Eng C Mater Biol Appl.* **2019**, *99*, 770-782.

105. Fani, N.; Farokhi, M.; Azami, M.; Kamali, A.; Bakhshaiesh, N. L.; Ebrahimi-Barough, S.; Ai, J.; Eslaminejad, M. B. Endothelial and osteoblast differentiation of adipose-derived mesenchymal stem cells using a cobalt-doped cap/silk fibroin scaffold. *ACS Biomater Sci Eng*. **2019**, *5*, 2134-2146.
106. Delafontaine, P.; Bernstein, K. E.; Alexander, R. W. Insulin-like growth factor I gene expression in vascular cells. *Hypertension*. **1991**, *17*, 693-699.
107. Shi, H.; Yang, S.; Zeng, S.; Liu, X.; Zhang, J.; Zhang, J.; Wu, T.; Ye, X.; Yu, T.; Zhou, C.; Ye, J. Enhanced angiogenesis of biodegradable iron-doped octacalcium phosphate/poly(lactic-co-glycolic acid) scaffold for potential cancerous bone regeneration. *Appl Mater Today*. **2019**, *15*, 100-114.
108. Lin, S.; Yang, G.; Jiang, F.; Zhou, M.; Yin, S.; Tang, Y.; Tang, T.; Zhang, Z.; Zhang, W.; Jiang, X. A magnesium-enriched 3D culture system that mimics the bone development microenvironment for vascularized bone regeneration. *Adv Sci (Weinh)*. **2019**, *6*, 1900209.
109. Ye, L.; Xu, J.; Mi, J.; He, X.; Pan, Q.; Zheng, L.; Zu, H.; Chen, Z.; Dai, B.; Li, X.; Pang, Q.; Zou, L.; Zhou, L.; Huang, L.; Tong, W.; Li, G.; Qin, L. Biodegradable magnesium combined with distraction osteogenesis synergistically stimulates bone tissue regeneration via CGRP-FAK-VEGF signaling axis. *Biomaterials*. **2021**, *275*, 120984.
110. Gu, Z.; Xie, H.; Huang, C.; Peng, H.; Tan, H.; Li, L.; Yu, X. Effects of strontium-doped calcium polyphosphate on angiogenic growth factors expression of co-culturing system in vitro and of host cell in vivo. *RSC Adv*. **2014**, *4*, 2783-2792.
111. Zhao, F.; Lei, B.; Li, X.; Mo, Y.; Wang, R.; Chen, D.; Chen, X. Promoting in vivo early angiogenesis with sub-micrometer strontium-contained bioactive microspheres through modulating macrophage phenotypes. *Biomaterials*. **2018**, *178*, 36-47.
112. Srinath, P.; Abdul Azeem, P.; Venugopal Reddy, K. Review on calcium silicate-based bioceramics in bone tissue engineering. *Int J Appl Ceram Technol*. **2020**, *17*, 2450-2464.
113. Li, H.; Chang, J. Stimulation of proangiogenesis by calcium silicate bioactive ceramic. *Acta Biomater*. **2013**, *9*, 5379-5389.
114. Zhai, W.; Lu, H.; Chen, L.; Lin, X.; Huang, Y.; Dai, K.; Naoki, K.; Chen, G.; Chang, J. Silicate bioceramics induce angiogenesis during bone regeneration. *Acta Biomater*. **2012**, *8*, 341-349.
115. Mao, L.; Xia, L.; Chang, J.; Liu, J.; Jiang, L.; Wu, C.; Fang, B. The synergistic effects of Sr and Si bioactive ions on osteogenesis, osteoclastogenesis and angiogenesis for osteoporotic bone regeneration. *Acta Biomater*. **2017**, *61*, 217-232.
116. Tang, Y. Q.; Wang, Q. Y.; Ke, Q. F.; Zhang, C. Q.; Guan, J. J.; Guo, Y. P. Mineralization of ytterbium-doped hydroxyapatite nanorod arrays in magnetic chitosan scaffolds improves osteogenic and angiogenic abilities for bone defect healing. *Chem Eng J*. **2020**, *387*, 124166.
117. Zhu, D.; Su, Y.; Zheng, Y.; Fu, B.; Tang, L.; Qin, Y. X. Zinc regulates vascular endothelial cell activity through zinc-sensing receptor ZnR/GPR39. *Am J Physiol Cell Physiol*. **2018**, *314*, C404-C414.
118. Ma, J.; Zhao, N.; Zhu, D. Endothelial cellular responses to biodegradable metal zinc. *ACS Biomater Sci Eng*. **2015**, *1*, 1174-1182.
119. Zhang, J.; Park, Y. D.; Bae, W. J.; El-Fiqi, A.; Shin, S. H.; Lee, E. J.; Kim, H. W.; Kim, E. C. Effects of bioactive cements incorporating zinc-bioglass nanoparticles on odontogenic and angiogenic potential of human dental pulp cells. *J Biomater Appl*. **2015**, *29*, 954-964.
120. Hassan, A.; Elebeedy, D.; Matar, E. R.; Fahmy Mohamed Elsayed, A.; Abd El Maksoud, A. I. Investigation of angiogenesis and wound healing potential mechanisms of zinc oxide nanorods. *Front Pharmacol*. **2021**, *12*, 661217.
121. Bosch-Ru e, E.; Diez-Tercero, L.; Giordano-Kelhoffler, B.; Delgado, L. M.; Bosch, B. M.; Hoyos-Nogu es, M.; Mateos-Timoneda, M. A.; Tran, P. A.; Gil, F. J.; Perez, R. A. Biological roles and delivery strategies for ions to promote osteogenic induction. *Front Cell Dev Biol*. **2020**, *8*, 614545.
122. Santos, C. J.; Ferreira Soares, D. C.; Ferreira, C. A.; de Barros, A. L. B.; Silva Cunha Junior, A. D.; Filho, F. M. Antiangiogenic evaluation of ZnWO(4) nanoparticles synthesised through microwave-assisted hydrothermal method. *J Drug Target*. **2018**, *26*, 806-817.
123. Song, Y.; Wu, H.; Gao, Y.; Li, J.; Lin, K.; Liu, B.; Lei, X.; Cheng, P.; Zhang, S.; Wang, Y.; Sun, J.; Bi, L.; Pei, G. Zinc silicate/nanohydroxyapatite/collagen scaffolds promote angiogenesis and bone regeneration via the p38 MAPK pathway in activated monocytes. *ACS Appl Mater Interfaces*. **2020**, *12*, 16058-16075.
124. Qing, T.; Mahmood, M.; Zheng, Y.; Biris, A. S.; Shi, L.; Casciano, D. A. A genomic characterization of the influence of silver nanoparticles on bone differentiation in MC3T3-E1 cells. *J Appl Toxicol*. **2018**, *38*, 172-179.
125. Wu, Y.; Cheng, Z.; Hu, W.; Tang, S.; Zhou, X.; Dong, S. Biosynthesized silver nanoparticles inhibit osteoclastogenesis by suppressing NF- B signaling pathways. *Adv Biol (Weinh)*. **2023**, e2300355.
126. Liu, X.; Lee, P. Y.; Ho, C. M.; Lui, V. C.; Chen, Y.; Che, C. M.; Tam, P. K.; Wong, K. K. Silver nanoparticles mediate differential responses in keratinocytes and fibroblasts during skin wound healing. *ChemMedChem*. **2010**, *5*, 468-475.
127. Nielsen, F. H. The emergence of boron as nutritionally important throughout the life cycle. *Nutrition*. **2000**, *16*, 512-514.
128. Dessordi, R.; Spirlandeli, A. L.; Zamarioli, A.; Volpon, J. B.; Navarro, A. M. Boron supplementation improves bone health of non-obese diabetic mice. *J Trace Elem Med Biol*. **2017**, *39*, 169-175.
129. Yin, C.; Jia, X.; Zhao, Q.; Zhao, Z.; Wang, J.; Zhang, Y.; Li, Z.; Sun, H.; Li, Z. Transcription factor 7-like 2 promotes osteogenic differentiation and boron-induced bone repair via lipocalin 2. *Mater Sci Eng C Mater Biol Appl*. **2020**, *110*, 110671.
130. Li, X.; Wang, X.; Jiang, X.; Yamaguchi, M.; Ito, A.; Bando, Y.; Golberg, D. Boron nitride nanotube-enhanced osteogenic differentiation of mesenchymal stem cells. *J Biomed Mater Res B Appl Biomater*. **2016**, *104*, 323-329.
131. Yin, C.; Jia, X.; Miron, R. J.; Long, Q.; Xu, H.; Wei, Y.; Wu, M.; Zhang, Y.; Li, Z. Setd7 and its contribution to Boron-induced bone regeneration in Boron-mesoporous bioactive glass scaffolds. *Acta Biomater*. **2018**, *73*, 522-530.
132. Ying, D.; Ouyang, Z.; Liu, T.; Liu, X.; Huang, Q. Boron-containing micro/nano-structured TiO2/bioceramics coatings with modulatory effects on SaOS-2 cell response. *Mater Lett*. **2018**, *228*, 29-32.
133. Cai, B.; Tan, P.; Jiang, N.; Guo, Z.; Ay, B.; Li, S.; Hou, Y.; Li, Y.; You, Y.; Zhang, L.; Zhu, S. Bioinspired fabrication of calcium-doped TiP coating with nanofibrous microstructure to accelerate osseointegration. *Bioconjug Chem*. **2020**, *31*, 1641-1650.
134. Peacock, M. Calcium metabolism in health and disease. *Clin J Am Soc Nephrol*. **2010**, *5 Suppl 1*, S23-30.
135. Foreman, M. A.; Gu, Y.; Howl, J. D.; Jones, S.; Publicover, S. J. Group III metabotropic glutamate receptor activation inhibits Ca²⁺ influx and nitric oxide synthase activity in bone marrow stromal cells. *J Cell Physiol*. **2005**, *204*, 704-713.
136. Riddle, R. C.; Taylor, A. F.; Genetos, D. C.; Donahue, H. J. MAP kinase and calcium signaling mediate fluid flow-induced human mesenchymal stem cell proliferation. *Am J Physiol Cell Physiol*. **2006**, *290*, C776-784.

137. Liu, D.; Genetos, D. C.; Shao, Y.; Geist, D. J.; Li, J.; Ke, H. Z.; Turner, C. H.; Duncan, R. L. Activation of extracellular-signal regulated kinase (ERK1/2) by fluid shear is Ca(2+)- and ATP-dependent in MC3T3-E1 osteoblasts. *Bone*. **2008**, *42*, 644-652.
138. Danciu, T. E.; Adam, R. M.; Naruse, K.; Freeman, M. R.; Hauschka, P. V. Calcium regulates the PI3K-Akt pathway in stretched osteoblasts. *FEBS Lett.* **2003**, *536*, 193-197.
139. Lee, M. N.; Hwang, H. S.; Oh, S. H.; Roshanzadeh, A.; Kim, J. W.; Song, J. H.; Kim, E. S.; Koh, J. T. Elevated extracellular calcium ions promote proliferation and migration of mesenchymal stem cells via increasing osteopontin expression. *Exp Mol Med*. **2018**, *50*, 1-16.
140. Gaharwar, A. K.; Mihaila, S. M.; Swami, A.; Patel, A.; Sant, S.; Reis, R. L.; Marques, A. P.; Gomes, M. E.; Khademhosseini, A. Bioactive silicate nanoplatelets for osteogenic differentiation of human mesenchymal stem cells. *Adv Mater*. **2013**, *25*, 3329-3336.
141. Westhauser, F.; Rehder, F.; Decker, S.; Kunisch, E.; Moghaddam, A.; Zheng, K.; Boccaccini, A. R. Ionic dissolution products of Cerium-doped bioactive glass nanoparticles promote cellular osteogenic differentiation and extracellular matrix formation of human bone marrow derived mesenchymal stromal cells. *Biomed Mater*. **2021**, *16*, 035028.
142. Hsu, S. H.; Chen, C. T.; Wei, Y. H. Inhibitory effects of hypoxia on metabolic switch and osteogenic differentiation of human mesenchymal stem cells. *Stem Cells*. **2013**, *31*, 2779-2788.
143. Yoo, H. I.; Moon, Y. H.; Kim, M. S. Effects of CoCl₂ on multi-lineage differentiation of C3H/10T1/2 mesenchymal stem cells. *Korean J Physiol Pharmacol*. **2016**, *20*, 53-62.
144. Burghardt, I.; Lüthen, F.; Prinz, C.; Kreikemeyer, B.; Zietz, C.; Neumann, H. G.; Rychly, J. A dual function of copper in designing regenerative implants. *Biomaterials*. **2015**, *44*, 36-44.
145. Lin, Z.; Cao, Y.; Zou, J.; Zhu, F.; Gao, Y.; Zheng, X.; Wang, H.; Zhang, T.; Wu, T. Improved osteogenesis and angiogenesis of a novel copper ions doped calcium phosphate cement. *Mater Sci Eng C Mater Biol Appl*. **2020**, *114*, 111032.
146. Zhang, J.; Wu, H.; He, F.; Wu, T.; Zhou, L.; Ye, J. Concentration-dependent osteogenic and angiogenic biological performances of calcium phosphate cement modified with copper ions. *Mater Sci Eng C Mater Biol Appl*. **2019**, *99*, 1199-1212.
147. Chen, M.; Wang, X. Q.; Zhang, E. L.; Wan, Y. Z.; Hu, J. Antibacterial ability and biocompatibility of fluorinated titanium by plasma-based surface modification. *Rare Met*. **2022**, *41*, 689-699.
148. Chen, L.; Song, W.; Markel, D. C.; Shi, T.; Muzik, O.; Matthew, H.; Ren, W. Flow perfusion culture of MC3T3-E1 osteogenic cells on gradient calcium polyphosphate scaffolds with different pore sizes. *J Biomater Appl*. **2016**, *30*, 908-918.
149. Qu, W. J.; Zhong, D. B.; Wu, P. F.; Wang, J. F.; Han, B. Sodium fluoride modulates caprine osteoblast proliferation and differentiation. *J Bone Miner Metab*. **2008**, *26*, 328-334.
150. Pan, X.; Huang, J.; Zhang, K.; Pei, Z.; Ding, Z.; Liang, Y.; Gu, Z.; Li, G.; Xie, H. Iron-doped brushite bone cement scaffold with enhanced osteoconductivity and antimicrobial properties for jaw regeneration. *Ceram Int*. **2021**, *47*, 25810-25820.
151. Strazic Geljic, I.; Melis, N.; Boukhechba, F.; Schaub, S.; Mellier, C.; Janvier, P.; Laugier, J. P.; Bouler, J. M.; Verron, E.; Scimeca, J. C. Gallium enhances reconstructive properties of a calcium phosphate bone biomaterial. *J Tissue Eng Regen Med*. **2018**, *12*, e854-e866.
152. Liao, F.; Peng, X. Y.; Yang, F.; Ke, Q. F.; Zhu, Z. H.; Guo, Y. P. Gadolinium-doped mesoporous calcium silicate/chitosan scaffolds enhanced bone regeneration ability. *Mater Sci Eng C Mater Biol Appl*. **2019**, *104*, 109999.
153. Zhao, P. P.; Hu, H. R.; Liu, J. Y.; Ke, Q. F.; Peng, X. Y.; Ding, H.; Guo, Y. P. Gadolinium phosphate/chitosan scaffolds promote new bone regeneration via Smad/Runx2 pathway. *Chem Eng J*. **2019**, *359*, 1120-1129.
154. Zhu, D. Y.; Lu, B.; Yin, J. H.; Ke, Q. F.; Xu, H.; Zhang, C. Q.; Guo, Y. P.; Gao, Y. S. Gadolinium-doped bioglass scaffolds promote osteogenic differentiation of hBMSC via the Akt/GSK3 β pathway and facilitate bone repair in vivo. *Int J Nanomedicine*. **2019**, *14*, 1085-1100.
155. Chu, M.; Sun, Z.; Fan, Z.; Yu, D.; Mao, Y.; Guo, Y. Bi-directional regulation functions of lanthanum-substituted layered double hydroxide nanohybrid scaffolds via activating osteogenesis and inhibiting osteoclastogenesis for osteoporotic bone regeneration. *Theranostics*. **2021**, *11*, 6717-6734.
156. Cheng, H.; Guo, Q.; Zhao, H.; Liu, K.; Kang, H.; Gao, F.; Guo, J.; Yuan, X.; Hu, S.; Li, F.; Yang, Q.; Fang, Z. An injectable hydrogel scaffold loaded with dual-drug/sustained-release PLGA microspheres for the regulation of macrophage polarization in the treatment of intervertebral disc degeneration. *Int J Mol Sci*. **2022**, *24*, 390.
157. Zhang, J.; Cai, L.; Tang, L.; Zhang, X.; Yang, L.; Zheng, K.; He, A.; Boccaccini, A. R.; Wei, J.; Zhao, J. Highly dispersed lithium doped mesoporous silica nanospheres regulating adhesion, proliferation, morphology, ALP activity and osteogenesis related gene expressions of BMSCs. *Colloids Surf B Biointerfaces*. **2018**, *170*, 563-571.
158. Mo, F.; Jiang, K.; Zhao, D.; Wang, Y.; Song, J.; Tan, W. DNA hydrogel-based gene editing and drug delivery systems. *Adv Drug Deliv Rev*. **2021**, *168*, 79-98.
159. Tan, Z.; Zhou, B.; Zheng, J.; Huang, Y.; Zeng, H.; Xue, L.; Wang, D. Lithium and copper induce the osteogenesis-angiogenesis coupling of bone marrow mesenchymal stem cells via crosstalk between canonical Wnt and HIF-1 α signaling pathways. *Stem Cells Int*. **2021**, *2021*, 6662164.
160. Huang, T. B.; Li, Y. Z.; Yu, K.; Yu, Z.; Wang, Y.; Jiang, Z. W.; Wang, H. M.; Yang, G. L. Effect of the Wnt signal-RANKL/OPG axis on the enhanced osteogenic integration of a lithium incorporated surface. *Biomater Sci*. **2019**, *7*, 1101-1116.
161. Wang, J.; Ma, X. Y.; Feng, Y. F.; Ma, Z. S.; Ma, T. C.; Zhang, Y.; Li, X.; Wang, L.; Lei, W. Magnesium ions promote the biological behaviour of rat calvarial osteoblasts by activating the PI3K/Akt signalling pathway. *Biol Trace Elem Res*. **2017**, *179*, 284-293.
162. Pantulap, U.; Arango-Ospina, M.; Boccaccini, A. R. Bioactive glasses incorporating less-common ions to improve biological and physical properties. *J Mater Sci Mater Med*. **2021**, *33*, 3.
163. Barrioni, B. R.; Norris, E.; Li, S.; Naruphontjirakul, P.; Jones, J. R.; Pereira, M. M. Osteogenic potential of sol-gel bioactive glasses containing manganese. *J Mater Sci Mater Med*. **2019**, *30*, 86.
164. Wu, T.; Shi, H.; Liang, Y.; Lu, T.; Lin, Z.; Ye, J. Improving osteogenesis of calcium phosphate bone cement by incorporating with manganese doped β -tricalcium phosphate. *Mater Sci Eng C Mater Biol Appl*. **2020**, *109*, 110481.
165. Su, Y.; Chen, L. J.; He, J. R.; Yuan, X. J.; Cen, Y. L.; Su, F. X.; Tang, L. Y.; Zhang, A. H.; Chen, W. Q.; Lin, Y.; Wang, S. M.; Ren, Z. F. Rubidium in breast cancers. *Clin Chim Acta*. **2011**, *412*, 2305-2309.
166. Ouyang, S.; Zheng, K.; Huang, Q.; Liu, Y.; Boccaccini, A. R. Synthesis and characterization of rubidium-containing bioactive glass nanoparticles. *Mater Lett*. **2020**, *273*, 127920.
167. Chen, M.; Wu, S.; Tan, Y.; Li, R.; Liu, Y.; Huang, Q. Rubidium-doped titanium surfaces with modulatory effects on MC3T3-E1 cell response

- and antibacterial capacity against *Staphylococcus aureus*. *Biomed Mater.* **2019**, *14*, 045016.
168. Tan, Y. N.; Chen, W. J.; Wei, W.; Huang, Q. L.; He, X. Rubidium-modified bioactive glass-ceramics with hydroxyapatite crystals for bone regeneration. *Trans Nonferrous Met Soc China.* **2021**, *31*, 521-532.
 169. Ren, N.; Yu, X.; Wang, A.; Liang, N.; Feng, Z.; Sun, C. Effects of scandium chloride on osteogenic and adipogenic differentiation of mesenchymal stem cells. *J Rare Earths.* **2022**, *40*, 161-168.
 170. Millucci, L.; Minetti, M.; Orlandini, M.; Braconi, D.; Schiavone, M. L.; Galderisi, S.; Marzocchi, B.; Spiga, O.; Rappuoli, R.; Spreafico, A.; Perretti, G.; Bernardini, G.; Santucci, A. Beer promotes differentiation and mineralization of human osteoblastic cells: Role of silicon. *J Funct Foods.* **2019**, *54*, 109-118.
 171. Reffitt, D. M.; Ogston, N.; Jugdaohsingh, R.; Cheung, H. F.; Evans, B. A.; Thompson, R. P.; Powell, J. J.; Hampson, G. N. Orthosilicic acid stimulates collagen type 1 synthesis and osteoblastic differentiation in human osteoblast-like cells in vitro. *Bone.* **2003**, *32*, 127-135.
 172. Dong, M.; Jiao, G.; Liu, H.; Wu, W.; Li, S.; Wang, Q.; Xu, D.; Li, X.; Liu, H.; Chen, Y. Biological silicon stimulates collagen type 1 and osteocalcin synthesis in human osteoblast-like cells through the BMP-2/Smad/RUNX2 signaling pathway. *Biol Trace Elem Res.* **2016**, *173*, 306-315.
 173. Zhou, H.; Jiao, G.; Dong, M.; Chi, H.; Wang, H.; Wu, W.; Liu, H.; Ren, S.; Kong, M.; Li, C.; Zhang, L.; Chen, Y. Orthosilicic acid accelerates bone formation in human osteoblast-like cells through the PI3K-Akt-mTOR pathway. *Biol Trace Elem Res.* **2019**, *190*, 327-335.
 174. Zhou, X.; Moussa, F. M.; Mankoci, S.; Ustiyana, P.; Zhang, N.; Abdelmagid, S.; Molenda, J.; Murphy, W. L.; Safadi, F. F.; Sahai, N. Orthosilicic acid, Si(OH)₄, stimulates osteoblast differentiation in vitro by upregulating miR-146a to antagonize NF- κ B activation. *Acta Biomater.* **2016**, *39*, 192-202.
 175. Ma, W.; Wang, F.; You, Y.; Wu, W.; Chi, H.; Jiao, G.; Zhang, L.; Zhou, H.; Wang, H.; Chen, Y. Ortho-silicic acid inhibits RANKL-induced osteoclastogenesis and reverses ovariectomy-induced bone loss in vivo. *Biol Trace Elem Res.* **2021**, *199*, 1864-1876.
 176. You, Y.; Ma, W.; Wang, F.; Jiao, G.; Zhang, L.; Zhou, H.; Wu, W.; Wang, H.; Chen, Y. Ortho-silicic acid enhances osteogenesis of osteoblasts through the upregulation of miR-130b which directly targets PTEN. *Life Sci.* **2021**, *264*, 118680.
 177. Liangjiao, C.; Ping, Z.; Ruoyu, L.; Yanli, Z.; Ting, S.; Yanjun, L.; Longquan, S. Potential proinflammatory and osteogenic effects of dicalcium silicate particles in vitro. *J Mech Behav Biomed Mater.* **2015**, *44*, 10-22.
 178. Geng, Z.; Sang, S.; Wang, S.; Meng, F.; Li, Z.; Zhu, S.; Cui, Z.; Jing, Y.; Wang, C.; Su, J. Optimizing the strontium content to achieve an ideal osseointegration through balancing apatite-forming ability and osteogenic activity. *Biomater Adv.* **2022**, *133*, 112647.
 179. Li, Y.; Yue, J.; Liu, Y.; Wu, J.; Guan, M.; Chen, D.; Pan, H.; Zhao, X.; Lu, W. W. Strontium regulates stem cell fate during osteogenic differentiation through asymmetric cell division. *Acta Biomater.* **2021**, *119*, 432-443.
 180. Stefanic, M.; Peroglio, M.; Stancic, A. M.; Machado, G. C.; Campbell, I.; Krz̄manc, M. M.; Alini, M.; Zhang, X. The influence of strontium release rate from bioactive phosphate glasses on osteogenic differentiation of human mesenchymal stem cells. *J Eur Ceram Soc.* **2018**, *38*, 887-897.
 181. Montagna, G.; Cristofaro, F.; Fassina, L.; Bruni, G.; Cucca, L.; Kochen, A.; Divieti Pajevic, P.; Bragdon, B.; Visai, L.; Gerstenfeld, L. An in vivo comparison study between strontium nanoparticles and rhBMP2. *Front Bioeng Biotechnol.* **2020**, *8*, 499.
 182. Huang, D.; Zhao, F.; Gao, W.; Chen, X.; Guo, Z.; Zhang, W. Strontium-substituted sub-micron bioactive glasses inhibit osteoclastogenesis through suppression of RANKL-induced signaling pathway. *Regen Biomater.* **2020**, *7*, 303-311.
 183. Barrio, D. A.; Etcheverry, S. B. Vanadium and bone development: putative signaling pathways. *Can J Physiol Pharmacol.* **2006**, *84*, 677-686.
 184. Cortizo, A. M.; Molinuevo, M. S.; Barrio, D. A.; Bruzzone, L. Osteogenic activity of vanadyl(IV)-ascorbate complex: evaluation of its mechanism of action. *Int J Biochem Cell Biol.* **2006**, *38*, 1171-1180.
 185. Jin, G.; Cao, H.; Qiao, Y.; Meng, F.; Zhu, H.; Liu, X. Osteogenic activity and antibacterial effect of zinc ion implanted titanium. *Colloids Surf B Biointerfaces.* **2014**, *117*, 158-165.
 186. Kwun, I. S.; Cho, Y. E.; Lomeda, R. A.; Shin, H. I.; Choi, J. Y.; Kang, Y. H.; Beattie, J. H. Zinc deficiency suppresses matrix mineralization and retards osteogenesis transiently with catch-up possibly through Runx 2 modulation. *Bone.* **2010**, *46*, 732-741.
 187. Moonga, B. S.; Dempster, D. W. Zinc is a potent inhibitor of osteoclastic bone resorption in vitro. *J Bone Miner Res.* **1995**, *10*, 453-457.
 188. Guo, B.; Yang, M.; Liang, D.; Yang, L.; Cao, J.; Zhang, L. Cell apoptosis induced by zinc deficiency in osteoblastic MC3T3-E1 cells via a mitochondrial-mediated pathway. *Mol Cell Biochem.* **2012**, *361*, 209-216.
 189. Hadley, K. B.; Newman, S. M.; Hunt, J. R. Dietary zinc reduces osteoclast resorption activities and increases markers of osteoblast differentiation, matrix maturation, and mineralization in the long bones of growing rats. *J Nutr Biochem.* **2010**, *21*, 297-303.
 190. O'Connor, J. P.; Kanjilal, D.; Teitelbaum, M.; Lin, S. S.; Cottrell, J. A. Zinc as a therapeutic agent in bone regeneration. *Materials (Basel).* **2020**, *13*, 2211.
 191. Hu, G.; Zhu, Y.; Xu, F.; Ye, J.; Guan, J.; Jiang, Y.; Di, M.; Li, Z.; Guan, H.; Yao, X. Comparison of surface properties, cell behaviors, bone regeneration and osseointegration between nano tantalum/PEEK composite and nano silicon nitride/PEEK composite. *J Biomater Sci Polym Ed.* **2022**, *33*, 35-56.
 192. Hwang, C.; Park, S.; Kang, I. G.; Kim, H. E.; Han, C. M. Tantalum-coated polylactic acid fibrous membranes for guided bone regeneration. *Mater Sci Eng C Mater Biol Appl.* **2020**, *115*, 111112.
 193. Zhou, Z.; Liu, D. Mesenchymal stem cell-seeded porous tantalum-based biomaterial: a promising choice for promoting bone regeneration. *Colloids Surf B Biointerfaces.* **2022**, *215*, 112491.
 194. Mas-Moruno, C.; Garrido, B.; Rodriguez, D.; Ruperez, E.; Gil, F. J. Biofunctionalization strategies on tantalum-based materials for osseointegrative applications. *J Mater Sci Mater Med.* **2015**, *26*, 109.
 195. Shi, L. Y.; Wang, A.; Zang, F. Z.; Wang, J. X.; Pan, X. W.; Chen, H. J. Tantalum-coated pedicle screws enhance implant integration. *Colloids Surf B Biointerfaces.* **2017**, *160*, 22-32.
 196. Qing, Y.; Li, R.; Li, S.; Li, Y.; Wang, X.; Qin, Y. Advanced black phosphorus nanomaterials for bone regeneration. *Int J Nanomedicine.* **2020**, *15*, 2045-2058.
 197. Kim, H. D.; Jang, H. L.; Ahn, H. Y.; Lee, H. K.; Park, J.; Lee, E. S.; Lee, E. A.; Jeong, Y. H.; Kim, D. G.; Nam, K. T.; Hwang, N. S. Biomimetic whitlockite inorganic nanoparticles-mediated in situ remodeling and rapid bone regeneration. *Biomaterials.* **2017**, *112*, 31-43.
 198. Eckart, R. E.; Shry, E. A.; Burke, A. P.; McNear, J. A.; Appel, D. A.; Castillo-Rojas, L. M.; Avedissian, L.; Pearse, L. A.; Potter, R. N.; Tremaine, L.; Gentlesk, P. J.; Huffer, L.; Reich, S. S.; Stevenson, W. G.; Department of Defense Cardiovascular Death Registry Group.

Biomaterials contain bioactive elements for bone repair

- Sudden death in young adults: an autopsy-based series of a population undergoing active surveillance. *J Am Coll Cardiol.* **2011**, *58*, 1254-1261.
199. Goretti Penido, M.; Alon, U. S. Phosphate homeostasis and its role in bone health. *Pediatr Nephrol.* **2012**, *27*, 2039-2048.
200. Liu, X.; Miller, A. L., 2nd; Park, S.; George, M. N.; Waletzki, B. E.; Xu, H.; Terzic, A.; Lu, L. Two-dimensional black phosphorus and graphene oxide nanosheets synergistically enhance cell proliferation and osteogenesis on 3D printed scaffolds. *ACS Appl Mater Interfaces.* **2019**, *11*, 23558-23572.
201. Avgoulas, E. I.; Sutcliffe, M. P. F.; Linderman, S. W.; Birman, V.; Thomopoulos, S.; Genin, G. M. Adhesive-based tendon-to-bone repair: failure modelling and materials selection. *J R Soc Interface.* **2019**, *16*, 20180838.

Received: November 1, 2023

Revised: November 21, 2023

Accepted: December 8, 2023

Available online: December 28, 2023