

Published in final edited form as:

Addit Manuf. 2024 March ; 84: . doi:10.1016/j.addma.2024.104082.

Results of an interlaboratory study on the working curve in vat photopolymerization

Thomas J. Kolibaba^{a,*}, Jason P. Killgore^{a,*}, Benjamin W. Caplins^a, Callie I. Higgins^a, Uwe Arp^b, C. Cameron Miller^b, Dianne L. Poster^c, Yuqin Zong^b, Scott Broce^d, Tong Wang^e, Vaidas Tala ka^f, Jonathan Andersson^g, Amelia Davenport^g, Matthew A. Panzer^h, John R. Tumbleston^h, Jasmine M. Gonzalezⁱ, Jesse Huffstetlerⁱ, Benjamin R. Lundⁱ, Kai Billerbeck^j, Anthony M. Clay^k, Marcus R. Fratarcangeli^l, H. Jerry Qi^l, Dominique H. Porcincula^m, Lindsey B. Bezekⁿ, Kenji Kikuta^o, Matthew N. Pearlson^p, David A. Walker^p, Corey J. Long^q, Erion Hasa^r, Alan Aguirre-Soto^s, Angel Celis-Guzman^s, Daniel E. Backman^t, Raghuvver Lalitha Sridhar^t, Kevin A. Cavicchi^u, RJ Viereckl^u, Elliott Tong^u, Christopher J. Hansen^v, Darshil M. Shah^v, Cecelia Kinane^w, Abdon Pena-Francesch^w, Carlo Antonini^x, Rajat Chaudhary^x, Gabriele Muraca^x, Yousra Bensouda^y, Yue Zhang^y, Xiayun Zhao^y

*Corresponding authors: Thomas.Kolibaba@nist.gov (T.J. Kolibaba), Jason.Killgore@nist.gov (J.P. Killgore).

CRedit authorship contribution statement

Benjamin R. Lund: Writing – review & editing, Formal analysis, Data curation. **Jesse Huffstetler:** Writing – review & editing, Formal analysis, Data curation. **Darshil M. Shah:** Writing – review & editing, Formal analysis, Data curation. **Jasmine M. Gonzalez:** Writing – review & editing, Formal analysis, Data curation. **Christopher J. Hansen:** Writing – review & editing, Formal analysis. **John R. Tumbleston:** Writing – review & editing, Formal analysis, Data curation. **Elliott Tong:** Writing – review & editing, Formal analysis, Data curation. **Matthew A. Panzer:** Writing – review & editing, Formal analysis, Data curation. **RJ Viereckl:** Writing – review & editing, Formal analysis, Data curation. **Amelia Davenport:** Writing – review & editing, Formal analysis, Data curation. **Kevin A. Cavicchi:** Writing – review & editing, Formal analysis, Data curation. **Jonathan Andersson:** Writing – review & editing, Formal analysis, Data curation. **Raghuvver Lalitha Sridhar:** Writing – review & editing, Formal analysis, Data curation. **Vaidas Tala ka:** Writing – review & editing, Formal analysis, Data curation. **Daniel E. Backman:** Writing – review & editing, Formal analysis, Data curation. **Tong Wang:** Writing – review & editing, Formal analysis, Data curation. **Angel Celis-Guzman:** Writing – review & editing, Formal analysis, Data curation. **Scott Broce:** Writing – review & editing, Formal analysis, Data curation. **Alan Aguirre-Soto:** Writing – review & editing, Formal analysis, Data curation. **Abdon Pena-Francesch:** Writing – review & editing, Formal analysis, Data curation. **Cecelia Kinane:** Writing – review & editing, Formal analysis, Data curation. **Yuqin Zong:** Writing – review & editing, Methodology. **Dianne L. Poster:** Writing – review & editing, Supervision. **Corey J. Long:** Writing – review & editing, Formal analysis, Data curation. **C. Cameron Miller:** Writing – review & editing, Methodology. **David A. Walker:** Writing – review & editing, Formal analysis, Data curation. **Uwe Arp:** Writing – review & editing, Methodology. **Matthew N. Pearlson:** Writing – review & editing, Formal analysis, Data curation. **Callie I. Higgins:** Writing – review & editing, Conceptualization. **Kenji Kikuta:** Writing – review & editing, Formal analysis, Data curation. **Benjamin W. Caplins:** Writing – review & editing, Software, Methodology, Formal analysis, Conceptualization. **Xiayun Zhao:** Writing – review & editing, Formal analysis, Data curation. **Lindsey B. Bezek:** Writing – review & editing, Formal analysis, Data curation. **Jason P. Killgore:** Writing – review & editing, Project administration, Investigation, Funding acquisition, Formal analysis, Data curation, Conceptualization. **Yue Zhang:** Writing – review & editing, Formal analysis, Data curation. **Dominique H. Porcincula:** Writing – review & editing, Formal analysis, Data curation. **Thomas J. Kolibaba:** Writing – review & editing, Writing – original draft, Project administration, Methodology, Investigation, Formal analysis, Data curation, Conceptualization. **Yousra Bensouda:** Writing – review & editing, Formal analysis, Data curation. **H. Jerry Qi:** Writing – review & editing, Formal analysis, Data curation. **Gabriele Muraca:** Writing – review & editing, Formal analysis, Data curation. **Marcus R. Fratarcangeli:** Writing – review & editing, Formal analysis, Data curation. **Rajat Chaudhary:** Writing – review & editing, Formal analysis, Data curation. **Anthony M. Clay:** Writing – review & editing, Formal analysis, Data curation. **Carlo Antonini:** Writing – review & editing, Formal analysis, Data curation. **Kai Billerbeck:** Writing – review & editing, Formal analysis, Data curation. **Erion Hasa:** Writing – review & editing, Formal analysis, Data curation.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Appendix A. Supporting information

Supplementary data associated with this article can be found in the online version at doi:10.1016/j.addma.2024.104082.

^aApplied Chemicals and Materials Division, National Institute of Standards and Technology, 325 Broadway, Boulder, CO 80305, USA

^bSensor Science Division, National Institute of Standards and Technology, 100 Bureau Drive, Gaithersburg, MD 20899, USA

^cMaterial Measurement Laboratory, National Institute of Standards and Technology, 100 Bureau Drive, Gaithersburg, MD 20899, USA

^d3D Systems, 26600 SW Parkway Ave #300, Wilsonville, OR 97070, USA

^eAllnex USA Inc., 9005 Westside Parkway, Alpharetta, GA 30009, USA

^fAmeraLabs, Draugystes g. 14, Kaunas, Lithuania

^gArkema, Inc., 1880 S. Flatirons Ct. Suite J, Boulder, CO 80301, USA

^hCarbon, Inc., 1089 Mills Way, Redwood City, CA 94063, USA

ⁱDesktop Metal, 1122 Alma Rd. Ste. 100, Richardson, TX 75081, USA

^jDMG Digital Enterprises SE, ElbgaustraÙe 248, Hamburg 22547, Germany

^kDEVCOM-Army Research Laboratory, FCDD-RLW-M, Manufacturing Science and Technology Branch, 6300 Roadman Road, Aberdeen Proving Ground, MD 21005, USA

^lSchool of Mechanical Engineering, Georgia Institute of Technology, 801 Ferst Dr, Atlanta, GA 30332, USA

^mLawrence Livermore National Laboratory, 7000 East Ave, Livermore, CA 94550, USA

ⁿLos Alamos National Laboratory, PO Box 1663, Los Alamos, NM 87545, USA

^oOsaka Organic Chemical Industry, Ltd., 1-7-2, Nihonbashi Honcho, Chuo, Tokyo 103-0023, Japan

^pPrintFoam, 230 James St. Ste C, Wales, WI 53183, USA

^qSartomer, 502 Thomas Jones Way, Exton, PA 19341, USA

^rStratasys, Inc., 1122 Saint Charles St, Elgin, IL 60120, USA

^sSchool of Engineering and Science, Tecnológico de Monterrey, Colonia Tecnológico, Avenida Eugenio Garza Sada 2501 Sur, Monterrey, Nuevo León 64849, Mexico

^tLung Biotechnology, PBC., 1000 Sprint Street, Silver Spring, MD 20910, USA

^uSchool of Polymer Science and Polymer Engineering, University of Akron., 250 S Forge St, Akron, OH 44325, USA

^vDepartment of Mechanical & Industrial Engineering, University of Massachusetts, Lowell, 1 University Ave, Lowell, MA 01854, USA

^wDepartment of Materials Science and Engineering, University of Michigan, 2800 Plymouth Rd, Ann Arbor, MI 48109, USA

^xDepartment of Materials Science, University of Milano-Bicocca, Via R. Cozzi 55, Milan 20125, Italy

^yDepartment of Mechanical Engineering & Materials Science, University of Pittsburgh, 3700 O'Hara Street, Pittsburgh, PA 15261, USA

Abstract

The working curve informs resin properties and print parameters for stereolithography, digital light processing, and other photopolymer additive manufacturing (PAM) technologies. First demonstrated in 1992, the working curve measurement of cure depth vs radiant exposure of light is now a foundational measurement in the field of PAM. Despite its widespread use in industry and academia, there is no formal method or procedure for performing the working curve measurement, raising questions about the utility of reported working curve parameters. Here, an interlaboratory study (ILS) is described in which 24 individual laboratories performed a working curve measurement on an aliquot from a single batch of PAM resin. The ILS reveals that there is enormous scatter in the working curve data and the key fit parameters derived from it. The measured depth of light penetration D_p varied by as much as 7x between participants, while the critical radiant exposure for gelation E_c varied by as much as 70x. This significant scatter is attributed to a lack of common procedure, variation in light engines, epistemic uncertainties from the Jacobs equation, and the use of measurement tools with insufficient precision. The ILS findings highlight an urgent need for procedural standardization and better hardware characterization in this rapidly growing field.

Keywords

Digital light processing; Stereolithography; Vat photopolymerization; Working curve; Jacobs equation

1. Introduction

Since the pioneering article by Paul Jacobs over three decades ago, the measurement of a resin's working curve has been seen as a fundamental measurement in the field of photopolymer additive manufacturing (PAM) [1]. Ideally a working curve will allow a user to determine optimal processing parameters for a particular photopolymer resin. Based on Beer-Lambert absorption of light through a resin and assuming some critical exposure of light must be absorbed prior to solid forming, the Jacobs equation then follows

$$C_d = D_p \ln\left(\frac{E_0}{E_c}\right) \quad (1)$$

Where C_d is a measured cure depth and E_0 is an incident radiant exposure. A semi-log fit of these data yields two parameters. The first is the light penetration depth D_p (the depth traveled before the incident light intensity has attenuated by $1/e \approx 37\%$) that is related to the absorptive/spectral properties of the resin-light source pairing. The second fit parameter is the critical exposure E_c , which is the radiant exposure of light required to form a solid (*i.e.*, the gel point). Both D_p and E_c are expected to be a function of irradiation wavelength due to varying molar absorptivity at different wavelengths. It should be noted that the PAM

field historically has referred to E_0 as a “dose”. A dose is measured in a mass-normalized basis in the Système International unit convention, while an area-normalized parameter like E_0 is more correctly referred to as a “radiant exposure”. Here the term radiant exposure, or sometimes simply exposure, will be used to refer to the area-normalized optical energy input into the system, with units of mJ cm^{-2} [2]. Recently, D_p and E_c values have been reported in the specification sheets of some commercially available photopolymer resins. Furthermore, these two fit parameters are now ubiquitous in the PAM literature. The topics of these literature studies include: sources of uncertainty in cure depth measurements [3], development of new methods of measuring the working curve [4–7], or revisiting the fundamental assumptions and functional form of the Jacobs equation [8–12]. Even in light of this ongoing research and a lack of standards, it is not uncommon for publications to include or reference working curve data as part of characterizing a novel photocurable resin [13–19].

Despite the recognized importance and ubiquitous use of this measurement, there remains no standardized method to perform a working curve measurement. Compounding this issue is the lack of a reference material available to benchmark a given working curve protocol. As the field continues to grow, it is imperative that PAM has rigorous standards to improve the reproducibility of commercial printed products and published works. Here we present an interlaboratory study on the working curve. Volunteer participants were given an aliquot from the same production lot of the open-source resin PR48, which has a known composition and has been widely studied previously [3,6,20–22]. A total of 35 datasets were collected from 24 participants. It was found that reported D_p values varied by as much as 7x while reported E_c values varied by up to 70x. The results suggest that the large variability stems from numerous aspects of the measurement including light engine characteristics, exposure range, thickness measurement, and epistemic (*i.e.*, model) uncertainty. These differences highlight the need for refinement and standardization in this field.

2. Methods and results

All participants were provided an aliquot of the same batch of the open-source resin, prototyping resin 48 (PR48), purchased from CPS (Boulder, CO). It is important to note that the current formulation of PR48 deviates from the version that has been studied in past publications [3,20,22]. The oligomer Ebecryl 8210 (ca. 40% by mass of the original PR48 formulation) has now been replaced by a similar oligomer, Sartomer PRO13514, in commercially available PR48. Participants were asked to provide a summary of their working curve measurement procedure. Key aspects from these reported procedures are summarized in Table 1. The instructions for reporting both data and procedural details were intentionally open-ended to avoid biasing how participants collected data for the interlaboratory study. Very few respondents gave specific details on the instrument used for measuring cure depths although thickness measurement method is known to strongly affect results [3]. The predominant nominal wavelength used was 405 nm. Despite many attempts in the literature to develop separate dedicated light sources for measuring working curves [3,6,8,12], the vast majority of respondents used a printer as their light engine. Only a few respondents provided a spectrum of their light engine, and only one explicitly noted that their peak wavelength, λ_{max} , did not match their light source’s nominal wavelength.

In general, there was little consistency to the substrate type or the lateral dimensions of cured areas that participants used for cure depth measurements. Some participants followed protocols resembling online guides for measuring a working curve [23,24], while others cured into resin droplets on top of glass slides placed atop the print window. While most measurements used a bottom-up configuration (*i.e.*, the light source was below the resin), some participants cured a droplet of resin top-down, collecting a floating film of cured photopolymer for cure depth measurements. Participants did not typically report the washing or postprocessing conditions used. However, washing and postprocessing are known to affect part surface finish and properties, which may affect thickness at the scale of working curve measurements [25–27]. Additionally, there was little reporting and no attempt by participants to exert control over laboratory environmental factors. Parameters such as partial pressure of oxygen (which would vary by elevation), relative humidity, and dissolved oxygen content (which can vary on the basis of lab temperature *or* elevation) may have an effect on the polymerization kinetics and thus E_c [28]. Consensus on substrate, pattern size, and postprocessing is a relatively straightforward means of reducing variability, although their specific impact was not explored systematically here.

Anonymized plots of C_d vs E_0 for the three predominant nominal wavelengths of interest (405 nm, 385 nm, and 365 nm) are shown in Fig. 1 (an additional dataset for a broad-spectrum mercury light source is shown in the supporting info, Fig. S1). The scatter in these data is clear upon visual inspection, highlighting the interlaboratory inconsistency in the chosen working curve methods. Several parameters from these plots are summarized in Table 1, including the fit parameters D_p and E_c along with the thinnest and thickest cure depths measured by each participant. Participant-provided information about instruments used for measuring cure depth are also shown in Table 1.

Fit parameters provided in Table 1 for every dataset were extracted from the LINEST function in Excel using the raw C_d vs $\ln(E_0)$ data provided by participants [29]. The associated error in E_c was obtained from propagating the LINEST uncertainty in the x-intercept through the Jacobs equation. The Jacobs equation fits are shown in the righthand panels of Fig. 1 to highlight the origin of the scatter in D_p and E_c . A consistent linear regression methodology was used across all individual participant datasets to ensure that extracted fit parameters and uncertainties were consistently calculated. Table 1 also shows participant-reported D_p and E_c , which were generally consistent with fit parameters obtained with the uniform methodology.

For the 405 nm datasets, the extracted D_p values (mean = 120 μm , σ = 40 μm) vary from as low as 60 μm to as high as 190 μm , which is a >3-fold difference. Showing even larger variation, the E_c values (mean = 60 mJ cm^{-2} , σ = 160 mJ cm^{-2}) span nearly 2 orders of magnitude from 10 mJ cm^{-2} to as much as 700 mJ cm^{-2} . One dataset reported an extreme outlier (Grubbs test $p < 0.01$)[30] in both E_c (700 mJ cm^{-2}) and in irradiance (between 402 mW cm^{-2} and 1660 mW cm^{-2}). Neither value was excluded from arithmetic mean calculation in Table 1. It is unclear if this very large E_c value is related to inaccurate optical power measurement or if this is an anomalous chemical phenomenon caused by extreme irradiances [31]. Within single participant datasets, data exist wherein more than 10% cure depth variation is observed at the same nominal radiant exposure (denoted by

arrows in the zoomed in graph shown in Fig. S2) indicating either poor print reproducibility or insufficient precision of the cure depth measurement. Print irreproducibility may originate from inhomogeneity of intensity and/or wavelength across the print window [21].

For the nominally 385 nm datasets, most of the data are clustered with similar slope (and thus D_p). D_p values (mean = 80 μm , $\sigma = 80 \mu\text{m}$) range from 37 μm to 310 μm . The E_c values (mean = 13 mJ cm^{-2} , $\sigma = 6 \text{mJ cm}^{-2}$) varied between 4.6 mJ cm^{-2} and 22 mJ cm^{-2} (roughly a 5-fold difference). Rejecting the two largest D_p data sets, the remainder have a mean of 49 μm and a standard deviation of 8 μm . For this reduced data set, E_c has a mean of 13 mJ cm^{-2} and a standard deviation of 6 mJ cm^{-2} , nearly identical to the full 385 nm data set. The relatively more consistent D_p values with a wider variance in E_c values for the reduced data set suggests that inaccurate radiometry may have contributed to these differences. Visually, inspection of Fig. 1c gives the appearance of several nearly parallel lines with varying x-intercepts. Four of the six collected datasets at 365 nm (Fig. 1e,f) also exhibit nearly-parallel line behavior. So long as precise (*i.e.*, consistent) relative irradiance values are obtained, inaccuracy in absolute irradiance measurement will reflect only in E_c and not in D_p (which is most strongly dependent on accurate measurement of thickness), which would explain the variance obtained in many of the 385 nm datasets.

The spread in the reported D_p and E_c values are shown in Fig. 2a and Fig. 2b, respectively. The tighter cluster of D_p values for the 385 nm datasets are apparent in this plot, as are the relatively larger variation in the 405 nm and 365 nm datasets. E_c values are reported on a logarithmic scale to capture the extreme outlying irradiance of Dataset 14 in the 405 nm dataset. The relatively smaller number of 365 nm datasets is responsible for the larger apparent variation in those data.

A naive data reduction was performed to investigate any potential irradiance effects on the reported D_p and E_c values. These reductions are shown in Fig. 2c,d. To evaluate the presence of a correlation between D_p or E_c and irradiance, t-tests of linear fits of D_p or E_c vs irradiance were performed for each wavelength considered in this interlaboratory study. The outputs of the t-test analysis can be found in Table S1. The 405 nm data were evaluated either including or excluding Dataset 14. The values from Dataset 14 are of significantly higher leverage on fit coefficients because of their order-of-magnitude higher irradiance value than the other submitted 405 nm datasets [32]. This influence can be seen from the extremely high Cook's Distance value of Dataset 14 (Figure S3), which suggest inadequate data in the vicinity of those points to draw conclusions about correlations [33]. The lack, generally, of a strong correlation between D_p or E_c and irradiance suggests that the differences among participant-supplied data is a result of systematic differences in how data are collected (printing, post-processing, and characterization) from one participant to another. The data shown in Fig. 2 also highlight the scatter in fit parameters, even at nominally identical wavelengths. The data also show that irradiances used span several orders of magnitude. Considering the non-reciprocal nature of photopolymerizations to intensity and radiant exposure [31,34], a standardized irradiance would be of interest to the field, in addition to further studies to understand the interplay between exposure, intensity, and cure depth.

3. Discussion

The variation in working curve results was generally larger than participants would like to tolerate, although not out of line with expectations given the lack of standardization. To improve reproducibility, numerous parts of the measurement should be considered and refined.

Some participants (particularly those who used a nominally 405 nm light source) commented on the tendency of the working curve to “bend” upwards (*i.e.*, exhibit nonlinear behavior on the semilog plot towards higher cure depths) as radiant exposure increased. Indeed this has been noted many times in the literature and is a well-known phenomenon [3, 6,12]. Despite this curvature, it is common in the literature to see a linear Jacobs equation fit applied to these nonlinear measured working curves. In Fig. 3 we demonstrate the inaccuracy of using this approach. An arbitrarily chosen subset of participant data at 405 nm were pooled and fit according to Jacobs equation. The subset was generally selected from the participants who used cure depth measurement techniques with 1 μm precision or better, and whose working curves were all polymerized bottom-up onto a substrate. The curvature to this collection of data is readily apparent on the semilog axes. Three different fits to the Jacobs equation are shown: One is fit on the lower quartile of measured cure depths, and another on the upper quartile. Finally, an “aggregate” fit for all data is included as well. The extracted Jacobs model fit parameters are displayed in Fig. 3a. From a single data set, the cure depth range used for fitting can alter D_p and E_c by a factor of ≈ 3 fold between the upper and lower quartile fits. It is apparent from the fit lines that the aggregate and upper-quartile fit lines intersect the x-axis above the range indicated by the experimental data. In contrast, the lower quartile fit intercepts the x-axis in the vicinity of the lowest cured depth experimental data. The sensitivity of D_p and E_c to the fitted cure depth highlights epistemic uncertainty with the current state of working curve methodologies. The Jacobs model was derived implying a number of assumptions including: (1) a nominally monochromatic, gaussian light source such as a laser (2) reciprocity such that the working curve is independent of irradiance (3) the system does not photobleach [1]. These assumptions are violated in many current printers and resins; thus, caution must be exercised when applying the Jacobs model to data where semi-log linearity is clearly not obeyed.

Additional possible sources of working curve variation were investigated by considering representative spectral variation observed in DLP printers and LED light engines. LED-driven DLP printers were the most common class of light engine amongst ILS participants. As discussed earlier, few participants reported spectral details of their printer. The spectra measured by NIST from five different, nominally 405 nm DLP printers are shown in Fig. 3b and show a range of λ_{max} values from 402 nm to 411 nm. This range overlaps with a significant shoulder in the absorption spectrum of common photoinitiators. We have reported previously on the significant change in initiation efficiency that would be expected from seemingly-small spectral shifts in the light engine [21]. An optical D_p can be extracted from the UV/Visible absorption spectrum of the resin at a particular wavelength (a sample calculation for this is shown in the supporting information). Fig. 3c shows optical D_p values for the five reported printer λ_{max} values, based on UV/Visible spectra from two different

spectrometers. In the range of 402 nm to 411 nm the optical D_p exhibits a nearly 4-fold increase. Working curve D_p values track optical D_p values in well-behaved systems, thus the inherent variability of the emission from different participant's printers could have strongly affected their working curve results [9]. While this possible difference is significant, it is much smaller than the range of D_p values reported by participants, suggesting that multiple sources of error are contributing to the reported variations.

Overall, these insights suggest that the Jacobs model could be refined or extended to fit a broader range of resin and light source characteristics, while working curve methodologies must strive for the utmost consistency between practitioners. Light engines must be carefully controlled to have nearly identical spectral emission and well-calibrated power output. Finally, accurate and precise thickness measurements are essential to accurate, reproducible working curves. Contact based measurements may prove adequate for measurements on stiff (giga-pascal modulus) plastics, but working curve methods for elastomers and gels likely require further consideration. The PAM field should strive for development of a standard practice for working curve measurements as soon as possible to facilitate continued growth and interoperability of data. Adoption of a standardized protocol for measuring working curves will also allow for quantitative understanding of the influence of environmental factors on the working curve measurement and facilitate standardization of those environmental factors if necessary.

4. Conclusion

An interlaboratory study on the working curve measurement was performed where participants all measured a working curve on aliquots of the same production lot of a resin. The fit parameters extracted from the 35 provided datasets indicates a scatter (notably, up to a 7-fold difference in D_p values and up to a 70-fold difference in E_c values) that prohibits the measurement in its current form from being useful across different laboratories or for technical data sheets. These differences are explained in part by a demonstrated sensitivity of D_p and E_c to the cure depth range studied, indicating epistemic uncertainty in the working curve measurement. An additional source of error is significant spectral variability among nominally similar commercial printers that can lead to a 4-fold change in D_p even in the absence of other uncertainties. Community consensus on a standardized working curve method with precise light engine and thickness measurement specification, along with consistency on other aspects of the protocol are expected to dramatically reduce variation. It is imperative that a standardized method be developed and adopted in short order for continued growth of the photopolymer AM field.

Supplementary Material

Refer to Web version on PubMed Central for supplementary material.

Acknowledgements

This work was performed while Thomas Kolibaba held a National Research Council Associateship Award at the National Institute of Standards and Technology (NIST). The authors acknowledge Standards Development funding from the Office of Reference Materials (NIST) to support this work. Certain commercial equipment, instruments, or materials are identified in this paper to specify the experimental procedure adequately. Such identification

is not intended to imply recommendation or endorsement by NIST. Parts of this work were performed under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under Contract DE-AC52-07NA27344, LLNL-JRNL-858222.

Data Availability

All data used for this study are available from NIST free of charge at: <https://doi.org/10.18434/mds2-3137>

References

- [1]. Jacobs PF Fundamentals of stereolithography, Proceedings of Solid Free Form Symposium 1992, 196–211.
- [2]. Thompson A, Guide for the Use of the International System of Units (SI), (n.d.).
- [3]. Bennett J, Measuring UV curing parameters of commercial photopolymers used in additive manufacturing, *Addit. Manuf* 18 (2017) 203–212, 10.1016/j.addma.2017.10.009. [PubMed: 29503807]
- [4]. Li Y, Mao Q, Yin J, Wang Y, Fu J, Huang Y, Theoretical prediction and experimental validation of the digital light processing (DLP) working curve for photocurable materials, *Addit. Manuf* 37 (2021) 101716, 10.1016/j.addma.2020.101716.
- [5]. Higgins CI, Brown TE, Killgore JP, Digital light processing in a hybrid atomic force microscope: in situ, nanoscale characterization of the printing process, *Addit. Manuf* 38 (2021) 101744, 10.1016/j.addma.2020.101744.
- [6]. Rau DA, Reynolds JP, Bryant JS, Bortner MJ, Williams CB, A rheological approach for measuring cure depth of filled and unfilled photopolymers at additive manufacturing relevant length scales, *Addit. Manuf* 60 (2022) 103207, 10.1016/j.addma.2022.103207.
- [7]. Killgore JP, Kolibaba TJ, Caplins BW, Higgins CI, Rezac JD, A data-driven approach to complex voxel predictions in Grayscale digital light processing additive manufacturing using u-nets and generative adversarial networks, *Small* (2023) 2301987, 10.1002/smll.202301987.
- [8]. Van Der Linden PJEM, Popov AM, Pontoni D, Accurate and rapid 3D printing of microfluidic devices using wavelength selection on a DLP printer, *Lab Chip* 20 (2020) 4128–4140, 10.1039/D0LC00767F. [PubMed: 33057528]
- [9]. Champion A, Metral B, Schuller A, Croutxé-Barghorn C, Ley C, Halbardier L, Allonas X, A simple and efficient model to determine the photonic parameters of a photopolymerizable Resin usable in 3D printing, *ChemPhotoChem* 5 (2021) 839–846, 10.1002/cptc.202100002.
- [10]. Stevens LM, Recker EA, Zhou KA, Garcia VG, Mason KS, Tagnon C, Abdelaziz N, Page ZA, Counting all photons: efficient optimization of visible light 3D printing, *Adv. Mater. Technol* (2023) 2300052, 10.1002/admt.202300052.
- [11]. Gong H, Beauchamp M, Perry S, Woolley AT, Nordin GP, Optical approach to resin formulation for 3D printed microfluidics, *RSC Adv* 5 (2015) 106621–106632, 10.1039/C5RA23855B. [PubMed: 26744624]
- [12]. Gong H, Bickham BP, Woolley AT, Nordin GP, Custom 3D printer and resin for 18 μm \times 20 μm microfluidic flow channels, *Lab Chip* 17 (2017) 2899–2909, 10.1039/C7LC00644F. [PubMed: 28726927]
- [13]. Wilts EM, Pekkanen AM, White BT, Meenakshisundaram V, Aduba DC, Williams CB, Long TE, Vat photopolymerization of charged monomers: 3D printing with supramolecular interactions, *Polym. Chem* 10 (2019) 1442–1451, 10.1039/C8PY01792A.
- [14]. Guit J, Tavares MBL, Hul J, Ye C, Loos K, Jager J, Folkersma R, Voet VSD, Photopolymer Resins with biobased methacrylates based on soybean oil for stereolithography, *ACS Appl. Polym. Mater* 2 (2020) 949–957, 10.1021/acsapm.9b01143.
- [15]. Nechausov S, Ivanchenko A, Morozov O, Miriyev A, Must I, Platnieks O, Jurinovs M, Gaidukovs S, Aabloo A, Kova M, Bulgakov B, Effects of ionic liquids and dual curing on vat photopolymerization process and properties of 3D-printed ionogels, *Addit. Manuf* 56 (2022) 102895, 10.1016/j.addma.2022.102895.

- [16]. Kolibaba TJ, Higgins CI, Crawford NC, Samaniuk JR, Killgore JP, Sustainable additive manufacturing of polyelectrolyte photopolymer complexes, *Adv. Mater. Technol* (2023) 2201681, 10.1002/admt.202201681.
- [17]. Stouten J, Schnelting GHM, Hul J, Sijstermans N, Janssen K, Darikwa T, Ye C, Loos K, Voet VSD, Bernaerts KV, Biobased photopolymer Resin for 3D printing containing dynamic imine bonds for fast reprocessability, *ACS Appl. Mater. Interfaces* 15 (2023) 27110–27119, 10.1021/acsami.3c01669. [PubMed: 37220092]
- [18]. Chaudhary R, Akbari R, Antonini C, Rational design and characterization of materials for optimized additive manufacturing by digital light processing, *Polymers* 15 (2023) 287, 10.3390/polym15020287. [PubMed: 36679168]
- [19]. Weyhrich CW, Will JW, Nayyar G, Westover CC, Patterson S, Arrington CB, Williams CB, Long TE, Temporally stable supramolecular polymeric salts enabling high-performance 3D all-aromatic polyimide lattices, *Small* (2023) 2303188, 10.1002/smll.202303188.
- [20]. Gojzewski H, Guo Z, Grzelachowska W, Ridwan MG, Hempenius MA, Grijpma DW, Vancso GJ, Layer-by-layer printing of photopolymers in 3D: how weak is the interface? *ACS Appl. Mater. Interfaces* 12 (2020) 8908–8914, 10.1021/acsami.9b22272. [PubMed: 31961120]
- [21]. Caplins BW, Higgins CI, Kolibaba TJ, Arp U, Miller CC, Poster DL, Zarobila CJ, Zong Y, Killgore JP, Characterizing light engine uniformity and its influence on liquid crystal display based vat photopolymerization printing, *Addit. Manuf* 62 (2023) 103381, 10.1016/j.addma.2022.103381.
- [22]. Kolibaba TJ, Iverson ET, Legendre H, Higgins CI, Buck ZN, Weeks TS, Grunlan JC, Killgore JP, Synergistic fire resistance of nanobrick wall coated 3D printed photopolymer lattices, *ACS Appl. Mater. Interfaces* 15 (2023) 16046, 10.1021/acsami.3c00177. [PubMed: 36926807]
- [23]. Adzima Brian, Making a Working Curve Measurement on the Form1, *Instructables* (n.d.). <https://www.instructables.com/Making-a-Working-Curve-Measurement-on-the-Form1/> (accessed August 11, 2023).
- [24]. Adzima Brian, How to Take a Working Curve Measurement and Create Exposure Settings From It, *Instructables* (n.d.). <https://www.instructables.com/How-to-Take-a-Working-Curve-Measurement-and-Create/> (accessed August 11, 2023).
- [25]. Commisso AJ, Sama GR, Scott TF, Radical-mediated ring-opening photopolymerization for semicrystalline thermoplastic additive manufacturing, *Chem. Mater* 35 (2023) 3825–3834, 10.1021/acs.chemmater.2c03352.
- [26]. Schittecatte L, Geertsen V, Bonamy D, Nguyen T, Guenoun P, From Resin formulation and process parameters to the final mechanical properties of 3D printed acrylate materials, *MRS Commun* 13 (2023) 357–377, 10.1557/s43579-023-00352-3.
- [27]. Snowwhite P, Snowwhite K, Peczynski H, Additive Manufacturing Post Process, in: *Radtech*, Orlando, FL, 2022: pp. 1–11. <https://www.radtech2022.com/wp-content/uploads/2022/05/8A-Snowwhite.pdf> (accessed October 4, 2023).
- [28]. Scherzer T, Langguth H, Temperature dependence of the oxygen solubility in acrylates and its effect on the induction period in UV photopolymerization, *Macro Chem. Phys* 206 (2005) 240–245, 10.1002/macp.200400300.
- [29]. Morrison FA, Obtaining Uncertainty Measures on Slope and Intercept of a Least Squares Fit with Excel's LINEST, (n.d.).
- [30]. Harris DC, *Exploring Chemical Analysis*, Fifth Ed., W.H. Freeman and Company, New York, 2013.
- [31]. Scott TF, Kloxin CJ, Draughon RB, Bowman CN, Nonclassical dependence of polymerization rate on initiation rate observed in Thiol Ene photopolymerizations, *Macromolecules* 41 (2008) 2987–2989, 10.1021/ma8002505.
- [32]. Pardo MC, Chapter 7: High leverage points and outliers in generalized linear models for ordinal data, in: Skiadas CH (Ed.), *Advances in Data Analysis: Theory and Applications to Reliability and Inference, Data Mining, Bioinformatics, Lifetime Data, and Neural Networks*, Birkhäuser Boston, Boston, 2010, 10.1007/978-0-8176-4799-5.
- [33]. Cook RD, Detection of Influential Observation in Linear Regression, *Technometrics* 19 (1977) 15–18.

- [34]. Uzcategui AC, Muralidharan A, Ferguson VL, Bryant SJ, McLeod RR, Understanding and improving mechanical properties in 3D printed parts using a dual-cure acrylate-based resin for stereolithography, *Adv. Eng. Mater* 20 (2018) 1800876, 10.1002/adem.201800876. [PubMed: 30766445]

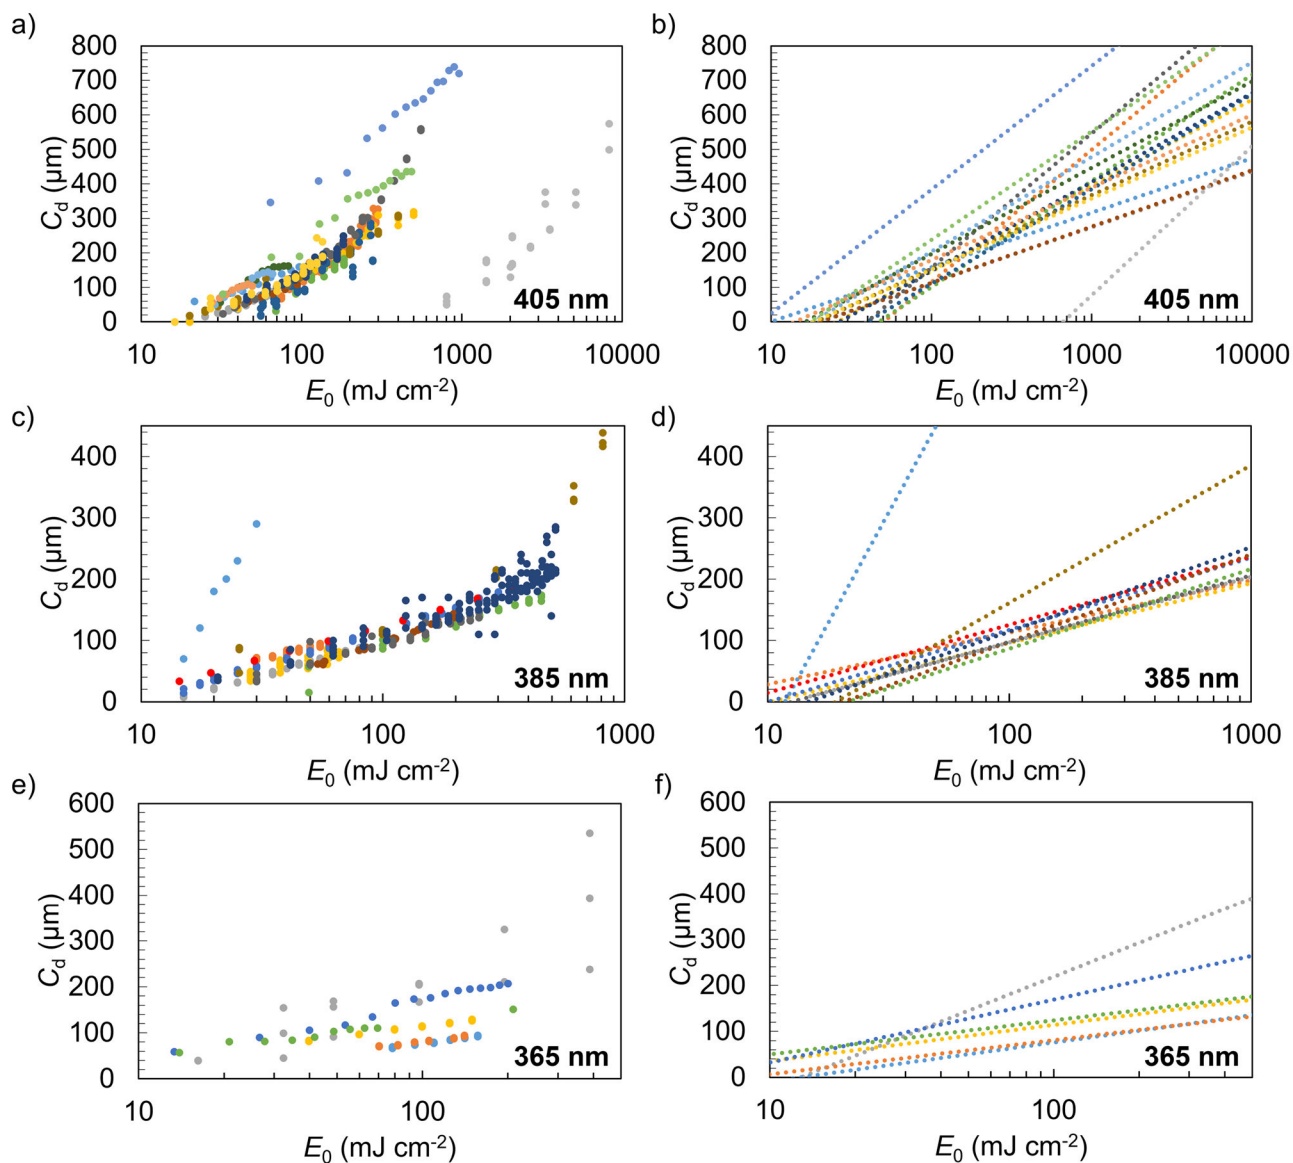


Fig. 1. Cure depth C_d vs exposure E_0 data reported by study participants at nominal wavelengths (a) 405 nm, (c) 385 nm, and (e) 365 nm. Fits to the Jacobs equation are shown in panels (b), (d), and (f) to highlight the origin of the scatter in D_p and E_c .

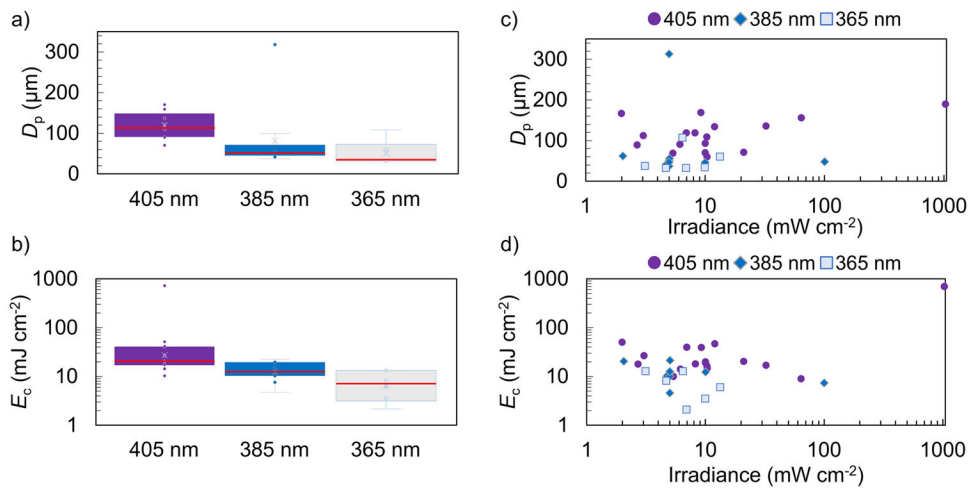


Fig. 2. Box plots of (a) D_p and (b) E_c displaying the spread in the fit parameters at the three wavelengths of note for this study. Data reductions are shown displaying (c) D_p vs irradiance and (d) E_c vs irradiance.

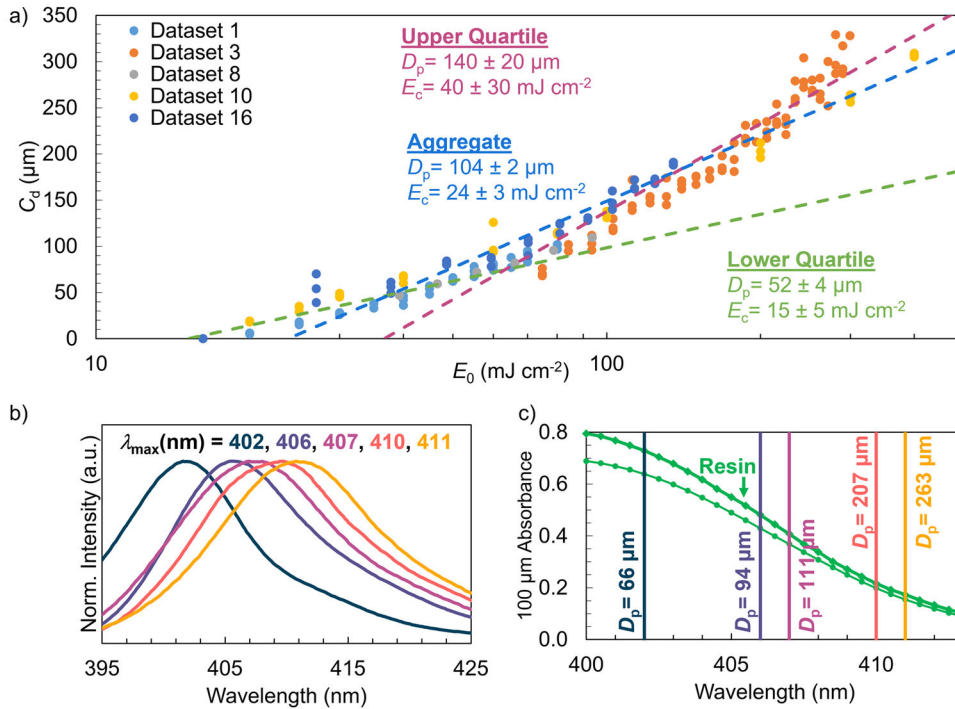


Fig. 3.

(a) Down-selected 405 nm dataset collected from ILS participants. The separate fits to the Jacobs model are shown for the lower quartile, upper quartile, and entire range (aggregate) of the data. The fit parameters and uncertainties are displayed in the plot area. The D_p values span a range of 52 μm to 140 μm , while the E_c values span a range of 15 mJ cm^{-2} to 40 mJ cm^{-2} for the different ranges of the same data. This variation in fit values highlights epistemic uncertainty in the working curve measurement. (b) Spectra from five nominally 405 nm printers showing nearly 10 nm variation in peak wavelength λ_{max} . (c) Green traces are UV/Visible spectra of the studied resin collected on a variable pathlength spectrometer (circles) and in a conventional spectrometer with a 100 μm cuvette (diamonds). The “optical” D_p that is extracted from the absorbance data are shown for each of the peak wavelengths in the LEDs shown in (b).

Table 1
Working curve fit parameters and experimental conditions for participant-provided datasets.

	λ^a (nm)	Irradiance (mW cm ⁻²)	D_p (μm)	E_c (mJ cm ⁻²)	$C_{d, \min}^b$ (μm)	$C_{d, \max}^c$ (μm)	$D_{p, \text{reported}}^d$ (μm)	$E_{c, \text{reported}}^d$ (mJ cm ⁻²)	Light Source	Thickness Measurement	Thickness Precision (μm)
Dataset 1	405	10.0	70 ± 2	20 ± 3	5	102	70 ± 2	20 ± 3	DLP printer	Low force micrometer	± 0.1
Dataset 2	405	5.36	69 ± 4	10 ± 3	60	160	69	9.951	Top-down light exposure	Digital thickness gauge	± 25
Dataset 3	405	1.987	167 ± 5	50 ± 9	68	329	168	50.486	DLP printer	Micrometer	± 1
Dataset 4	405	Unknown	108 ± 3	26 ± 5	40	320	116.3	30.0	SLA printer	Calipers	Unknown
Dataset 5	405	12	134 ± 7	50 ± 20	32	184	127 ± 10	45 ± 6	Laser	Not reported	Unknown
Dataset 6	405	6.96	119 ± 8	40 ± 20	17.50	286.14	121 ± 4	40 ± 2	Filtered broadband UV lamp	Rheometer	Unknown
Dataset 7	405	21	71 ± 2	20 ± 2	46.94	109.51	70.825	20.284	DLP printer	LSCM ^h	± < 0.05
Dataset 8	405	9.231	169 ± 5	40 ± 7	24.13	560.07	132	33.476	DLP printer	Micrometer	Unknown
Dataset 9	405	10.0	93 ± 3	19 ± 3	18	309	95.3	20.2	DLP printer	Dial micrometer	± 1
Dataset 10	405	3.031	112 ± 4	27 ± 5	64	250	113.85	26.811	LCD printer	Micrometer	Unknown
Dataset 11	405	10.33	109 ± 9	16 ± 6	57.5	162.5	109 ± 9	16 ± 2	DLP printer	Digital caliper	Unknown
Dataset 12	405	8.22	119 ± 8	18 ± 6	50.0	145.0	119 ± 8	18 ± 1	DLP printer	Digital caliper	Unknown
Dataset 13	405	6.15	90 ± 10	14 ± 7	57.5	110.0	92 ± 10	14 ± 2	DLP printer	Digital caliper	Unknown
Dataset 14	405	402–1660	190 ± 20	700 ± 500	50	575	173.7 201.5	625.9 698.9	Top-down LED spot curing system	Calipers	Unknown
Dataset 15	405	2.7	89 ± 6	18 ± 6	0	244	89	18.376	LCD printer	Dial micrometer	± 1
Dataset 16	405	63.9	156 ± 7	9 ± 2	346.8	736.7	155.77	8.54	Top-down Independent LED	Stylus profilometer	± < 0.05
Dataset 17	405	32.34	136 ± 6	17 ± 5	81.3	436.5	136.34	17.45	Top-down Independent LED	Stylus profilometer	± < 0.05
Average 405^e			120 ± 40	60 ± 160	58	295					
Aggregate 405^f			89 ± 4	18 ± 4	–	–					
Dataset 18	385	10.0	46.3 ± 0.6	12.4 ± 0.7	7	88	46.3 ± 0.6	12.4 ± 0.7	DLP printer	Low force micrometer	± 0.1
Dataset 19	385	5.0	310 ± 20	12 ± 2	70	290	–	–	DLP printer	Calipers	Unknown

	λ^d (nm)	Irradiance (mW cm ⁻²)	D_p (μm)	E_c (mJ cm ⁻²)	$C_{d,min}^b$ (μm)	$C_{d,max}^c$ (μm)	$D_{p,reported}^d$ (μm)	$E_{c,reported}^d$ (mJ cm ⁻²)	Light Source	Thickness Measurement	Thickness Precision (μm)
Dataset 20	385	5.0	37 ± 2	4.6 ± 0.9	68	95	37	4.632	DLP printer	Digital thickness gauge	Unknown
Dataset 21	385	4.74	42 ± 5	10 ± 5	34	86	43	10.3	DLP printer	Calipers	Unknown
Dataset 22	385	5.0	51.2 ± 0.4	10.1 ± 0.4	14	179	51.2	10.1	DLP printer	Dial micrometer	± 1
Dataset 23	385	5.03	56 ± 2	22 ± 5	15	174	56	21.5	DLP printer	Calipers	Unknown
Dataset 24	385	100	48.2 ± 0.4	7.4 ± 0.3	11.908	209.613	47.93 48.52	7.40 7.41	DLP printer	LSCM ^b	± < 0.05
Dataset 25	388.5 ^g	0.9 – 3.2	62 ± 1	21 ± 2	60.7	143.5	63 ± 2	21 ± 1	DLP printer	Micrometer	Unknown
Dataset 26	385	5.0	47 ± 2	13 ± 3	33	148	47	12.598	DLP printer	Dial micrometer	± 1
Dataset 27	385	0.85 – 27.1	100 ± 10	20 ± 10	47	439	–	–	Projector	–	–
Dataset 28	385	10.37	60 ± 2	15 ± 3	35	285	60 ± 5	0.86 ± 0.02	DLP printer	Micrometer	Unknown
<i>Average 385^e</i>			80 ± 80	13 ± 6	33	192					
<i>Aggregate 385^f</i>			55 ± 2	12 ± 2	–	–					
Dataset 29	365	6.48	110 ± 20	13 ± 9	39	535	203	13.931	Independent LED	Optical profilometer	± 1
Dataset 30	365	3.131	37 ± 1	13 ± 2	66	94	36.93	12.789	DLP printer	Micrometer	Unknown
Dataset 31	365	4.688	32 ± 1	8 ± 1	70	94	32.12	8.089	DLP printer	Micrometer	Unknown
Dataset 32	365	9.96	34.1 ± 0.4	3.5 ± 0.2	81	129	34.14	3.550	DLP printer	Micrometer	Unknown
Dataset 33	365	13.34	60 ± 3	6 ± 1	58.838	206.97	5.89	59.367	Top-down Independent LED	Stylus profilometer	± < 0.05
Dataset 34	365	6.95	32 ± 2	2.1 ± 0.4	42.148	150.83	2.11	32.122	Top-down Independent LED	Stylus profilometer	± < 0.05
<i>Average 365^e</i>			50 ± 30	8 ± 5	60	202					
<i>Aggregate 365^f</i>			50 ± 8	9 ± 7	–	–					
Dataset 35	Broad Spectrum	Unknown	97 ± 1	11.0 ± 0.7	160	299	97	11.0	Mercury lamp	Digital micrometer	± 3

^{a)}Nominal unless otherwise reported.

^{b)}Minimum measured cure depth.

^{c)}Maximum measured cure depth.

^{d)}Participant-reported fit parameters and uncertainty, if provided.

NIST Author Manuscript

NIST Author Manuscript

NIST Author Manuscript

- e) Unweighted arithmetic mean of reported fit parameters from participants. Uncertainty is standard deviation of fit parameters.
- f) Data reported from pooling and fitting all datasets within a wavelength.
- g) Wavelength measured and reported by participant.
- h) Laser scanning confocal microscopy.