

Electronic, Vibrational, and Structural Properties of the Natural Mineral Ferberite (FeWO_4): A High-Pressure Study

Daniel Diaz-Anichtchenko, Jesus E. Aviles-Coronado, Sinhué López-Moreno,* Robin Turnbull, Francisco J. Manjón, Catalin Popescu, and Daniel Errandonea*



Cite This: *Inorg. Chem.* 2024, 63, 6898–6908



Read Online

ACCESS |



Metrics & More



Article Recommendations



Supporting Information

ABSTRACT: This paper reports an experimental high-pressure study of natural mineral ferberite (FeWO_4) up to 20 GPa using diamond-anvil cells. First-principles calculations have been used to support and complement the results of the experimental techniques. X-ray diffraction patterns show that FeWO_4 crystallizes in the wolframite structure at ambient pressure and is stable over a wide pressure range, as is the case for other wolframite AWO_4 ($A = \text{Mg, Mn, Co, Ni, Zn, or Cd}$) compounds. No structural phase transitions were observed for FeWO_4 , in the pressure range investigated. The bulk modulus ($B_0 = 136(3)$ GPa) obtained from the equation of state is very close to the recently reported value for CoWO_4 (131(3) GPa). According to our optical absorption measurements, FeWO_4 has an indirect band gap that decreases from 2.00(5) eV at ambient pressure to 1.56(5) eV at 16 GPa. First-principles simulations yield three infrared-active phonons, which soften with pressure, in contrast to the Raman-active phonons. These results agree with Raman spectroscopy experiments on FeWO_4 and are similar to those previously reported for MgWO_4 . Our results on FeWO_4 are also compared to previous results on other wolframite-type compounds.



1. INTRODUCTION

Wolframite-type AWO_4 compounds ($A = \text{Mg, Mn, Fe, Co, Ni, Zn, Cd}$) form an interesting class of bimetallic oxides because of their properties,^{1,2} including the magnetic properties for $A = \text{Fe, Co, and Ni}$,³ and even multiferroic properties in the case of MnWO_4 .^{4,44} The magnetism is dominated by partially filled 3d orbitals of the divalent A cations.⁵ In addition to interesting magnetic properties, wolframites, such as FeWO_4 , have been used to develop supercapacitors and photocatalytic and photoluminescent materials.^{6–8} FeWO_4 can be used for the cheap and environmentally friendly production of ammonia⁹ and for applications in phase-change optical recording devices.¹⁰ Therefore, accurate knowledge of the physical properties of this material is essential for its technological applications.

FeWO_4 is one of the less studied AWO_4 wolframites.¹ Curiously, most studies on this material have focused on nanoparticles,^{11,12} with single crystals mainly synthesized to characterize their magnetic properties.¹⁰ FeWO_4 showed an antiferromagnetic behavior at low temperatures with a Néel temperature of 75 K.¹⁰ In particular, the characterization of the band gap energy at ambient conditions has been conducted on compacted powders using diffuse reflectance^{10,12–14} rather than accurate optical absorption measurements on single crystals.¹⁵ As a consequence, the reported values of the band gap energy range from 1.8 to 2.2 eV. Additionally, there are previous Raman studies at ambient pressure, but not all of the expected Raman-active modes have been measured in these studies.^{2,11,16} On the other hand, nothing is known about the

compressibility and structural stability of FeWO_4 under high-pressure (HP) conditions.

The crystal structure of FeWO_4 is monoclinic (space group $P2_1/c$) and contains two formula units per unit cell.¹⁷ The structure is shown in Figure 1a. The metal ions (Fe^{2+} and W^{6+}) occupy half of the octahedral holes in a slightly deformed hexagonal close-packed lattice of oxygen atoms. The crystal structure can be described as two zigzag chains of edge-sharing FeO_6 or WO_6 octahedral units running along [001]. The high-spin d^6 electronic configuration of Fe^{2+} distorts the FeO_6 octahedron due to the Jahn–Teller effect.¹⁸


It is well known that pressure can drastically change the interatomic distances in solids, which in turn can lead to a variety of fascinating phenomena such as metallization,¹⁹ superconductivity,²⁰ changes in chemical bonding,²¹ and the formation of new compounds.²² Wolframites have been studied under compression over the past decade by several research groups.¹ Due to their bulk modulus, an external pressure of 10 GPa causes a 10% change in the unit-cell volume. Consequently, the electronic, magnetic, vibrational, and elastic properties can be dramatically altered.^{23,24} However, it is known that several AWO_4 wolframite-type

Received: January 25, 2024

Revised: March 8, 2024

Accepted: March 12, 2024

Published: March 30, 2024



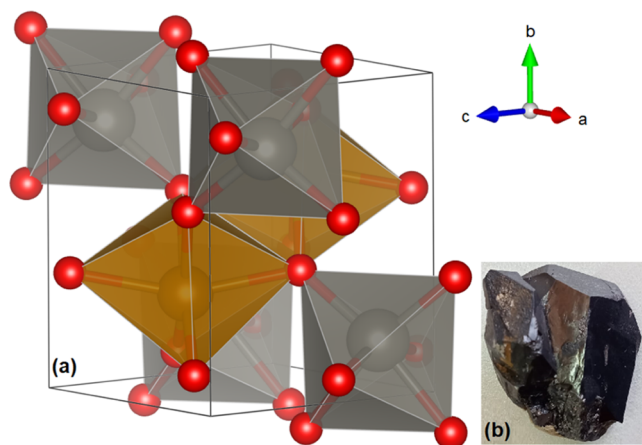


Figure 1. (a) Crystal structure of the mineral ferberite (FeWO_4). FeO_6 octahedra are shown in brown, and WO_6 octahedra are shown in gray. The oxygen atoms are shown in red. The black solid lines represent the unit cell. The arrows indicate the crystal axes. (b) Photograph of the ferberite crystal used for experiments.

compounds do not undergo phase transitions up to pressures of around 20 GPa.^{1,2,7,23–25}

In the stability range of the wolframite structure, compression is anisotropic, with the symmetry of the structure decreasing with increasing pressure.^{23,24} The structural changes cause a decrease in the electronic band gap energy of NiWO_4 , MnWO_4 , and CoWO_4 ,^{5,23,26} which has been attributed to an increase in hybridization between the 3d electrons of the divalent A cation and the 2p electrons of the oxygen atoms. However, the influence of the pressure on the properties of FeWO_4 has not been investigated. The influence of the pressure on the crystal structure of FeWO_4 has also not been studied experimentally. Therefore, we considered it timely to conduct a study of the HP behavior of FeWO_4 and to investigate the Raman spectrum and optical absorption of single crystals of FeWO_4 in detail. Here, we report optical absorption, Raman, and X-ray diffraction (XRD) measurements at ambient pressure and HP in a natural crystal of the mineral ferberite (FeWO_4). The experimental results are complemented by first-principles calculations.

2. EXPERIMENTAL DETAILS

The experiments were performed on samples obtained from natural ferberite crystals provided by Fabre Minerals from the Monte Cambillaya mining district, La Paz, Bolivia. An image of the original crystal is shown in Figure 1b. The dimensions of the natural crystal were 2.9 cm \times 2.4 cm \times 1.3 cm. Electron microprobe analysis was performed to determine the impurities present in the natural crystal. Nb (0.06%) and Ta (0.02%) were the only detected impurities. Such a minimal concentration of impurities is not expected to affect the properties studied in this work. Optical absorption and Raman experiments were performed on 40 μm \times 40 μm \times 10 μm platelets oriented perpendicular to the cleavage plane (010).¹⁰ The color of the crystals was dark brown in transmitted light. Powder XRD measurements were performed on a finely ground powder from a fragment of the original single crystal. All experiments at HP were performed using a membrane-driven diamond-anvil cell with diamond culets of 500 μm in diameter. Stainless steel gaskets preindented to a thickness of 55 μm were used. The pressure-transmitting medium was a 4:1 methanol–ethanol mixture, which provides quasi-hydrostatic conditions up to 10 GPa.²⁷ Pressure was measured using ruby fluorescence with an error of less than 0.05 GPa.²⁸

Synchrotron powder XRD experiments were performed at the BL04-MSPD beamline of ALBA synchrotron²⁹ using a monochromatic X-ray beam with a wavelength of 0.4642 Å. The X-ray beam was focused down to a 20 μm \times 20 μm spot. XRD was collected with a Rayonix SX165 charge-coupled device (CCD) image plate. The two-dimensional (2D) patterns were integrated using FIT2D,³⁰ and FullProf was used to analyze (Rietveld refinement) the integrated 1D XRD patterns.³¹ Raman experiments were performed using an inVia Renishaw Raman spectrometer system with a 5 \times magnification objective. A laser wavelength of 682 nm with an output of less than 10 mW was used to avoid sample heating. The spectral resolution was greater than 2 cm^{-1} . The optical absorption experiments were carried out in visible (Vis)–near-infrared (NIR) range using an optical setup consisting of a halogen lamp, reflecting optical objectives, and a Vis–NIR Ocean Optics spectrometer.³² The optical absorption was calculated by dividing the transmittance spectrum of the sample in normal incidence by the spectrum of the reference source.

3. COMPUTATIONAL DETAILS

First-principles calculations were performed within the framework of the density functional theory (DFT)³³ and the projector-augmented wave (PAW)^{34,35} method as implemented in the Vienna Ab initio Simulation Package (VASP).³⁶ A plane-wave energy cutoff of 520 eV was used to ensure high precision in calculations. The exchange–correlation energy was described within the generalized gradient approximation (GGA) in the GGA + U method with the Perdew–Burke–Ernzerhof for solids (PBEsol) functional³⁷ to account for the strong correlation between the electrons in the d shell based on the method developed by Dudarev.³⁸ In this method, Coulomb interaction U and onsite exchange interaction J_{H} are treated together as $U_{\text{eff}} = U - J_{\text{H}}$. For our GGA + U calculations, we chose $U = 6$ eV and $J_{\text{H}} = 0.95$ eV. Similar values were previously used with success in the study of other iron and ABO_4 compounds.^{39–42} All properties computed in this study were calculated under the GGA + U approach. For the calculations, we considered nonmagnetic, ferromagnetic, and antiferromagnetic configurations. We found that for the pressures covered by this study, the configuration with the lowest energy is the antiferromagnetic one. All physical properties simulated in this work were calculated for this configuration.

The Monkhorst–Pack scheme⁴³ was employed to discretize the Brillouin zone (BZ) integrations with a mesh 4 \times 4 \times 4, which corresponds to a set of 16 special k -points in the irreducible BZ for the wolframite structure. In the relaxed equilibrium configuration, the forces are less than 1 meV/Å per atom in each Cartesian direction. The highly converged results on forces are required to calculate the dynamical matrix using the direct force constant approach.⁴⁴ This allows us to identify the irreducible representation and the character of the phonon modes at the zone center (Γ point). The electronic structure was obtained by using the primitive cell with a larger set of k -points.

4. RESULTS AND DISCUSSION

4.1. XRD Measurements. Figure 2 shows powder XRD patterns of mineral ferberite (FeWO_4) measured at selected pressures. The bottom trace of the figure shows the results at ambient pressure together with the results from the Rietveld refinement performed using the structural model reported in the literature.¹⁷ All measured peaks can be explained by the wolframite-type structure (space group $P2_1/c$).¹⁷ The goodness-of-fit parameters of the refinement are $R_{\text{WP}} = 4.16\%$, $R_{\text{p}} =$

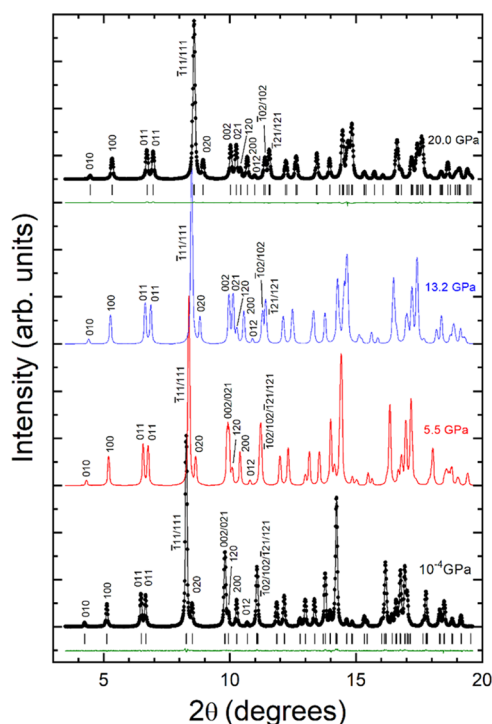


Figure 2. XRD patterns measured in natural mineral ferberite (FeWO_4) at selected pressures. At ambient pressure (bottom, 10^{-4} GPa) and the highest pressure (top, 20.0 GPa), experimental data are shown with black symbols, Rietveld refinements with black lines, and residuals with green lines. Vertical ticks are the calculated positions for reflections. The Miller indices of the low-angle peaks are indicated.

2.82%, and $\chi^2 = 1.39$, supporting a good agreement of the model with the experimental data. In Table 1, we can observe the good agreement between our structural parameters obtained at ambient pressure, those reported in the literature¹⁷ and those obtained from our DFT calculations.

Figure 2 shows that the only change induced by pressure in the powder XRD pattern is the shift of peaks toward higher angles due to the contraction of the lattice parameters. We did

Table 1. Unit-Cell Parameters (a , b , c , and β), Volume (V), and Atomic Positions of Natural Mineral Ferberite (FeWO_4) Obtained from the Rietveld Refinements at Ambient Pressure^a

	exp.	theo.	ref 17	
a (Å)	4.742(2)	4.7142	4.730(3)	
b (Å)	5.722(2)	5.7369	5.703(2)	
c (Å)	4.971(2)	4.9512	4.952(2)	
β (deg)	90.14(6)	90.513	90.0(2)	
V (Å ³)	134.9(2)	133.9	133.6(4)	
atom	site	exp.	theo.	ref 17
Fe	2f	(0.5, 0.3234(5), 0.25)	(0.5, 0.32182, 0.25)	(0.5, 0.3256, 0.25)
W	2e	(0, 0.1854(3), 0.25)	(0, 0.16597, 0.25)	(0, 0.1799, 0.25)
O1	4g	(0.2158(9), 0.1049(9), 0.5775(9))	(0.21576, 0.10476, 0.56913)	(0.2159, 0.1050, 0.5660)
O2	4g	(0.2584(9), 0.3836(9), 0.0958(9))	(0.25518, 0.37562, 0.10428)	(0.2538, 0.3744, 0.1096)

^aThey are compared with results from present calculations and previous experiments.¹⁷

not detect the emergence of any extra peaks up to 20 GPa. In fact, all XRD patterns up to this pressure can be properly refined assuming the same structural model used for the ambient pressure results. This is illustrated in Figure 2 by the Rietveld refinement of the XRD pattern measured at 20 GPa, which is the highest pressure measured. At this pressure, we obtained $R_{\text{WP}} = 6.33\%$, $R_p = 3.98\%$, and $\chi^2 = 1.98$, thereby confirming the assignment of the wolframite-type structure. Therefore, we can conclude that, as in other wolframites,¹¹ there is no phase transition in FeWO_4 up to 20 GPa.

Two important additional observations can be made from the XRD patterns. The first one is that we did not observe any significant peak broadening beyond the quasi-hydrostatic limit of the pressure medium (10 GPa).³¹ This suggests that the influence of nonhydrostatic stresses is negligible in our experiments. The second one is the splitting of several peaks as the pressure increases, which can be seen in Figure 2 by following the evolution of the 002/021 peaks and 102/102/ $\bar{1}21/121$ peaks, which are close to 8 and 11°, respectively. This fact indicates that the compression is not isotropic, as we show next.

From the XRD results, the pressure dependence of the unit-cell parameters is obtained and compared with the results from the calculations (see Figure 3). Both experiments and calculations show a similar pressure dependence for the lattice parameters of the crystal structure. The only slight difference between calculations and experiments is that according to calculations the unit-cell parameters are slightly less compressible than in experiments. Such discrepancies are within the typical discrepancies between experiments and computational results in other wolframites.²³ It might be possible to overcome them using different exchange-correlation functionals in calculations, but a systematic study of the optimum functional for FeWO_4 is beyond the scope of this study. Our results confirm that the compression of FeWO_4 is slightly anisotropic. In particular, the b parameter is the most compressible lattice parameter, and the c parameter is the least compressible, as is the case for CdWO_4 , MgWO_4 , and MnWO_4 according to single-crystal XRD measurements.⁴⁵ This result is confirmed by the fact that the Miller indices with $k \neq 0$ move faster with pressure than those with $k = 0$.

In Figure 3, it can be seen that according to the XRD data, there is an increase in the β angle with pressure, which also favors the aforementioned peak splitting described above. In experiments, two different trends are observed below and above 5 GPa. However, the slope change in the behavior of β at 5 GPa is within the experimental uncertainties, which suggests that the two different trends in the behavior of the β angle can be an experimental artifact. In fact, such a slope change is not observed in calculations (see the inset of Figure 3). Calculations predict a smooth behavior for the β angle, with a steeper increase than in experiments. A similar difference is observed when comparing the behavior of the β angle obtained from DFT calculations and XRD experiments in NiWO_4 .²³

As shown in Figure 4a, the computed polyhedral volume of the distorted FeO_6 octahedra compresses faster than that of the WO_6 octahedra. This result is due to the stronger compression of the Fe–O distances ($d_{\text{Fe-O}}$) than the W–O distances ($d_{\text{W-O}}$) (see Figure 4b). Note that W–O bonds are stronger (more ionic) than Fe–O bonds in terms of the Laplacian of the charge density at the respective bond critical point ($\nabla^2\rho$).^{46,47} This is the reason behind the stiffness of W–

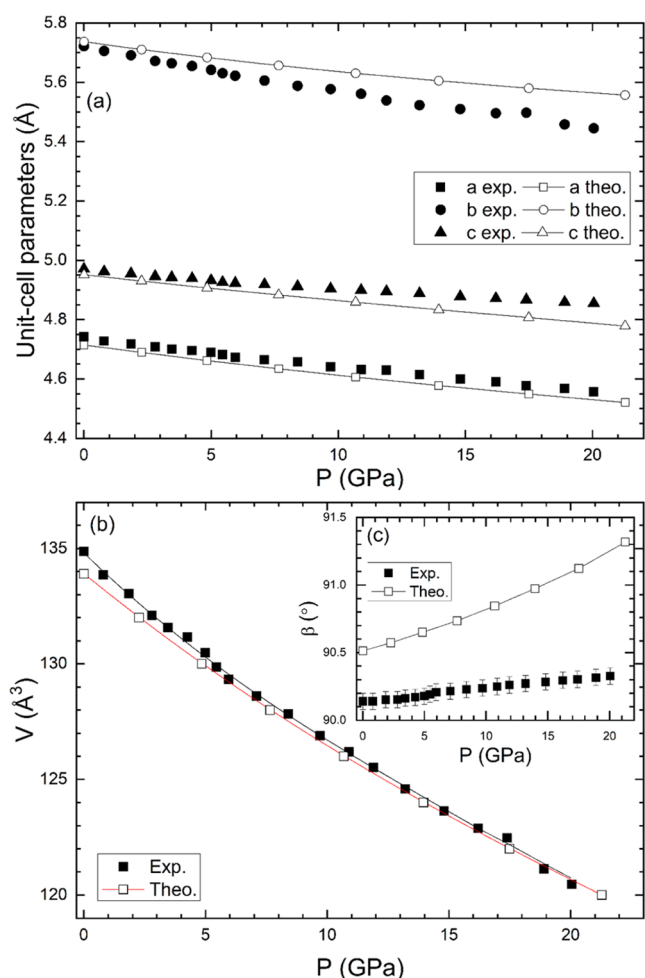


Figure 3. Pressure dependence of (a) lattice parameters a , b , and c , (b) unit-cell volume V , and (c) angle β of FeWO_4 . Solid (empty) symbols are results obtained from experiments (calculations). (b) Equations of state obtained from experiments (black line) and calculations (red line).

O bonds in comparison to that of Fe–O bonds. On the other hand, Figure 4c shows that the polyhedral distortion index Δ_d , calculated using the definition established by Baur,⁴⁸ decreases with pressure for the WO_6 octahedra, but remains almost constant for FeO_6 . In Figure 4c, it can be seen that up to 20

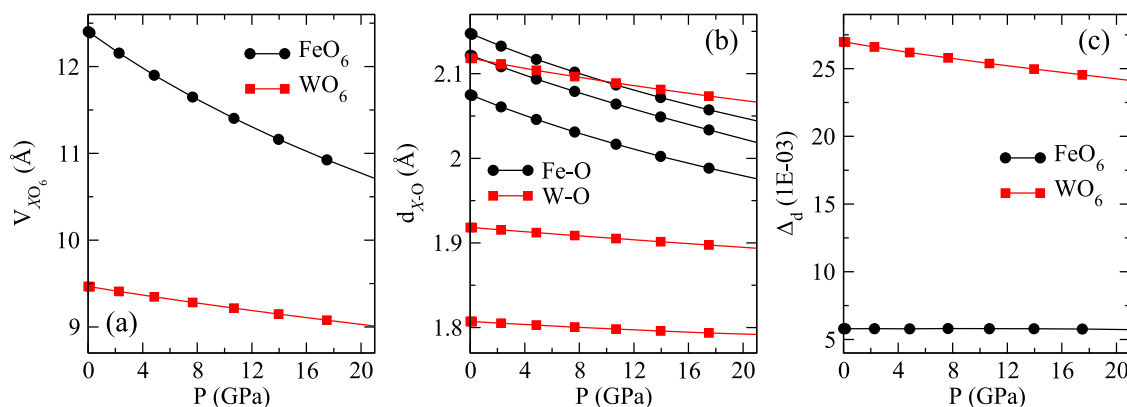


Figure 4. Pressure dependence of the computed (a) polyhedral volume, (b) interatomic distances $d_{\text{Fe-O}}$ and $d_{\text{W-O}}$, and (c) distortion index Δ_d in FeWO_4 .

GPa, the Jahn–Teller distortion is not suppressed by pressure effects. The fact that FeO_6 octahedra are more compressible than WO_6 octahedra can be correlated with the slightly anisotropic compressibility of FeWO_4 . The wolframite structure is formed by chains of FeO_6 and WO_6 octahedra, which alternate along the b -axis, and thus the change in volume of the FeO_6 octahedra favors the compressibility along the b -axis rather than along the other axes.⁴⁵ On the other hand, the fact that zigzag chains of WO_6 octahedra run along the c -axis makes it the least compressible one.

Since the crystal structure of FeWO_4 is monoclinic, the compressibility tensor is not diagonal, and a proper description of the compressibility of the material is obtained from the eigenvalues and eigenvectors of the compressibility tensor.⁴⁹ We obtained these from our experiments using PASCAL.⁵⁰ The results are reported in Table 2. Among the principal axes of compressibility, the most compressible one is parallel to the b -axis, in agreement with our previous conclusions on axial compressibility.

Table 2. Eigenvalues, λ_i , and Eigenvectors, $e_{i,j}$, of the Isothermal Compressibility Tensor of FeWO_4

$\lambda_1 = 2.33(5) \times 10^{-3} \text{ GPa}^{-1}$	$e_{v1} = (0,1,0)$
$\lambda_2 = 1.92(2) \times 10^{-3} \text{ GPa}^{-1}$	$e_{v2} = (10,0,1)$
$\lambda_3 = 1.09(1) \times 10^{-3} \text{ GPa}^{-1}$	$e_{v3} = (1,0,-10)$

The results for the pressure dependence of the volume were fitted with a third-order Birch–Murnaghan equation of state⁵¹ using the program EoSFit.⁵² The obtained bulk modulus (B_0), its pressure derivative (B'_0), and the volume (V_0) at zero pressure are given in Table 3. The bulk modulus determined

Table 3. Unit-Cell Volume (V_0), Bulk Modulus (B_0), and Bulk Modulus Pressure Derivative (B'_0) at Zero Pressure of FeWO_4 Determined Using a Third-Order Birch–Murnaghan EOS^a

	V_0 (\AA^3)	B_0 (GPa)	B'_0
experiment	134.9(5)	136(2)	5.0(4)
theoretical	133.9(1)	150(1)	4.8(2)

^aWe present results from experiments and calculations.

from our experiments, $B_0 = 136(2)$ GPa, agrees within two standard deviations with the bulk modulus previously reported

for the rest of the AWO_4 wolframites.¹ The calculated bulk modulus is 10% larger than that determined from experiments. Such a difference is within the typical range of discrepancies between DFT calculations and experiments. A detailed discussion of the reason for this discrepancy can be found in ref 53.

4.2. Raman Measurements. According to group-theory analysis, FeWO_4 has 36 vibrational modes at the Γ point of the Brillouin zone: $\Gamma = 8A_g + 10B_g + 8A_u + 10B_u$. Three vibrations correspond to acoustic modes ($A_u + 2B_u$); the rest are optical modes. This means that 18 Raman-active modes ($8A_g + 10B_g$) and 15 infrared (IR)-active modes ($7A_u + 8B_u$) are expected. To the best of our knowledge, no IR experiments have been reported on FeWO_4 . Regarding the Raman-active modes, only seven modes were reported for FeWO_4 in refs 11 and 16. In contrast, 15 were reported for FeWO_4 in ref 2. The nondetection of all Raman modes in previous studies was due to mainly single-crystal orientation or overlapped peaks.

In Figure 5, we show the Raman spectrum of the natural ferberite mineral (FeWO_4) at ambient pressure together with

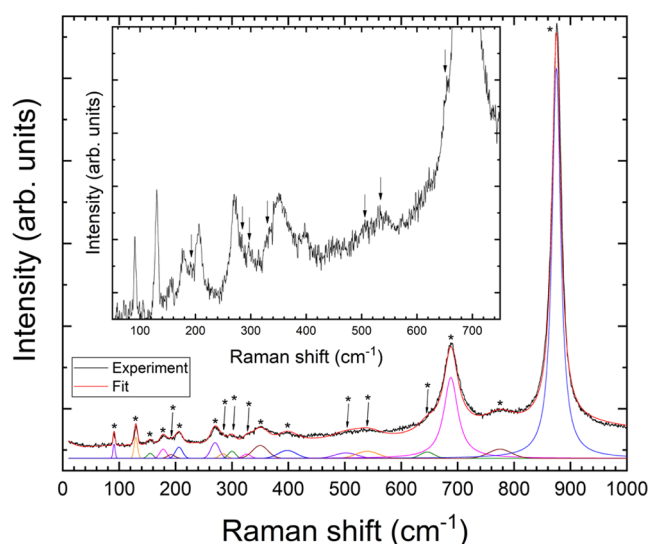


Figure 5. Raman spectrum of the natural mineral ferberite (FeWO_4) measured at ambient conditions in a sample before loading it into the diamond-anvil cell. The black line corresponds to the experimental spectrum. The red line represents the overall fit. The contribution of each phonon to the fit is shown in different colors in the lower part of the figure. The 18 phonons are identified by asterisks (*). The arrows identify the weakest modes. The inset shows a zoom of the 50–750 cm^{-1} region to facilitate the identification of these peaks.

the fit we made, assuming peaks with a Lorentzian shape. The symmetry assignment of each Raman mode has been done with the theoretical results. Note that our Raman spectrum is similar to that reported for the mineral ferberite in the RRUFF database.⁵⁴ In our measurements, we detected the 18 Raman-active modes predicted for FeWO_4 . Eleven modes can be directly visualized in Figure 5. The other seven modes are indicated by arrows in the figure. To clearly show the other, we have included a zoom of the 50–750 cm^{-1} region of the Raman spectrum. In this zoom, the seven weakest modes are also identified by arrows.⁵⁵

The values obtained for all Raman modes of FeWO_4 are summarized in Table 4. They compare well to those previously reported.² The good match obtained with the Lorentzian

Table 4. Wavenumbers of Raman-Active Modes in FeWO_4 at Ambient Pressure^a

mode	ω_{exp} (cm^{-1}), this work	ω_{DFT} (cm^{-1}), this work	ω_{exp} (cm^{-1}), ref 2	ω_{DFT} (cm^{-1}), ref 2
B_g	91	97.8	86	92
A_g	129	130.9	124	132
B_g	155	159	154	162
B_g	178	183.7	174	179
B_g	192	194.9		184
A_g	206	222.9	208	213
B_g	271	275.5	266	263
A_g	284	279.1	299	278
B_g	300	301.1		295
A_g	328	333.1	330	330
B_g	350	350.2		350
A_g	398	393.7	401	406
B_g	502	502.1	500	483
A_g	539	536.3	534	530
B_g	648	644.1	653	637
A_g	688	686.8	692	676
B_g	775	764.4	777	754
A_g	875	869.2	878	866

^aResults from the present work are compared with those reported in the literature.²

multipeak fitting analysis used for the deconvolution of the different modes and the comparison with previous studies make us confident in our mode identification. The modes at 192, 300, and 350 cm^{-1} were never reported before. The difference in wavenumber between this work and ref 2 is within 5 cm^{-1} (the accuracy of both setups is 2 cm^{-1}). This could be due to an offset in the calibrations between the two setups and/or to the fact that the present study was carried out in a natural mineral and the previous study was performed in a synthetic sample.

Regarding calculations, the present results agree slightly better with our experiments than those of previous investigations.² This difference could be mainly due to the exchange-correlation functional and the slight difference in the U_{eff} parameter. The relative difference between the present calculations and experiments is within 5%, which can be considered quite good.⁵⁴ Figure 4 shows that the strongest modes are in the highest-frequency region, corresponding to two A_g modes that can be assigned to internal symmetric vibrations of the WO_6 octahedron. Not surprisingly, the strongest mode, which is assigned to the symmetric stretching vibration, in FeWO_4 has nearly the same frequency (875 cm^{-1}) as in MnWO_4 (887.5 cm^{-1}), NiWO_4 (881 cm^{-1}), and CoWO_4 (887 cm^{-1}).² This is because the W–O distances and, hence, the force constants are nearly identical in the four compounds.

A selection of Raman spectra measured at different pressures is shown in Figure 6. The only changes observed in the spectra are a shift in the position of the modes and a decrease in their intensity. All spectra up to the highest pressure are compatible with the wolframite-type structure. We have observed the 18 modes only up to 2 GPa. The two weakest high-frequency modes cannot be distinguished from the background at this pressure. There are other modes that also cannot be detected up to the highest pressure (19.8 GPa), where only 12 Raman modes are observed.

The pressure dependence of the Raman-active modes of ferberite is plotted in Figure 7a. A few low-frequency modes

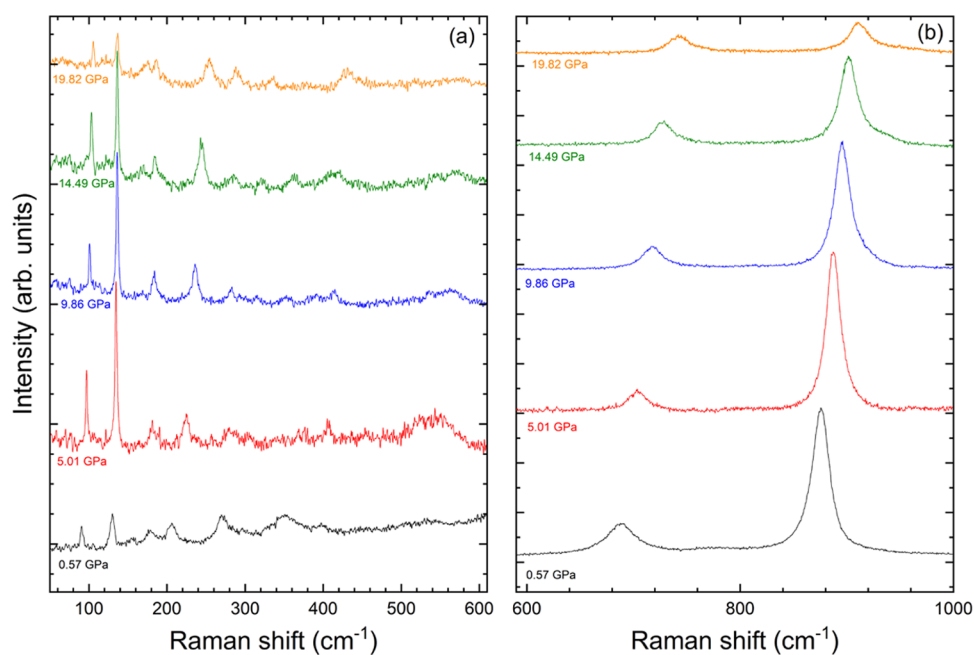


Figure 6. Raman spectra of natural mineral ferberite (FeWO_4) at selected pressures. (a) The 50–600 cm^{-1} region. The spectra have been magnified five times to facilitate the identification of weak peaks. (b) The 600–1000 cm^{-1} region without magnification.

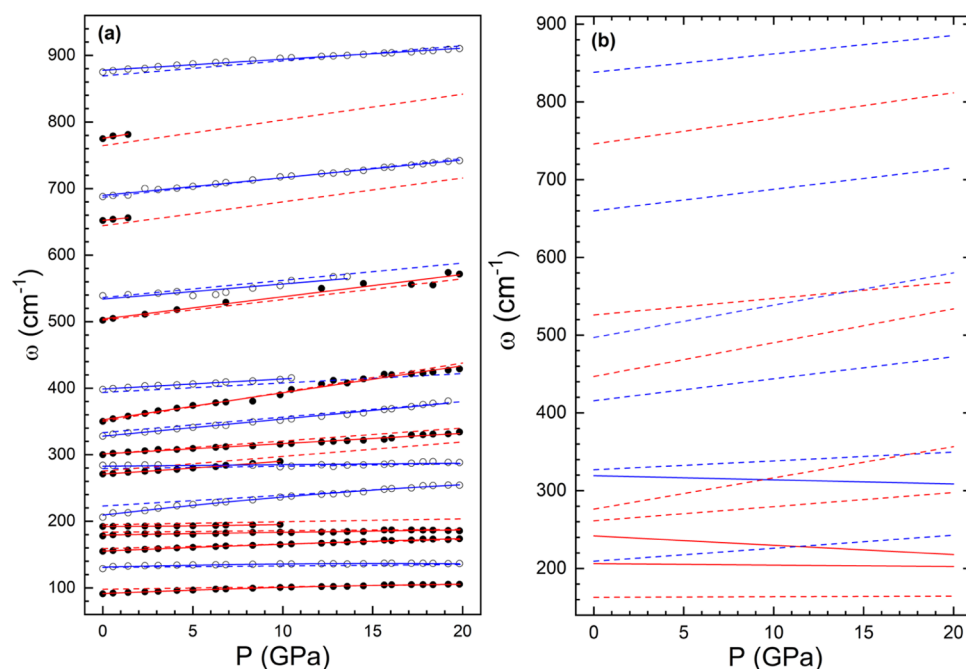


Figure 7. (a) Pressure dependence of the Raman-active modes in FeWO_4 . Black (empty) symbols represent the experimental B_g (A_g) modes. Red (blue) solid lines are quadratic or linear fits to the experimental B_g (A_g) modes. The dashed lines represent the results of calculations (the color code is the same as for experiments). (b) Calculated pressure dependence of IR-active modes. Red (blue) lines represent the B_u (A_u) modes. Solid lines have been used to identify the modes which soften under compression.

follow a quadratic pressure dependence, and the rest follow a linear trend. All modes harden under compression. In Figure 7a, we also plot the results of the DFT calculations, which are in very good agreement with the experimental results. In Table 5, we summarize the wavenumber (ω), the pressure coefficients at zero pressure ($d\omega/dP$), and the Grüneisen parameter ($\gamma = -\frac{B_0}{\omega_0} \frac{d\omega}{dP}$, where ω_0 is the wavenumber at zero pressure). The mode with the larger γ , i.e., the mode whose frequency varies more with the volume, is the B_g mode with

wavenumber 350 cm^{-1} . This is the internal bending mode of the WO_6 octahedron. This is in agreement with the results reported for MgWO_4 and MnWO_4 .^{2,7} Figure 7a also shows that there are two phonon crossings between the A_g and B_g modes. One occurs at 5 GPa and the other at 15 GPa.

From the DFT calculations, we have obtained the frequency and symmetry assignment of the IR-active modes of FeWO_4 as well as their pressure dependences. The results are summarized in Figure 7b and Table 5. They are presented for the sake of

Table 5. Wavenumber (ω), Pressure Coefficient ($d\omega/dP$), and Grüneisen Parameter (γ) for Raman-Active and IR-Active Modes in FeWO₄

mode	ω_{exp} (cm ⁻¹)	$d\omega/dP$ (cm ⁻¹ /GPa)	γ	ω_{DFT} (cm ⁻¹)	$d\omega/dP$ (cm ⁻¹ /GPa)	γ	mode	ω_{DFT} (cm ⁻¹)	$d\omega/dP$ (cm ⁻¹ /GPa)	γ
B _g	91	0.66	0.99	97.8	0.38	0.73	B _u	163.0	0.07	0.10
A _g	129	0.59	0.62	130.9	0.22	0.32	B _u	206.3	-0.19	-0.17
B _g	155	0.89	0.78	159.0	0.69	0.82	A _u	209.2	1.68	1.45
B _g	178	0.46	0.35	183.7	0.21	0.22	B _u	241.9	-1.20	-0.99
B _g	192	0.22	0.16	194.9	0.44	0.41	B _u	261.2	1.82	1.27
A _g	206	1.64	1.08	222.9	1.61	1.31	B _u	276.1	4.03	2.48
B _g	271	2.67	1.34	275.5	2.18	1.44	A _u	319.2	-0.53	-0.32
A _g	284	0.53	0.25	279.1	0.37	0.25	A _u	326.8	1.14	0.66
B _g	300	1.95	0.88	301.1	1.95	1.18	A _u	415.6	2.83	1.23
A _g	328	2.53	1.05	333.1	2.34	1.27	B _u	446.9	4.35	1.71
B _g	350	4.36	1.69	350.2	4.38	2.18	A _u	496.9	4.16	1.50
A _g	398	0.59	0.20	393.7	1.41	0.67	B _u	526.0	2.12	0.75
B _g	502	3.13	0.85	502.1	3.11	1.13	A _u	660.0	2.77	0.79
A _g	539	1.95	0.49	536.3	2.59	0.90	B _u	746.0	3.28	0.82
B _g	648	3.33	0.69	644.1	3.59	1.02	A _u	838.1	2.37	0.54
A _g	688	2.87	0.57	686.8	2.92	0.79				
B _g	775	3.91	0.69	764.4	3.87	0.94				
A _g	875	1.95	0.30	869.2	2.28	0.50				

completeness and to help in mode assignment and identification in future IR absorption experiments. It can be observed that IR-active modes have a similar frequency distribution to Raman-active modes. In contrast to Raman-active modes, three IR-active modes soften with increasing pressure according to our calculations. The pressure dependence of IR modes has not yet been studied for other wolframites, so we do not know if the pressure-induced IR softening observed in FeWO₄ is a fingerprint of this material or a common feature of the wolframite family. The IR mode with the largest Grüneisen parameter is the B_u mode with a wavenumber of 276.1 cm⁻¹. Regarding phonon crossings and anticrossings, there are five phonon crossings and no phonon anticrossing predicted to occur up to 20 GPa, as shown in Figure 7a,b.

4.3. Optical Absorption Measurements. To study the electronic properties of FeWO₄ at ambient pressure and under compression, we performed optical absorption experiments as well as DFT simulations of the electronic band structure and density of states. The optical absorption spectrum of the natural mineral ferberite at different pressures is shown in Figure 8. The shape of the absorption edge supports an indirect band gap. We have also observed a typical Urbach-type⁵⁶ exponential sub-band gap absorption, which is normally observed in tungstates and related ternary oxides.⁵⁷ According to our simulations, the band gap of FeWO₄ is indirect, in agreement with our experiments. The band structure is shown in Figure 9. The top of the valence band is at the Y point of the BZ and the bottom of the conduction band is at the Γ point of the BZ. DFT calculations give a band gap energy (E_g) of 1.79 eV. Experimentally, we have determined the band gap energy by means of a Tauc analysis⁵⁸ (see the inset of Figure 8); therefore, the reported value should be assumed as the lower limit value of E_g .⁵⁹ We obtained $E_g = 2.00(5)$ eV, which is between the previously reported values.^{10,12–14} This means that the calculated band gap energy is slightly underestimated, but the underestimation, 0.2 eV, is within typical differences between DFT and experiments.^{23,60} However, this does not affect the determination of the pressure dependence of E_g .⁶⁰ In Figure 10, we present the electronic density of states, which

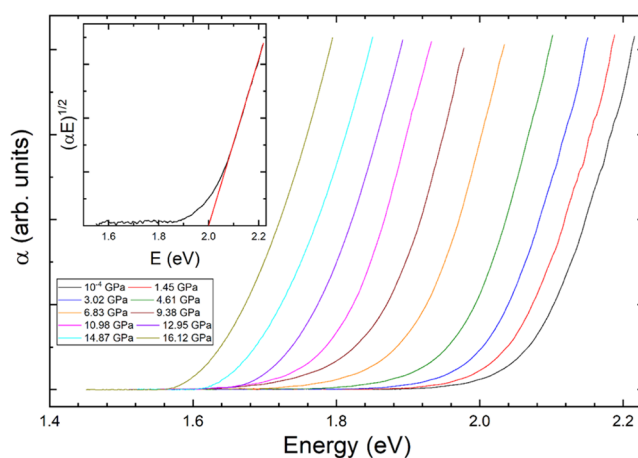


Figure 8. Optical absorption spectra of the natural mineral ferberite (FeWO₄) measured at different pressures are indicated in the legend. The inset shows the Tauc plot used to determine the band gap energy at ambient pressure.

shows that Fe states are the main contributors to the top of the valence band and hybridized W and O orbitals dominate the bottom of the conduction band.

The pressure dependence of the band gap energy from experiments and calculations is shown in Figure 11. Both methods give a qualitatively similar behavior, with the band gap closing at a rate of 25 and 20 meV/GPa according to experiments and calculations, respectively. This phenomenon is similar to the HP band gap closure reported for NiWO₄,¹⁹ CoWO₄,²² and MnWO₄,⁶¹ and different from that found in CdWO₄, ZnWO₄, and MgWO₄.⁵⁹ The main reason for the band gap closure in FeWO₄ at HP is the contribution of Fe orbitals to the top of the valence band. They move more quickly to higher energies under compression than the states at the bottom of the conduction band, causing the narrowing observed in E_g . This can be seen in Figures 9 and 10 where the band structure and electronic density of states at different pressures are compared. In addition to reducing the band gap, the main change induced by pressure in the band structure is in

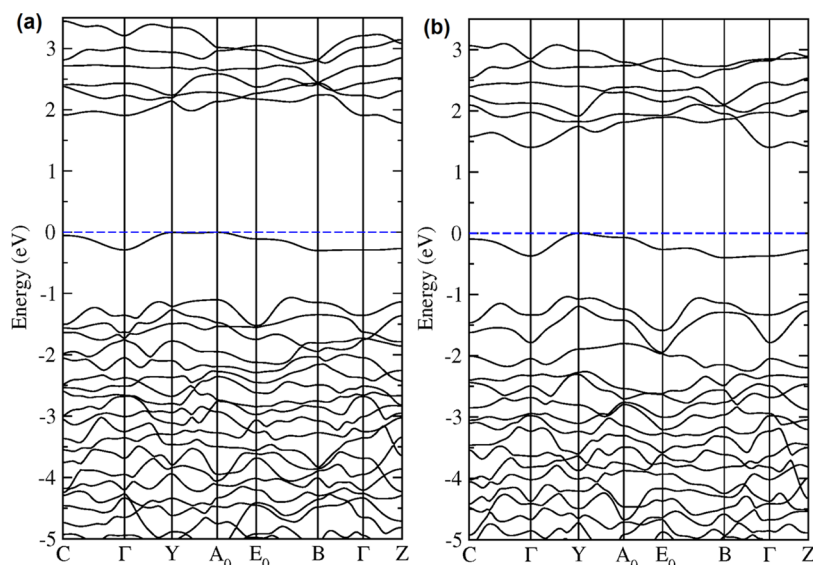


Figure 9. Calculated band structure of FeWO_4 at (a) ambient pressure and (b) 13.4 GPa. The dashed blue line is the Fermi level, which has been set at 0 eV.

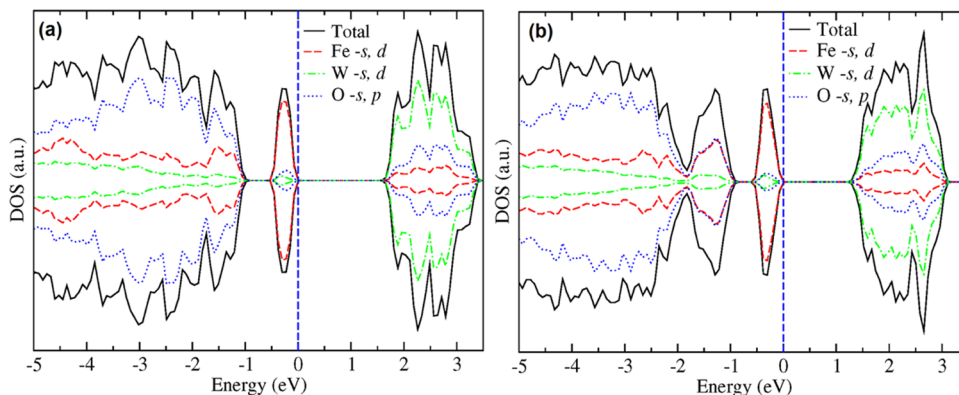


Figure 10. Electronic density of states of FeWO_4 at (a) ambient pressure and (b) 13.4 GPa. The blue line is the Fermi level, which has been set at 0 eV.

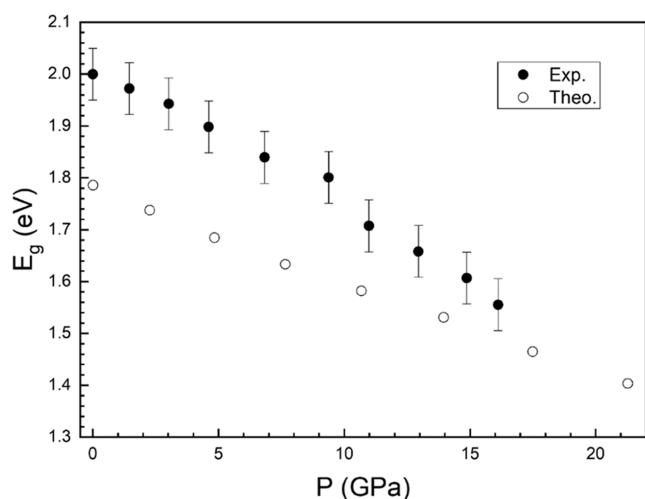


Figure 11. Pressure dependence of the band gap energy of FeWO_4 . Solid (empty) symbols are results from experiments (calculations).

the topology of the conduction band, which becomes more dispersive at high pressure. On the other hand, in the figure of the density of states, it can be seen that the orbital composition

of the bands near the Fermi level is not modified under compression, but the Fe orbitals in the top of the valence band get closer to the bottom of the conduction band.

5. CONCLUSIONS

We report an experimental and theoretical study of the natural mineral ferberite (FeWO_4). The crystal structure, Raman-active phonons, and band gap energy have been accurately characterized both experimentally and computationally at ambient pressure and under compression up to 20 GPa, and we have found them to be in good agreement. We found that the ambient pressure wolframite-type structure of FeWO_4 does not undergo any phase transition up to 20 GPa. FeWO_4 exhibits an indirect band gap of 2.00(5) eV at ambient pressure, which decreases at a rate of 25 meV/GPa similar to other magnetic AWO_4 ($A = \text{Mn}, \text{Ni}, \text{and Co}$) wolframites. The pressure dependence of Raman-active and IR-active modes has been reported, with all Raman-active modes hardening with pressure, as it is characteristic of the AWO_4 wolframite compounds, and several IR-active modes showing pressure-induced softening. In general, we have found that FeWO_4 follows a similar trend to other wolframites, with the behavior of the electronic structure being particularly different from the

nonmagnetic AWO_4 ($A = \text{Mg, Zn, Cd}$) wolframites due to the valence band electrons from Fe.

■ ASSOCIATED CONTENT

Data Availability Statement

The data that support the findings of this study are available from the corresponding author upon reasonable request.

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.inorgchem.4c00345>.

Crystallographic data (PDF)

■ AUTHOR INFORMATION

Corresponding Authors

Sinhué López-Moreno – CONAHCYT—División de Materiales Avanzados and Grupo de Ciencia e Ingeniería Computacionales—Centro Nacional de Supercómputo, IPICYT, San Luis Potosí 78216, Mexico; orcid.org/0000-0001-6292-8275; Email: sinhue.lopez@ipicyt.edu.mx

Daniel Errandonea – Departamento de Física Aplicada-ICMUV, MALTA Consolider Team, Universidad de Valencia, 46100 Valencia, Spain; orcid.org/0000-0003-0189-4221; Email: daniel.errandonea@uv.es

Authors

Daniel Diaz-Anichtchenko – Departamento de Física Aplicada-ICMUV, MALTA Consolider Team, Universidad de Valencia, 46100 Valencia, Spain

Jesus E. Aviles-Coronado – División de Materiales Avanzados, IPICYT, San Luis Potosí 78216, Mexico

Robin Turnbull – Departamento de Física Aplicada-ICMUV, MALTA Consolider Team, Universidad de Valencia, 46100 Valencia, Spain; orcid.org/0000-0001-7912-0248

Francisco J. Manjón – Instituto de Diseño para la Fabricación y Producción Automatizada, MALTA Consolider Team, Universitat Politècnica de València, 46022 València, Spain; orcid.org/0000-0002-3926-1705

Catalin Popescu – CELLS-ALBA Synchrotron Light Facility, Cerdanyola 08290 Barcelona, Spain

Complete contact information is available at: <https://pubs.acs.org/doi/10.1021/acs.inorgchem.4c00345>

Author Contributions

D.E. conceived the project. D.D.-A., R.T., F.J.M., C.P., and D.E. performed experiments. D.D.-A. and D.E. performed data analysis. J.E.A.-C. and S.L.-M. performed density functional theory calculations. All authors participated in discussions and writing and editing of the manuscript. All authors have approved the final version of the manuscript.

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

D.E. and F.J.M. gratefully acknowledge the financial support from the Spanish Research Agency (AEI) and Spanish Ministry of Science and Investigation (MCIN) under Projects PID2019-106383GB-41/42, PID2022-138076NB-C41/42, and RED2022-134388-T (DOI: 10.13039/501100011033). D.E. and F.J.M. also thank the financial support of Generalitat Valenciana under grants PROMETEO CIPROM/2021/075 (GREENMAT), MFA/2022/007, and MFA/2022/025 (AR-CANGEL). This study forms part of the Advanced Materials

program and is supported by MCIN with funding from European Union Next Generation EU (PRTR-C17.I1) and by the Generalitat Valenciana. C.P. acknowledges the grant Proyectos de Generación de Conocimiento PID2021-125927NB-C21. R.T. and D.E. thank the Generalitat Valenciana for the Postdoctoral Fellowship No. CIAPOS/2021/20. The authors thank ALBA synchrotron for providing beam time for the HP XRD experiments (Proposal 2014071024). S.L.-M. thanks CONAHCYT of Mexico for financial support through the program “Programa de Investigadoras e Investigadores por México”. The authors gratefully acknowledge the computing time granted by LANCAD and CONAHCYT on the supercomputer Miztli at LSVP DGTIC UNAM, and also the IPICYT Supercomputing National Center for Education & Research, grant TKII-R2024-SLM/-JEAC.

■ REFERENCES

- (1) Errandonea, D.; Ruiz-Fuertes, J. A Brief Review of the Effects of Pressure on Wolframite-type Oxides. *Crystals* **2018**, *8* (2), No. 71.
- (2) Ruiz-Fuertes, J.; Errandonea, D.; López-Moreno, S.; González, J.; Gomis, O.; Vilaplana, R.; Manjón, F. J.; Muñoz, A.; Rodríguez-Hernández, P.; Friedrich, A.; Tupitsyna, I. A.; Nagornaya, L. L. High-Pressure Raman Spectroscopy and Lattice-Dynamics Calculations on Scintillating MgWO_4 : Comparison with Isomorphous Compounds. *Phys. Rev. B* **2011**, *83* (21), No. 214112.
- (3) Liu, C. B.; He, Z. Z.; Liu, Y. J.; Chen, R.; Shi, M. M.; Zhu, H. P.; Dong, C.; Wang, J. F. Magnetic Anisotropy and Spin-flop, Transition of NiWO_4 Single Crystals. *J. Magn. Magn. Mater.* **2017**, *444*, 190–192.
- (4) Heyer, O.; Hollmann, N.; Klassen, I.; Jodlauk, S.; Bohaty, L.; Becker, P.; Mydosh, J. A.; Lorenz, T.; Khomskii, D. A new Multiferroic Material: MnWO_4 . *J. Phys.: Condens. Matter* **2006**, *18* (39), L471–L475.
- (5) Guillen, R.; Regnard, J. R. Magnetic Properties of Natural and Synthetic Wolframites $\text{Fe}_x\text{Mn}_{1-x}\text{WO}_4$. *Phys. Chem. Miner.* **1985**, *12* (4), 246–254.
- (6) Almeida, M. A. P.; Cavalcante, L. S.; Morilla-Santos, C.; Dalmaschio, C. J.; Rajogopal, S.; Li, M. S.; Longo, E. Effect of Partial Preferential Orientation and Distortions in Octahedral Clusters on the Photoluminescence Properties of FeWO_4 Nanocrystals. *CrystEngComm* **2012**, *14* (21), 7127–7132.
- (7) Ruiz-Fuertes, J.; Friedrich, A.; Gomis, O.; Errandonea, D.; Morgenroth, W.; Sans, J. A.; Santamaría-Pérez, D. High-Pressure Structural Phase Transition in MnWO_4 . *Phys. Rev. B* **2015**, *91* (10), No. 104109.
- (8) Hoang, K. Polaron Formation, Native Defects, and Electronic Conduction in Metal Tungstates. *Phys. Rev. Mater.* **2017**, *1* (2), No. 024603.
- (9) Zhao, Y.; Li, F.; Li, W.; Li, Y.; Liu, C.; Zhao, Z.; Shan, Y.; Ji, Y.; Sun, L. Identification of $\text{M-NH}_2\text{-NH}_2$ Intermediate and Rate Determining Step for Nitrogen Reduction with Bioinspired Sulfur-Bonded FeW Catalyst. *Angew. Chem., Int. Ed.* **2021**, *60*, 20331–20341.
- (10) Maignan, A.; Schmidt, M.; Prots, Y.; Lebedev, O. I.; Daou, R.; Chang, C.-F.; Kuo, C.-Y.; Hu, Z.; Chen, C.-T.; Weng, S.-C.; Altendorf, S.-G.; Tjeng, L. H.; Grin, Y. FeWO_4 Single Crystals: Structure, Oxidation States, and Magnetic and Transport Properties. *Chem. Mater.* **2022**, *34* (2), 789–797.
- (11) Gao, Q.; Liu, Z. FeWO_4 Nanorods with Excellent UV-Visible Light Photocatalysis. *Prog. Nat. Sci.: Mater. Int.* **2017**, *27* (5), 556–560.
- (12) Chidambaram, S.; Ramachandran, K.; Gaidi, M.; Daoudi, K.; Natarajamoorthy, M. Solution Combustion Synthesis of Iron Tungstate Nanoparticles for Photoelectrochemical Water Splitting Towards Oxygen Evolution. *J. Mater. Sci.: Mater. Electron.* **2022**, *33* (12), 9134–9143.

- (13) Ojha, D. P.; Karki, H. P.; Song, J. H.; Kim, H. J. Amine-assisted Synthesis of FeWO_4 Nanorod $g\text{-C}_3\text{N}_4$ for Enhanced Visible Light-driven Z-scheme Photocatalysis. *Composites, Part B* **2019**, *160* (1), 277–284.
- (14) Deng, X.; Xie, G.; Liu, X.; Wu, Y.; Qin, L.; Li, Q. Convenient Synthesis of Peony-like FeWO_4 with Super Adsorbent Properties for Efficient Degradation of Organic Dye. *Mater. Res. Express* **2017**, *4* (7), No. 075008.
- (15) Errandonea, D.; Bandiello, E.; Segura, A.; Hamlin, J. J.; Maple, M. B.; Rodríguez-Hernández, P.; Muñoz, A. Tuning the Band Gap of PbCrO_4 through High-Pressure: Evidence of Wide-to-narrow Semiconductor Transitions. *J. Alloys Compd.* **2014**, *587* (1), 14–20.
- (16) Qian, J.; Peng, Z.; Wu, D.; Fu, X. FeWO_4/Fe Core/shell Nanorods Fabricated by Thermal Evaporation. *Mater. Lett.* **2014**, *122* (1), 86–89.
- (17) Ülkü, D. Untersuchungen zur Kristallstruktur und Magnetischen Struktur des Ferberits FeWO_4 . *Z. Krist.* **1967**, *124* (1–6), 192–219.
- (18) García-Matres, E.; Stüßer, N.; Hofmann, M.; Reehuis, M. Magnetic Phases in $\text{Mn}_{1-x}\text{Fe}_x\text{WO}_4$ Studied by Neutron Powder Diffraction. *Eur. Phys. J. B* **2003**, *32* (1), 35–42.
- (19) Rahman, S.; Saqib, H.; Liang, X.; Errandonea, D.; Resta, A. S.; Molina-Sanchez, A.; Gao, G.; Wang, L.; Tian, Y.; Mao, H.-K. Pressure-induced metallization and robust superconductivity in pristine 1T-HfSe_2 . *Mater. Today Phys.* **2022**, *25*, No. 100698.
- (20) Torikachvili, M. S.; Bud'ko, S. L.; Ni, N.; Canfield, P. C. Pressure induced superconductivity in CaFe_2As_2 . *Phys. Rev. Lett.* **2008**, *101*, No. 057006.
- (21) Liang, A.; Turnbull, R.; Errandonea, D. A review on the advancements in the characterization of the high-pressure properties of iodates. *Prog. Mater. Sci.* **2023**, *136*, No. 101092.
- (22) Zhang, L.; Wang, Y.; Lv, J.; Ma, Y. Materials discovery at high pressures. *Nat. Rev. Mater.* **2017**, *2*, No. 17005.
- (23) Errandonea, D.; Rodriguez, F.; Vilaplana, R.; Vie, D.; Garg, S.; Nayak, B.; Garg, N.; Singh, J.; Kanchana, V.; Vaitheeswaran, G. Band-Gap Energy and Electronic d-d Transitions of NiWO_4 Studied under High-Pressure Conditions. *J. Phys. Chem. C* **2023**, *127* (31), 15630–15640.
- (24) Errandonea, D.; Manjón, F. J.; Garro, N.; Rodríguez-Hernández, P.; Radescu, S.; Mujica, A.; Muñoz, A.; Tu, C. Y. Combined Raman Scattering and ab initio Investigation of Pressure-Induced Structural Phase Transitions in the Scintillator ZnWO_4 . *Phys. Rev. B* **2008**, *78* (5), No. 054116.
- (25) Lacomba-Perales, R.; Errandonea, D.; Martínez-García, D.; Rodríguez-Hernández, P.; Radescu, S.; Mujica, A.; Muñoz, A.; Chervin, J. C.; Polian, A. Phase Transitions in Wolframite-type CdWO_4 at High Pressure Studied by Raman Spectroscopy and Density-Functional Theory. *Phys. Rev. B* **2009**, *79* (9), No. 094105.
- (26) Bandiello, E.; Rodríguez-Hernández, P.; Muñoz, A.; Buenestado, M. B.; Popescu, C.; Errandonea, D. Electronic Properties and High-Pressure Behavior of Wolframite-type CoWO_4 . *Mater. Adv.* **2021**, *2* (18), 5955–5966.
- (27) Klotz, S.; Chervin, J.-C.; Munsch, P.; Marchand, G. L. Hydrostatic Limits of 11 Pressure Transmitting Media. *J. Phys. D: Appl. Phys.* **2009**, *42* (7), No. 075413.
- (28) Mao, H. K.; Bell, P. M.; Shaner, J. W.; Steinberg, D. J. Specific Volume Measurements of Cu, Mo, Pd, and Ag and Calibration of the Ruby R, Fluorescence Pressure Gauge from 0.06 to 1 Mbar. *J. Appl. Phys.* **1978**, *49* (6), 3276–3283.
- (29) Fauth, F.; Peral, I.; Popescu, C.; Knapp, M. The New Material Science Powder Diffraction Beamline at ALBA Synchrotron. *Powder Diffr.* **2013**, *28* (S2), S360–S370.
- (30) Hammersley, A. P.; Svensson, S. O.; Hanfland, M.; Fitch, A. N.; Häusermann, D. Two-Dimensional Detector Software: From Real Detector to Idealised Image or Two-Theta Scan. *High Pressure Res.* **1996**, *14* (4–6), 235–248.
- (31) Rodríguez-Carvajal, J. Recent Advances in Magnetic Structure Determination by Neutron Powder Diffraction. *Phys. B Condens. Matter* **1993**, *192* (1–2), 55–69.
- (32) Panchal, V.; Errandonea, D.; Segura, A.; Rodríguez-Hernández, P.; Muñoz, A.; Lopez-Moreno, S.; Bettinelli, M. The Electronic Structure of Zircon-type Orthovanadates: Effects of High-Pressure and Cation Substitution. *J. Appl. Phys.* **2011**, *110* (4), No. 043723.
- (33) Jones, R. O. Density Functional Theory: Its Origins, Rise to Prominence, and Future. *Rev. Mod. Phys.* **2015**, *87* (3), No. 897.
- (34) Blöchl, P. E. Projector Augmented-Wave Method. *Phys. Rev. B* **1994**, *50* (24), 17953–17979.
- (35) Kresse, G.; Joubert, D. From Ultrasoft Pseudopotentials to the Projector Augmented-Wave Method. *Phys. Rev. B* **1999**, *59* (3), 1758–1775.
- (36) Kresse, G.; Hafner, J. Ab Initio Molecular Dynamics for Liquid Metals. *Phys. Rev. B* **1993**, *47* (1), S58–S61.
- (37) Perdew, J. P.; Ruzsinsky, A.; Csonka, G. I.; Vydrov, O. A.; Scuseria, G. E.; Constantin, L. A.; Zhou, X.; Burke, K. Restoring the Density-Gradient Expansion for Exchange in Solids and Surfaces. *Phys. Rev. Lett.* **2008**, *100* (13), No. 136406.
- (38) Dudarev, S. L.; Botton, G. A.; Savrasov, S. Y.; Humphreys, C. J.; Sutton, A. P. Electron-Energy-Loss Spectra and the Structural Stability of Nickel Oxide: An LSDA+U Study. *Phys. Rev. B* **1998**, *57* (3), No. 1505.
- (39) López-Moreno, S.; Errandonea, D.; Pellicer-Porres, J.; Martínez-García, D.; Patwe, S. J.; Achary, S. N.; Tyagi, A. K.; Rodríguez-Hernández, P.; Muñoz, A.; Popescu, C. Stability of FeVO_4 under Pressure: An X-ray Diffraction and First-Principles Study. *Inorg. Chem.* **2018**, *57* (13), 7860–7876.
- (40) Gonzalez-Platas, J.; López-Moreno, S.; Bandiello, E.; Bettinelli, M.; Errandonea, D. Precise Characterization of the Rich Structural Landscape Induced by Pressure in Multifunctional FeVO_4 . *Inorg. Chem.* **2020**, *59* (9), 6623–6630.
- (41) Romero-Vázquez, P. B.; López-Moreno, S.; Errandonea, D. Stability of FeVO_4 -II under Pressure: A First-Principles Study. *Crystals* **2022**, *12* (12), No. 1835.
- (42) López-Moreno, S.; Sánchez-Martín, J.; Bandiello, E.; Bettinelli, E.; Bull, C. L.; Ridley, C. J.; Errandonea, D. The Effect of Pressure on the Band-Gap Energy in FePO_4 and FeVO_4 . *J. Phys. Chem. Solids* **2023**, *183*, No. 111604.
- (43) Monkhorst, H. J.; Pack, J. D. Special Points for Brillouin-Zone Integrations. *Phys. Rev. B* **1976**, *13* (12), 5188–5192.
- (44) Parlinski, K. Computer Code PHONON, 2008. <http://wolf.ifj.edu.pl/phonon>.
- (45) Macavei, J.; Schulz, H. The Crystal Structure of Wolframite type Tungstates at High Pressure. *Z. Kristallogr.* **1993**, *207* (1–2), 193–208.
- (46) Romero-Vázquez, P. B.; López-Moreno, S.; Errandonea, D. Stability of FeVO_4 -II under Pressure: A First-Principles Study. *Crystals* **2022**, *12*, No. 1835.
- (47) Romero-Vázquez, P. B.; López-Moreno, S. Ab initio Study of RaWO_4 : Comparison with Isoelectronic Tungstates. *J. Solid State Chem.* **2023**, *317*, No. 123709.
- (48) Baur, W. H. The geometry of polyhedral distortions. Predictive relationships for the phosphate group. *Acta Crystallogr.* **1974**, *30*, 1195–1215.
- (49) Yuan, H.; Rodríguez-Hernández, P.; Muñoz, A.; Errandonea, D. Putting the Squeeze on Lead Chromate Nanorods. *J. Phys. Chem. Lett.* **2019**, *10* (16), 4744–4751.
- (50) Cliffe, M. J.; Goodwin, A. L. PASCAL: A Principal Axis Strain Calculator for Thermal Expansion and Compressibility Determination. *J. Appl. Crystallogr.* **2012**, *45* (6), 1321–1329.
- (51) Birch, F. Finite Elastic Strain of Cubic Crystals. *Phys. Rev.* **1947**, *71* (11), 809–824.
- (52) Gonzalez-Platas, J.; Alvaro, M.; Nestola, F.; Angel, R. EosFit7-GUI: A New Graphical User Interface for Equation of State Calculations, Analyses and Teaching. *J. Appl. Crystallogr.* **2016**, *49* (4), 1377–1382.
- (53) Zhang, G.-X.; Reilly, A. M.; Tkatchenko, A.; Scheffler, M. Performance of Various Density-Functional Approximations of Cohesive Properties of 64 Bulk Solids. *New J. Phys.* **2018**, *20*, No. 063020.

- (54) <https://rruff.info/all/chemistry/asc/R050632>.
- (55) Errandonea, D.; Muñoz, A.; Rodríguez-Hernández, P.; Gomis, O.; Achary, S. N.; Popescu, C.; Patwe, S. J.; Tyagi, A. K. High-Pressure Crystal Structure, Lattice Vibrations, and Band Structure of BiSbO₄. *Inorg. Chem.* **2016**, *55* (10), 4958–4969.
- (56) Urbach, F. The Long-Wavelength Edge of Photographic Sensitivity and of the Electronic Absorption of Solids. *Phys. Rev.* **1953**, *92* (5), No. 1324.
- (57) Errandonea, D.; Bandiello, E.; Segura, A.; Hamlin, J. J.; Maple, M. B.; Rodríguez-Hernández, P.; Muñoz, A. Tuning the Band Gap of PbCrO₄ through High-Pressure: Evidence of Wide-to-Narrow Semiconductor Transitions. *J. Alloys Compd.* **2014**, *587*, 14–20.
- (58) Tauc, J. Optical properties and electronic structure of amorphous Ge and Si. *Mater. Res. Bull.* **1968**, *3*, 37–46.
- (59) Garg, A. B.; Vie, D.; Rodríguez-Hernández, P.; Muñoz, A.; Segura, A.; Errandonea, D. Accurate Determination of the Bandgap Energy of the Rare-Earth Niobate Series. *J. Phys. Chem. Lett.* **2023**, *14* (7), 1762–1768.
- (60) Botella, P.; Errandonea, D.; Garg, A. B.; et al. High-pressure characterization of the optical and electronic properties of InVO₄, InNbO₄, and InTaO₄. *SN Appl. Sci.* **2019**, *1*, No. 389.
- (61) Ruiz-Fuertes, J.; López-Moreno, S.; López-Solano, J.; Errandonea, D.; Segura, A.; Lacomba-Perales, R.; Muñoz, A.; Radescu, S.; Rodríguez-Hernández, P.; Gospodinov, M.; Nagornaya, L. L.; Tu, C. Y. Pressure Effects on the Electronic and Optical Properties of AWO₄ Wolframites (A = Cd, Mg, Mn, and Zn): The Distinctive Behavior of Multiferroic MnWO₄. *Phys. Rev. B* **2012**, *86* (12), No. 125202.