



Published in final edited form as:

Biomaterials. 2007 May ; 28(15): 2438–2445.

Non-Invasive Evaluation of Alginate/Poly-L-lysine/Alginate Microcapsules by Magnetic Resonance Microscopy

Ioannis Constantinidis^{1,2,*}, Samuel C. Grant^{2,3,4,#,*}, Susanne Celper⁵, Isabel Gauffin-Holmberg⁵, Kristina Agering⁵, Jose A. Oca-Cossio¹, Jonathan D. Bui⁴, Jeremy Flint^{3,4}, Christine Hamaty¹, Nicholas E. Simpson¹, and Stephen J. Blackband^{2,3,4}

¹ Division of Endocrinology, Department of Medicine, University of Florida, Gainesville, FL, 32610

² National High Magnetic Field Laboratory, Tallahassee, FL, 32310

³ Department of Neuroscience, University of Florida, Gainesville, FL, 32610

⁴ McKnight Brain Institute, University of Florida, Gainesville, FL, 32610

⁵ Royal Institute of Technology and the Royal Karolinska Medical and Surgical Institute, Stockholm, Sweden.

Abstract

In this report, we present data to demonstrate the utility of ¹H MR microscopy to noninvasively examine alginate/poly-L-lysine/alginate (APA) microcapsules. Specifically, high-resolution images were used to visualize and quantify the poly-L-lysine (PLL) layer, and monitor temporal changes in the alginate gel microstructure during a month long *in vitro* culture. The thickness of the alginate/PLL layer was quantified to be 40.6±6.2 μm regardless of the alginate composition used to generate the beads or the time of alginate/PLL interaction (2, 6, or 20 minutes). However, there was a notable difference in the contrast of the PLL layer that depended upon the guluronic content of the alginate and the alginate/PLL interaction time. The T₂ relaxation time and the apparent diffusion coefficient (ADC) of the alginate matrix were measured periodically throughout the month long culture period. Alginate beads generated with a high guluronic content alginate demonstrated a temporal decrease in T₂ over the duration of the experiment, while ADC was unaffected. This decrease in T₂ is attributed to a reorganization of the alginate microstructure due to periodic media exchanges that mimicked a regular feeding regiment for cultured cells. In beads coated with a PLL layer, this temporal decrease in T₂ was less pronounced suggesting that the PLL layer helped maintain the integrity of the initial alginate microstructure. Conversely, alginate beads generated with a high mannuronic content alginate (with or without a PLL layer) did not display temporal changes in either T₂ or ADC. This observation suggests that the microstructure of high mannuronic content alginate beads is less susceptible to culture conditions.

Keywords

MR imaging; alginate encapsulation; poly-L-lysine

Author to whom correspondence should be addressed: Ioannis Constantinidis Division of Endocrinology Department of Medicine PO Box 100226 University of Florida Gainesville, FL, 32610-0226 consti@medicine.ufl.edu.

*Both authors have contributed equally to this study.

#Current address: Department of Chemical & Biomedical Engineering, The Florida State University & National High Magnetic Field Laboratory, Tallahassee, FL 32310.

Publisher's Disclaimer: This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final citable form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

INTRODUCTION

Evaluation of tissue engineered constructs by non-invasive imaging techniques can focus on the cellular component of the constructs - providing information critical to their function - or the biomaterials utilized in making the constructs - providing information critical to their structural integrity. Both tasks are equally important and synergistic to understanding the structure/function relationship of a construct under examination. Nuclear Magnetic Resonance (NMR) is a versatile, non-invasive modality with a range of active nuclei and contrast mechanisms that has the ability to provide both metabolic and structural information. Although the use of NMR in medical and biological research is widespread, its application to tissue engineering has been limited [1-3].

In the development of a bioartificial pancreas, most studies employing NMR techniques have focused on ^{31}P and ^1H NMR spectroscopy to investigate the correlation between cellular metabolism and insulin secretion under various environmental conditions [4-8]. One of the conclusions derived by ^1H NMR was that the resonance at 3.20 ppm, attributed to the trimethylamine protons of choline and its phosphorylated mono- and diesters, was sensitive to the overall metabolic activity of encapsulated cells maintained within a perfusion bioreactor [8]. This resonance was subsequently utilized to quantify viable cell numbers within a disk-shaped pancreatic construct both *in vitro* and *in vivo* [9,10]. Although these studies provide invaluable information on the cellular function of the construct, they do not offer insight into potential structural changes of the biomaterials utilized.

The ability to monitor the structural integrity of a tissue engineered construct either *in vitro* or *in vivo* is critical in evaluating or predicting its structural demise. This assessment is particularly important for alginate-based constructs that have been known to deteriorate with time. Alginate is a naturally occurring biopolymer that has been used extensively as a vehicle to encapsulate a variety of biological materials including enzymes and cells of both microbial and mammalian origin. However, its long-term structural integrity is questioned given the soft gelatinous nature of the material. In tissue engineering, and particularly in the development of a bioartificial pancreas, alginates have been used to encapsulate islets [11-14] and transformed β -cells [4, 15-17] with considerable success. A layer of a polycation, such as poly-L-lysine (PLL), followed by an additional layer of alginate is commonly used to coat the central alginate matrix, providing mechanical stability to the matrix [18] and at least partial immunoprotection [19].

MR imaging at microscopic resolutions ($<100\ \mu\text{m}$), commonly referred to as MR Microscopy, has been used to monitor alginate beads [20-25] immediately following encapsulation or shortly thereafter, but has not been used to track alginate beads during a long-term culture. Because changes in the T_2 relaxation time have been shown to correlate with changes in material porosity [26], we postulated that MR microscopy can be used to examine alginate/poly-L-lysine/alginate (APA) microcapsules integrity over time. In this report, ^1H MR microscopy was employed to (i) visualize and quantify the thickness of the PLL layer by taking advantage of the contrast generated by the interaction between alginate and PLL and (ii) monitor temporal changes in alginate gel microstructure by quantifying the MR properties of the alginate matrix.

METHODS

Alginate Microcapsules

Two types of alginate were used in this study (FMC BioPolymer, Drammen, Norway): (i) a high guluronic content alginate (MVG) composed of 73% guluronic acid (60% consecutive guluronic residues) and 27% mannuronic acid (manufacturer's data); and (ii) a high mannuronic content alginate (MVM) composed of 38% guluronic acid (20% consecutive guluronic

residues) and 62% mannuronic acid (manufacturer's data). All alginate solutions were prepared by dissolving powder alginate in physiological saline (0.85% NaCl) at a concentration of 2% (w/v). The presence of non-crosslinking Na⁺ ions generates a more homogeneous gel bead [27]. Alginate beads were generated with the aid of an electrostatic bead generator (Nisco, Basel, Switzerland) by crosslinking alginate with 100 mM CaCl₂. APA beads were produced based on the protocol developed by Lim and Sun [13] and modified to suit our requirements [16]. Briefly, alginate beads were washed with solutions of CaCl₂, CHES, 0.05% PLL and 0.2% alginate (of the same type as that used for the core material) to create the final APA beads at a diameter of 750±50 µm. The APA beads in this study were not treated with citrate to liquefy the central alginate core.

To assess differences in the alginate/PLL interaction, two PLL polymers were tested; one of low molecular weight (19,200 g/mol) and one of higher molecular weight (240,000 g/mol) (Sigma, St. Louis, MO). Furthermore, alginate beads were exposed to a 0.05% PLL solution for either 2, 6 or 20 minutes. Table 1 shows the various combinations of alginate composition, PLL molecular weight and interaction times examined. From the time the beads were generated to the end of the experiment, they were maintained in Dulbecco's Minimum Essential Medium (DMEM; Sigma, St. Louis, MO).

Temporal effects due to a 30 days long *in vitro* culture on alginate gel microstructure were assessed on both PLL coated and uncoated alginate beads composed of either MVG or MVM alginate. For these longitudinal experiments, alginate beads were coated with the lower molecular weight PLL using an exposure time of 6 minutes. The beads were maintained in a fashion similar to the culture of encapsulated cells; the DMEM medium was changed with fresh medium three times weekly. Because all experiments presented in this study were performed with cell-free alginate beads, temporal changes reflect the effect of frequent media switches, characteristic of *in vitro* cell culture, on the microstructure of the alginate gel without the confounding effects of cell growth and/or metabolic activity, which may contribute to these changes as well.

MR Microscopy

All MR images were acquired using a vertical 17.6-T 89-mm bore cryopumped magnet equipped with a Bruker Avance console and Micro2.5 gradients (maximum strength of 1 T/m). Three to six beads immersed in DMEM were loaded into a glass capillary (inner diameter, 1 mm) that was placed within a homebuilt solenoidal microcoil (**6 mm length, 1.7 mm in diameter**). Coupled with the high magnetic field, these small RF solenoids greatly improve the sensitivity of the NMR experiment and are susceptibility-matched to reduce magnetic field perturbations [28].

The images presented here were acquired using a gradient recall echo (GRE) sequence with averaging (NEX) = 4, echo time (TE) = 7.5, 15 and 25 ms, recovery time (TR) = 150 ms, matrix (MTX) of 512×128×128, field of view (FOV) of 6.4×1.6×1.6 mm³. Thus, an isotropic spatial resolution of 12.5 µm for each image was acquired in approximately 2.75 hrs. To assess the contribution of T₂* in the detection of the PLL layer, GRE images of high mannuronic content APA beads were collected at variable TEs (4 - 40 msec) or variable bandwidths (15,000 - 100,000 Hz). These images were obtained by holding one of the two acquisition parameters (i.e. TE and bandwidth) constant while varying the other. For these T₂* assessments, APA beads were composed of the lower molecular weight PLL and the time that the PLL solution was allowed to interact with the alginate beads was 6 mins.

MR images were also acquired using a conventional spin-echo (SE) imaging sequence that employed a bipolar read-refocusing gradient pair located after the second radio frequency pulse to minimize the effect of unintended water diffusion resulting from the read gradient [29]. To

quantify T_2 , separate images were acquired at echo times ranging from 15 to 120 ms. These T_2 -weighted images were acquired in 25.5 min/image with NEX = 4, TR = 1.5 s, MTX = 512×256 , field of view of $2.4 \times 1.2 \text{ cm}^2$ and slice thickness of $60 \mu\text{m}$. Diffusion weighted images were acquired at five diffusion weightings **using the same spin echo sequence and by** incrementing the diffusion gradient strength (b values = 195, 507, 748, 977 and 1200 s/mm^2). All other imaging parameters remained constant between images. The nominal resolution of both T_2 - and diffusion-weighted images was $47 \times 47 \times 60 \mu\text{m}^3$. Quantification of T_2 relaxation and the apparent diffusion coefficient (ADC) was performed based on a region of interest (ROI) analysis. Circular ROIs encompassing the entire bead and the center of the bead were generated and the average signal intensity over the entire ROI was measured. Based on these measurements, the T_2 relaxation time and the ADC were calculated by fitting signal intensity as a function of TE or b value respectively using a non-linear Levenberg-Marquardt regression analysis for a single decaying exponential function. The total acquisition time for quantitative imaging experiments on a single bead preparation was 6.5 hrs.

Quantification of the PLL layer

The amount of PLL deposited on the alginate matrix was quantified by measuring the concentration of the PLL solution before and after exposure to the alginate beads. Briefly, samples of the PLL solution were collected before and after exposure with alginate beads, lyophilized and dissolved in $100 \mu\text{l}$ of saline. Ten microliters of the resuspended solution were placed in different wells within a 96-well-plate, and $100 \mu\text{l}$ of a fluorescamine (Sigma, St. Louis, MO) solution (3 mg of fluorescamine per ml of DMSO) were added to each well. The microwell plate was placed in a Synergy HT plate reader (Bio-Tek, Winooski, VT) and allowed to incubate at 37°C for 20 minutes. Fluorescence was measured using an excitation filter centered at 360 nm with a bandwidth of 40 nm and an emission filter centered at 460 nm with a bandwidth of 10 nm. The values measured from our samples were compared against a calibration curve of known PLL concentrations. The amount of PLL deposited per ml of beads was calculated by subtracting the measurements before and after exposure. Thus, when small quantities of PLL are deposited on the beads, the error in this measurement is large. Each measurement was performed twice and a t-test analysis was used to determine the statistical significance of the results.

RESULTS

Visualization and Quantification of the PLL layer

Figure 1 illustrates SE images (TE = 25 and 65 ms) of four MVM beads. The bottom two beads are coated with a PLL layer (lower molecular weight PLL with 6 minutes exposure time) while the top two are not coated with PLL. The non-coated beads show a faint ring around the bead attributed to a small susceptibility (T_2^*) effect induced by the gel/media interface. The PLL coated beads show a dark circle at the periphery of the alginate matrix that clearly demarcates the beads from the surrounding medium. Compared to the signal intensity of the (a) inner bead and (b) external media, the PLL layer in Figure 1 shows a contrast enhancement of (a) $27 \pm 5\%$ and (b) $39 \pm 2\%$, respectively, for a TE = 25 ms and an enhancement of (a) $54 \pm 0.8\%$ and (b) $70 \pm 0.07\%$ for a TE = 65 ms. For reference, the periphery of the uncoated beads in Figure 1 displays a contrast enhancement of only 3.5 ± 0.8 to $4.8 \pm 8.8\%$ compared to the interior of the bead. These averages and standard deviations were determined based on $n=7$ measurements. Additionally, the thickness of the observed layer did not increase by increasing either TE or decreasing bandwidth and was the same for both SE and GRE images (data not shown). These observations suggest that the contrast generated by the PLL layer is largely due to intrinsic T_2 relaxation with a small contribution by local field inhomogeneities. Conversely, the contrast generated by the small air bubble located on the top PLL coated bead, is dominated by $T_{2>}^*$ as demonstrated by the increase in its size with increasing TE. However, it is possible that

T_2^* contribution may be underestimated given the limited number of pixels across the PLL layer.

Figure 2 shows GRE images illustrating differences in the alginate/PLL contrast as a function of the alginate composition and the exposure time between alginate beads and the PLL solution. Specifically, for alginate beads coated with the lower molecular weight PLL, the contrast due to the PLL layer increased as the interaction time between alginate and PLL increased from 2 to 6 to 20 minutes. This effect was observed for both alginate compositions examined, but it was more pronounced for beads generated with MVM alginate. However, when the high molecular weight PLL polymer was used, there were no distinguishable differences in contrast as a function of either interaction times or alginate composition. To quantify these alterations in contrast, the signal-to-noise ratio (SNR) of the PLL layer was calculated for each exposure time and echo time. For the images of Figure 2, the SNRs of the low molecular weight PLL layer MVM beads were 23 ± 0.6 , 20 ± 0.8 and 17 ± 0.1 for exposure times of 2, 6 and 20 minutes, respectively. These values correspond to a contrast enhancement relative to the minimal exposure time of 12% and 26% with the longer PLL exposures. This enhancement also is reflected in the calculated T_2^* coefficients for the low molecular weight PLL layer of the MVM beads: 21.2, 20.2 and 16.6 ms for exposures of 2, 6 and 20 minutes, respectively. By comparison, the high molecular weight PLL layer of the MVM beads of Figure 2 displayed only an average contrast enhancement relative to the minimum exposure of $2.3 \pm 1.0\%$ and T_2^* coefficient of 18.1 ms. Meanwhile, the PLL enhancement seen in the MVM beads relative to the minimum exposure improved by $3.8 \pm 0.1\%$ and $8.6 \pm 0.02\%$ with increasing exposure times while the T_2^* coefficient was calculated as 24.0, 23.3 and 22.7 ms for PLL exposures of 2, 6 and 30 minutes, respectively. Clearly, though not evident with the high molecular weight PLL, contrast enhancements could be identified and quantified for both alginates for the lower molecular weight PLL as a function of the exposure time.

In support of these images, the amount of PLL deposited on the alginate beads was quantified for the various experimental conditions examined in this study. Figure 3 shows a bar graph depicting the amount of PLL deposited per milliliter of APA beads. These data show that when the lower molecular weight PLL was used, there was a statistically significant ($p < 0.05$) increase in the amount of PLL deposited on the alginate beads with increasing time of exposure. Furthermore, the quantities of PLL deposited on MVM based beads exposed for either 6 or 20 minutes to PLL were statistically higher ($p < 0.05$) than the corresponding MVM based beads. Conversely, when the higher molecular weight PLL was used, the amount of PLL deposited on the alginate beads could not be reliably quantified regardless of exposure time or alginate composition.

Figure 4 shows a profile of the alginate/PLL thickness measured on four MVM APA beads (lower molecular weight PLL with 6 minutes exposure time) imaged with a GRE sequence and $TE = 25$ ms. Each point corresponds to a different slice through the bead, and thus, the values on the x-axis correspond to the relative location of the PLL measurement proceeding from one edge of a bead to the diametrically opposed side. The PLL thickness in each slice was measured by using a spatially defined histogram of MR signal intensity to count individual pixels in the MR microimage. Pixels were counted in the PLL thickness measurement if their signal intensity decreased by more than 20% from the signal intensity of the center of the bead. In Figure 4, the center point of the graph corresponds to the equator of the bead and represents the most accurate measurement of the PLL thickness at $40.6 \pm 6.2 \mu\text{m}$. The increased apparent thickness at each edge of the profile is attributed to the curvature of the bead and the slice thickness of the images. Despite the detected changes in contrast intensity and PLL deposited on the beads, the thickness of the PLL layer measured by MR was constant for all combinations of PLL molecular weight, exposure time and alginate composition examined. In all cases, the thickness at the equator of the bead ranged between 35-50 μm . Furthermore, the thickness of the PLL

layer did not change during the 30 days of culture, suggesting that the PLL layer is stable during this period.

Using 3D volume rendering, the PLL layer was segmented to produce 3D images of the entire bead to assess the uniformity of the PLL coat, as seen in Figure 5. The left panel shows a GRE image (a single slice from a 3D dataset acquired with TE = 25 ms) of a single APA bead (MVM alginate, lower molecular weight PLL, 6 min exposure). The panel on the right shows the 3D segmentation of the PLL shell generated from the GRE data set. The darker hue represents the PLL shell while the lighter hue represents the surrounding media. Segmentation was performed using AMIRA 3.1 (Mercury Computer Systems, Inc., Chelmsford MA). To simplify segmentation, a Gaussian filter was applied directly to the processed image dataset to enhance contrast between the internal bead and PLL layer and reduce the number of false positive points included in the rendered PLL layer. Segmentation was based on an automated selection of pixels determined by MR signal intensity thresholds (PLL layer fell between 15 and 30% of the peak signal intensity of the dataset), with nominal manual correction. The resulting image shows that there are no visible defects in the coating of the alginate beads with PLL, which underscores the continuity of this layer even at short exposure times.

Longitudinal changes in alginate NMR relaxation parameters due to long term culture

Figure 6A illustrates the temporal changes in T_2 relaxation monitored over a month for MVG based alginate beads, while Figure 6B shows the temporal changes for MVM based alginate beads. Our data show that MVG beads exhibit a decrease in T_2 relaxation time reaching a minimum value within 15 days. This decrease is markedly higher in non-PLL coated beads. In contrast, MVM beads did not exhibit an appreciable change in T_2 relaxation for either PLL coated or non-coated beads. Diffusion-weighted images did not yield statistically significant temporal changes in ADC for any of the culture combinations examined (data not shown). This observation is in agreement with previous studies reporting a lack of change in ADC as a function of alginate composition [21,22].

DISCUSSION

Visualization of the PLL layer in APA beads is not new; it was recently demonstrated with the use of fluorescent-labeled PLL and the aid of a confocal laser scanning microscope [30]. However, the MR techniques utilized in this study do not require the synthesis of fluorescent-labeled PLL. Commonly purchased PLL and standard SE and GRE MR sequences were utilized throughout this study. Our data show that T_2 - and T_2^* -weighted MR images are sensitive measures of the presence and thickness of the PLL layer. MR-based measurements of PLL thickness ranged from 35-50 μm for all combinations of PLL exposure times, PLL molecular weights and alginate compositions examined. This thickness is in agreement with data presented by Strand, *et al.* (30-50 μm for exposure times up to 30 minutes), and it is attributed to the infiltration of PLL into the alginate matrix [30]. Such PLL infiltration is also reported in the studies by de Vos, *et al.* and Tam, *et al.* [31,32]. This agreement between MR and non-MR methods further indicates that susceptibility effects do not significantly contribute to the thickness of the PLL layer in the MR images acquired under these conditions, which underscores the robust nature of the technique.

The contrast observed in either GRE or SE images is sensitive to changes in the interaction between lower molecular weight PLL and alginate beads regardless of their composition. Specifically, MVM or MVG beads displayed higher contrast (darker bead periphery) when exposed for 20 minutes than when exposed for 2 minutes. Similarly, the contrast of the PLL layer is higher (i.e. darker) in MVM beads than in corresponding MVG beads at a given exposure time. These observations were confirmed by the quantification of the PLL deposited on the beads. Thus, for the lower molecular weight PLL utilized in this study, the MR contrast

of the PLL layer and the quantity of PLL deposited onto alginate beads correlated to the guluronic content of the beads and the exposure intervals.

Previous studies describing the interaction of similarly low molecular weight PLL and alginate are contradictory. The studies by Thu, *et al.* demonstrated that the binding affinity of PLL to alginate was lower for high guluronic content alginates, suggesting that more PLL can be deposited on alginates with a high mannuronic content [33,34]. Conversely, the study by van Hoogmoed, *et al.* demonstrated that alginate capsules made with a high guluronic content alginate contained 20% more PLL than similar capsules made with an intermediate guluronic content alginate [35]. The cause of this discrepancy is not fully understood. However, a new study by Tam, *et al.* suggests that the conformation of the alginate/PLL complex depends on the strength of the interaction between the two molecules [32]. Specifically, when the interaction between alginate and PLL is weak (e.g., for high guluronic content alginates), the alginate/PLL complex has a random coil conformation. Alternatively, when the interaction between the two molecules is strong (e.g., for high mannuronic content alginates), the alginate/PLL complex has a specific helical conformation, namely an α -helix of interwoven with alginate [32]. Because the helical conformation is tighter than the random coil conformation, it will lead to more spin-spin interactions and shorten the T_2 relaxation time (i.e., darker contrast for the PLL/alginate interface). Therefore, it is possible that the difference in the contrast of the PLL layer in APA beads is attributed to the conformational differences of PLL/alginate complex and not solely to the quantity of PLL deposited on the beads.

In a similar vein, these data also demonstrate that the correlation between MR contrast and PLL exposure time on alginate does not hold for the higher molecular weight PLL utilized in the study. This is best illustrated by comparing preparations of MVG based beads. The contrast of the PLL layer on all MVG preparations is similar, regardless of the molecular weight of the PLL used to coat the beads. This observation suggests that similar quantities of PLL are deposited on these MVG beads. However, quantification of PLL showed statistically higher quantities of PLL were deposited on the beads when the lower molecular weight PLL was utilized. This is attributed to the restricted diffusion of the higher molecular weight PLL as it penetrates and interacts with alginate and it is in agreement with the study by Thu, *et al.* [33]. Therefore, MR Microscopy provides an excellent method to assess non-invasively and non-destructively the interaction and dynamics of a polycation such as PLL with anionic hydrogels such as alginate.

A key concern with the use of alginate in tissue engineered constructs is the long-term stability of the alginate gel. Given that alginate gel is formed by the ionic interaction between negatively charged alginate molecules and positively charged calcium ions (or other similarly charged cations), it is reasonable to hypothesize that calcium ions may diffuse out of the alginate matrix during a prolonged culture. This process may cause the alginate/calcium bond to weaken, resulting in a weaker gel that may dissolve or break. A recent study by Simpson *et al.* [36] demonstrated that alginates with a higher guluronic content are more susceptible to changes in Ca^{+2} ion concentration. Thus, it is reasonable to assume that the “egg-box” configuration [37] of the gelled MVG alginate will weaken with time in culture, due to the diffusion of Ca^{+2} ions, causing a collapse of the gel structure and a decrease in gel porosity. From the NMR perspective, this decrease should manifest as a decrease in T_2 values, which is indicated by the data presented in Figure 6. The fact that the observed decrease in T_2 is more pronounced in non-PLL-coated MVG beads than in PLL coated beads supports a previous study suggesting that the PLL layer hinders the transport of Ca^{+2} ions across the PLL layer [22]. Thus, the MVG gel microstructure is better maintained in PLL-coated beads than in non-coated beads.

Metabolic studies with β TC3 cells encapsulated in MVG APA beads show that encapsulated cells begin to grow after 20 days in culture, whereas β TC3 cells encapsulated in MVM grow

continuously from the onset of the culture [38]. T_2 data presented in Figure 6, show that MVG beads undergoes a gel microstructure re-organization during the first 2 weeks of culture. It is particularly interesting to note that the minimum T_2 values measured from MVG APA beads are similar to those measured from MVM beads throughout the study. These observations suggest that MVG gels re-organize during *in vitro* culture, reaching a configuration that is more conducive to cell growth. One way to prevent the re-organization of the MVG gel is to periodically wash the alginate beads in CaCl_2 as was recently demonstrated [36]. Unlike MVG alginate, MVM alginate does not experience the same change in porosity due to the weaker Ca^{+2} /alginate interaction. Consequently, the MVM microstructure does not undergo a significant re-organization over the culture period, which is consistent with the static T_2 value measured in this study.

Finally, T_2 values for MVG and MVM alginate beads measured 24 hours after encapsulation and maintained in DMEM media were compared to measurements reported previously with similar beads maintained in CaCl_2 for a day [22]. While T_2 values of MVG beads were similar in both media conditions, T_2 values for MVM beads maintained in DMEM were higher than those reported for beads maintained in CaCl_2 . This observation suggests that MVG alginate beads maintained their initial organization after 24 hours of DMEM incubation while MVM alginate beads underwent a rapid alteration during this period. This difference may be attributed to the difference swelling properties between MVG and MVM alginates. High guluronic content alginates maintain their rigid structure initially due to their strong Ca^{+2} /alginate interaction, while high mannuronic content alginates swell more readily resulting in an increase in T_2 once the presence of external CaCl_2 is removed. Notably, the swelling of the MVM alginate takes place rapidly during this first 24-hour timeframe, after which the structure of the MVM bead remains very constant during the remainder of the culture time as reflected by the T_2 measurements over the 30 day period.

CONCLUSION

In summary, we have demonstrated that MR microscopy can non-invasively and non-destructively visualize and quantify the PLL layer and monitor temporal changes in the structure of alginate beads during a prolonged culture. The data show that the thickness of the PLL layer at the periphery of alginate beads is between 35-50 μm regardless of the alginate composition or the time of exposure to the PLL solution (up to 20 minutes). The data also show that high guluronic content alginate beads undergo reorganization of their gel structure during an *in vitro* culture, while high mannuronic content alginate beads are not susceptible to such changes under similar culture conditions. It should be emphasized that the imaging techniques utilized in this study are generic and can be applied to study other hydrogels and/or other polycation layers.

ACKNOWLEDGEMENTS

The authors would like to acknowledge the financial support of the NIH through grants R01 DK56890, R01 DK47858, and P41 RR16105. All MR data were obtained at the Advanced Magnetic Resonance Imaging and Spectroscopy (AMRIS) facility in the McKnight Brain Institute of the University of Florida. Pilot funds for imaging time were provided by AMRIS and the National High Magnetic Field Laboratory.

REFERENCES

1. Constantinidis I, Sambanis A. Non-invasive monitoring of tissue engineered constructs by nuclear magnetic resonance methodologies. *Tissue Engineering* 1998;4:9–17.
2. Burg KJ, Delnomdedieu M, Beiler RJ, Culberson CR, Greene KG, Halberstadt CR, Holder WDJ, Loeb sack AB, Roland WD, Johnson GA. Application of magnetic resonance microscopy to tissue engineering: a polylactide model. *Journal Biomedical Material Research* 2002;5:380–390.

3. Neves AA, Medcalf N, Brindle K. Functional assessment of tissue-engineered meniscal cartilage by magnetic resonance imaging and spectroscopy. *Tissue Engineering* 2003;9:51–62. [PubMed: 12625954]
4. Papas KK, Long RC Jr, Constantinidis I, Sambanis A. Role of ATP and P_i on the mechanism of insulin secretion in the mouse insulinoma βTC3 cell line. *Biochemical Journal* 1997;326:807–814. [PubMed: 9307031]
5. Papas KK, Long RC Jr, Constantinidis I, Sambanis A. Development of a bioartificial pancreas: I. Long-term propagation and basal and induced secretion from entrapped βTC3 cell cultures. *Biotechnology and Bioengineering* 1999;66:219–230. [PubMed: 10578092]
6. Papas KK, Long RC Jr, Constantinidis I, Sambanis A. Development of a bioartificial pancreas: II. Effects of oxygen on long-term entrapped βTC3 cell cultures. *Biotechnology and Bioengineering* 1999;66:231–237. [PubMed: 10578093]
7. Papas KK, Long RC Jr, Sambanis A, Constantinidis I. Effects of short-term hypoxia on a bioartificial pancreatic construct. *Cell Transplantation* 2000;9:415–422. [PubMed: 10972340]
8. Long RC Jr, Papas KK, Sambanis A, Constantinidis I. In vitro monitoring of total choline levels in a bioartificial pancreas: ¹H NMR spectroscopic studies of the effects of oxygen level. *Journal of Magnetic Resonance* 2000;146:49–57. [PubMed: 10968957]
9. Stabler CL, Long RC Jr, Constantinidis I, Sambanis A. Noninvasive measurement of viable cell number in tissue engineered constructs in vitro using ¹H NMR spectroscopy. *Tissue Engineering*. 2004In press
10. Stabler CL, Long RC Jr, Constantinidis I, Sambanis A. In vivo noninvasive monitoring of viable cell number in tissue engineered constructs using ¹H NMR spectroscopy. *Cell Transplantation*. 2004In press
11. Soon-Shiong P, Feldman E, Nelson R, Heintz T, Yao Q, Yao Z, Zheng T, Merideth N, Skjak-Braek G, Espevik R, Smidsrod O, Sandford P. Long-term reversal of diabetes by the injection of immunoprotected islets. *Proc. Natl. Acad. Sci. USA* 1993;90:5843–5847. [PubMed: 8516335]
12. Reach G. Bioartificial pancreas. *Diabetic Medicine* 1993;10:105–109. [PubMed: 8458185]
13. Lim F, Sun AM. Microencapsulated islets as bioartificial endocrine pancreas. *Science* 1980;210:908–910. [PubMed: 6776628]
14. Lanza RP, Chick WL. Transplantation of encapsulated cells and tissues. *Surgery* 1997;121:1–9. [PubMed: 9001544]
15. Sambanis A, Papas KK, Flanders PC, Long RC Jr, Kang H, Constantinidis I. Towards the development of a bioartificial pancreas: Immunoisolation and NMR monitoring of mouse insulinomas. *Cytotechnology* 1994;15:351–363. [PubMed: 7765950]
16. Constantinidis I, Sambanis A. Towards the development of artificial endocrine tissues: ³¹P NMR spectroscopic studies of immunoisolated, insulin-secreting AtT-20 cells. *Biotechnology and Bioengineering* 1995;47:431–443.
17. Hicks BA, Stein R, Efrat S, Grant S, Hanahan D, Demetriou AA. Transplantation of β cells from transgenic mice into nude athymic diabetic rats restores glucose regulation. *Diabetes Res. Clin. Pract* 1991;14:157–164. [PubMed: 1778108]
18. Benson JP, Papas KK, Constantinidis I, Sambanis A. Towards the development of a bioartificial pancreas: effects of poly-L-lysine on alginate beads with βTC3 cells. *Cell Transplantation* 1997;6:395–402. [PubMed: 9258513]
19. Lanza RP, Chick WL. Immunoisolation: at a turning point. *Immunol. Today* 1997;18:135–139. [PubMed: 9078686]
20. Duez JM, Mestdagh M, Demeure R, Goudemant JF, Hills BP, Godward J. NMR studies of calcium-induced alginate gelation. Part I - MRI tests of gelation models. *Magnetic Resonance in Chemistry* 2000;38:324–330.
21. Hills BP, Godward J, Debatty M, Barras L, Saturio CP, Ouwerx C. NMR studies of calcium induced alginate gelation. Part II. The internal bead structure. *Magnetic Resonance in Chemistry* 2000;38:719–728.
22. Simpson NE, Grant SC, Blackband SJ, Constantinidis I. NMR properties of alginate microbeads. *Biomaterials* 2003;24:4941–4948. [PubMed: 14559007]

23. Emmerichs N, Wingender J, Flemming H-C, Mayer C. Interaction between alginates and manganese cations: identification of preferred cation binding sites. *International Journal of Biological Macromolecules* 2004;34:73–79. [PubMed: 15178012]
24. Manz B, Hillgartner M, Zimmermann H, Zimmermann D, Volke F, Zimmermann U. Cross-linking properties of alginate gels determined by using advanced NMR imaging and Cu(2+) as contrast agent. *European Biophysics Journal* 2004;33:50–58. [PubMed: 13680210]
25. Thu B, Gaserod O, Paus D, Mikkelsen A, Skjak-Braek G, Toffanin R, Vittur F, Rizzo R. Inhomogeneous alginate gel spheres: An assessment of the polymer gradients by synchrotron radiation-induced x-ray emission, magnetic resonance microimaging, and mathematical modeling. *Biopolymers* 2000;53:60–71. [PubMed: 10644951]
26. As HV, Lens P. Use of 1H NMR to study transport processes in porous biosystems. *J. Ind. Microbiol. Biotechnol* 2001;26:43–52.
27. Skjak-Braek G, Grasdale H, Smidsrod O. Inhomogeneous polysaccharide ionic gels. *Carbohydrate Polymer* 1989;10:31–54.
28. Webb AG, Grant SC. Signal-to-noise and magnetic susceptibility trade-offs in solenoidal microcoils for NMR. *Journal Magnetic Resonance B* 1996;113:83–87.
29. Hsu EW, Schoeniger JS, Bowtell R, Aiken NR, Horsman A, Blackband SJ. A modified imaging sequence for accurate T2 measurements using NMR microscopy. *Journal Magnetic Resonance B* 1995;109:66–69.
30. Strand BL, Yrr AM, Espevik T, Skjak-Braek G. Visualization of alginate-poly-L-lysine-alginate microcapsules by confocal laser scanning microscopy. *Biotechnology and Bioengineering* 2003;82:386–394. [PubMed: 12632394]
31. de Vos P, van Hoogmoed CG, Busscher HJ. Chemistry and biocompatibility of alginate-PLL capsules for immunoprotection of mammalian cells. *Journal of Biomedical Materials Research* 2002;60:252–259. [PubMed: 11857431]
32. Tam SK, Dusseault J, Polizu S, Menard M, Halle JP, Yahia L. Physicochemical model of alginate-poly-L-lysine microcapsules defined at the micrometric/nanometric scale using ATR-FTIR, XPS, and ToF-SIMS. *Biomaterials* 2005;26:6950–6961. [PubMed: 15975648]
33. Thu B, Bruheim P, Espevik T, Smidsrod O, Soon-Shiong P, Skjak-Braek G. Alginate polycation microcapsules. I. Interaction between alginate and polycation. *Biomaterials* 1996;17:1031–1040. [PubMed: 8736740]
34. Thu B, Bruheim P, Espevik T, Smidsrod O, Soon-Shiong P, Skjak-Braek G. Alginate polycation microcapsules. II. Some functional properties. *Biomaterials* 1996;17:1069–1079. [PubMed: 8718966]
35. van Hoogmoed CG, Busscher HJ, de Vos P. Fourier transform infrared spectroscopy studies of alginate-PLL capsules with varying compositions. *Journal of Biomedical Materials Research* 2003;67A:172–178. [PubMed: 14517874]
36. Simpson NE, Stabler CL, Sambanis A, Constantinidis I. The role of the CaCl₂-guluronic acid interaction on alginate encapsulated βTC3 cells. *Biomaterials* 2004;25:2603–2610. [PubMed: 14751746]
37. Grant GT, Morris ER, Rees DA, Smith PJC, Thom D. Biological interactions between polysaccharides and divalent cations: The egg-box model. *FEBS Letters* 1973;32:195–198.
38. Stabler C, Wilks K, Sambanis A, Constantinidis I. The effects of alginate composition on encapsulated βTC3 cells. *Biomaterials* 2001;22:1301–1310. [PubMed: 11336302]

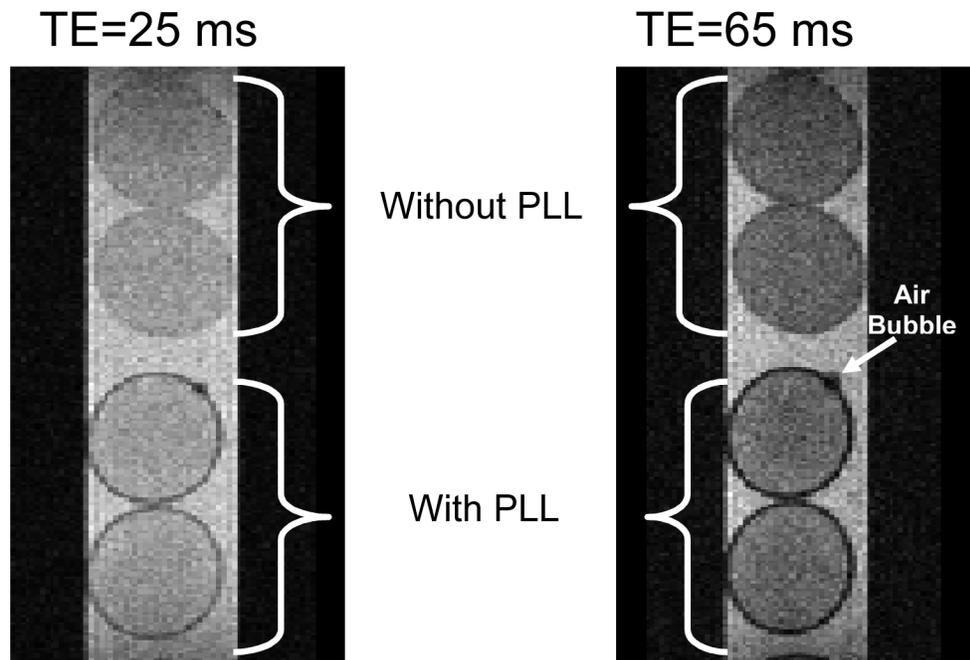


FIGURE 1. Spin echo MR microimages of MVM alginate beads with and without PLL coating (6 minute exposure to low molecular weight PLL) at two different echo times. Note that the dark circle around the alginate beads coated with PLL does not significantly change in size with longer TE – unlike the air bubble (white arrow)

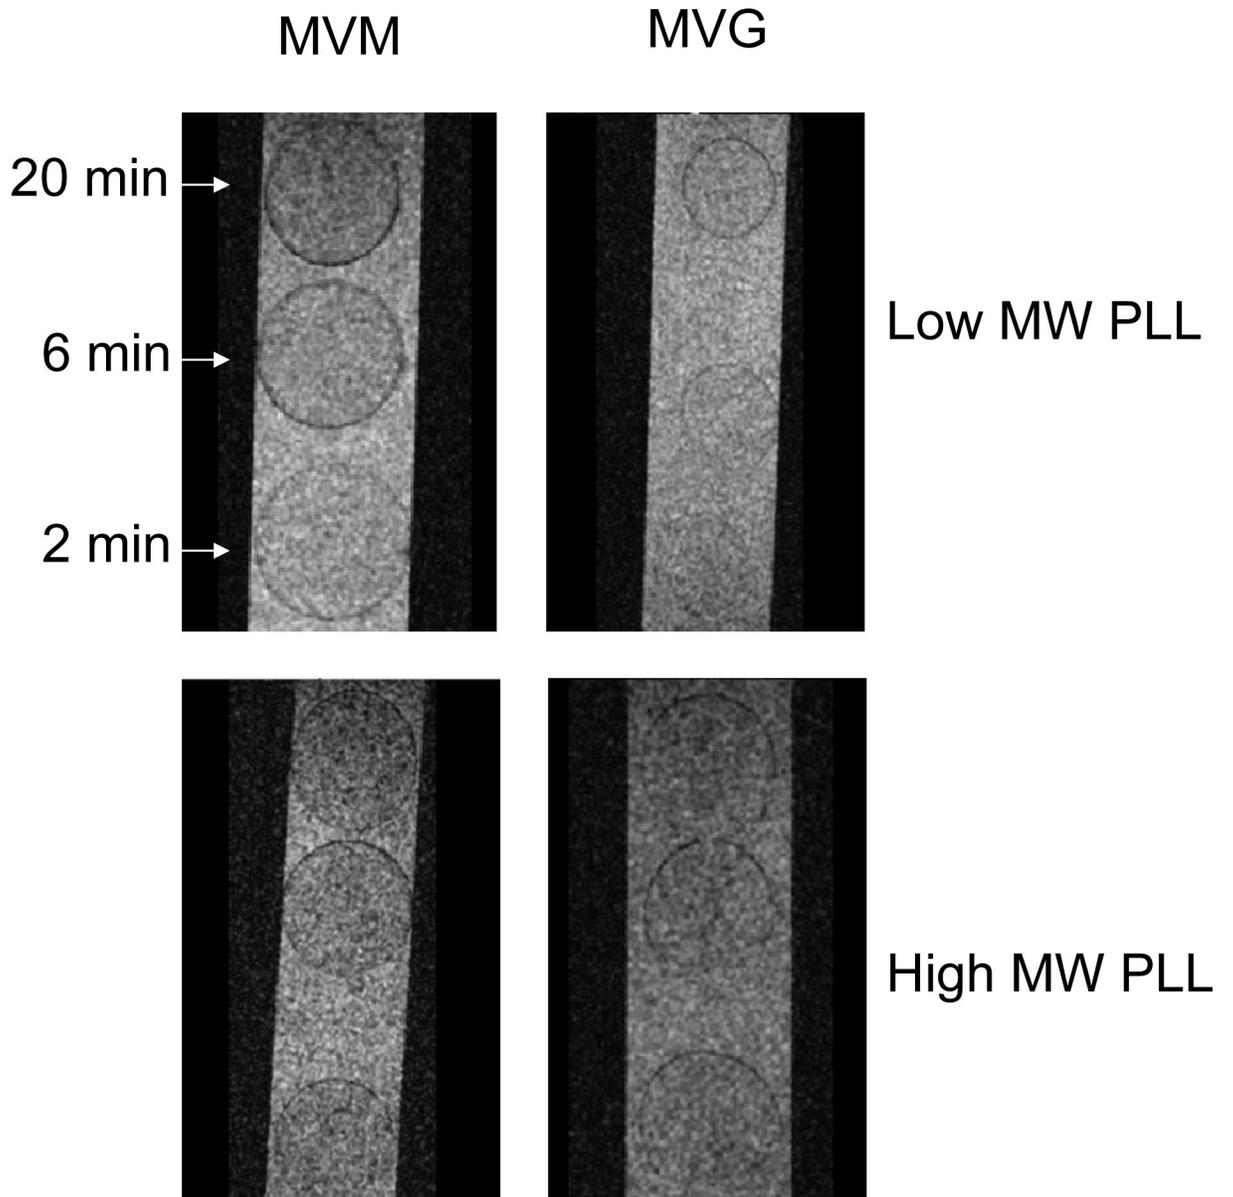


FIGURE 2. GRE MR microimages of MVM APA beads showing the intensity of the PLL layer as a function of alginate composition and interaction time. The isotropic resolution of these images is 12.5 μm .

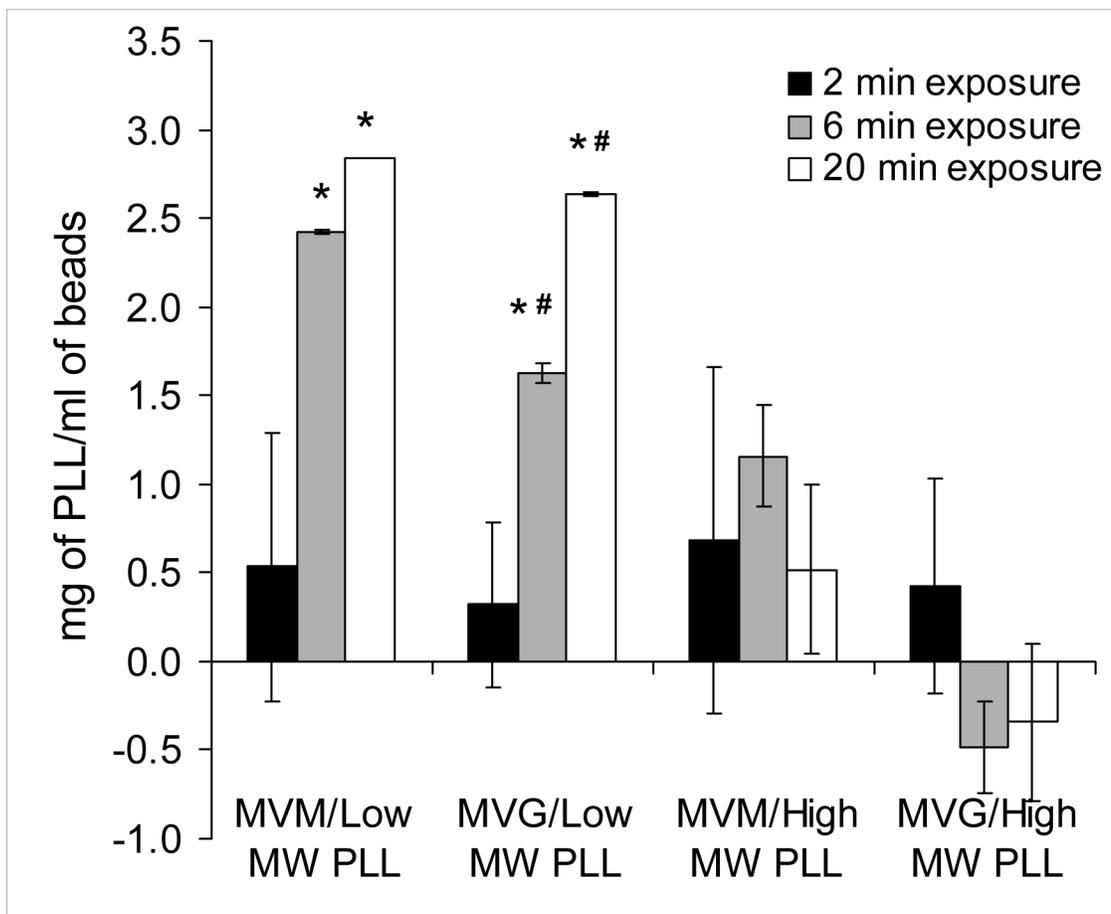


FIGURE 3.

A bar graph depicting the amount of PLL deposited per milliliter of alginate beads. Solid black, grey and white bars represent measurements based on 2, 6 and 20 minutes of exposure respectively between the various alginate and PLL combinations. Each bar is the average of duplicate measurements within the same experiment. This experiment was repeated three times with consistent results. An (*) indicates statistically significant differences ($P < 0.05$) between the 6 or 20 minute exposures and to the corresponding alginate exposed for 2 minute to PLL. A (#) indicates statistically significant differences ($P < 0.05$) between MVM and MVG alginates at the corresponding time exposures to PLL.

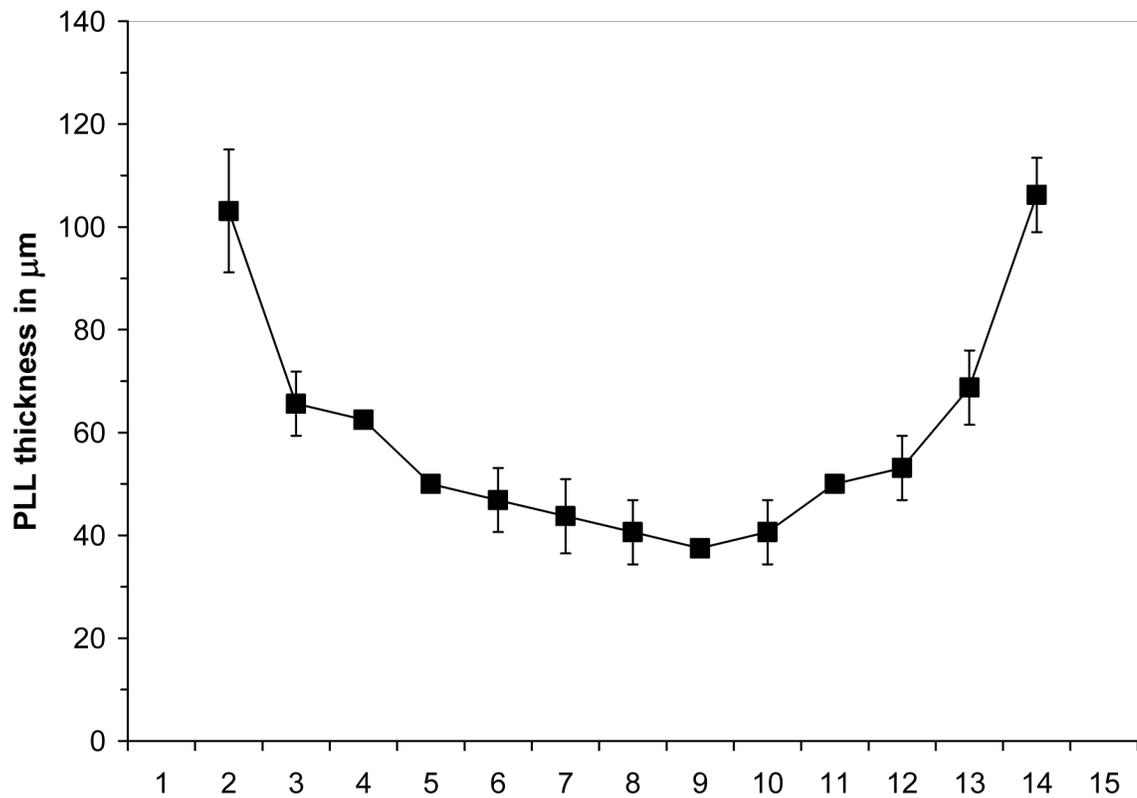


FIGURE 4.

A profile of PLL layer thickness measurements performed on MVM beads coated with the lower molecular weight PLL following a 6 minute exposure. The beads were imaged with a GRE sequence and a TE = 25 ms. The x-axis represents arbitrary slice numbers with effective thickness of 50 μm . The error bars represent the standard deviation of the mean based on four measurements.

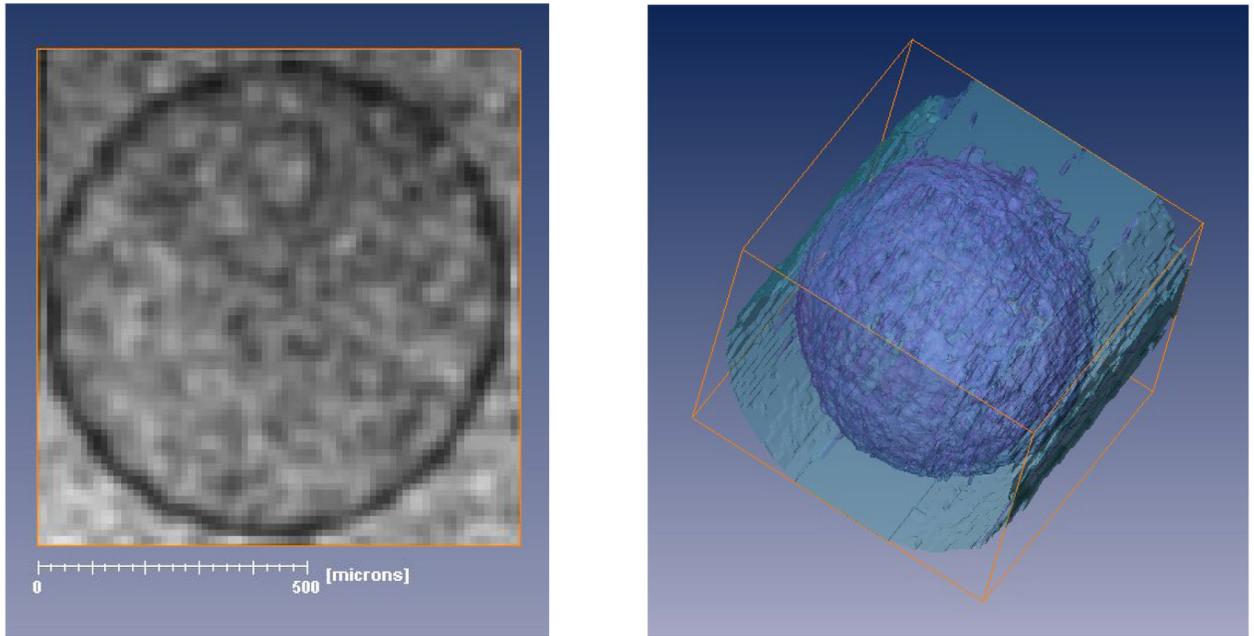
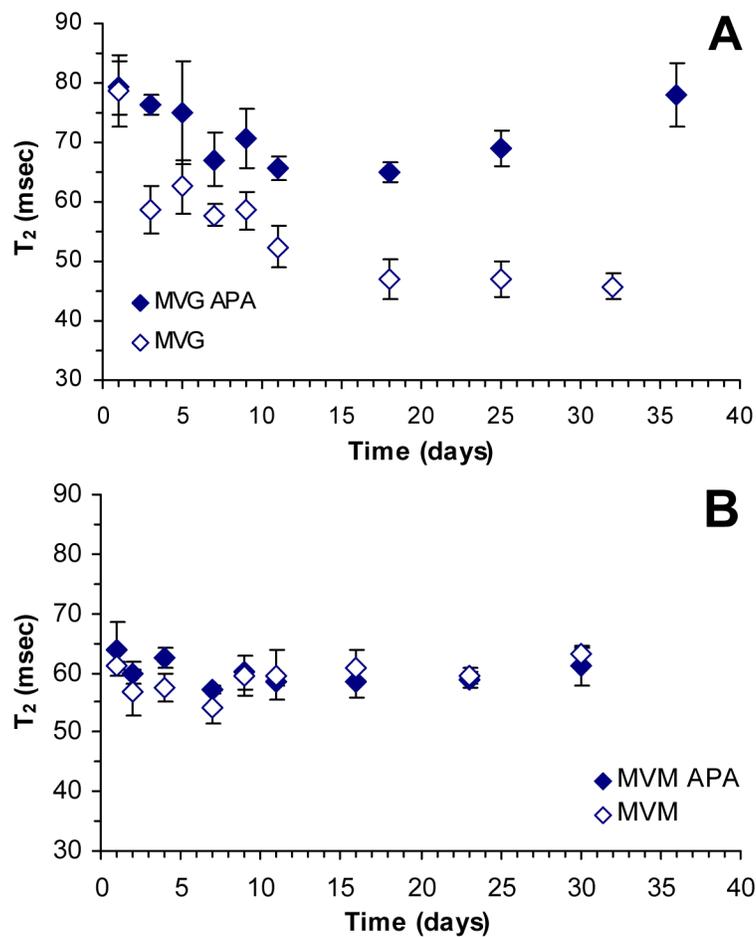


FIGURE 5.

The MR image on the left shows a single slice from a 3D GRE dataset with a TE = 25 ms of a single MVM alginate bead coated with the lower molecular weight PLL following a 6 minute exposure. The dark contrast generated by the PLL layer has been segmented in the 3D rendering shown on the right. The darker hue of the 3D rendering represents the PLL shell while the lighter hue represents the surrounding media. Segmentation was performed based on pixel intensity values. Although a 3D Gaussian filter was applied to the image for the purpose of segmentation, the acquisition voxel size in the 3D dataset was $12.5 \times 12.5 \times 12.5 \mu\text{m}^3$.

**FIGURE 6.**

A: Temporal changes in the T₂ relaxation time of MVG alginate beads. Solid diamonds represent data acquired from MVG APA beads and open diamonds represent data acquired from MVG beads that were not coated with PLL. B: Temporal changes in the T₂ relaxation time of MVM alginate beads. Solid diamonds represent data acquired from MVM APA beads and open diamonds represent data acquired from MVM beads that were not coated with PLL. The error bars represent the standard deviation of the T₂ relaxation measurement.

TABLE 1

Combinations of alginate composition, PLL molecular weight and time of interaction between alginate and PLL examined

Alginate Type	MVM						MVG					
	Low (19,200)			High (240,000)			Low (19,200)			High (240,000)		
Molecular Weight of PLL (Daltons)												
Exposure Time (minutes)	2	6	20	2	6	20	2	6	20	2	6	20