



Published in final edited form as:

Bioorg Med Chem. 2008 March 1; 16(5): 2412–2418.

Glyconanobiotics: Novel carbohydrate nanoparticle antibiotics for MRSA and *Bacillus anthracis*

Sampath C. Abeylath^a, Edward Turos^{a*}, Sonja Dickey^b, and Daniel V. Limb^b

^aCenter for Molecular Diversity in Drug Design, Discovery, and Delivery, Department of Chemistry, CHE 205, 4202 East Fowler Avenue, University of South Florida, Tampa, FL 33620, USA

^bDepartment of Biology, 4202 East Fowler Avenue, University of South Florida, Tampa, FL 33620, USA

Abstract

This report describes the synthesis and evaluation of glycosylated polyacrylate nanoparticles that have covalently-bound antibiotics within their framework. The requisite glycosylated drug monomers were prepared from one of three known antibiotics, an *N*-sec-butylthio β -lactam, ciprofloxacin, and a penicillin, by acylation with 3-*O*-acryloyl-1,2-*O*-isopropylidene-5,6 bis((chlorosuccinyl)oxy)-D-glucofuranose (**7**) or 6-*O*-acetyl-3-*O*-acryloyl-1,2-*O*-isopropylidene-5-(chlorosuccinyl)oxy- α -D-glucofuranose (**10**). These acrylated monomers were subjected to emulsion polymerization in a 7:3 (w:w) mixture of butyl acrylate-styrene in the presence of sodium dodecyl sulfate as surfactant (3 weight %) and potassium persulfate as a radical initiator (1 weight %). The resulting nanoparticle emulsions were characterized by dynamic light scattering and found to have similar diameters (~40 nm) and size distributions to those of our previously studied systems. Microbiological testing showed that the *N*-sec-butylthio β -lactam and ciprofloxacin nanoparticles both have powerful *in vitro* activities against methicillin-resistant *Staphylococcus aureus* and *Bacillus anthracis*, while the penicillin-bound nanoparticles have no antimicrobial activity. This indicates the need for matching a suitable antibiotic with the nanoparticle carrier. Overall, the study shows that even relatively large, polar acrylate monomers (MW>1000 amu) can be efficiently incorporated into the nanoparticle matrix by emulsion polymerization, providing opportunities for further advances in nanomedicine.

Keywords

carbohydrates; emulsion polymerization; nanoparticle; MRSA; anthrax; drug delivery

1. Introduction

Recent advances in biotechnology have accelerated the discovery of new drug molecules. However, many of these compounds suffer from sensitivity to degradative processes in the blood, or have limited water solubility that provides for minimal dissolution in the gastrointestinal tract and low bioavailability. There has been a renewed effort to find strategies for protecting and delivering such drugs, including the use of liposomes and various nanoparticles. These drug delivery vehicles improve bioavailability, efficacy, and specificity of some pharmaceutical compounds.^{1,2} Recently, our laboratory has investigated the

*Corresponding author. Tel.: +1 813 974 7312; fax: +1 813 974 1733; E-mail address: eturos@cas.usf.edu (E. Turos).

Publisher's Disclaimer: This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final citable form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

properties of polyacrylate emulsions that contain nanoparticles measuring 30–50 nm in diameter, and onto which an antibiotic molecule can be covalently attached.³

These nanoparticles can be prepared easily in water by radical-induced emulsion polymerization using an acrylated derivative of the antibiotic as a co-monomer in a warmed mixture of butyl acrylate and styrene. Sodium dodecyl sulfate (3 weight %) and sodium persulfate (1 weight %) are used as surfactant and radical initiator, respectively. The resulting emulsions are stable indefinitely up to at least 80°C. Also by extending this emulsion polymerization procedure, we established that penicillin-containing polyacrylate nanoparticles can be easily prepared and are effective at rejuvenating the *in vitro* antibacterial activity of penicillin drugs against β -lactamase-producing microbes such as methicillin-resistant *Staphylococcus aureus* (MRSA).⁴ More recently, we described the application of this polymerization methodology to the synthesis of carbohydrated poly(ethyl acrylate) nanoparticles which contain a variety of *O*-protected and even unprotected monosaccharides within the polymeric framework.⁵ These carbohydrated nanoparticles appear to be the first examples of polymeric glyconanoparticles reported in the literature, and required that relatively bulky, water-soluble glycosylated acrylates be used as monomers in the emulsion polymerization process. Glycosylated nanoparticles have been employed to study carbohydrate interactions in the field of chemical glycobiology, but their potential in drug delivery is relatively unexplored particularly in the context of antibacterials research.⁶ Consequently, a number of issues regarding this capability need to be better investigated, and the first thing we wanted to explore was whether the glycosylated nanoparticles could be made to have antibacterial activity. Thus, the goal of the present work was to adapt our previous studies on antibiotic-conjugated nanoparticles and carbohydrated nanoparticles to construct an amalgamated system we refer to as *glyconanoparticle antibiotics*, or *glyconanobiotics* for short, and to evaluate their *in vitro* antibacterial capabilities against two dangerous pathogenic microbes, MRSA and *B. anthracis*. A graphic of what this nanoparticle is comprised of is depicted in Scheme 1. Secondly, we also were interested in whether the relatively large monomeric acrylates required for the formation of these nanoparticles could even be successfully employed, since this would then signal the potential use of other surrogates needed for biomedical applications. At the outset of this study, it was not obvious that this could in fact be achieved, since until now only small (MW<250) lipophilic monomers have been successfully introduced as polyacrylates by emulsion polymerization. Therefore, our study is focused on three representative antibiotic agents having entirely different biological modes of action, an *N*-thiolated β -lactam, a fluoroquinolone, and a penicillin. To prepare the nanoparticles (designated **NP1–3**), it was necessary to first convert each of the antibiotics to their glycosylated monomers **1–3**, where the critical acrylate moiety is located at the 3' center of the furanose ring (Fig. 1). Acrylate monomer **1** contains two appended *N*-thiolated β -lactams, while monomers **2** and **3** bear a single ciprofloxacin or 6-aminopenicillanic acid moiety, respectively. The latter acrylate was used as a control, since our prior investigation on penicillin-bound nanoparticles identified it as being devoid of antibacterial activity against MRSA, with a broth minimum inhibitory concentration of >256 $\mu\text{g/mL}$.⁴

2. Results and discussion

To construct acrylates **1–3**, it was first necessary to synthesize the two acyl chlorides **7** and **10** from the protected glucofuranose **4** as shown in Scheme 2. Subsequently, the antibiotics were attached by direct acylation according to the procedures described below.

2.1. Synthesis of acyl chlorides **7** and **10**

3-*O*-acryloyl-1,2-*O*-isopropylidene-5,6-bis((chlorosuccinyl)oxy)-*D*-glucofuranose (**7**) and 6-*O*-acetyl-3-*O*-acryloyl-1,2-*O*-isopropylidene-5-(chlorosuccinyl)oxy- α -*D*-glucofuranose (**10**)

were both synthesized from 1,2:5,6-di-*O*-isopropylidene- α -D-glucofuranose-3-acrylate (**4**) as shown in Scheme 2. Partial deacetonation of **4** with 80% acetic acid at 80°C afforded product **5** in 62% isolated yield. Diol **5** was diacylated with succinic anhydride in the presence of Et₃N in CH₂Cl₂ to give di-acid **6** in 65% yield. Thionyl chloride was used to convert compound **6** to the corresponding di-acyl chloride **7** in 98% yield. Acyl chloride **10** was obtained similarly by selective acylation⁷ of the primary hydroxyl group of diol **5** with acetyl chloride in dichloromethane in the presence of 2,4,6-collidine at -40°C to afford compound **8** in 72% yield. Following succinic acid acylation of alcohol **8** to afford carboxylic acid **9**, conversion to the mono-acyl chloride **10** with thionyl chloride proceeded in 65% yield for the two steps. A significant feature revealed in this synthesis is the stability of the endo-cyclic acetonide of the monosaccharide during the reaction of thionyl chloride (generation of HCl).

2.2. Synthesis of antibiotic-conjugated acrylates 1–3

With the two key acyl chlorides in hand, we evaluated their use for acylating the three selected antibiotic drugs to prepare monomers **1–3** (Scheme 3–Scheme 5). *N*-Thiolated β -lactams discovered in our group are a new family of antibacterial agents active against *Staphylococcus* bacteria, including methicillin-resistant strains of *Staphylococcus aureus* (MRSA)^{8,9}, and *Bacillus anthracis*¹⁰ which is the causative agent of anthrax infections. For the goal of preparing glyconanoparticle variants of this class of antibacterial agents, bis-*N*-thiolated β -lactam glucose acrylate **1** was prepared. Monomer **1** was synthesized in 62% yield from *N*-*sec*-butylthio β -lactam derivative **11**¹¹ by coupling with di-acyl chloride **7** and Et₃N in CH₂Cl₂ (Scheme 3). As it was expected that similar ciprofloxacin and bis-penicillin glucose acrylates would be less lipophilic due to the presence of their carboxylic acid moieties, which in turn could cause problems in the emulsion polymerization due to poor solubility in the butyl acrylate-styrene mixture, we decided to instead try to prepare the mono-antibiotic acrylate forms. Monociprofloxacin acrylate **2** was successfully synthesized in 56% yield from ciprofloxacin by coupling with acyl chloride **10** and Et₃N in CH₂Cl₂ (Scheme 4) whereas the mono-penicillin acrylate **3** was synthesized⁴ in 51% yield from 6-aminopenicillanic acid (**13**) via its trimethylsilyl ester **14**, which was then reacted with acyl chloride **10** (Scheme 5). The structures of the carbohydrate monomers **1** and **2** were determined by ¹H and ¹³C NMR, and mass spectrometry.¹²

2.3 Preparation of glyconanobiotics

The carbohydrate-conjugated antibiotic monomers (**1–3**) prepared from *N*-*sec*-butylthio β -lactam, ciprofloxacin, and 6-aminopenicillanic acid were found to be readily soluble in a warm 7:3 (w:w) mixture of butyl acrylate and styrene, and undergo emulsion polymerization with ease using the prescribed protocol. In this way, the nanoparticles bearing one of the three antibiotics could be prepared by emulsion polymerization of antibiotic monomers **1–3** (2 weight %) in a 7:3 (w:w) blend of butyl acrylate-styrene, upon stirring in water for 6 hours at 70°C. Sodium dodecyl sulfate (3 weight %) and potassium persulfate (1 weight %) were used as surfactant and radical initiator, respectively. Dynamic light scattering (DLS) analysis of the final emulsion revealed that the average diameter of the glyconanoparticles is uniformly about 40 nm with narrow size distributions spanning only from about 30–50 nm, as has been previously reported for similar polyacrylate nanoparticles.⁴

2.4 Biological activity

The glycosylated nanoparticle antibiotics **NP1–3** were evaluated for *in vitro* antibacterial activity against three pathogenic bacteria, namely *Staphylococcus aureus*, a strain of methicillin-resistant *Staphylococcus aureus* (MRSA), and *Bacillus anthracis*. Additionally, the acrylated monomers **1–3** were also examined for comparison. Activity was assessed by determining the minimum inhibitory concentration (MIC) values by broth serial dilution, and

is summarized in Table 1. The concentration of antibiotic in the nanoparticle was assumed to be equivalent to that used for the polymerization, as expressed in μg of drug per mL of undiluted emulsion. The results show that the glyconanoparticles containing *N*-thiolated β -lactam and ciprofloxacin exhibited significant antibacterial activity, while the penicillin-bound glyconanoparticles and non-drug containing nanoparticles made of just butyl acrylate-styrene (7:3) (controls) were completely inactive against these microbes, with MIC values of $>256 \mu\text{g}/\text{mL}$. The bioactivities are similar to or better than that of the corresponding drug monomers. The finding that the *N*-thiolated β -lactam and cipro nanoparticles are active, while the penicillin variant is not, suggests that the type of antibiotic and the comparative activity of the free drug being released (presumably by ester or amide cleavage) are both critical. Our laboratories' attempts to measure the rate of drug release from the nanoparticles has not yet been successful, and are ongoing, as are experiments to identify the mechanism of how these nanoparticle antibiotics may exert their effects on bacterial cells.

3. Experimental

Solvents and chemicals were purchased from Acros Organics and used without further purification. 1,2:5,6-Di-*O*-isopropylidene- α -D-glucofuranose-3-acrylate (**4**)¹³ was prepared following the cited literature procedure. ¹H NMR and ¹³C NMR spectra were recorded on Bruker DPX-250 and Varian Inova 400 spectrometers. Mass spectra were obtained with on an ESI LC MS system (Agilent Technologies).

3.1 Synthesis

3.1.1 Synthesis of 3-*O*-acryloyl-1,2-*O*-isopropylidene-5,6 bis((chlorosuccinyl)oxy)-D-glucofuranose (7)—1,2:5,6-Di-*O*-isopropylidene- α -D-glucofuranose-3-acrylate (**4**) (0.5g, 1.59 mmol) was dissolved in 4 mL of 80% acetic acid and stirred 4 hours at 80°C. The solvents were removed *in vacuo* and the residue was purified by column chromatography (silica gel, hexane-EtOAc, 1:1) to afford compound **5** (0.32 g, 62%) as a syrup. This monoacetonide product (0.3g, 1.09 mmol) and succinic anhydride (0.65g, 6.54 mmol) were stirred with Et₃N (0.76 mL, 5.45 mmol) in CH₂Cl₂ (10 mL) at rt for 5h. The reaction mixture was washed with 5% KHSO₄, then water. The organic layer was dried over Na₂SO₄, filtered and evaporated to dryness. The brown oil obtained was chromatographed on silica gel (EtOAc) and a solid material was obtained that contained ammonium salt and succinic acid, which could easily be removed by centrifugation in 10 mL of CH₂Cl₂. After evaporation, compound **6** (0.34g, 65%) was obtained as a colorless syrup. This di-acid (0.3g, 0.80 mmol) was dissolved in 3 mL of thionyl chloride, stirred 45 min. at room temperature, and the solvents were removed *in vacuo* to afford compound **7** (0.31g, 98%) as a syrup. ¹H NMR (400 MHz, CDCl₃): δ 6.39 (m, 1H), 6.04 (m, 1H), 5.87 (m, 2H), 5.28 (m, 2H), 4.50 (m, 3H), 4.17 (m, 1H), 3.13 (m, 4H), 2.62 (m, 4H) 1.48 (s, 3H), 1.27 (s, 3H); ¹³C NMR (100 MHz, CDCl₃): δ 173.2, 172.9, 171.0, 170.1, 169.8, 165.7, 164.7, 132.5, 127.5, 112.8, 105.3, 83.3, 76.6, 75.2, 68.5, 63.8, 41.8, 29.3, 28.6, 26.9.

3.1.2 Synthesis of 6-*O*-acetyl-3-*O*-acryloyl-1,2-*O*-isopropylidene-5-(chlorosuccinyl)oxy- α -D-glucofuranose (10)—3-*O*-acryloyl-1,2-*O*-isopropylidene- α -D-glucofuranoside (**5**) (0.4 g, 1.52 mmol) was dissolved in 10 mL of CH₂Cl₂ and cooled to -40 °C. Collidine (0.36 g, 3.04 mmol) was added to the solution, then acetyl chloride (0.14g, 1.82 mmol), and the mixture was stirred at -40 °C for 3 h and at rt for an additional hour. The mixture was washed with water and extracted into CH₂Cl₂ (3 \times 25 mL). The solvents were evaporated and the residue was purified by column chromatography to afford compound **8** (0.33 g, 72 %) as a syrup. This intermediate product (0.3 g, 0.98 mmol) and succinic anhydride (0.29 g, 2.96 mmol) were stirred with Et₃N (0.34 mL, 2.45mmol) in CH₂Cl₂ (10 mL) at rt for 5h. The reaction mixture was washed with 5% KHSO₄, then water. The organic layer was dried

over Na₂SO₄, filtered and evaporated to dryness. The brown oil obtained was chromatographed on silica gel (EtOAc), and a solid material was obtained that contained ammonium salt and succinic acid, which could easily be removed by centrifugation in 10 mL of CH₂Cl₂. After evaporation, compound **9** (0.26 g, 65%) was obtained as a syrup. Subsequently, this acid was dissolved in 3 mL of thionyl chloride, stirred 45 min. at room temperature, and the solvents were removed *in vacuo* to afford compound **10** (0.34 g, 98%) as a syrup. ¹H NMR (400 MHz, CDCl₃): δ 6.35 (d, 1H, *J*=17.2 Hz), 6.04 (dd, 1H, *J*=10.4, 17.2 Hz), 5.87 (m, 2H), 5.33 (d, 1H, *J*=2.8 Hz), 5.17 (m, 1H), 4.52 (m, 3H), 4.08 (dd, 1H, *J*=5.6, 12.4 Hz), 3.10 (m, 3H), 2.57 (m, 3H), 2.00 (s, 3H), 1.49 (s, 3H), 1.27 (s, 3H); ¹³C NMR (100 MHz, CDCl₃): δ 172.8, 170.8, 169.8, 164.8, 132.7, 127.3, 112.7, 105.3, 83.3, 76.8, 75.2, 68.6, 63.2, 41.7, 29.4, 28.6, 26.3, 20.8.

3.1.3 Synthesis of bis-*N*-sec-butylthio β-lactam acrylate (1**)**—To a stirred solution of *N*-sec-butylthio β-lactam derivative **11**¹¹ (0.2 g, 0.7 mmol) and triethylamine (0.29 mL, 2.1 mmol) in CH₂Cl₂ (5 mL) at 0 °C was added dropwise diacyl chloride **7** (0.173g, 0.42 mmol in 0.5 mL of CH₂Cl₂). The solution was stirred at rt for 10 h, then treated with water (10 mL) and extracted with CH₂Cl₂ (3×15 mL). The combined organic layers were washed with water (2×50 mL), dried (MgSO₄) and evaporated under reduced pressure. The residue was purified by column chromatography (hexane-EtOAc, 2:1) to afford compound **1** (0.22 g, 62%) as a syrup. ¹H NMR (400 MHz, CDCl₃): δ 7.35 (m, 8H), 6.35 (d, 1H, *J*=17.2 Hz), 6.14 (m, 2H), 6.03 (dd, 1H, *J*=10.8, 17.6 Hz), 5.84 (m, 2H), 5.47 (m, 2H), 5.25 (s, 1H), 5.09 (m, 1H), 4.45 (m, 2H), 4.33 (m, 1H), 4.05 (m, 1H), 3.04 (m, 2H), 2.17 (m, 8H), 1.56 (m, 4H), 1.47 (s, 3H), 1.26 (m, 9H), 0.96 (m, 6H); ¹³C NMR (100 MHz, CDCl₃): δ 171.2, 170.3, 169.8, 169.0, 164.7, 134.6, 123.6, 130.7, 130.1, 130.0, 128.9, 127.3, 126.9, 112.7, 105.3, 83.3, 75.3, 68.0, 63.7, 63.6, 48.6, 28.5, 28.3, 26.9, 26.4, 19.2, 18.9, 11.3. ESI-MS calcd for [M+NH₄]⁺, 1028.0; found, 1028.3.

3.1.4 Synthesis of ciprofloxacin acrylate (2**)**—To a stirred solution of ciprofloxacin hydrochloride (0.2g, 0.6 mmol) and triethylamine (0.5 mL, 3.6 mmol) in CH₂Cl₂ (8 mL) at 0 °C was added dropwise acyl chloride **10** (0.31g, 0.66 mmol in 0.5 mL of CH₂Cl₂). The solution was stirred at rt for 10 h then treated with water (10 mL) and extracted with CH₂Cl₂ (3×15 mL). The combined organic layers were washed with water (2×50 mL), dried (MgSO₄) and evaporated under reduced pressure. The residue was purified by column chromatography (EtOAc) to afford compound **2** (0.23 g, 56%) as a syrup. ¹H NMR (400 MHz, CDCl₃): δ 8.64 (s, 1H), 7.90 (d, 1H, *J*=12.4 Hz), 7.32 (d, 1H, *J*=6.8 Hz), 6.39 (d, 1H, *J*=17.2 Hz), 6.05 (dd, 1H, *J*=10.4, 17.2 Hz), 5.88 (d, 1H, *J*=3.6 Hz), 5.86 (d, 1H, *J*=10.4 Hz), 5.32 (d, 1H, *J*=2.8 Hz), 5.24(m, 1H), 4.52(m, 3H), 4.12 (dd, 1H, *J*=5.2, 12.0 Hz), 3.79(m, 2H), 3.68(m, 2H), 3.53(m, 1H), 3.33(m, 2H), 3.25(m, 2H), 2.59(m, 4H), 2.02(s, 3H), 1.49(s, 3H), 1.37(m, 2H), 1.27(s, 3H), 1.18(m, 2H); ¹³C NMR (100 MHz, CDCl₃): δ 177.1, 171.8, 170.8, 169.6, 166.9, 164.8, 155.0, 152.5, 147.6, 145.6, 145.5, 139.1, 132.3, 127.7, 120.2, 112.7, 112.4, 108.2, 105.3, 105.2, 83.3, 75.5, 68.0, 63.3, 53.6, 50.2, 49.5, 45.2, 41.5, 35.5, 29.4, 28.1, 26.9, 26.4, 20.9, 8.4. ESI-MS calcd for [M+Na]⁺, 752.6; found, 752.2.

3.1.5 Synthesis of 6-aminopenicillanic acid acrylate (3**)¹²**—6-Aminopenicillanic acid (2 g, 0.924 mmol) and *N,O*-bis(trimethylsilyl)acetamide (0.21 g, 1.02 mmol) were added to CH₂Cl₂ (10 mL) and stirred at rt overnight. Triethylamine (0.19 mL, 1.38 mmol) was added and cooled on ice. Acyl chloride **10** (0.52 g, 1.11 mmol in 0.5 mL of CH₂Cl₂) was added dropwise and stirred at room temperature for 10 h. The reaction mixture was treated with water (10 mL) and extracted into CH₂Cl₂ (3×15 mL). The combined organic layers were washed with water (2×50 mL), dried (MgSO₄) and evaporated under reduced pressure. The residue was purified by column chromatography (EtOAc) to afford compound **3**¹² (0.23 g, 56%) as a syrup. ¹H NMR (400 MHz, CDCl₃): δ 6.55 (d, 1H, *J*=8.8 Hz), 6.39 (d, 1H, *J*=17.2 Hz), 6.02

(m, 1H), 5.88 (m, 2H), 5.63 (dd, 1H, $J=4.0, 8.8$ Hz), 5.48 (d, 1H, $J=4.0$ Hz), 5.31 (m, 1H), 5.19 (m, 1H), 4.48 (m, 3H), 4.04 (m, 1H), 2.55 (m, 4H), 2.01 (s, 3H), 1.62 (s, 3H), 1.54 (s, 3H), 1.48 (s, 3H), 1.27 (s, 3H).

3.2 Emulsion polymerization

The general procedure is as previously reported.^{3,4} The drug monomer (2 weight %) was pre-dissolved in a 7:3 (w:w) mixture of butyl acrylate-styrene, and sodium dodecyl sulfate in purified water was added to pre-emulsify the mixture with stirring under a nitrogen atmosphere. The amounts of each component added to the mixture are given in Table 2. The polymerized nanoparticles were prepared by adding potassium persulfate to a rapidly stirred (magnetic stirrer) mixture at 70°C for 6 hours, at which time heating and stirring were stopped and the sample could be transferred to a vial for storage or biological testing.

3.3 Dynamic light scattering analysis

Sample size and distribution of the emulsions was examined by dynamic light scattering using a UPA 150 Honeywell MicroTrac DLS instrument equipped with a laser beam at 780 nm. The sample was pre-diluted with deionized distilled water (0.05 mL of emulsion in 9.95 mL of water, polymer concentration 0.1% wt) and sonicated for 3 minutes for the analysis. The value is expressed in weight-averaged scales as unimode at a scattering angle of 180° (backscatter) at a temperature of 25 °C.

4. Conclusions

In summary, these studies have demonstrated the preparation and *in vitro* evaluation of polyacrylate glyconanoparticles that bear a covalently-attached antibiotic. With this methodology, even large monomers (MW > 1000 amu) can be efficiently incorporated into the polyacrylate nanoparticle matrix up to 2 weight % of the total solid content. The antibiotic-conjugated acrylate monomers needed for the polymerization are readily prepared by a simple one-step procedure, from acylation of the antibiotic with the corresponding carbohydrate acyl chloride. These structurally-complex acrylate drug monomers show excellent solubility in the butyl acrylate-styrene mixture required for radical-induced emulsion polymerization in aqueous media. The resulting nanoparticles measure around 40 nm in diameter according to dynamic light scattering experiments, with narrow size distributions (30–50 nm), and possess equivalent or improved *in vitro* antibacterial activity to that of the corresponding acrylated antibiotic monomer. Further investigations in our laboratory are attempting to fully assess the underlying reasons for antibiotic effects of these nanoparticles, including how, where and at what rate the drug is being released, and their *in vivo* properties as potential treatment of life-threatening bacterial infections.

Acknowledgements

We sincerely thank Gil Brubaker (University of Florida Particle Engineering Research Center) for providing assistance with the particle analyses, and generous financial support from the National Institutes of Health (Grant AI05135) and National Science Foundation (NSF 0620572).

References

1. Alle'mann E, Gurny R, Doelker E. Eur. J. Pharm. Biopharm 1993;39:173–191.
2. Couvreur P, Dubernet C, Puisieux F. Eur. J. Pharm. Biopharm 1995;41:2–13.
3. Turos E, Shim YJ, Wang Y, Greenhalgh K, Reddy GSK, Dickey S, Lim DV. Bioorg. Med. Chem. Lett 2007;17:53–56. [PubMed: 17049850]
4. Turos E, Reddy GSK, Greenhalgh K, Ramaraju P, Abeylath SC, Jang S, Dickey S, Lim DV. Bioorg. Med. Chem. Lett 2007;17:3468–3472. [PubMed: 17420125]

5. Abeylath SC, Turos E. *Carbohydr. Polymer* 2007;70:32–37.
6. Fuente JM, Penadés S. *Biochim. Biophys. Acta* 2006;1760:636–651. [PubMed: 16529864]
7. Ishihara K, Kurihara H, Yamamoto H. *J. Org. Chem* 1993;58:3791–3793.
8. Turos E, Konaklieva MI, Ren RXF, Shi H, Gonzalez J, Dickey S, Lim D. *Tetrahedron* 2002;56:5571–5578.
9. Turos E, Long TE, Konaklieva MI, Coates C, Shim JY, Dickey S, Lim DV, Cannons A. *Bioorg. Med. Chem. Lett* 2002;12:2229–2231. [PubMed: 12127544]
10. Turos E, Long TE, Heldreth B, Leslie JM, Reddy SK, Wang Y, Coates C, Konaklieva M, Dickey S, Lim DV, Alonso E, Gonzalez J. *Bioorg. Med. Chem. Lett* 2006;16:2084–2090. [PubMed: 16473509]
11. Heldreth B, Long TE, Jang S, Reddy SK, Turos E, Dickey S, Lim DV. *Bioorg. Med. Chem* 2006;14:3773–3784.
12. A small amount of carboxylic acid **9** mixed with penicillin acrylate **3** showed up in the ^1H NMR spectrum after eluting with ethyl acetate, and this mixture was used for the emulsion polymerization as a mixture.
13. Krishna PR, Kannan V, Ilangovan A, Sharma GVM. *Tetrahedron: Asymmetry* 2001;12:829–837.



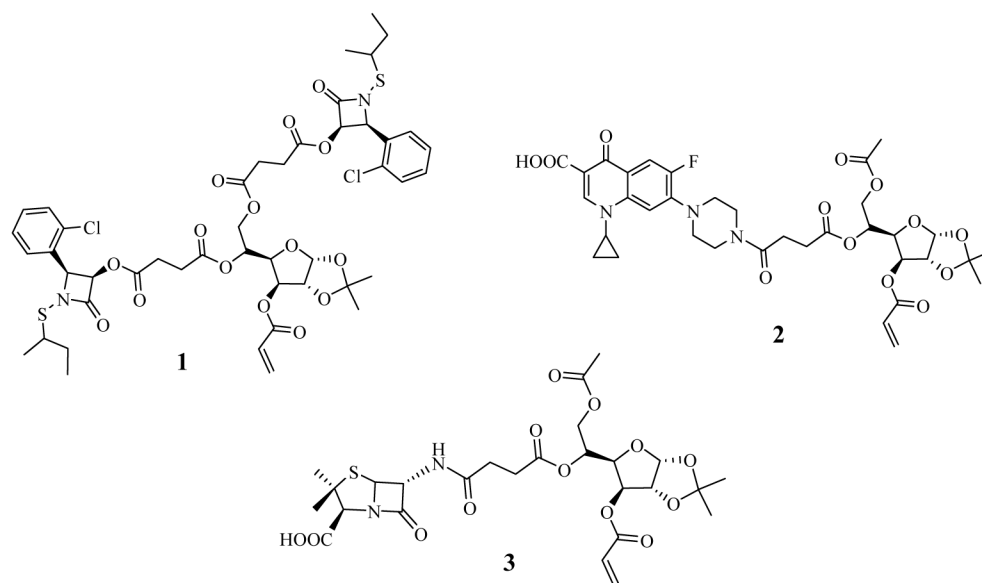



Figure 1. Glycosylated antibiotic acrylates used for the formation of glyconanobiotics: bis-*N*-sec-butylthio β -lactam acrylate (**1**), ciprofloxacin acrylate (**2**), 6-aminopenicillanic acid acrylate (**3**).

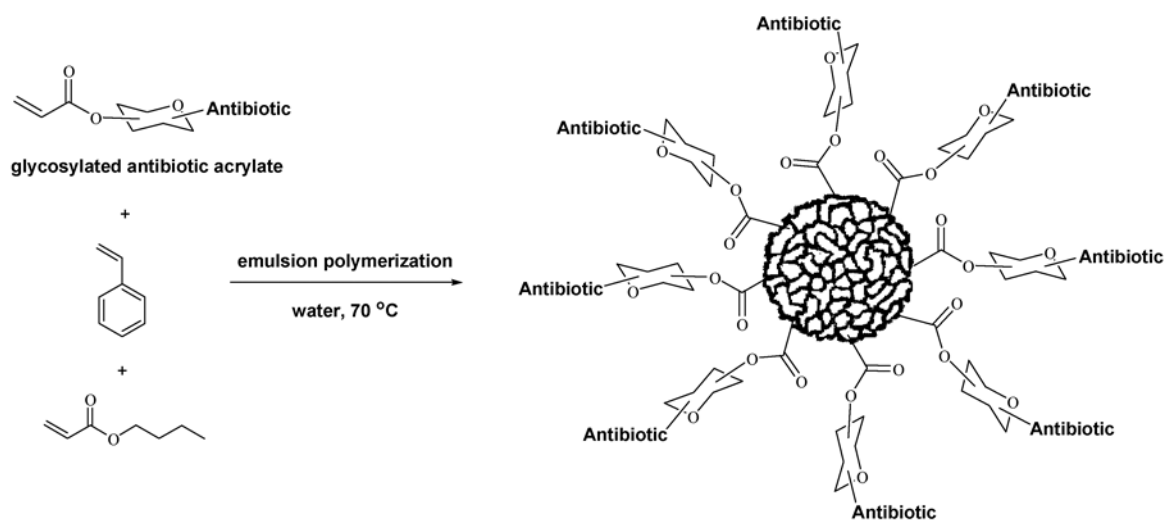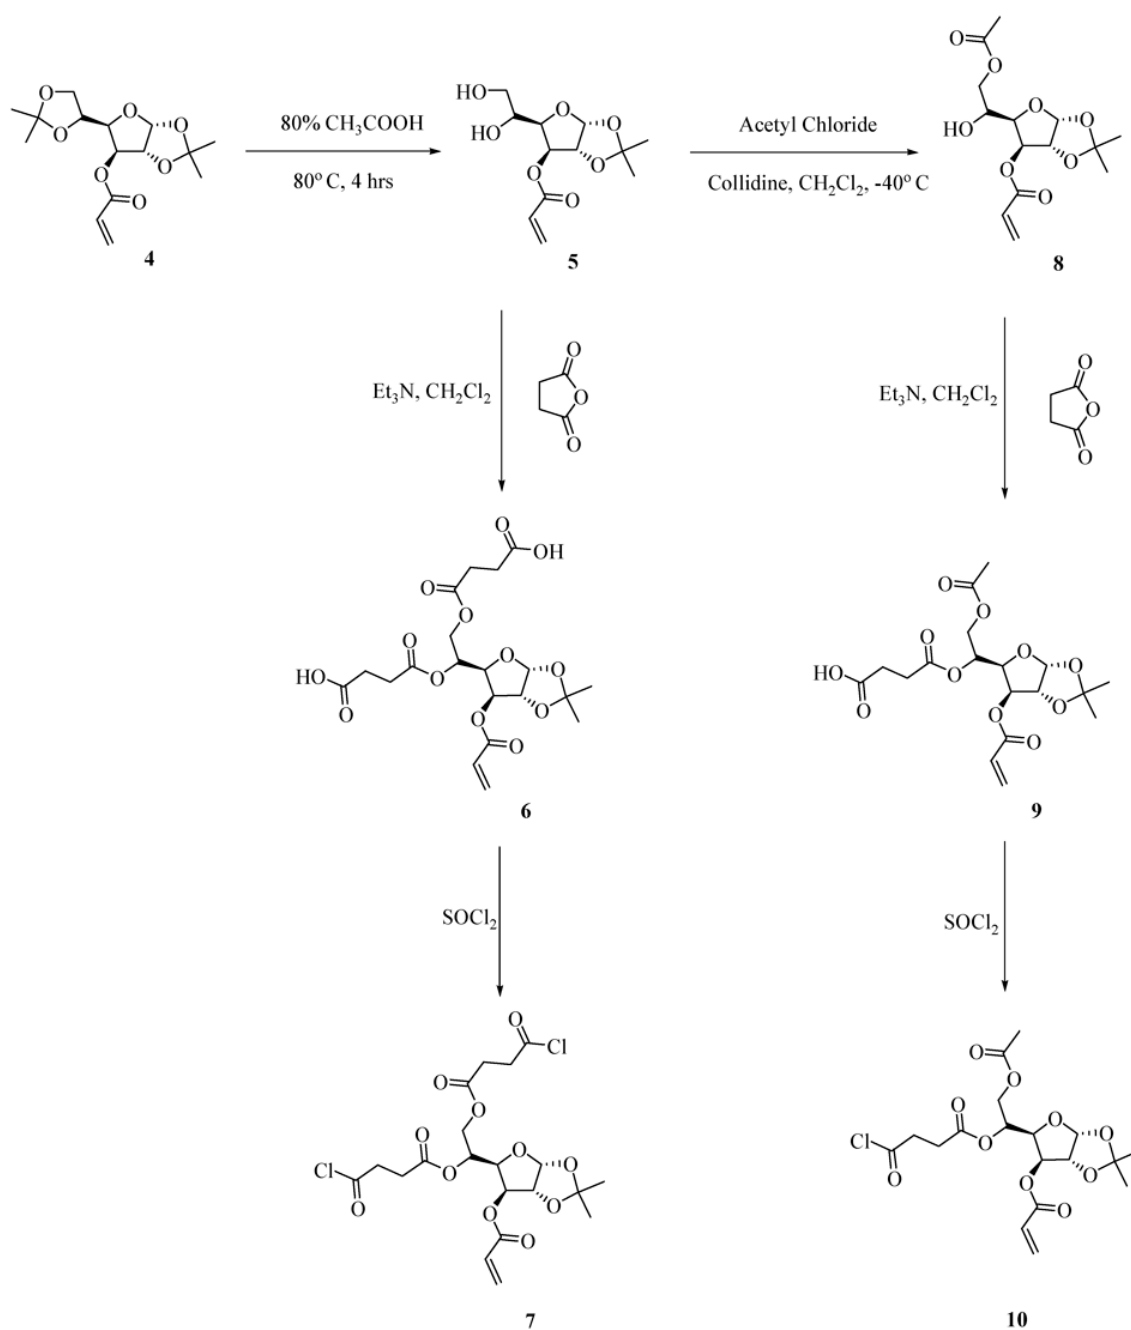


Scheme 1.
Synthesis of glyconanobiotics by emulsion polymerization

**Scheme 2.**


Synthesis of 3-*O*-acryloyl-1,2-*O*-isopropylidene-5,6 bis((chlorosuccinyl)oxy)-*D*-glucufuranose (**7**) and 6-*O*-acetyl-3-*O*-acryloyl-1,2-*O*-isopropylidene-5-(chlorosuccinyl)oxy- α -*D*-glucufuranose (**10**).

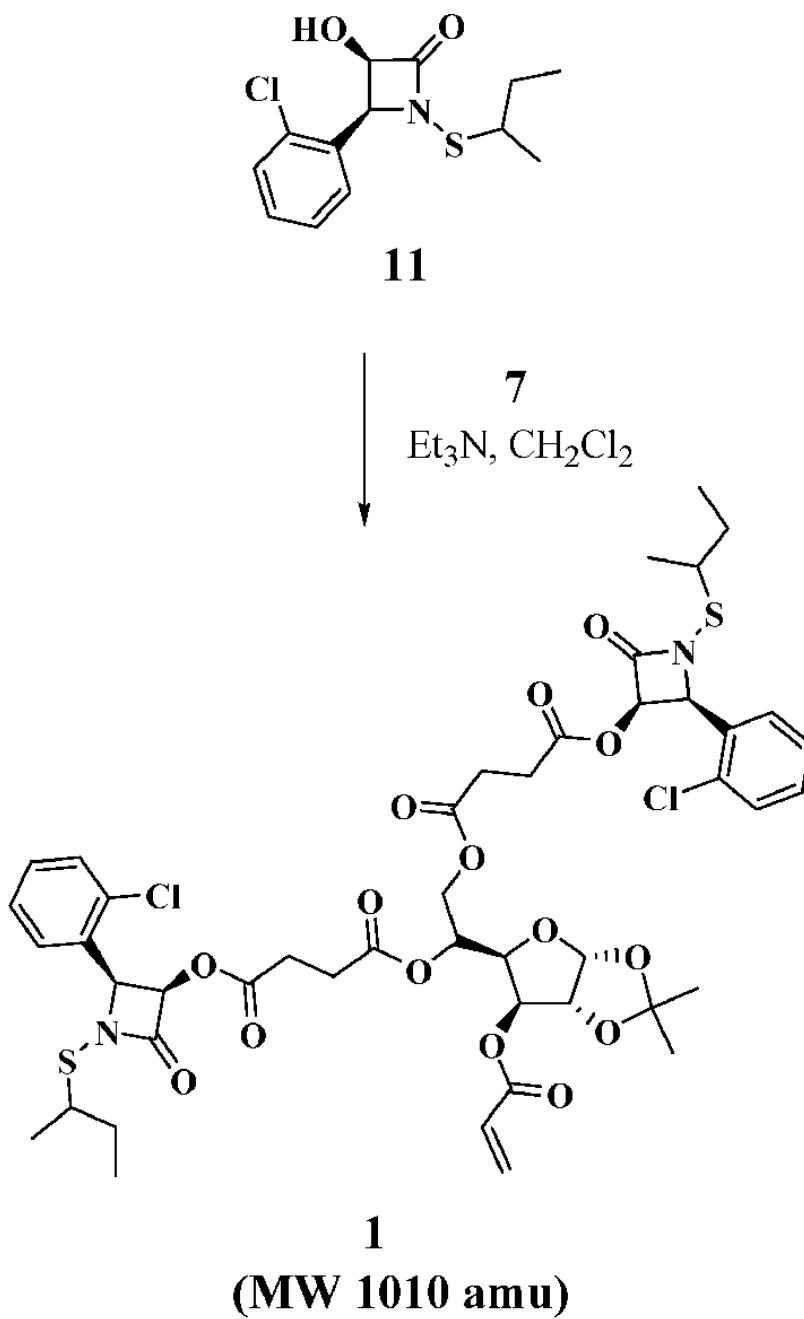

Scheme 3.
Synthesis of bis-*N-sec*-butylthio β-lactam acrylate (**1**)

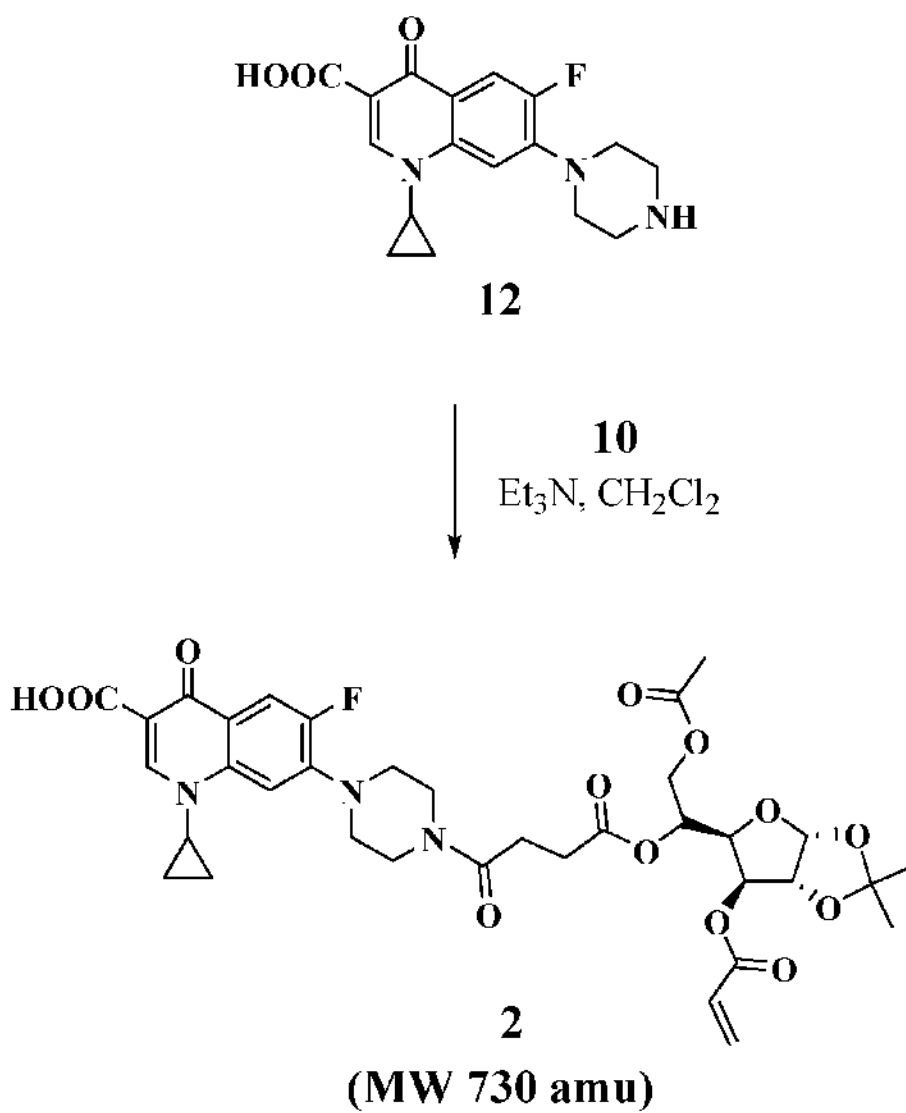

Scheme 4.
Synthesis of ciprofloxacin acrylate (**2**).

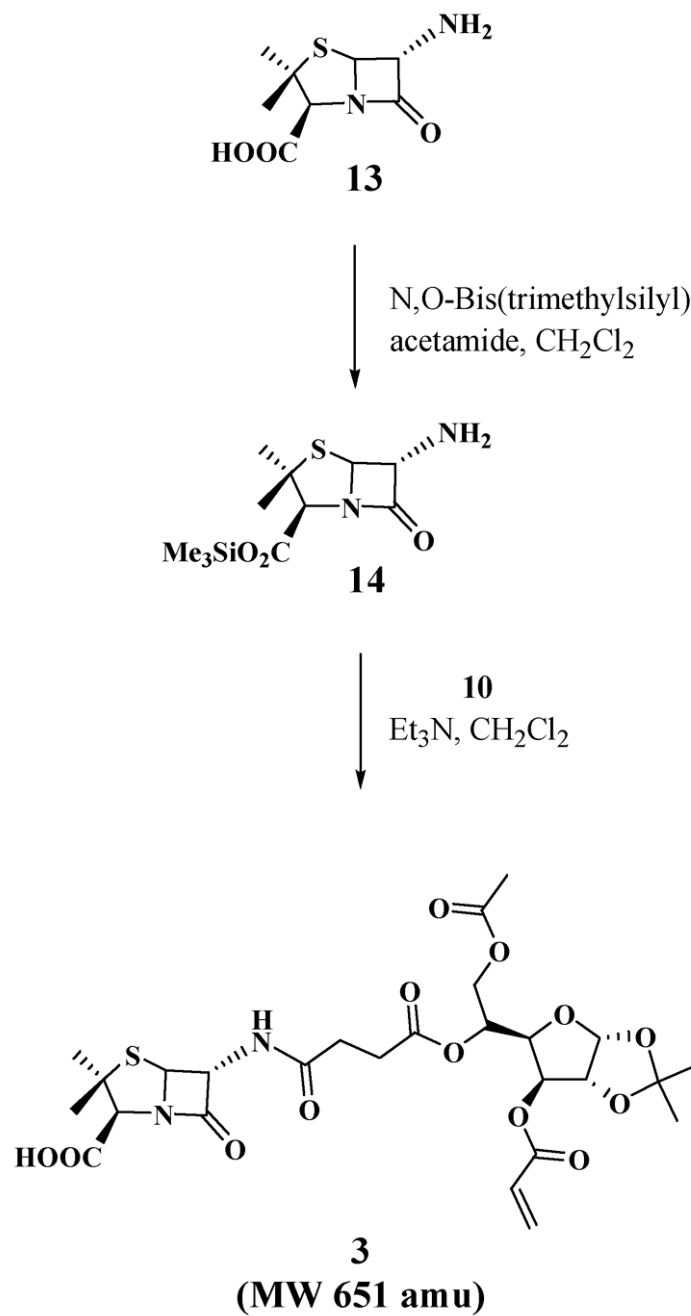

Scheme 5.
Synthesis of 6-aminopenicillanic acid acrylate (3).

Table 1

Antibacterial activity of glycosylated monomers **1–3** and their nanoparticle emulsions **NP 1–3** against *Staphylococcus aureus* (ATCC 25923), MRSA (ATCC 43300) and *Bacillus anthracis*, as determined by broth dilution MIC assays^a

Sample	Microbe		
	<i>S. aureus</i> (µg/mL)	MRSA (µg/mL)	<i>B. anthracis</i> (µg/mL)
Penicillin G (control)	0.012	16	n/a
Lactam monomer 1	128	128	64
Lactam NP 1	64	64	64
Cipro monomer 2	32	32	16
Cipro NP 2	32	32	16
Penicillin monomer 3	>256	>256	>256
Penicillin NP 3	>256	>256	>256

^a MIC values refer to the lowest concentration of the bound drug (µg/mL) required to completely inhibit bacterial growth for 24 h in culture.

Table 2
Formulation parameters used for emulsion polymerization

Components	Amounts	Solid Content
Drug monomer	20 mg	2%
Butyl acrylate	658 mg	66%
Styrene	282 mg	28%
Sodium dodecyl sulfate	30 mg	3%
Potassium persulfate	10 mg	1%
Water	4 mL	