

NIH Public Access

Author Manuscript

Org Lett. Author manuscript; available in PMC 2008 October 2

Published in final edited form as:


Org Lett. 2007 May 24; 9(11): 2051–2054. doi:10.1021/ol062949h.

Monofunctionalization of Dendrimers Using Microwave–Assisted 1,3 Dipolar Cycloadditions

Kunsang Yoon, Poorva Goyal, and Marcus Weck*

School of Chemistry and Biochemistry, Georgia Institute of Technology, Atlanta, GA 30332-0400

Abstract

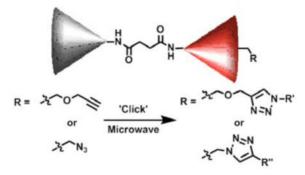

Monofunctionalized polyamide-based dendrimers containing either a terminal azide or alkyne moiety have been designed and synthesized *via* a convergent synthetic approach. The monofunctionalization allows for the single attachment of a functional moiety in quantitative yields using 1,3 dipolar cycloadditions thereby opening the possibility for targeted dendrimer functionalization.

Dendrimers are important materials for biological applications as a result of their unique features such as the precise control of size and shape, uncommon physical properties, and the placement of numerous functional groups on the periphery and/or core.¹ Polyamide-based dendrimers are of particular interest because they are based solely on a peptide like amide backbone and have demonstrated low toxicities and non-immunogenicities.² Accordingly, polyamide- and polyamidoamine-based dendrimers have been used extensively as biomaterials in gene and drug delivery³ and for nanoparticle encapsulation⁴ in imaging.⁵ Although dendrimers containing a single functionality have been reported,⁶ few of these examples are using the important polyamide backbone. Furthermore, one desired property that has not been realized to date for dendrimers is the possibility to monofunctionalize them selectively in quantitative yields thereby allowing for the single attachment of biological specific targeting and recognition moieties onto the dendrimer surface. Such a strategy would allow for the transportation of the dendrimer to the biological target of interest via a specific binding process and the targeted delivery of drugs or imaging moieties. The main prerequisite for such a functionalization is that the chemical handle for the attachment has to be high yielding and chemoselective. Furthermore, the transformation of choice must allow for the reaction to take place under physiological conditions. One chemical transformation that fulfills these requirements is the 1,3-dipolar cycloaddition between an azide and an alkyne.^{7,8} Herein, we present the first synthesis of polyamide-based dendrimers that contain a single alkyne or azide group on the dendrimer surface and can be monofunctionalized via 1,3 dipolar cycloaddition chemistry in quantitative yields.⁹

marcus.weck@chemistry.gatech.edu.

Our research design is based on the convergent synthetic approach and some recent building block developments by the Newkome group.¹⁰ Newkome and coworkers reported the syntheses of the nonfunctionalized dendrons **C** and **D** shown in Figure 1 (building block **C** is also known as Behera's amine).¹¹ Furthermore, they introduced $1 \rightarrow (2+1)$ *C*-branching monomers and monofunctionalized dendron monomers that are ideal for our purpose to prepare monofunctionalized dendrimers with peptide like amide backbones and a single chemoselective handle (Figure 1).

The key building block in our design that will introduce the single functionality onto the dendrimer surface, monomer **3**, was prepared by a Michael type addition using 6-nitrohexanol¹² and an excess of *t*-butyl acrylate in the presence of Triton-B to provide monomer **1** in 55% yield (Scheme 1) followed by the protection of the hydroxyl group with Ac₂O in pyridine and the catalytic reduction of the nitro group under 60 psi of hydrogen in EtOH. The quantitative reduction of the nitro group to the corresponding amine was supported by the chemical shift (¹³C NMR) for the nitro-carbon from 92.8 ppm to 52.5 ppm, respectively. Other building blocks (**A**, **C**, and **D**) were prepared as reported by Newkome and coworkers. 10, 11

With the basic building blocks in hand, we prepared the second generation of the monofunctionalized dendrons via the selective deprotection of the *tert*-butyl groups of **A** followed by the amidation coupling with two equivalents of **C** (Scheme 2) to afford compound **4** in 87% isolated yield. After the deprotection of the benzyl ester group using Pd/C under 60 psi of hydrogen at room temperature for 12 h, subsequent amidation reaction of the monoacid species with **3** yielded **5** in 93% yield. The nitro group reduction of **5** with Raney-Ni at 55 °C for 24 h under 60 psi of hydrogen provided the desired second generation dendron **6** in 98% yield which was identified by the chemical shift change for C^4 moiety from 92.5 ppm to 52.6 ppm as well as the molecular ion peak (HRMS MALDI-TOF) at m/z 1439.9455 [M + H]⁺. The overall yield of dendron **6** from its building blocks was 72%.

Scheme 3 outlines the synthesis of the monofunctionalized dendrimers **10** and **11** containing the single chemical handle. The synthesis commences with the stepwise incorporation of **D** and **6** onto the core molecule. The treatment of **D** with succinic anhydride in pyridine afforded the half shell of dendrimer **7** with an acid moiety at the core. Dendron **6** was then coupled onto the core using DCC and 1-HOBT to provide the protected monofunctionalized dendrimer **8** in 84% yield. Deprotection using K_2CO_3 in a mixture of MeOH and H_2O (10:1) at room temperature for 2 h provided the hydroxyl dendrimer **9** in 92% yield.

For our purposes, both acetylene and azide were introduced onto the dendrimer at the hydroxyl moiety. Dendrimer **9** was treated with propargyl bromide in the presence of Cs_2CO_3 in DMF at 80 °C for three days to afford the desired acetylenic dendrimer **10** in 83% isolated yield. The transformation was demonstrated by the observation of a new ¹H NMR signal at 2.54 ppm for the terminal acetylene proton and two new ¹³C NMR signals at 75.7 and 77.8 ppm for acetylene carbons.

To obtain the target azide dendrimer **12**, **9** was tosylated and subsequently treated with sodium azide in DMF to give **12** in quantitative yields. The conversions were confirmed by the observation of the chemical shift change (¹H NMR) for the methylene protons (CH_2R) from 3.60 ppm (R = OH) to 3.97 ppm (R = OTs) and 3.26 ppm (R = N₃).

The establishment of an easy protocol for the monofunctionalization is key to our research strategy. Therefore, we investigated the functionalization of dendrimers **10** and **12** using 1,3 dipolar cycloadditions between an azide and an alkyne moiety. Unlike the typical 1,3 dipolar cycloaddition conditions at moderate temperature, our preliminary study using acetylene dendrimer **10** and benzyl azide under the 'typical' reaction conditions showed incomplete

Org Lett. Author manuscript; available in PMC 2008 October 2.

conversions and temperatures of 80 °C for 20 h were needed to obtain quantitative yields (Scheme 4). To reduce the reaction time and to have less harsh reaction conditions, we investigated the monomodal microwave reactor assisted 1,3 dipolar cycloaddition-based functionalization of our dendrimers. 1,3 Dipolar cycloadditions can be assisted by microwave irradiation to reduce the reaction time significantly and to provide near perfect regioselectivity. ¹³ The microwave assisted 1,3 dipolar cycloadditon has been utilized for biological systems including the attachment of peptides onto a dendritic molecules¹⁴ and the conjugation of oligonucleotides and carbohydrates.¹⁵

For the microwave experiments, **10** was treated with benzyl azide¹⁶ under typical 1,3 dipolar cycloaddition conditions using Na ascorbate and $CuSO_4 \cdot 5H_2O$ in a 1:1 mixture of *t*-BuOH and H₂O in a sealed glass vial. The microwave reactor was set-up using the power-time control method at 100 W irradiation power and a shut-off temperature of 100 °C.¹⁴ The reaction was terminated after 10 minutes to afford the desired triazole product **13a** in 98% isolated yields. While the yields are similar to the ones described above using conventional heating methods, the microwave irradiation significantly cuts down the reaction time from hours to minutes. Table 1 summarizes the microwave assisted 1,3 dipolar cycloaddition reactions that were carried out on dendrimers **10** and **12**. For all reactions studied under microwave conditions, we obtained excellent isolated yields (95–98%). Furthermore, when comparing the alkyne functionalized dendrimer (**10**) with the azide functionalized one (**12**), we did not detect any significant reactivity differences.

In conclusion, we have prepared monofunctionalized dendrons and dendrimers containing either a single alkyne or azide moiety. The resulting dendrimers containing a single chemical handle can be functionalized via 1,3 dipolar cycloadditon in outstanding yields. Along with the attachment of biological moieties on a single chemical handle, further functionalizations are available for these dendrimers *via* a deprotection of the *tert*-butyl esters on the periphery and subsequent reaction using the terminal carboxylic acids. The employed convergent approach potentially allows for the introduction of a second orthogonal functionality on the surface of the dendrimers. Such studies are currently under investigation.

Supplementary Material

Refer to Web version on PubMed Central for supplementary material.

Acknowledgements

We gratefully thank the National Institute of Health (NIH P20-GM072021) for financial support of this research. MW acknowledges a 3M Untenured Faculty Award, a DuPont Young Professor Award, a Camille Dreyfus Teacher/Scholar Award and an Alfred P. Sloan Fellowship.

References

- (a) Fischer M, Vögtle F. Angew Chem Int Ed 1999;38:884–905. (b) Bosman AW, Janssen HM, Meijer EW. Chem Rev 1999;99:1665–1688. [PubMed: 11849007]Newkome, GR.; Moorefield, CN.; Vögtle, F. Dendrimers and Dendrons: Concepts, Syntheses, Applications. Wiley; New York: 2001. (d) Helms B, Meijer EW. Science 2006;313:929–923. [PubMed: 16917051]
- 2. (a) Cloninger MJ. Curr Opin Biotechnol 2002;6:742–748. (b) Roberts JC, Bhalgat MK, Zera RT. J Biomed Mat Res 1996;30:53–65.
- 3. (a) Dykes GM. J Chem Tech Biotech 2001;76:903–918. (b) Esfand R, Tomalia DA. Drug Dis Today 2001;6:427–436.
- 4. (a) Balogh L, Tomalia DA. J Am Chem Soc 1998;120:7355–7356. (b) Crooks RM, Zhao MQ, Sun L, Chechik V, Yeung LK. Acc Chem Res 2001;34:181–190. [PubMed: 11263876]

- 5. (a) Bielinska A, Eichman JD, Lee I, Baker JR Jr, Balogh L. J Nanopart Res 2002;4:395–403. (b) Zheng J, Dickson RM. J Am Chem Soc 2002;124:13982–13983. [PubMed: 12440882] (c) Huang K, Cohen MJ, Croce T, Hamilton S, Evans BL, Voss B, Hamm HE, Harth E. Bioconjugate Chem 2007;18:403–409.
- 6. For examples of multiple functionalities on the periphery of dendrimers, see: (a) Hawker CJ, Fréchet JMJ. Macromolecules 1990;23:4726–4729. (b) Bo Z, Schäfer A, Franke P, Schlüter AD. Org Lett 2000;2:1645–1648. [PubMed: 10841500] (c) Zhang W, Nowlan DT III, Thomson LM, Lackowski WM, Simanek EE. J Am Chem Soc 2001;123:8914–8922. [PubMed: 11552798] (d) Ganesh RN, Shraberg J, Sheridan PG, Thayumanavan S. Tetrahedron Lett 2002;43:7217–7220. (e) Mihov G, Scheppelmann I, Müllen K. J Org Chem 2004;69:8029–8037. [PubMed: 15527287]
- (a) Kolb HC, Finn MG, Sharpless KB. Angew Chem Int Ed 2001;40:2004–2021. (b) Wu P, Feldman AK, Nugent AK, Hawker CJ, Scheel A, Voit B, Pyun J, Fréchet JMJ, Sharpless KB, Fokin VV. Angew Chem Int Ed 2004;43:3928–3932. (d) Hawker CJ, Wooley KL. Science 2005;309:1200–1205. [PubMed: 16109874]
- For some recent examples of the use of 1,3 dipolar cycloaddition in polymer chemistry see: (a) Helms B, Mynar JL, Hawker CJ, Fréchet JMJ. J Am Chem Soc 2004;126:15020–15021. [PubMed: 15547986] (b) Binder WH, Sachsenhofer R. Macromol Rapid Commun 2007;28:15–54. (c) Hoogenboom R, Moore BC, Schubert US. Chem Commun 2006;38:4010–4012. (d) Wang XY, Kimyonok A, Weck M. Chem Commun 2006;37:3933–3935. (e) Quemener D, Davis TP, Barner-Kowollik C, Stenzel MH. Chem Commun 2006;48:5051–5053. (f) Opsteen JA, Van Hest JCM. Chem Commun 2005;1:57–59.
- For the employment of 1,3 dipolar cycloaddition in dendrimer chemistry see: (a) Gopin A, Ebner S, Attali B, Shabat D. Bioconjugate Chem 2006;17:1432–1440. (b) Lee JW, Kim JH, Kim B. Tetrahedron Lett 2006;47:2683–2686. (c) Wu P, Malkoch M, Hunt JN, Vestberg R, Kaltgrad E, Finn MG, Fokin VV, Sharpless KB, Hawker CJ. Chem Commun 2005;46:5775–5777. (d) Rijkers DTS, Van Esse GW, Merkx R, Brouwer AJ, Jacobs HJF, Pieters RJ, Liskamp RMJ. Chem Commun 2005;36:4581–4583. (e) Joralemon MJ, O'Reily RK, Matson JB, Nugent AK, Hawker CJ, Wooley KL. Macromolecules 2005;38:5436–5443.
- 10. Newkome GR, Kim HJ, Moorefield CN, Maddi H, Yoo KS. Macromolecules 2003;36:4345-4354.
- (a) Newkome GR, Behera RK, Moorefield CN, Baker GR. J Org Chem 1991;56:7162–7167. (b) Newkome GR, Yoo KS, Moorefield CN. Designed Monomers Polym 2002;5:67–77.
- 12. Ballini R, Petrini M, Rosini G. Tetrahedron 1990;46:7531-7538.
- Appukkuttan P, Dehaen W, Fokin VV, Van der Eycken E. Org Lett 2004;6:4223–4225. [PubMed: 15524448]
- 14. Rijkers DTS, van Esse GW, Merkx R, Brouwer AJ, Jacobs HJF, Pieters RJ, Liskamp RMJ. Chem Commun 2005:4581–4583.
- Bouillon C, Meyer A, Vidal S, Jochum A, Chevolot Y, Cloarec JJ, Praly JP, Vasseur JJ, Morvan F. J Org Chem 2006;71:4700–4702. [PubMed: 16749812]
- 16. Demko ZP, Sharpless KB. Angew Chem Int Ed 2002;41:2110–2113.


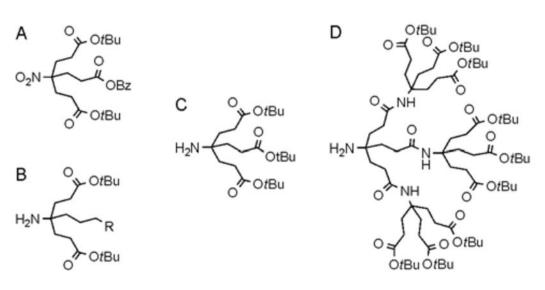



Figure 1.

Newkome type monomers; $1 \rightarrow (2+1)$ *C*-branching monomer (**A**), monofunctionalized monomer (**B**), and the first (**C**) and the second (**D**) generation of nonfunctionalized monomers.




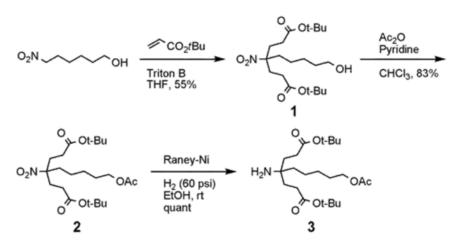


Scheme 1. Synthesis of monofunctionalized G1 dendron.

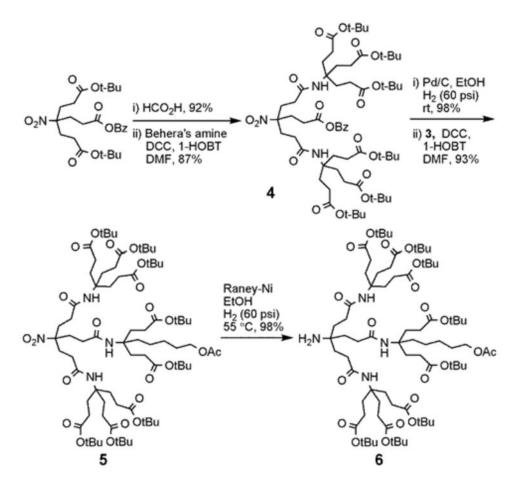

Scheme 2. Synthesis of monofunctionalized G2 dendron.

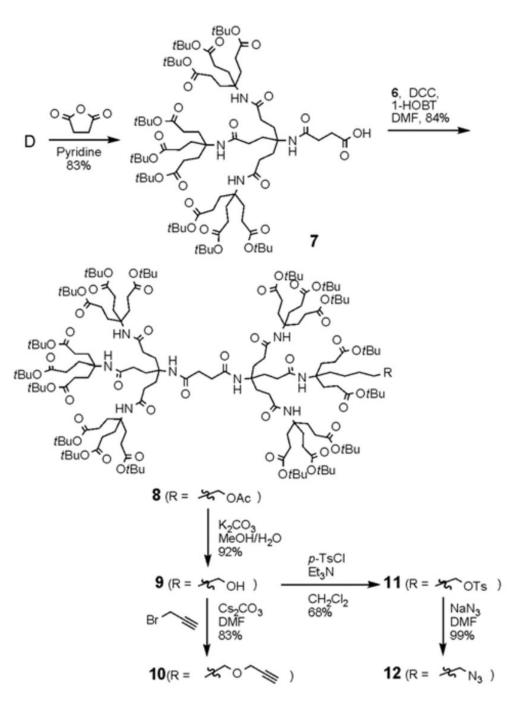



Scheme 3. Synthesis of monofunctionalized dendrimers (G2).

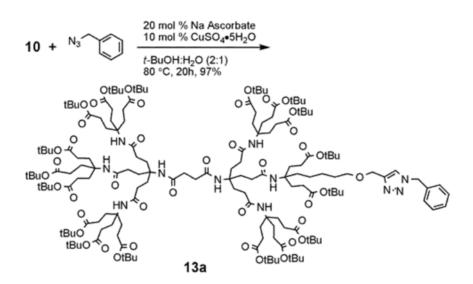

Scheme 4.

1,3 Dipolar cycloaddition functionalization using conventional heating conditions.



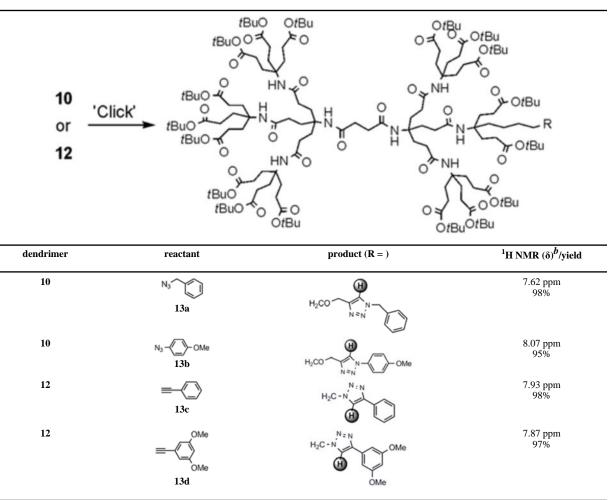

^{*a*}Reaction conditions: *t*-BuOH:H₂O (1:1), 10 mol % Na ascorbate, 5 mol %CuSO4·5H₂O. Microwave setting: Power-time control method, 100W, 10 min, $P_{max} = 65$ psi, and $T_{max} = 100^{\circ}$ C.

^bChemical shift for the newly formed triazole protons.