

Published in final edited form as:

J Am Chem Soc. 2007 September 5; 129(35): 10668–10669. doi:10.1021/ja074144q.

Synthesis and Characterization of Manganese Doped Silicon Nanoparticles:


Bifunctional Paramagnetic-Optical Nanomaterial

Xiaoming Zhang¹, Marcin Brynda, R. David Britt², Elizabeth Carroll², Delmar S. Larsen², Angelique Y. Louie¹, and Susan M. Kauzlarich²

¹Department of Biomedical Engineering, University of California, Davis, CA 95616

²Department of Chemistry, University of California, Davis, CA 95616

Abstract

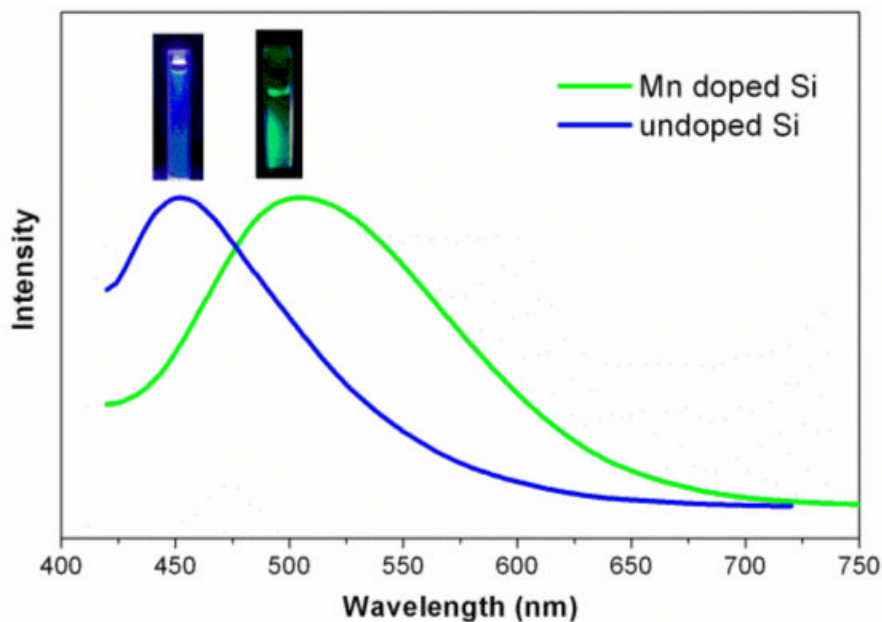

Mn doped Si nanoparticles have been synthesized via a low temperature solution route and characterized by X-ray powder diffraction, TEM, optical and emission spectroscopy and by EPR. The particle diameter was 4 nm and the surface was capped by octyl groups. 5% Mn doping resulted in a green emission with slightly lower quantum yield than undoped Si nanoparticles prepared by the same method. Mn²⁺ doped into the nanoparticle is confirmed by epr hyperfine and the charge carrier dynamics were probed by ultrafast transient absorption spectroscopy. Both techniques are consistent with Mn²⁺ on or close to the surface of the nanoparticle.

Multifunctional nanomaterials are multi-phase nanostructures with combined functionality such as detection by multiple imaging modalities, or detection and therapy. These nanomaterials possess combinations of properties that do not exist in single-phase materials. Nanoparticles, in particular, have potential for multimodal biological applications by the

addition of functionality to augment their luminescence.¹⁻³ Nanoparticles have intense visible luminescence because of quantum confinement and the color can be tuned throughout the visible spectrum by changing the particle size.^{4,5} Due to their biocompatibility, high photoluminescence quantum efficiency, and stability against photobleaching, silicon nanoparticles are expected to be an ideal candidate in many biological assays and fluorescence imaging techniques.⁶⁻⁸ The addition of paramagnetism to silicon nanoparticles would allow combination of optical detection with magnetic resonance imaging detection or magnetic separation.

An effective method for manipulating the physical properties of semiconductors involves impurity doping.⁹ II-VI semiconductor quantum dots can be doped with metal ions that have energy states within the bandgap. As a result, light emission from these introduced trap states can be observed.¹⁰ The advantage of this approach is that color can be controlled by the nature of the dopant, which allows for similar sized quantum dots with a full spectrum of colors. Doped nanomaterials provide the possibility for enhanced, multimodal functionality in contrast to their single-component counterparts.¹¹ Recently, Mn doped group IV semiconductors have attracted much attention both in experiment and theory.¹²⁻¹⁴

In this communication, we describe our syntheses of Mn doped Si nanoparticles and characterize the optical and magnetic properties of the system. Recently, a solution route has been used to produce macroscopic amounts of either amorphous or crystalline hydrogen terminated Si nanoparticles in our laboratory.^{15,16} Herein, Mn doped Zintl salts ($\text{NaSi}_{1-x}\text{Mn}_x$, $x = 0.05, 0.1, 0.15$) were prepared as precursors, followed by the reaction with ammonium bromide to make hydrogen capped nanocomposites.



The hydride-capped Mn doped silicon nanoparticles can be modified further via a hydrosilylation process to form chemically robust Si-C bonds on the surface and to protect the silicon particles from oxidation.^{17,18} The nanoparticles described herein were capped with octyne to form organic soluble nanoparticles.

Figure 1A shows representative TEM image of 5% Mn doped Si nanoparticles collected on a carbon TEM grid. The percentage of Mn in the Si nanoparticle sample was confirmed by elemental analysis with a molar ratio of Si:Mn of 18.2:1, consistent with 5% Mn doped Si nanoparticles and all the characterization described herein are on samples with nominally 5% Mn doping. The average diameter of Si nanoparticles is 4.2 ± 0.9 nm based on a survey of 530 particles from different regions of the grid. This result is similar to that for undoped Si nanoparticles prepared by this same method.¹⁵

The inset of Figure 1A shows the X-ray powder diffraction pattern of the obtained Mn doped Si nanoparticles. The diffraction pattern shows two broad diffraction peaks at approximately 33° and 60° , consistent with observations for amorphous silicon.^{16,19} The narrow peaks at 32° and 56° could correspond to the (111) and (220) reflections of crystalline silicon. The diffraction pattern can be interpreted as due to mainly amorphous Si.¹⁶ No diffraction due to Mn and MnO_x phases are observed, suggesting that Mn is incorporated into the Si nanoparticles.

Photoluminescence (PL) spectra (excitation and emission) were used to investigate the optical properties of the Mn doped silicon nanoparticles in chloroform (Figure 1B). The excitation spectrum (black curve) shows that monitored at excitation wavelength 510 nm, the Mn doped Si nanoparticle sample gave the strongest peak when excited at 420 nm. The emission spectra show a relatively narrow region of intense luminescence with maximum intensity from 490 to 520 nm, with excitation from 380 to 440 nm. The maximum intensity emission spectrum is

centered at 510 nm with an excitation wavelength of 420 nm. Compared to the undoped Si nanoparticles,¹⁵ there is an obvious red shift from 430 nm to 520 nm. Changes in the excitation wavelength excited different size populations of nanoparticles, resulting in the varying emission wavelengths observed. Quantum yields of up to 16% in chloroform were obtained relative to the standard fluorescein solution²⁰ for the Mn doped Si sample, lower than that reported for undoped Si prepared in the same manner (18%).¹⁵ With larger amounts of Mn, the quantum yield decreased significantly.

Electron Paramagnetic Resonance (EPR) measurements (Figure 2) were used to confirm the presence of Mn²⁺ in the Si nanoparticles. The EPR spectrum of the undoped samples (insert in Fig. 2) shows a sharp signal at $g = 2.0$, attributed to dangling bonds in the Si nanoparticles.²¹ In addition to the $g = 2.0$ signal, the Mn doped sample exhibits a six-line spectrum, arising from the hyperfine interaction with the ⁵⁵Mn nuclear spin ($I = 5/2$).²² The observed hyperfine splitting is 96 G, and is similar to the hyperfine splitting observed for Mn²⁺ ions isolated on the surface of Si rather than in the interior.²³ To rule out possible presence of the Mn²⁺ ions simply physisorbed on the Si surface, an additional set of samples were prepared by successive purification (washed four times with a chloroform/methanol mixture) followed by ligand exchange with pyridine in order to remove Mn²⁺ from the surface of the particles.¹¹ The corresponding EPR spectra are almost identical to the one obtained with the nonwashed samples and the Mn hyperfine splitting value remains the same, suggesting that Mn²⁺ is covalently bound to the surface or near the surface of the nanoparticle (supporting information). The presence of Mn²⁺ near or at the surface would be optimal for MRI applications.

Additional evidence for Mn doped into the nanoparticles can be provided by transient absorption (TA) spectroscopy. TA data show that the excited state dynamics of the 5% Mn doped Si nanoparticles differs distinctly from undoped Si nanoparticles (Figure 3). At least two trapped electronic populations can be distinguished spectroscopically in the undoped Si nanoparticles (Inset, Figure 3). The population associated with higher energy electron trap states decays ~20% more quickly in the Mn doped Si nanoparticles, suggesting that photogenerated excitons have additional relaxation paths. Similarly faster trapped electron relaxation has been observed in Er³⁺ doped Si nanocrystals.²⁴ A ns plateau in absorption also indicates a longer lived charge separation in the Mn doped Si nanoparticles. One explanation for the differences in dynamics is a terminal migration of charge carriers from Si traps to Mn states. The red-shifted emission spectrum of Mn doped Si indicates recombination from trap states that are on average > 0.1 eV lower in energy than trap states in undoped Si. These states are likely associated with Mn²⁺, from which radiative recombination is inhibited both by a highly localized electron and because the $d-d$ transition is not spin allowed.²⁵ Because radiative trap sites in Si nanoparticles are attributed to non-quantized surface states²⁶ electron transfer from deep Si traps suggests that Mn²⁺ is coupled to the Si surface.

Supplementary Material

Refer to Web version on PubMed Central for supplementary material.

Acknowledgements

This work was supported by the NIH (HL081108-01).

References

- (1). Huh Y-M, Jun Y.-w. Song H-T, Kim S, Choi J.-s. Lee J-H, Yoon S, Kim K-S, Shin J-S, Suh J-S, Cheon J. J. Am. Chem. Soc 2005;127:12387–12391. [PubMed: 16131220]
- (2). Santra S, Yang H, Holloway PH, Stanley JT, Mericle RA. J. Am. Chem. Soc 2005;127:1656–1657. [PubMed: 15700997]

- (3). Michalet X, Pinaud FF, Bentolila LA, Tsay JM, Doose S, Li JJ, Sundaresan G, Wu AM, Gambhir SS, Weiss S. *Science* 2005;307:538–544. [PubMed: 15681376]
- (4). Canham LT. *Appl. Phys. Lett* 1990;57:1046–1048.
- (5). Veinot JGC. *Chem. Commun* 2006:4160–4168.
- (6). Li ZF, Ruckenstein E. *Nano Lett* 2004;4:1463–1467.
- (7). Wang L, Reipa V, Blasic J. *Bioconjugate Chem* 2004;15:409–412.
- (8). Buriak JM. *Phil. Trans. R. Soc. A* 2006;364:217–225. [PubMed: 18272462]
- (9). Shi W, Zeng H, Sahoo Y, Ohulchanskyy TY, Ding Y, Wang ZL, Swihart M, Prasad PN. *Nano letters* 2006;6:875–881. [PubMed: 16608302]
- (10). Murphy CJ, Coffey JL. *Appl. Spectro* 2002;56:16A–27A.
- (11). Wang S, Jarrett BR, Kauzlarich SM, Louie AY. *J. Am. Chem. Soc* 2007;129:3848–3856. [PubMed: 17358058]
- (12). Yoon IT, Park CJ, Kang TW. *J Magn Magn Mater* 2007;311:693–696.
- (13). Li AP, Shen J, Thompson JR, Weiting HH. *Applied Physics Letters* 2005;86:152507/1–152507/3.
- (14). Jamet M, Barski A, Devillers T, Poydenot V, Dujardin R, Bayle-Guillemaud P, Rothman J, Bellet-Amalric E, Marty A, Cibert J, Mattana R, Tatarenko S. *Nat Mater* 2006;5:653–659. [PubMed: 16845420]
- (15). Zhang X, Neiner D, Wang S, Louie AY, Kauzlarich SM. *Nanotechnology* 2007;18:095601.
- (16). Neiner D, Chiu HW, Kauzlarich SM. *J. Am. Chem. Soc* 2006;128:11016–11017. [PubMed: 16925406]
- (17). Liao Y-C, Roberts JT. *J. Am. Chem. Soc* 2006;128:9061–9065. [PubMed: 16834379]
- (18). Liu SM, Yang Y, Sato S, Kimura K. *Chem. Mater* 2006;18:637–642.
- (19). Kapaklis V, Politis C, Pouloupoulos P, Schweiss P. *Appl Phys Lett* 2005;87:123114/1–123114/3.
- (20). Brannon JH, Magde D. *J Phys. Chem* 1978;82:705–9.
- (21). Arul Dhas N, Raj CP, Gedanken A. *Chem. Mater* 1998;10:3278–3281.
- (22). Norris DJ, Yao N, Charnock FT, Kennedy TA. *Nano Letters* 2001;1:3–7.
- (23). Ludwig GW, Woodburg HH, Carlson RO. *J. Phys. Chem. Solids* 1959;8:490–492.
- (24). Samia ACS, Lou Y, Burda C, Senter RA, Coffey JL. *J. Chem. Phys* 2004;120:8716–8723. [PubMed: 15267802]
- (25). Smith BA, Zhang JZ, Joly A, Liu J. *Phys. Rev. B* 2000;62:2021–2028.
- (26). Klimov VI, Schwarz CJ, McBranch DW, White CW. *Appl. Phys. Lett* 1998;73:2603–2605.

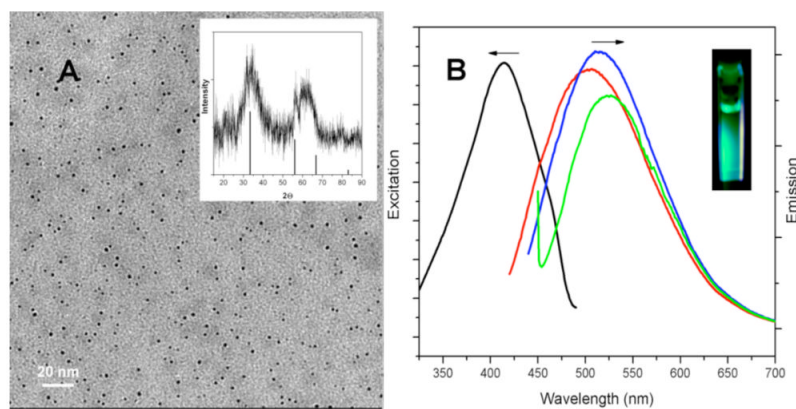


Figure 1. (A) TEM image of 5% Mn doped Si nanoparticles. Inset is XRD pattern of Mn doped silicon nanoparticles. The lines indicate the X-ray diffraction peak position for diamond structure silicon. (B) Excitation spectra (black) and Room temperature PL spectra of Si nanoparticles in chloroform at different excitation wavelengths: 400 nm (red); 420 nm (blue), and 440 nm (green). Inset: fluorescence from a cuvette of Mn doped Si nanoparticles when excited with a handheld UV lamp.

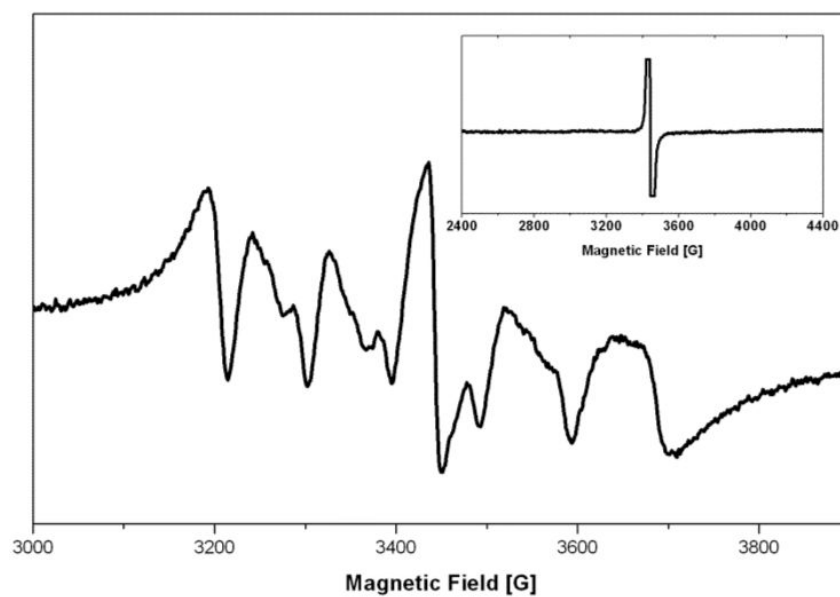


Figure 2. EPR spectrum of the Mn²⁺ doped Si nanoparticles. Inset: EPR spectra of the undoped Si nanoparticles.

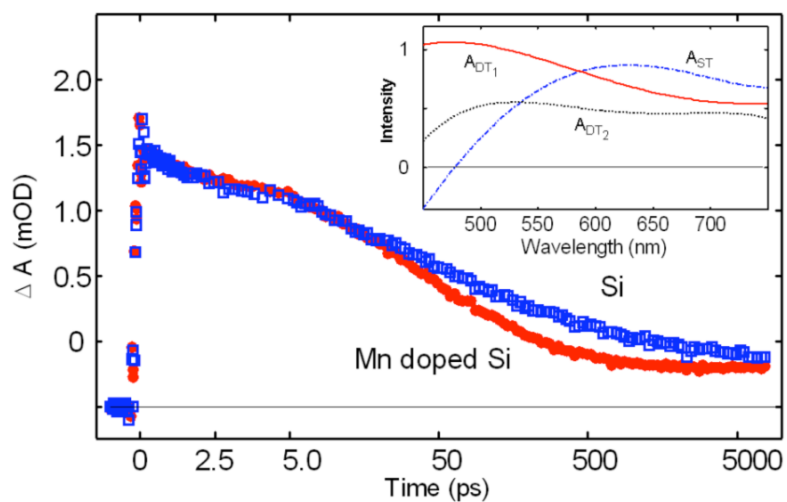


Figure 3. Transient absorption spectroscopy probed at 525 nm in Mn doped Si and undoped Si nanoparticles. Inset: Global analysis was used to determine species associated spectra for three electron populations in shallow traps (ST), deep traps (DT1 and DT2).