

Research Article

Stomach-Specific Controlled Release Gellan Beads of Acid-Soluble Drug Prepared by Iontropic Gelation Method

Mrunalini Narkar,^{1,2} Praveen Sher,¹ and Atmaram Pawar^{1,3}

Received 12 March 2009; accepted 23 January 2010; published online 24 February 2010

Abstract. The purpose of the present work was the development and evaluation of stomach-specific controlled release mucoadhesive drug delivery system prepared by ionotropic gelation of gellan beads, containing acid-soluble drug amoxicillin trihydrate, using 3² factorial design with concentration of gellan gum and quantity of drug as variables. The study showed that beads prepared in alkaline cross-linking medium have higher entrapment efficiency than the acidic cross-linking medium. The entrapment efficiency was in the range of 32% to 46% w/w in acidic medium, which increased up to 60% to 90% w/w in alkaline medium. Batches with lowest, medium, and highest drug entrapment were subjected to chitosan coating to form a polyelectrolyte complex film. As polymer concentration increases, entrapment efficiency and particle size increases. Scanning electron microscopy revealed spherical but rough surface due to leaching of drug in acidic cross-linking solution, dense spherical structure in alkaline cross-linking solution, and rough surface of chitosan-coated beads with minor wrinkles. The *in vitro* drug release up to 7 h in a controlled manner following the Peppas model ($r=0.9998$). *In vitro* and *in vivo* mucoadhesivity study showed that beads have good mucoadhesivity and more than 85% beads remained adhered to stomach mucosa of albino rat even after 7 h. *In vitro* growth inhibition study showed complete eradication of *Helicobacter pylori*. These results indicate that stomach-specific controlled release mucoadhesive system of amoxicillin gellan beads may be useful in *H. pylori* treatment.

KEY WORDS: acid-soluble drug; amoxicillin trihydrate; gellan gum; *H. pylori*; mucoadhesive controlled release drug delivery system.

INTRODUCTION

In the last decade, the number of patients suffering from peptic ulcer and gastric cancer due to *Helicobacter pylori* infection has increased tremendously. *H. pylori* are spiral, gram-negative, microaerophilic rod-shaped bacteria with multiple flagella (1,2). *H. pylori* remains present on the luminal surface of the gastric mucosa under mucous gel layer, is highly motile, and produces enzyme urease to alter surrounding pH to protect itself from gastric acid (2). The current therapy for the treatment of *H. pylori* involves use of proton pump inhibitors with antibiotics and has drawbacks like poor patient compliance and increased bacterial resistance due to higher multiple dosage of antibiotics (3). Delivering drug at the site of infection for a longer period of time is one of the approaches to improve the efficacy of antibiotic therapy (4,5).

Mucoadhesive dosage forms have been widely used for site-specific targeting for both local and systemic drug delivery and have also been beneficial for the treatment of

H. pylori infection (6–10). Mucoadhesion involves strong interaction between polymer and mucus lining of the tissue which increases contact time, permits localization, and prolongs drug absorption.

Hydrogels found applications in formulating controlled and mucoadhesive drug delivery systems. Their hydrophilic and three-dimensional network structure helps to encapsulate and regulate the release of the drug. Polysaccharide hydrogels have useful properties like biocompatibility, biodegradation, mucoadhesivity, and ease of formulations mostly by ionotropic gelation method. By controlling their degree of swelling and cross-linking, they can be useful as potential carriers of drugs for controlled release applications. Gellan gum is an extracellular anionic heteropolysaccharide consisting of a linear structure of repeating tetrasaccharide units of glucose, glucuronic acid, and rhamnose in a molar ratio of 2:1:1. It has a characteristic temperature and ionic-dependent gelling property (11). The mechanism of gelation involves the formation of double helical junction zones followed by aggregation of double helical segments to form a three-dimensional network by complexation with cations and hydrogen bonding with water. Another polysaccharide, chitosan, is a linear random copolymer of D-glucosamine and N-acetyl-D-glucosamine and is obtained by N-deacetylation of chitin (12–14). Chitosan hydrogel can be formed by covalent cross-linking or ionic cross-linking. Chitosan is a well-known polycation that reacts with negatively charged

¹ Department of Pharmaceutics, Poona College of Pharmacy, Bharti Vidyapeeth University, Erandwane, Pune, 411038 Maharashtra, India.

² Interactive Research School for Health Affairs, Bharathi Vidyapeeth University, Dhankawadi, Pune, 411043 Maharashtra, India.

³ To whom correspondence should be addressed. (e-mail: p_atmaram@rediffmail.com)

components, either ions or molecules, leading to the formation of polyelectrolyte complex through ionic bridges between polymer chains. Their mucoadhesive property is mainly based on the ionic interaction with anionic substructures of mucous layer.

Amoxicillin is the model drug for the treatment against *H. pylori* (15). Due to its acid-soluble nature, it is very difficult to control its drug release for an extended period in the acidic environment of stomach. In the present study, beads were prepared using gellan gum and chitosan by ionotropic gelation method. Initially, drug-loaded gellan beads were prepared using 3^2 factorial design to ensure high entrapment efficiencies by employing acidic and alkaline cross-linking mediums. All the batches showed complete drug release within 2 h in acidic media. Therefore, to obtain controlled drug release, the drug-loaded gellan beads with lowest, medium, and highest drug entrapment were subjected to chitosan coating. Uncoated and coated beads were evaluated and characterized for yield, entrapment efficiency, micromeritic properties, scanning electron microscopy (SEM), thermal properties, swelling behavior, *in vitro* drug release, *in vivo* and *in vitro* mucoadhesive properties of beads, and *in vitro* growth inhibition study.

MATERIALS AND METHODS

Materials

Amoxicillin trihydrate was gifted by Alkem (Daman, India). Gellan gum LA was gifted by C.P. Kelco Pvt. Limited (Mumbai, India). Chitosan was a gifted by A & E Connock (UK). Calcium chloride was purchased from Sisco Research Lab Pvt. Ltd., Mumbai, India. All other chemicals and reagents were of analytical grade.

Method of Preparation

Amoxicillin Gellan Beads

Beads were prepared by the cation-induced ionotropic gelation method using acidic and alkaline cross-linking medium. Gellan solution (1.5%, 1.75%, and 2.0% *w/v*) was prepared by dissolving the gellan in double-distilled water by heating at 90°C. Different quantities of amoxicillin were

dispersed uniformly in 10 ml of gellan solution with constant stirring (300 rpm) at 40°C until a homogeneous solution was formed. The homogeneous bubble-free solution was extruded dropwise through 18 G syringe needle into the 100 ml cross-linking solution containing 5% calcium chloride of pH 5 or pH 9 with constant stirring (100 rpm) and curing time 5 min to provide sufficient mechanical strength (16). The beads were separated by filtration, washed with double-distilled water, and dried at 25–30°C for 24 h. All formulations were prepared in triplicate. The pH of the cross-linking media was adjusted using dilute HCl and 10% ethylamine solution. A total of nine formulations were prepared and the assigned formulation codes are given in Table I.

Gellan Beads Coated with Chitosan

Drug-loaded gellan beads obtained using alkaline cross-linking medium were selected for chitosan coating. Chitosan solution was prepared by dissolving 1% *w/v* chitosan in 5% *v/v* acetic acid solution containing 1% *w/v* CaCl₂. The drug-loaded beads were dispersed in chitosan solution with continuous stirring at 100 rpm for 15 min, filtered, and dried at 25°C to 30°C for 24 h. All formulations were prepared in triplicate.

Factorial Design Experiments

A 3^2 randomized reduced factorial design was used in this study where two factors each at three levels were evaluated to find the interaction between the selected variables. The variables selected were concentration of gellan gum (X_1) and quantity of drug (X_2) at three different levels. The coded and the actual values of the experimental design are given in Table I.

Evaluation and Characterization of Beads

Yield and Entrapment Efficiency of Beads

The weight of the dried beads was recorded as yield of the process. For determination of entrapment efficiency, the dried beads (100 mg) were placed in 50 ml of phosphate buffer (pH 7.4) for 2 h and sonicated at 125 W for 30 min (Imeco Ultrasonics, India). The obtained dispersion was

Table I. Experimental Variables of Factorial Design with Their Coded Levels and Actual Values of Amoxicillin Gellan Beads, Results of Percent Yield, Percent Entrapment Efficiency, and Particle Size

Batch	Gellan (X_1)	Amoxicillin (X_2)	Yield (%) ^a		Entrapment efficiency (%) ^a		Diameter (mm) ^a	
			Acidic	Alkaline	Acidic	Alkaline	Acidic	Alkaline
AM-1	1.5 (-1)	700 (-1)	53.87±1.2	78.66±1.1	35.78±1.76	68.25±1.77	0.70±0.41	0.80±0.4
AM-2	1.5 (-1)	800 (0)	48.78±1.1	76.25±1.2	33.88±2.1	66.25±1	0.73±0.5	0.83±0.6
AM-3	1.5 (-1)	900 (+1)	40.89±1	70.45±1.5	32.45±2.13	60.45±1.6	0.81±0.4	0.84±0.34
AM-4	1.75 (0)	700 (-1)	45.34±1.4	73.43±1.2	42.08±1.98	63.43±1.88	0.82±0.8	0.85±0.78
AM-5	1.75 (0)	800 (0)	57.98±1.3	91.3±0.97	39.45±1.43	81.3±1.33	0.83±0.5	0.88±0.6
AM-6	1.75 (0)	900 (+1)	56.45±0.9	89.27±0.76	37.56±1.89	79.27±1.67	0.85±0.5	0.89±0.5
AM-7	2.0 (+1)	700 (-1)	54.04±1.8	79.74±0.89	45.79±2.1	69.74±2	0.94±0.3	0.98±0.4
AM-8	2.0 (+1)	800 (0)	65.34±0.8	97.57±0.5	40.01±1.5	89.57±1.54	0.99±0.21	1.1±0.4
AM-9	2.0 (+1)	900 (+1)	63.45±1.4	94.89±0.9	38.2±1.98	86.89±1.78	1.1±0.52	1.2±0.5

^a Mean ± SD, *n*=3

filtered through a 0.45- μm filter. The drug content of filtrate was determined spectrophotometrically at 272 nm (Shimadzu,

UV/Visible 1601, Japan). Each sample determination was made in triplicate:

$$\text{Entrapment efficiency} = \frac{\% \text{ Drug content} \times \text{Amount of dried beads produced}}{(\text{Amount of drug added}) - (\text{Amount of drug remaining in apparatus})}. \quad (1)$$

Particle Size Determination

The microscopic photographs of beads ($n=100$) was taken using a stereomicroscope (Carl Zeiss, Oberkochen, Germany) attached with a digital camera (Watec, Wat-202, Tokyo, Japan). The captured images were analyzed using the Biovis Image Plus software (Expert Tech Vision, Mumbai, India). Average diameter and different surface factors such as circulatory factor, elongation, roundness, and perimeter ratio were determined.

Differential Scanning Calorimetric (DSC) Analysis

Thermograms of amoxicillin trihydrate, gellan beads, drug-loaded gellan beads and chitosan-coated beads were obtained using a Mettler–Toledo differential scanning calorimeter (DSC) 821e instrument (Mettler Toledo, Greifensee, Switzerland) equipped with an intracooler. Indium standard was used to calibrate the DSC temperature and enthalpy scale. The samples were separately weighed and hermetically sealed in perforated aluminum pans. The system was purged with nitrogen gas at a flow rate of 80 ml/min, and heating was performed from 25°C to 250°C at a rate of 5°C/min.

Powder X-ray Diffraction

Powder X-ray diffraction (PXRD) patterns of amoxicillin trihydrate, gellan beads, drug-loaded gellan beads, and chitosan-coated beads of different batches were recorded by using a Philips PW1729 X-ray diffractometer (Philips PW 1729 X-ray diffractometer, Netherlands). Samples were irradiated with monochromatized Cu K α radiation (1.542 Å) and analyzed at 2θ between 2° and 60°. The voltage and current used were 30 kV and 30 mA, respectively. The data were recorded over a range of 2° to 60° at a scanning rate of 5×10^3 cps using a chart speed of 10 mm/2 θ .

Fourier Transform Infrared Analysis

Fourier transform infrared analysis (FTIR) measurements of amoxicillin trihydrate, gellan beads, drug-loaded gellan beads, and chitosan-coated beads of different batches were obtained on JASCO V5300 FTIR (Tokyo, Japan). The pellets were prepared on KBr-press (Spectra Lab, Pune, India) under hydraulic pressure of 150 kg/cm 2 . The spectra were scanned over the wave number range of 3,600 to 400 cm $^{-1}$ at ambient temperature.

Surface Topography

Photomicrographs of the beads were observed at $\times 50$ magnification using SEM Cambridge Stereoscan 120 (Cambridge, UK) operated with an acceleration voltage of 10 kV. The beads were mounted on the standard specimen mounting

stubs and were coated with a thin layer (20 nm) of gold by sputter coater unit (VG Microtech, Uckfield, East Sussex, UK).

Swelling Study

Chitosan-coated beads were studied for swelling characteristics. One hundred milligrams of beads were placed in the wire basket of the USP-26 dissolution test apparatus II (Electrolab TDT-06P Mumbai, India). The basket containing beads were put in a beaker containing 100 ml of 0.1 N HCl (pH 1.2) and phosphate buffer IP (pH 7.4) maintained at 37°C. The beads were periodically removed at predetermined intervals and weighed. Then the swelling ratio was calculated as per the following formula:

$$\text{Swelling ratio} = \frac{\text{Weight of wet beads}}{\text{Weight of dried beads}}. \quad (2)$$

In Vitro Drug Release Studies

The release rate of drug-loaded gellan beads and chitosan-coated beads was studied using USP-26 Type II dissolution test apparatus (Electrolab TDT-06P Mumbai, India) containing 900 ml of 0.1 N HCl (pH 1.2) and maintained at $37 \pm 0.5^\circ\text{C}$ and stirred at 100 rpm. Samples were collected periodically and replaced with a fresh dissolution medium. Analysis of data was done using the PCP Disso v2.08 software (Poona College of Pharmacy, Pune, India).

Evaluation of Mucoadhesiveness of Beads

In Vitro Evaluation of Mucoadhesiveness of Beads. *In vitro* mucoadhesion of beads was tested on rat stomach tissue using bioadhesive tester (Memesis with AFG England). The tissue was glued on the surface of the lower plate and beads were glued on the surface of the upper plate. The surface of the plates was facing each other. The upper plate holding the beads was lowered slowly ensuring proper contact of beads with tissue surface without application of external pressure. After 10 min contact time, the detachment force was determined by measuring the force required for separation of the beads from the tissue surface.

In Vivo Evaluation of Mucoadhesiveness of Beads. The beads with highest *in vitro* mucoadhesivity were selected for the *in vivo* mucoadhesivity study (17). Three groups (six rats in each group) of albino rats (Sprague–Dawley strain, 200–300 g) of either sex were fasted for 24 h before the experiments but were allowed free access to water. Ten beads were orally administered with 2 ml of water to conscious rats. The rats were kept fasted and killed after 2, 4, and 7 h. The

Table II. Regression Analysis Data of 3² Factorial Design

Coefficient	Percent yield		Percent entrapment efficiency	
	Acidic	Alkaline	Acidic	Alkaline
β_0	54.015	73.95	39.69	79.4
β_1	6.548	8.4733	3.66	6.3983
β_2	–	–	–2.5733	–2.368
β_{11}	–	–	–2.025	–6.7
β_{22}	–	–	–	–
β_{12}	5.59	–	–1.065	–
R^2	0.7445	0.4831	0.9773	0.9941
Significance	0.014	0.0377	0.0015	0.0000
F	8.745	6.543	43.172	285

beads that remained adhered to the gastrointestinal tract were counted. The gastric mucoadhesion was expressed as the percentage of beads remaining in the stomach after perfusion.

In Vitro Growth Inhibition Studies

The bacterial strain used in the study was isolated from a hospitalized human patient (age 45 years) with gastric ulcer in Owaisi Hospital, Hyderabad, India. *In vitro* growth inhibition studies were performed for chitosan-coated gellan beads using a broth culture of *H. pylori*. *H. pylori* broth culture was incubated in a brain–heart infusion containing 0.25% yeast extract and 10% fetal calf serum and supplemented with 0.4% *Campylobacter*-selective supplement (Skirrow supplement). *H. pylori* strain was grown in *Brucella* broth at 37°C for 7 days in a microaerophilic atmosphere (5% O₂, 10% CO₂, and 85% N₂). Growth of the bacteria was monitored by measuring the optical density of broth cultures spectrophotometrically at 600 nm. The number of bacteria was determined

by optical density with one optimal density unit corresponding to 10⁸ colony-forming units (CFU) ml⁻¹. The colonies were identified as *H. pylori* by morphology and urease activity (9). To study the effect of formulations on *H. pylori* growth inhibition, 10 ml of nutrient broth was inoculated with a loopful of the *H. pylori* from stock culture to make a final culture of 100 CFU ml⁻¹ (18). Amoxicillin suspension and chitosan-coated beads were incubated at 37°C in a microaerophilic atmosphere. Amoxicillin was used at a concentration of 8 µg/ml (this concentration is approximately fourfold of the reported MIC₅₀ for *H. pylori* urease) (19). The culture containing tubes were shaken at 100 rpm at 37°C in a microaerobic atmosphere in an incubator. One hundred microliters of nutrient broth sample were removed at various time intervals and serial dilutions were plated on modified Skirrow's medium. The agar plates were incubated for 4 days at 37°C under microaerobic conditions. The viable cell counts for each sample were calculated by counting the number of colonies on the agar plates.

RESULTS AND DISCUSSION

Process Design

Gellan beads were prepared by ionotropic gelation that involved interaction between negatively charged gellan gum with positively charged calcium ion. Preliminary study to obtain cross-linked gellan beads was carried out by using 0.5–2.5% w/v gellan solution and 1–5% w/v calcium chloride solution as cross-linking medium (20,21). The 1.5–2% w/v gellan gum solutions in 5% w/v calcium chloride solution produced satisfactory beads at agitation speed of 100 rpm. Therefore, 1.5%, 1.75%, and 2% w/v gellan concentrations were used for further studies.

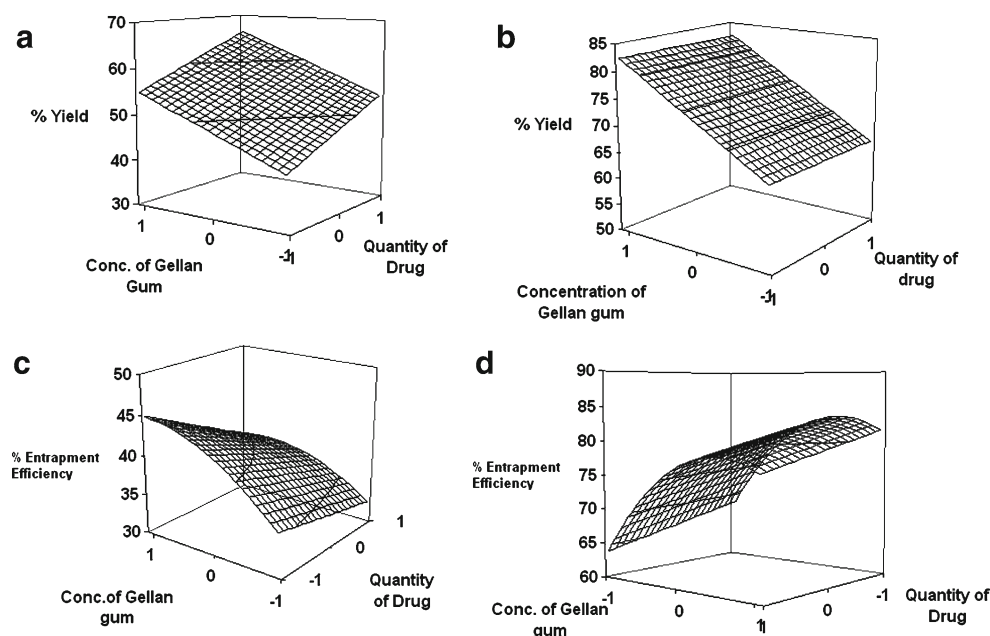


Fig. 1. Response surface plot showing effect of factorial variables on **a** percent yield (acidic), **b** percent yield (alkaline), **c** percent entrapment efficiency (acidic), and **d** percent entrapment efficiency (alkaline)

Yield and Entrapment Efficiency of Beads

The yield of drug-loaded gellan beads obtained using acidic and alkaline cross-linking medium was found to be in the range of 40% to 65% w/w and 70% to 97% w/w and the entrapment efficiency was in the range of 32% to 40% w/w and 60% to 89% w/w, respectively. Comparatively lower values of responses obtained using acidic cross-linking medium may be due to loss of drug present on the surface of beads (Table I).

The data of values obtained for yield and entrapment efficiencies were subjected to multiple regression analysis using statistical software UNISTAT® (statistic version 3, Meglon US). The equation fitted was:

$$Y = \beta_0 + \beta_1 X_1 + \beta_2 X_2 + \beta_{11} X_1^2 + \beta_{22} X_2^2 + \beta_{12} X_1 X_2 \quad (3)$$

where Y represents the measured response, X represents the levels of factors, and β represents the coefficient computed from the responses of the formulations.

The regression equation for yield (acidic) was:

$$Y = 54.015 + 6.548 X_1 + 5.59 X_1 X_2 (r^2 = 0.7445). \quad (4)$$

The regression equation for yield (alkaline) was:

$$Y = 73.95 + 8.4733 X_1 (r^2 = 0.4831). \quad (5)$$

The regression equation for entrapment efficiency (acidic) was:

$$Y = 39.69 + 3.66 X_1 - 2.5733 X_2 - 2.025 X_1 X_1 - 1.065 X_1 X_2 (r^2 = 0.9773). \quad (6)$$

The regression equation for entrapment efficiency (alkaline) was:

$$Y = 79.4 + 6.3983 X_1 - 2.368 X_2 - 6.7 X_1 X_1 (r^2 = 0.9941). \quad (7)$$

The regression analysis for yield and entrapment efficiency shows a positive effect of polymer concentration (Table II; Fig. 1). The increase in gel viscosity with polymer concentration develops cohesive interactions among gellan monomers and provides resistance to diffusion and leaching of drug, thus increasing the extent of agglomeration. The intramolecular cohesive interactions in polymers ($X_1 X_1$) reduce space for accommodation of drug, resulting to lower drug entrapment. It is also reflected by negative effect of X_2

Table III. Result of Chitosan-Coated Amoxicillin Gellan Beads Yield, Entrapment Efficiency, and Particle Size

Batch	Yield (%) ^a	Entrapment efficiency (%) ^a	Diameter (mm) ^a
AM-3	76.85±1	71.67±1.1	0.86±0.6
AM-6	91.2±0.52	84.23±1.2	0.91±0.7
AM-8	98.23±0.4	91.76±0.82	1.3±0.5

^a Mean ± SD, $n=3$

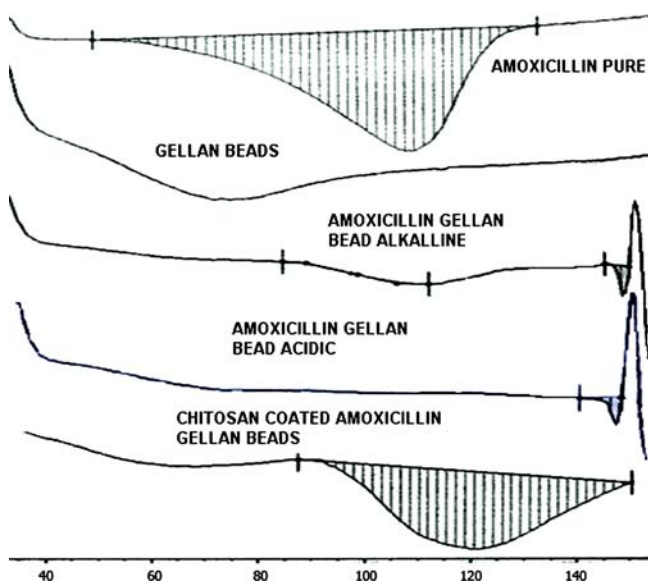


Fig. 2. DSC thermograms of amoxicillin, amoxicillin gellan beads, and chitosan-coated amoxicillin gellan beads

(Eqs. 6 and 7). Higher value of yield and drug entrapment for beads obtained using alkaline medium can be explained on the basis of decreased solubility of drug.

The beads were spherical with circularity factor in the range of 1.1 to 1.2 and roundness in the range of 0.4 to 0.6, but no significant difference was observed in these parameters. The mean particle size of beads obtained from acidic cross-linking medium and alkaline cross-linking medium was in the range of 0.70 to 1.1 mm and 0.80 to 1.2 mm,

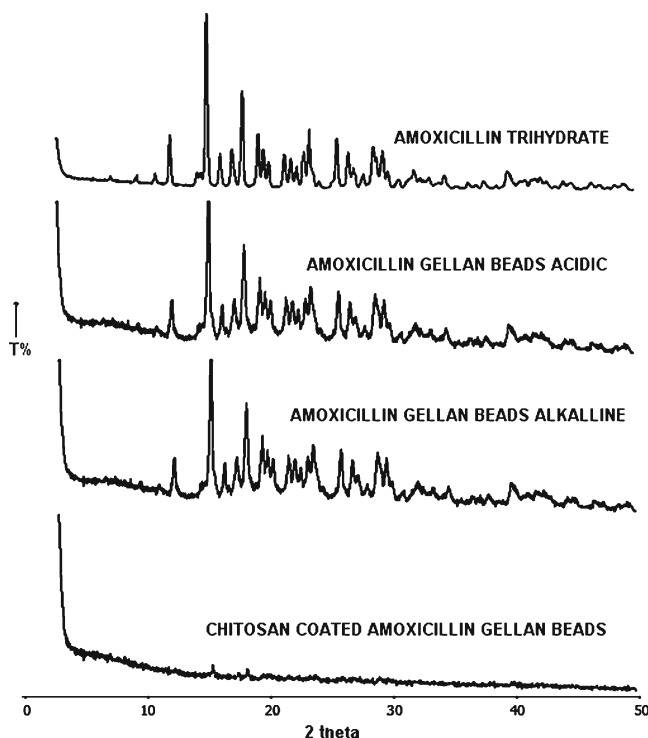


Fig. 3. XRD patterns of amoxicillin, amoxicillin gellan beads, and chitosan-coated amoxicillin gellan beads

respectively (Table I). Size of the beads increased with increase in the concentration of gellan gum and amount of drug. This could be attributed to the increased diffusion resistance and agglomerating properties in viscous polymeric dispersion. The pH-dependent swelling of gellan gum in alkaline medium and, in turn, loose packing can also enlarge bead size (22). The mean diameter of chitosan-coated beads marginally increased with an increase in drug loading and chitosan concentration (Table III). This could be attributed to

formation of a thick chitosan coating over the beads due to its ionic interaction.

Characterization of Beads

The DSC thermogram of pure amoxicillin showed exothermic peak at $109.6 \pm 1.0^\circ\text{C}$ which disappeared in cross-linked gellan beads; this may be due to dispersion of drug in molecular state. The endothermic peak of drug observed in

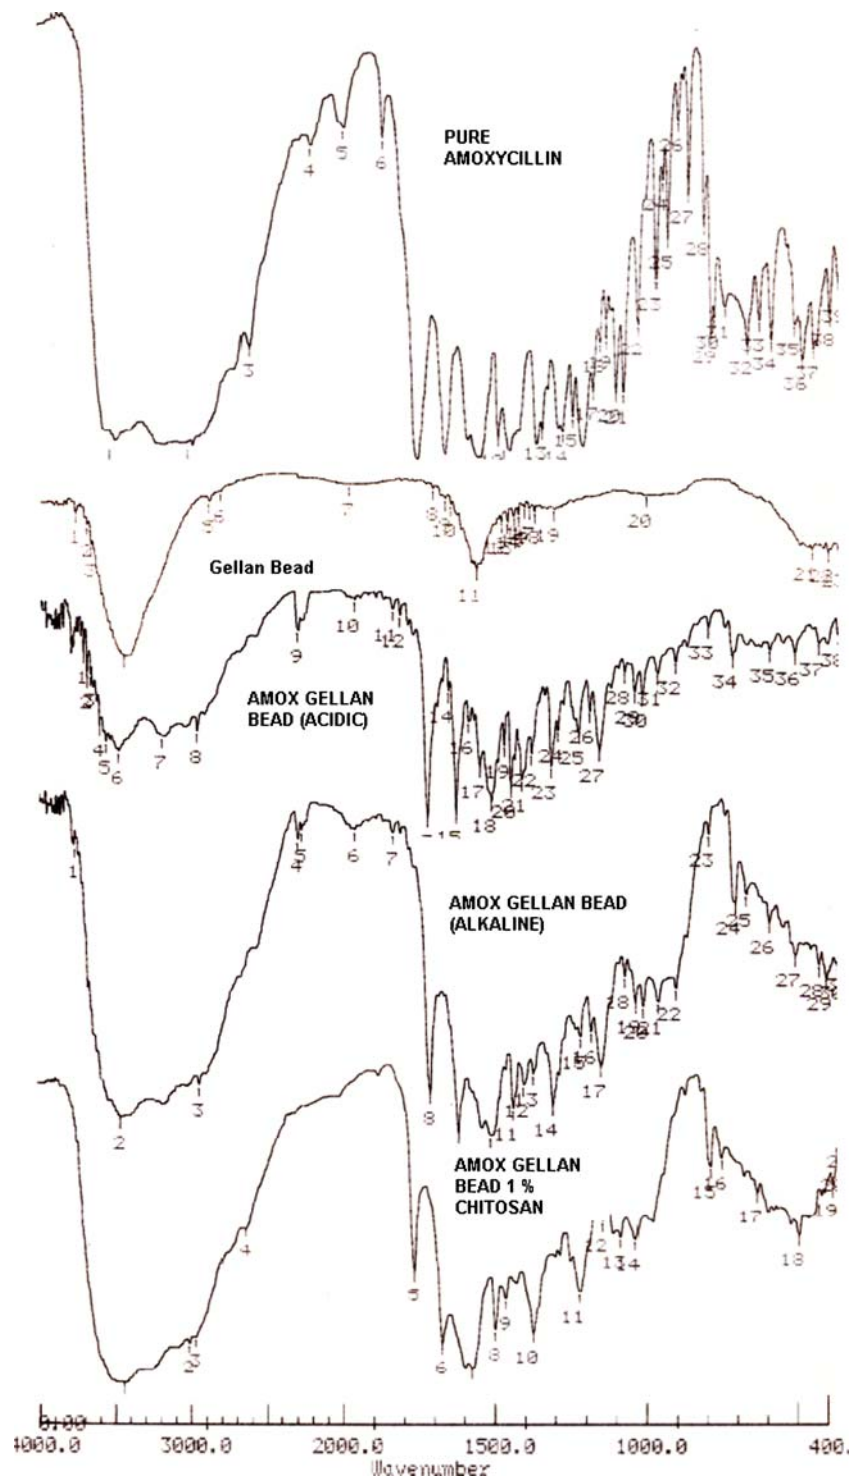


Fig. 4. FTIR spectra of amoxicillin gellan beads

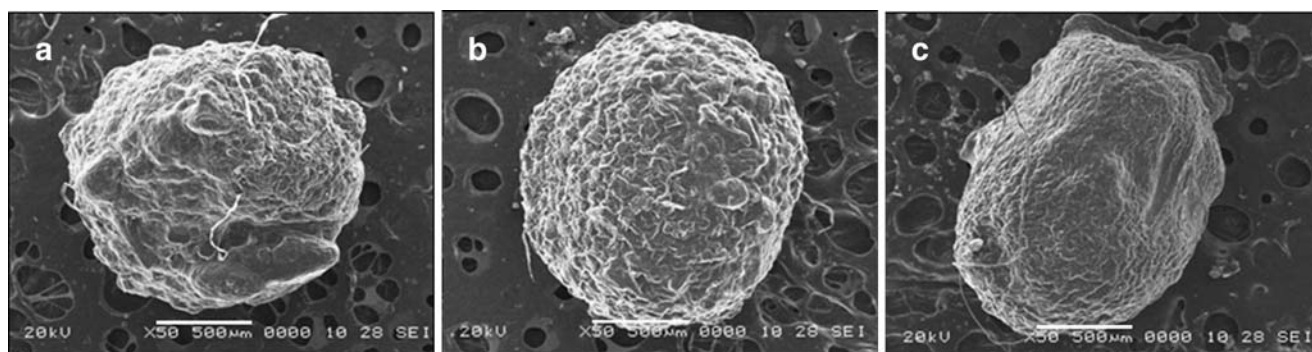


Fig. 5. SEM photographs of **a** amoxicillin gellan bead (acidic), **b** amoxicillin gellan bead (alkaline), and **c** chitosan-coated amoxicillin gellan bead

chitosan-coated beads and shifting of peak to higher temperature (125.5°C), which may be attributed to recrystallization of drug during chitosan coating and slower heat transfer within beads, respectively, are given in Fig. 2.

PXRD of amoxicillin gellan beads and chitosan-coated beads is shown in Fig. 3. The intensity of peaks referred for the crystalline nature of pure drug was decreased significantly in the formulations which can be due to the effect of polymer or formulation process. PXRD of amoxicillin showed characteristic peaks at about 12° , 14.5° , 18.5° , 23.5° , and 29° (2θ). Peak at 14.5° and 18.5° (2θ) was used to compare X-ray diffraction pattern of drug with beads. Significant reduction in peak intensities was observed in X-ray diffraction pattern of beads when compared with pure drug; PXRD of amoxicillin gellan beads (acidic and alkaline) shows peak at 14.5° and 18.5° (2θ) as in amoxicillin, but intensity of peak was decreased so it shows polymorphism. PXRD of 1% chitosan-coated amoxicillin gellan beads shows absence of characteristic peaks, indicating reduction in crystallinity of drug in the presence of thick coating of chitosan.

Fourier transfer infrared spectroscopy (FTIR) study that was carried out to determine interactions and structural changes in drug and excipient are given in Fig. 4. FTIR spectrum of pure amoxicillin showed characteristic peaks at $1,620\text{ cm}^{-1}$ ($\text{C}=\text{O}$ stretching), $3,292\text{ cm}^{-1}$ (sec. $-\text{NH}$ or $-\text{OH}$) and some prominent bands like $846\text{--}567\text{ cm}^{-1}$ ($-\text{CH}$ aromatic ring bending and heteroaromatics). Characteristic peaks of drug were also present in FTIR spectrum of beads with some

broadening and reduction in intensity, indicating the absence of chemical interactions between drug, polymer, and counterions after production of beads.

SEM photomicrographs of dried beads are shown in Fig. 5. The beads were spherical and dense with thick polymer coat. The drug-loaded gellan beads obtained using acidic medium was spherical but discrete with irregular rough surface due to leaching of drug in cross-linking solution forming large perturbations (Fig. 5a). The beads prepared in alkaline medium were large and spherical with more organized dense structure (Fig. 5b). The rough surface of chitosan-coated beads with minor wrinkles may be due to dehydration of the chitosan during drying (Fig. 5c). The increase in size of beads could be attributed to the increase in microviscosity of the polymeric dispersion with increase in gellan concentration.

Chitosan-coated gellan beads were subjected to swelling studies in both acidic and alkaline medium same as the gastric pH and microenvironment at the *H. pylori*-infected area, respectively. Gellan being an anionic polyelectrolyte, pH affects the conformation of gellan chains in acidic medium by increasing the shielding effect of repulsion of carboxyl groups which is also enhanced by the addition of cations and change in anionic nature of gellan determined by the dissociation of carboxyl group (23), whereas in alkaline medium gellan has high swelling properties (24). Chitosan with a degree of deacetylation $>87\%$ bears positive charge with high charge density in acidic medium and exists in the neutral form in alkaline medium. In gastric fluid (pH 1.2), the

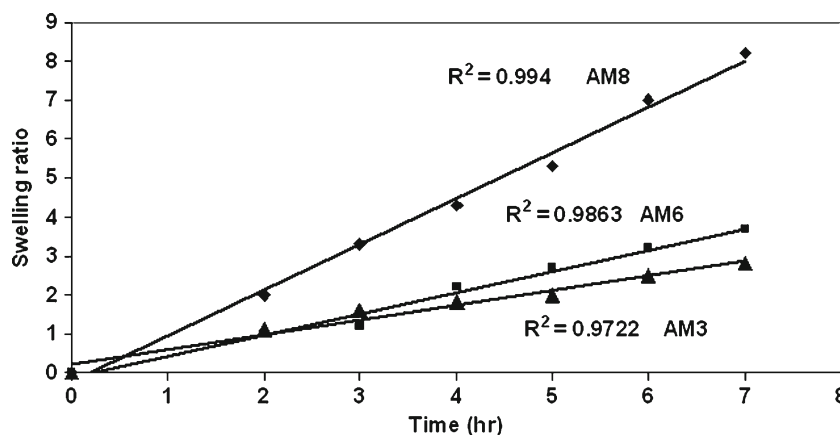


Fig. 6. Swelling study of chitosan-coated amoxicillin gellan beads at pH 1.2

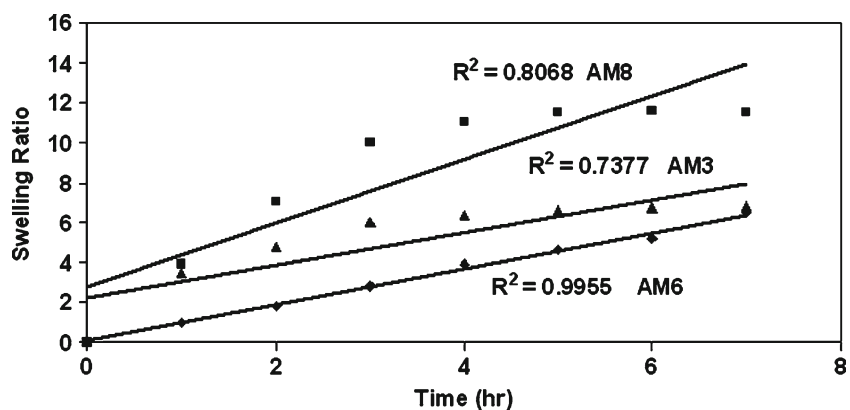


Fig. 7. Swelling study of chitosan-coated amoxicillin gellan beads at pH 7.4

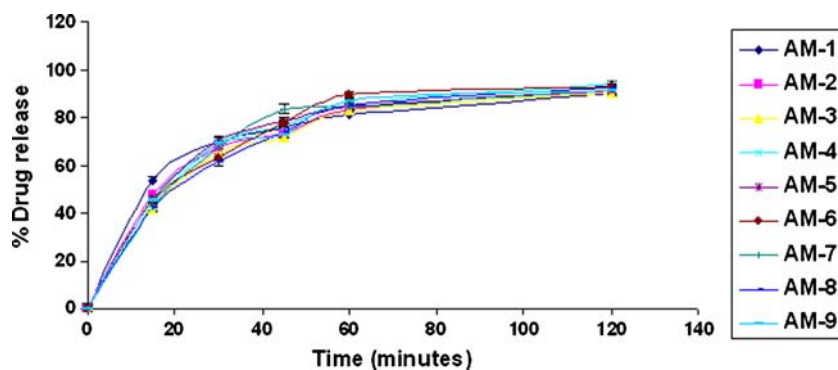


Fig. 8. *In vitro* drug release of amoxicillin gellan beads (acidic) in 0.1 N HCl

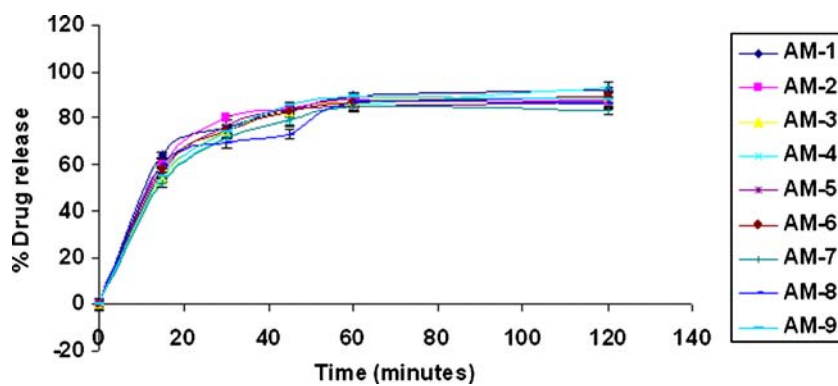


Fig. 9. *In vitro* drug release of amoxicillin gellan beads (alkaline) in 0.1 N HCl

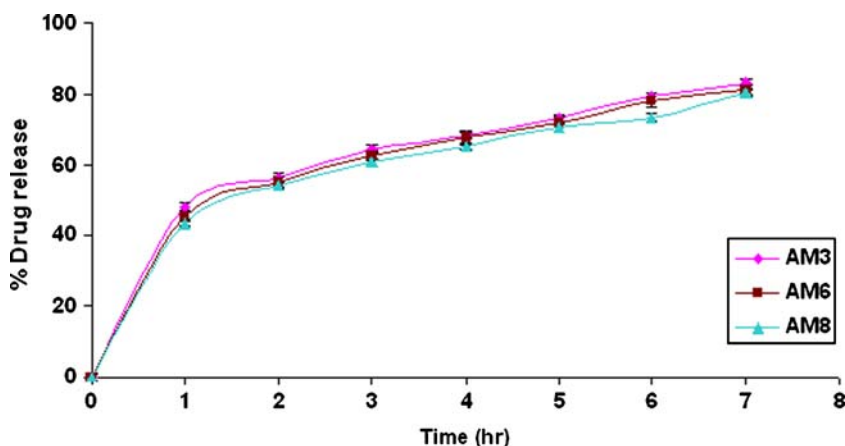


Fig. 10. *In vitro* drug release of chitosan-coated amoxicillin gellan beads in 0.1 N HCl

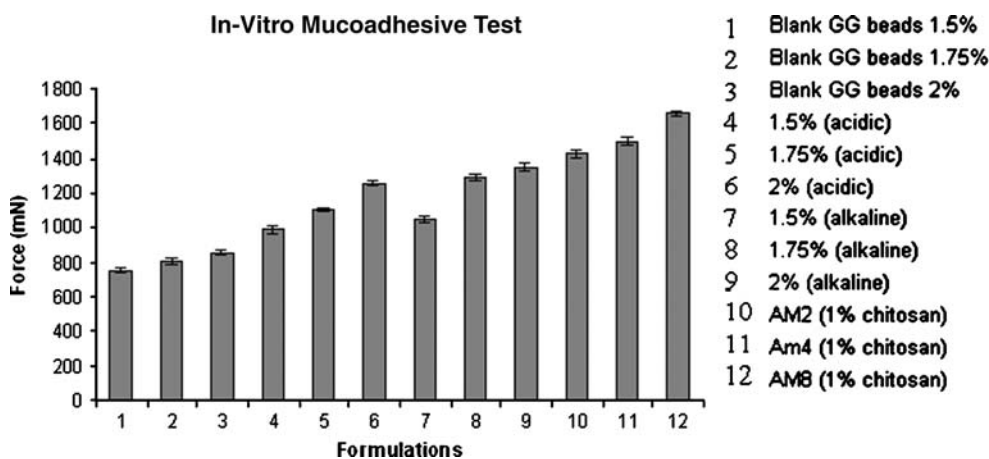


Fig. 11. *In vitro* evaluation of mucoadhesiveness of beads

positively charged matrix swells due to electrostatic repulsion between like charges and the osmotic effect of bound counterions. Chitosan have more protonation of amino groups in acidic medium and rapid swelling and erosion in alkaline medium (pH 7.4) (25,26). In acidic medium, chitosan-coated beads showed linear increase in swelling due to the combined effect of both the polymers (Fig. 6). In alkaline medium, chitosan-coated gellan beads have more swelling ratio than in acidic medium probably due to predominate swelling effect of gellan (Fig. 7).

When amoxicillin gellan beads and chitosan-coated amoxicillin gellan beads were evaluated for drug release in 0.1 N HCl, pH 1.2 (Figs. 8, 9, and 10), the beads prepared in acidic and alkaline cross-linking medium show more than 80% drug release at the end of 1 h with $t_{50\%}$ of 16 ± 3 min (acidic cross-linking medium) and 15 ± 1.5 min (alkaline cross-linking medium) which was mainly governed by acidic solubility of the drug. The delayed $t_{50\%}$ values of 65 ± 15 min of the chitosan-coated beads may be due to thick chitosan coating that not only minimizes penetration of dissolution

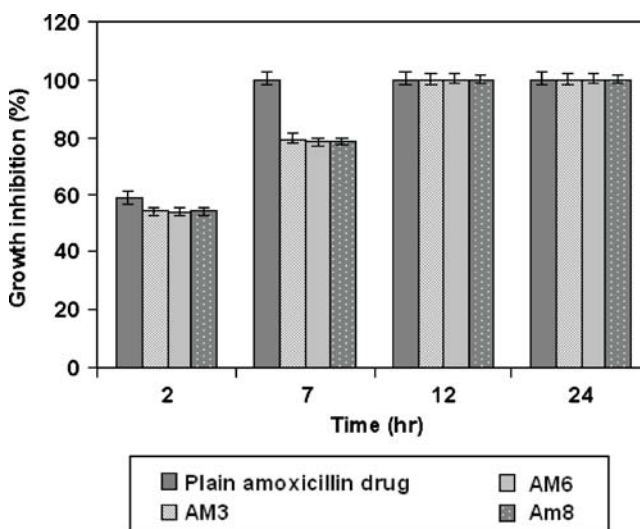


Fig. 12. *In vitro* growth inhibition study

medium but slows down the drug diffusion (27,28). In addition, the increased crystallinity of drug during chitosan coating may contribute for slow drug release. The chitosan-coated beads showed controlled drug release over a period of 7 h following the Peppas model ($r=0.9998$).

Mucoadhesive properties of amoxicillin gellan beads increased with increased concentration of gellan and drug, which was superior to the gellan beads without drug (Fig. 11). The gellan–gellan interactions produces compact beads reducing mucoadhesivity; this may also be the reason for poor mucoadhesivity of beads obtained using acidic medium than alkaline medium. Beads obtained from alkaline cross-linking medium showed improved mucoadhesivity; this might be due to (1) the decreased intramolecular cohesivity in gellan chains in the presence of drug and increase in adhesivity with stomach mucosa and (2) induced capillary forces due to channels formed by dissolution of drug (9,27). Chitosan-coated beads showed higher mucoadhesivity with increasing gellan amount, suggesting increased gellan–chitosan cross-linking and, in turn, availability of polymer chains for mucous membrane interactions (29,30). Batch AM8 having higher *in vitro* mucoadhesivity was further tested for *in vivo* mucoadhesion where more than 85% beads retained on stomach mucosa after 7 h.

The chitosan-coated drug-loaded beads that were evaluated for *in vitro* *H. pylori* growth inhibition studies are given in Fig. 12. The antimicrobial effect of amoxicillin and beads were determined in terms of percentage growth inhibition, which was calculated as the ratio of colony counts of a given mixture against that of tubes containing *H. pylori* alone. The percentage growth inhibition values decreased gradually with increasing incubation time. Beads showed about 54% and 79% growth inhibition at the end of 2 and 7 h, respectively, where pure amoxicillin showed comparatively more growth inhibition of about 59% and 100% after 2 and 7 h, respectively. However, the usual gastric residence of pure drug may be up to 2 h only. All batches showed complete growth inhibition after 12 h of incubation. Overall, the results suggested that chitosan-coated amoxicillin gellan beads prolonged drug release and gastric retention and showed better *H. pylori* growth inhibition than plain drug.

CONCLUSION

The present study gave an overview of formulating ready to use controlled release drug therapy for the treatment of *H. pylori* using calcium–gellan beads coated with 1% chitosan. The alkaline cross-linking medium showed improvement in entrapment efficiency. Chitosan-coated gellan beads containing amoxicillin showed good mucoadhesivity and complete growth inhibition of *H. pylori*. Thus, chitosan-coated amoxicillin gellan beads might be a promising drug delivery system for the treatment of *H. pylori* infection.

REFERENCES

- Marshall BJ. Unidentified curved bacilli in gastric epithelium in active chronic gastritis. *Lancet*. 1983;1:1273–5.
- Marshall BJ, Warren JR. Unidentified curved bacilli in the stomach of patients with gastritis and peptic ulceration. *Lancet*. 1984;1:1311–5.
- Vakil N, Cutler A. Ten-day triple therapy with ranitidine, bismuthcitrate, amoxicillin and clarithromycin in eradicating *Helicobacter pylori*. *Am J Gastroenterol*. 1999;94:1197–9.
- Amiji MM. Tetracycline-containing chitosan microspheres for local treatment of *Helicobacter pylori* infection. *Cellulose*. 2007;14:3–14.
- Umamaheshwari RB, Suman R, Jain NK. Anti *Helicobacter pylori* effect of mucoadhesive nanoparticle bearing amoxicillin in experimental gerbils. *AAPS PharmSciTech*. 2004;5:60–8.
- Bardonnet PL, Faivre V, Pugh WJ, Piffaretti JC, Falson F. Gastroretentive dosage forms: overview and special case of *Helicobacter pylori*. *J Control Release*. 2006;111:1–18.
- Chen CJ, Jacob J, Klein AB, Chayaprugs T, Mathiowitz E. Bioadhesive polymers for stomach targeted drug delivery. *Proceedings of the 24th International Symposium on Controlled Release of Bioactive Materials*, Stockholm; 1997. p. 259–260.
- Cuna M, Alonso MJ, Torres D. Preparation and *in vivo* evaluation of mucoadhesive microparticles containing amoxicillin–resin complexes for drug delivery to the gastric mucosa. *Eur J Pharm Biopharm*. 2001;51:199–205.
- Nagahara N, Akiyama Y, Tada M, Nakao M, Kitano M, Ogawa Y. Mucoadhesive microspheres containing amoxicillin for clearance of *Helicobacter pylori*. *Antimicrob Agents Chemother*. 1998;42:2492–4.
- Wang J, Tauchi Y, Deguchi Y, Morimoto K, Tabata Y, Ikada Y. Positively charged gelatin microspheres as gastric mucoadhesive drug delivery system for eradication of *H. pylori*. *Drug Deliv*. 2000;7:237–43.
- Maoa R, Tanga J, Swanson BG. Texture properties of high and low acyl mixed gellan gels. *Carbohydr Polym*. 2000;41:331–8.
- Domard A, Cartier N. Glucosamine oligomers: IV. Solid state-crystallization and sustained dissolution. *Int J Biol Macromol*. 1992;14:100–6.
- Hoppe-Seiler F. Chitin and chitosan. *Ber Dtsch Chem Ges*. 1994;27:3329–31.
- Roberts GAF. Structure of chitin and chitosan. In: Roberts GAF, editor. *Chitin chemistry*. Houndmills: MacMillan; 1992. p. 1–53.
- Rajinikanth PS, Balasubramanian J, Mishra B. Development and evaluation of a novel floating *in situ* gelling system of amoxicillin for eradication of *Helicobacter pylori*. *Int J Pharm*. 2007;335:114–22.
- Patel YL, Sher P, Pawar AP. The effect of drug concentration and curing time on processing and properties of calcium alginate beads containing metronidazole by response surface methodology. *AAPS PharmSciTech*. 2006;7:24–30.
- Liu Z, Lua W, Qianb L, Zhanga X, Zenga P, Pana J. *In vitro* and *in vivo* studies on mucoadhesive microspheres of amoxicillin. *J Control Release*. 2005;102:135–44.
- Rajinikanth PS, Mishra B. Preparation and *in vitro* characterization of gellan based floating beads of acetohydroxamic acid for eradication of *H. pylori*. *Acta Pharm*. 2007;57:413–27.
- Mergaud F, Trimoulet P, Lamouliatte H, Boyanova L. Bactericidal effect of amoxicillin on *Helicobacter pylori* in an *in vitro* model using epithelial cells. *Antimicrob Agents Chemother*. 1991;35:869–72.
- Pawar AP, Gadhe AR, Venkatachalam P, Sher P, Mahadik KR. Effect of core and surface cross-linking on the entrapment of metronidazole in pectin beads. *Acta Pharm*. 2008;58:75–85.
- Huanga Y, Tanga J, Swanson BG, Rasco BA. Effect of calcium concentration on textural properties of high and low acyl mixed gellan gels. *Carbohydr Polym*. 2003;54:517–22.
- Agnihotri SA, Jawalkar SS, Aminabhavi TM. Controlled release of cephalixin through gellan gum beads: effect of formulation parameters on entrapment efficiency, size, and drug release. *Eur J Pharm Biopharm*. 2006;63:249–61.
- Yamamoto F, Cunha RL. Acid gelation of gellan: effect of final pH and heat treatment conditions. *Carbohydr Polym*. 2007;68:517–27.
- Patil S, Sharma S, Nimbalkar A, Pawar A. Study of formulation variables on properties of drug–gellan beads by factorial design. *Drug Dev Ind Pharm*. 2006;32:315–26.
- Chandy T, Sharma CP. Chitosan—as a biomaterial. *Biomater Artif Cells Artif Organs*. 1990;18:1–24.
- Yao KD, Peng T. Swelling kinetics and release characteristics of crosslinked chitosan:polyether polymer network (semi-

- IPN) hydrogels. *J Polym Sci Part A Polym Chem.* 1994;32:1213–23.
27. Chena S, Liu M, Jin S, Wang B. Preparation of ionic-crosslinked chitosan-based gel beads and effect of reaction conditions on drug release behaviors. *Int J Pharm.* 2008;349:180–7.
 28. Shu XZ, Zhu KJ. Controlled drug release properties of ionically cross-linked chitosan beads: the influence of anion structure. *Int J Pharm.* 2002;233:217–25.
 29. Hagerstrom H, Paulsson M, Edsman K. Evaluation of mucoadhesion for two polyelectrolyte gels in simulated physiological conditions using a rheological method. *Eur J Pharm Sci.* 2000;9:301–9.
 30. Keely S, Rullay A, Wilson C, Carmichael A, Carrington S, Corfield A, *et al.* *In vitro* and *ex vivo* intestinal tissue models to measure mucoadhesion of poly(methacrylate) and *N*-trimethylated chitosan polymers. *Pharm Res.* 2005;22:38–49.