



Published in final edited form as:

Angew Chem Int Ed Engl. 2010 December 3; 49(49): 9401–9404. doi:10.1002/anie.201004693.

One-Step Modification of Superhydrophobic Surfaces by a Mussel-Inspired Polymer Coating

Dr. Sung Min Kang,

Department of Chemistry and Graduate School of Nanoscience & Technology, KAIST, Daejeon, 305-701, Korea

Inseong You,

Department of Chemistry and Graduate School of Nanoscience & Technology, KAIST, Daejeon, 305-701, Korea

Dr. Woo Kyung Cho,

Department of Medicine, Brigham and Women's Hospital, Harvard Medical School, Harvard-MIT Division of Health Sciences and Technology, 65 Landsdowne Street PRB 313, Cambridge, Massachusetts 02139, USA

Hyun Kyong Shon,

Center for Nano-Bio Technology, Korea Research Institute of Standards and Science, Daejeon, 305-600, Korea

Dr. Tae Geol Lee,

Center for Nano-Bio Technology, Korea Research Institute of Standards and Science, Daejeon, 305-600, Korea

Prof. Dr. Insung S. Choi,

Department of Chemistry, KAIST, Daejeon, 305-701, Korea


Prof. Dr. Jeffery M. Karp, and

Department of Medicine, Brigham and Women's Hospital, Harvard Medical School, Harvard-MIT Division of Health Sciences and Technology, 65 Landsdowne Street PRB 313, Cambridge, Massachusetts 02139, USA

Prof. Dr. Haeshin Lee*

Department of Chemistry and Graduate School of Nanoscience & Technology, KAIST, Daejeon, 305-701, Korea

Abstract

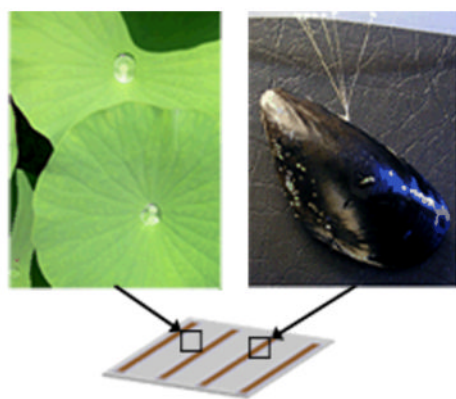

Micropatterned Superhydrophobic Surface



Water Adhesion Water Collection

A bio-inspired approach for superhydrophobic surface modification was investigated. Hydrophilic conversion of the superhydrophobic surface was easily achieved through this method, and the superhydrophobic-hydrophilic alternating surface was generated by the method combined with soft-lithography. The resulting patterned surface showed high water adhesion property in addition to superhydrophobic property.

Keywords

Superhydrophobicity; Surface modification; Bio-inspired coating; Soft-lithography; High-water adhesion

Mussels, a promiscuous, underwater fouling organism, attach to virtually any natural or synthetic organic/inorganic substrates. Major components of mussels' adhesive pads include proteins that contain the unusual amino acid, 3,4-dihydroxy-L-phenylalanine (DOPA).[1] In particular, *Mytilus edulis* foot protein-5 (Mefp-5), a protein located at a distal side of adhesive pads that attaches to opposing substrates, shows an exhaustive repeat of DOPA-lysine.[1c,d] Recently, Lee and Messersmith identified dopamine that contains both side chain functionalities of DOPA and lysine and reported a new surface chemistry called polydopamine coating.[2] Unlike other surface chemistries, polydopamine modified a wide variety of material surfaces including noble metals, metal oxides, ceramics, and synthetic polymers on which protein immobilization, metallization, bio-mineralization, and cell adhesion were demonstrated.[2] Albeit the unparalleled capability of polydopamine, functionalization of superhydrophobic surfaces remains unexplored.

Superhydrophobic surfaces have received significant attention due to their extraordinary surface properties. A great deal of effort has been made to fabricate such surfaces.[3] The well-known biological model system of superhydrophobicity is the lotus leaf which exhibits a static contact angle for water greater than 150°. Most superhydrophobic surfaces have been prepared by various lithographic techniques: photolithography,[4] e-beam lithography,[5] assembly of colloidal particles,[6] capillary lithography and others.[7] The non-wetting

properties of superhydrophobic surfaces have shown a variety of applications as anti-reflectivity,[8] self-cleaning,[9] anti-fouling,[10] a long lifetime microfluidic valve and so on.[11] Despite the large effort to develop methods to prepare superhydrophobic surfaces and to seek useful applications, few strategies to tailor the superhydrophobic surface properties have been developed. In particular, a facile strategy to modify superhydrophobic surfaces that can be integrated with widely implemented soft-lithographic techniques has not been achieved.

Herein, we report a one-step, solution-based surface chemistry that modifies superhydrophobic surfaces (Scheme 1). The surface chemistry to enable this innovation is inspired by adhesion mechanisms of marine mussels, and is compatible with the established soft-lithography techniques. By immersing substrates into a solution containing dopamine, a mussel-mimetic adhesive molecule, the superhydrophobic surface is immediately transformed into a hydrophilic substrate. By partial exposure of the substrate via a soft-lithographic technique, micromolding in capillaries (MIMIC),[12] the micropatterned surface remained superhydrophobic but was found to be adhesive to water. Similar to the mechanism of water collection by a desert beetle, *Stenocara sp.*, the modified surface can be used to capture, guide, and collect water droplets.[13]

We hypothesized that polydopamine formed by oxidative self-polymerization of dopamine could modify superhydrophobic surfaces as it demonstrated functionalization of all other tested surfaces. For preparation of superhydrophobic surfaces, anodic aluminum oxide (AAO) membranes were utilized as templates on which fluorosilane was coated by a gas-phase deposition.[14] The resulting AAO superhydrophobic surfaces were immersed into the dopamine solution to test the hypothesis. The superhydrophobic surface became hydrophilic with the dramatic decrease in contact angle from $158.5 \pm 2.8^\circ$ to $37.3 \pm 2.6^\circ$ after 18 hr polydopamine functionalization (Figure 1A). The partially modified surface prepared by half immersion of the superhydrophobic substrate into the dopamine solution showed drastic differences in the behavior of water droplets on the surface (Figure 1B). This conversion of surface properties supported the hypothesis, clearly demonstrating that the polydopamine can control surface hydrophobicity. The surface was characterized by scanning electron microscopy (SEM) and X-ray photoelectron spectroscopy (XPS). SEM images showed that polydopamine was coated on top and side-wall of porous AAO nanostructures (Figure 1C). The XPS spectra revealed the change in surface chemical compositions caused by the polydopamine coating; the photoelectron peaks detected in the unmodified surface originated from the AAO substrate, Al 2s (119.9 eV), Al 2p (74.5 eV), and O 1s (529.9 eV), and from the fluorosilane, F 1s (685.6 eV) and C 1s (290.5 eV for C-F). In addition to the observed peaks, a newly appeared N 1s peak was observed in the polydopamine-modified surface (Figure 1D, right).

Quantitative analysis of the surface chemical composition unambiguously supported the polydopamine functionalization; nitrogen and carbon were increased due to the presence of polydopamine (N 1s: 0.98 \rightarrow 3.74%, C 1s: 6.56 \rightarrow 48.2%) and aluminum and fluorine from the underlying layer were decreased (Al 2p: 14.26 \rightarrow 5.26%, F 1s: 41.2 \rightarrow 14.09%).

The demonstrated one-step, in-solution functionalization of superhydrophobic surface can be easily combined with widely used soft-lithographic techniques. MIMIC can be a suitable technique to control the properties of the AAO superhydrophobic surfaces at a micrometer scale. MIMIC was chosen among a number of other soft-lithographic techniques because it involves a solution process in which the solution is injected into micro-capillaries. Thus, it can be expected that the solution of interest (i.e. polydopamine) in the capillaries can create microscale patterns on the superhydrophobic surfaces with ease.

Applying an alkaline dopamine solution (2 mg/mL) into the microchannels followed by incubation for 18 hrs generated line patterns with 50 μm width (Figure 2A). This superhydrophobic (unmodified AAO) – hydrophilic (polydopamine) alternating micropatterns were characterized by time-of-flight secondary ion mass spectrometry (ToF-SIMS) (Figure 2B). ToF-SIMS provided images that exhibited clear 50- μm -width line patterns in which a strong nitrogen-containing CN^- fragment ($m/z = 26$) was detected from the polydopamine-modified area (Figure 2B, left). Detection of nitrogen in ToF-SIMS experiments from the modified area is consistent with the XPS result in which the N 1s photoelectron peak appeared (Figure 1D, right). Another characteristic mass fragment from the polydopamine-modified region was $\text{C}_8\text{H}_5\text{N}_2\text{O}^-$ ($m/z = 145$) (Figure 2B, right). The exact chemical structure of the ion fragment is not clear yet, but may be an indole-like structure originated from the polydopamine layer.[2] The micropatterned surface remained superhydrophobic with a slight decrease in contact angle from $158.5 \pm 2.8^\circ$ to $151.4 \pm 1.2^\circ$ (Figure 2C, lower, left). Interestingly, however, the wetting property of the functionalized superhydrophobic surfaces was considerably different. In contrast to the water droplet on the unmodified superhydrophobic surfaces which rapidly roll down an incline due to gravity (Figure 2C, upper), a droplet placed on the patterned surface did not roll even when the surface was tilted vertically (90° tilt, Figure 2C, lower, middle) or was inverted (180° tilt, Figure 2C, lower, right). The 90° tilted surface could hold up to a 20 mg water droplet. The alternating superhydrophobic and hydrophilic areas on the surface created capillary interactions (i.e. surface tension) between the droplet and the polydopamine-modified area. This interfacial surface energy is a key contributor to the observed adhesion of water droplets. Determination of surface energy created by the alternating micropatterns on the superhydrophobic surface is a challenging task. We utilized the law of energy conservation. The law states that the amount of energy in a system remains constant. The falling water droplet loses energy by interacting (i.e. collision) with the unmodified superhydrophobic surface (Figure 3B). The difference in height ($h_1 - h_2$) indicated the energy lost, which can be calculated by potential energy difference: $(h_1 - h_2) \cdot g \cdot m$, where h_1 is 1.73×10^{-2} m, h_2 is 5.76×10^{-3} m, g is 9.8 m/s², and m is 1.25×10^{-5} kg. However, the falling water droplet with the same initial height (h_1) onto the modified superhydrophobic remains attached on the surface. Thus, to safely hold the droplet, the surface energy (E_{super}) contributed by the micropatterns should be equal or greater than the potential energy after collision (mgh_2) otherwise the water droplet would be detached from the modified surface. Time-resolved observation of the falling water droplets using a high-speed camera enabled us to reveal the surface energy. The calculated E_{super} is equal to or greater than mgh_2 , which is 706 nJ. Considering the contact surface area, 1.81×10^{-5} m², of the water droplet, the calculated surface tension of the patterned superhydrophobic surface was 39 mN m⁻¹, which is similar to the surface energy of synthetic polymers for example poly(vinyl chloride) (PVC) and poly(methyl methacrylate) (PMMA).[15] Other causes for energy loss such as interactions between water molecules, friction at the air- water interface were excluded.

The polydopamine-modified superhydrophobic surface could be used as a water-capturing device. When vapor-like fine water was continuously sprayed to the modified superhydrophobic surface (400 μm in width at center), water was concentrated and rolled specifically down along the polydopamine-coated area (Figure 3E). The ability of water collection utilizing hydrophilic micropatterns on superhydrophobic surface mimics the primary water collection mechanism utilized by the Namib desert beetle that lives in an extremely dry environment.[13]

In conclusion, we demonstrated a facile, one-step superhydrophobic surface modification strategy utilizing the adhesion mechanism of mussels. Hydrophilic conversion of the superhydrophobic surface was easily achieved by polydopamine, a functional polymeric mimic of the mussel adhesive protein, *Mytilus edulis* foot protein-5 (Mefp-5). This

superhydrophobic surface modification is compatible with widely used soft-lithographic techniques such as MIMIC to enable facile functionalization of superhydrophobic surfaces. The modified surface remained to be superhydrophobic but showed high-water adhesion property. A general approach to determine surface energy of the modified superhydrophobic surface was demonstrated. Finally, the modified superhydrophobic surface can be used as a part of a water-capturing device that mimics the mechanism of collecting water shown in the cuticle of the Namib desert beetle. This new superhydrophobic surface chemistry can be applied to potentially advance superhydrophobic surface engineering for a variety of applications.

Acknowledgments

This study was supported by National Research Foundation of S. Korea: World Class University Program (WCU, R31-2008-000-10071-0, HL), Molecular-level Interface Research Center (2010-0001954, HL), by The Ministry of Health and Welfare (920340, HL), and by NSF NIRT grant 0609182 (JMK), and NIH grant GM086433 (JMK). We thank Prof. Choongsik Bae at KAIST for high-speed camera analysis.

References

1. a) Waite JH. *Ann NY Acad Sci.* 1999; 875:301. [PubMed: 10415577] b) Papov VV, Diamond TV, Biemann K, Waite JH. *J Biol Chem.* 1995; 270:20183. [PubMed: 7650037] c) Waite JH, Qin XX. *Biochemistry.* 2001; 40:2887. [PubMed: 11258900] (d) Waite JH. *Integr Comp Biol.* 2002; 42:1172. [PubMed: 21680402] (e) Harrington MJ, Masic A, Holten-Andersen N, Waite JH, Fratzl P. *Science.* 2010; 328:216. [PubMed: 20203014]
2. a) Lee H, Dellatore SM, Miller WM, Messersmith PB. *Science.* 2007; 318:426. [PubMed: 17947576] b) Waite JH. *Nature Mater.* 2008; 7:8. [PubMed: 18167496] c) Ryu J, Ku SH, Lee H, Park CB. *Adv Funct Mater.* 2010; 20:2132. d) Lee H, Rho J, Messersmith PB. *Adv Mater.* 2009; 21:431. [PubMed: 19802352] e) Ku SH, Ryu J, Hong SK, Lee H, Park CB. *Biomaterials.* 2010; 31:2535. [PubMed: 20061015]
3. a) Ma ML, Hill RM. *Curr Opin Colloid Interface Sci.* 2006; 11:193. b) Roach P, Shirtcliffe NJ, Newton MI. *Soft Matter.* 2008; 4:224. c) Zhang X, Shi F, Niu J, Jiang YG, Wang ZQ. *J Mater Chem.* 2008; 18:621.
4. a) Notsu H, Kubo W, Shitanda I, Tatsuma T. *J Mater Chem.* 2005; 15:1523. (b) Oner D, McCarthy TJ. *Langmuir.* 2000; 16:7777.
5. Martines E, Seunarine K, Morgan H, Gadegaard N, Wilkinson CDW, Riehle MO. *Nano Lett.* 2005; 5:2097. [PubMed: 16218745]
6. a) Shiu JY, Kuo CW, Chen PL, Mou CY. *Chem Mater.* 2004; 16:561. b) Wang JX, Wen YQ, Hu JP, Song YL, Jiang L. *Adv Funct Mater.* 2007; 17:219.
7. a) Pozzato A, Dal Zilio s, Fois G, Vendramin D, Mistura G, Belotti M, Chen Y, Natali M. *Microelectron Eng.* 2006; 83:884. b) Lee S, Kwon TH. *J Micromech Microeng.* 2007; 17:687. c) Jeong HE, Kwak R, Kim JK, Suh KY. *Small.* 2008; 4:1913. [PubMed: 18937242]
8. a) Nakajima A, Abe K, Hashimoto K, Watanabe T. *Thin Solid Films.* 2000; 376:140. b) Bravo J, Zhai L, Wu ZZ, Cohen RE, Rubner MF. *Langmuir.* 2007; 23:7293. [PubMed: 17523683]
9. a) Furstner R, Barthlott W, Neinhuis C, Walzel P. *Langmuir.* 2005; 21:956. [PubMed: 15667174] b) Miyachi Y, Ding B, Shiratori S. *Nanotechnology.* 2006; 17:5151.
10. a) Wang YL, Sims CE, Marc P, Bachman M, Li GP, Allbritton NL. *Langmuir.* 2006; 22:8257. [PubMed: 16952271] b) Sun TL, Tan H, Han D, Fu Q, Jiang L. *Small.* 2005; 1:959. [PubMed: 17193377]
11. a) Washizu M. *IEEE Trans Ind Appl.* 1998; 34:732. b) Hong X, Gao XF, Jiang L. *J Am Chem Soc.* 2007; 129:1478. [PubMed: 17243677] c) Feng L, Zhang ZY, Mai ZH, Ma YM, Liu BQ, Jiang L, Zhu DB. *Angew Chem Int Ed.* 2004; 43:2012. d) Lu CM, Xie YB, Yang Y, Cheng MMC, Koh CG, Bai YL, Lee LJ. *Anal Chem.* 2007; 79:994. [PubMed: 17263327]
12. a) Xia YN, Whitesides GM. *Annu Rev Mater Sci.* 1998; 28:153. b) Xia YN, Whitesides GM. *Angew Chem Int Ed.* 1998; 37:551.
13. Parker AR, Lawrence CR. *Nature.* 2001; 414:33. [PubMed: 11689930]

14. Cho WK, Park S, Jon S, Choi IS. *Nanotechnology*. 2007; 18:395602. [PubMed: 21730422]
15. Owens DK, Wendt RC. *J Appl Polym Sci*. 1969; 13:1741.

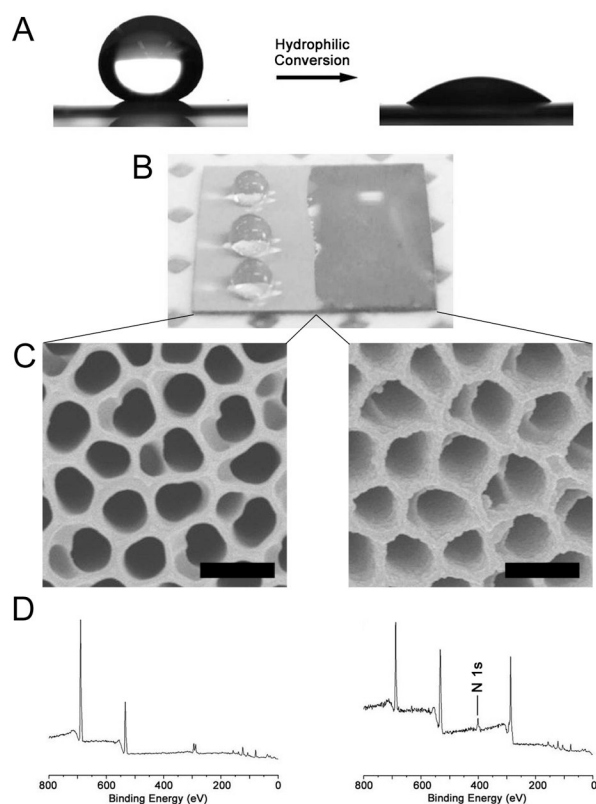


Figure 1. Characterization of the polydopamine-functionalized superhydrophobic surface. (A) Contact angle images of superhydrophobic surface before and after polydopamine coating. (B) A photograph of wetting properties of water droplets on the partially modified superhydrophobic AAO surface. (C) SEM images of the unmodified superhydrophobic AAO surface (left), and the modified surface (right). The scale bar is 500 nm. (D) XPS spectra of the unmodified (left) and polydopamine-functionalized surface (right).

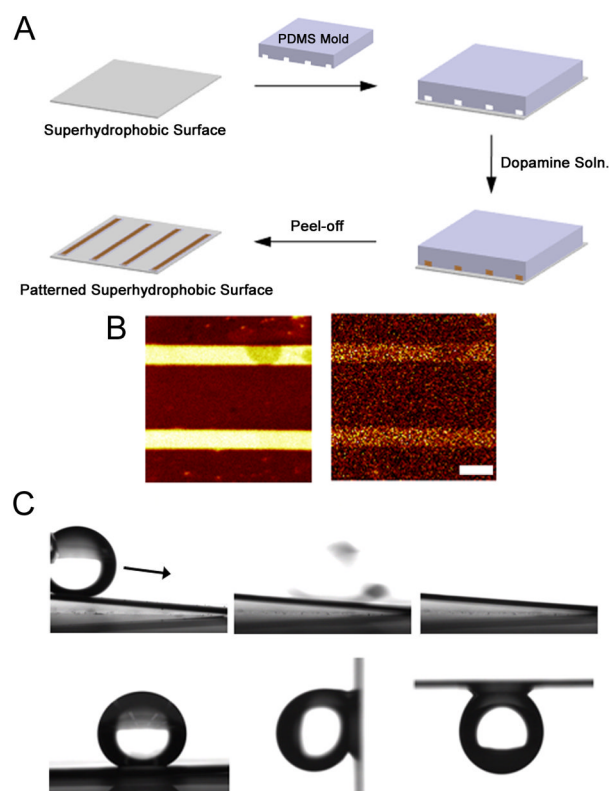


Figure 2. Micropatterning of superhydrophobic surfaces and wetting properties. (A) Schematic description for preparing polydopamine-patterned superhydrophobic surface and (B) ToF-SIMS images of the polydopamine-patterned superhydrophobic surface: CN^- (left) and $\text{C}_8\text{H}_5\text{N}_2\text{O}^-$ (right) (The scale bar is $100\ \mu\text{m}$) (C,D) Rolling vs. staying water droplets: the water droplet on the unmodified superhydrophobic rapidly rolled down when the surface was tilted (4°) (C); however, the water droplet on the polydopamine-micropatterned superhydrophobic surface remained attached even when the surface was tilted at 90° and 180° (D).

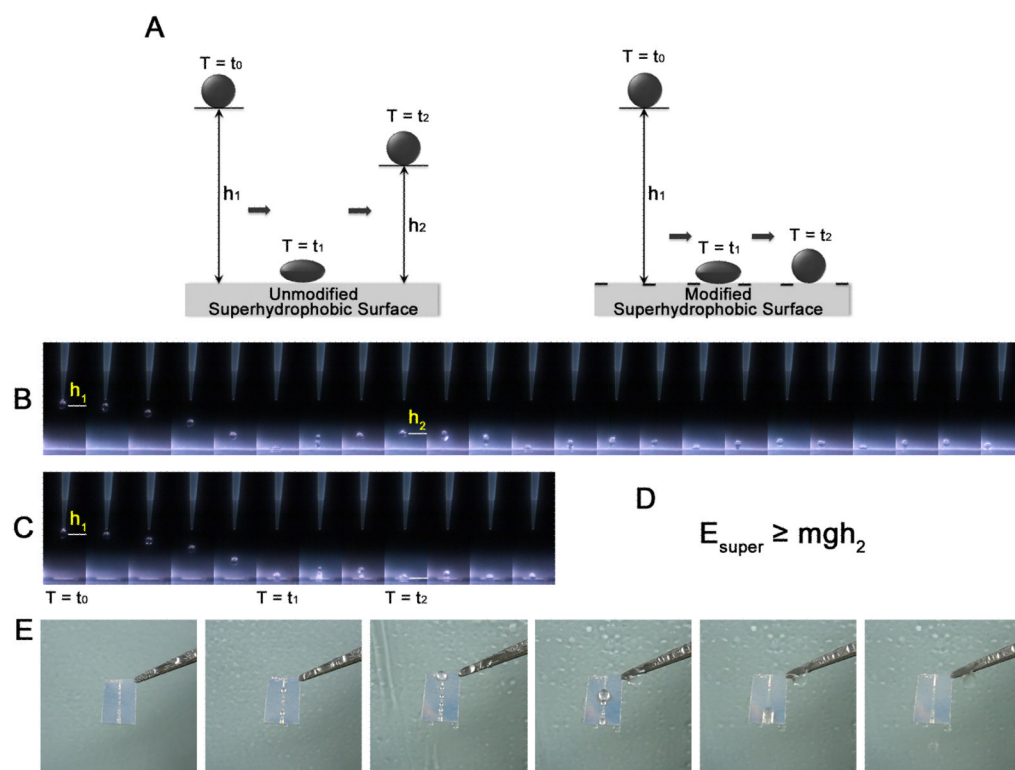
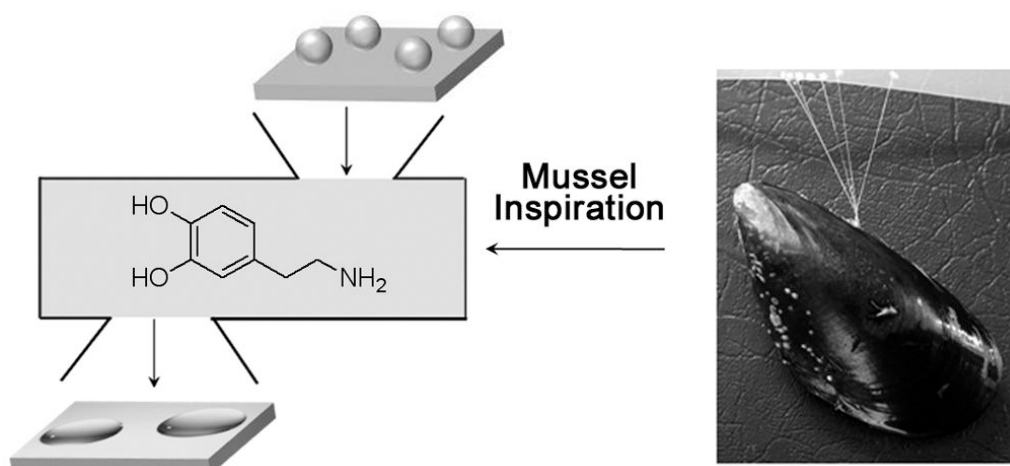


Figure 3. Determination of the surface energy of the micropatterned superhydrophobic surface. (A) Schematic description of the behavior of a falling water droplet on the unmodified superhydrophobic and patterned superhydrophobic/hydrophilic surfaces. Sequences of time-resolved high-speed camera images (12 ms interval) of the falling water droplet on the (B) superhydrophobic surface and (C) micropatterned superhydrophobic surface. (D) An equation for calculation of surface energy generated by polydopamine micropatterns. (E) The ability of capturing and collecting water by the micropatterned superhydrophobic surface is demonstrated. Water droplets approaching to the surface from air were collected in the modified area. As the size of water droplets became large, the droplet started to roll down along the track of polydopamine, resulting in the collection of water.

**Scheme 1.**

Mussel-inspired superhydrophobic surface modification. One-step immersion of a superhydrophobic surface into a solution of dopamine, a functional mimic of mussel adhesive proteins, modifies superhydrophobic surfaces.