

# Activated drying in hydrophobic nanopores and the line tension of water

Ludvine Guillemot<sup>a</sup>, Thierry Biben<sup>a</sup>, Anne Galarneau<sup>b</sup>, Gérard Vigier<sup>c</sup>, and Élisabeth Charlaix<sup>d,1</sup>

<sup>a</sup>Laboratoire de Physique de la Matière Condensée et Nanostructures, Université Lyon 1, Centre National de la Recherche Scientifique Unité Mixte de Recherche 5586, 69622 Villeurbanne Cedex, France; <sup>b</sup>Institut Charles Gerhardt Montpellier, Unité Mixte de Recherche 5253 Université Montpellier 2, Ecole Nationale Supérieure de Chimie de Montpellier, Université Montpellier 1, 34296 Montpellier Cedex 5, France; <sup>c</sup>Laboratoire Matériaux Ingénierie et Sciences, Institut National des Sciences Appliquées de Lyon, 69621 Villeurbanne Cedex, France; and <sup>d</sup>Laboratoire Interdisciplinaire de Physique, Université Joseph Fourier, Unité Mixte de Recherche 5588, 38402 St. Martin d'Heres, France

Edited by Pablo Gaston Debenedetti, Princeton University, Princeton, NJ, and approved October 4, 2012 (received for review May 6, 2012)

**We study the slow dynamics of water evaporation out of hydrophobic cavities by using model porous silica materials grafted with octylsilanes. The cylindrical pores are monodisperse, with a radius in the range of 1–2 nm. Liquid water penetrates in the nanopores at high pressure and empties the pores when the pressure is lowered. The drying pressure exhibits a logarithmic growth as a function of the driving rate over more than three decades, showing the thermally activated nucleation of vapor bubbles. We find that the slow dynamics and the critical volume of the vapor nucleus are quantitatively described by the classical theory of capillarity without adjustable parameter. However, classical capillarity utterly overestimates the critical bubble energy. We discuss the possible influence of surface heterogeneities, long-range interactions, and high-curvature effects, and we show that a classical theory can describe vapor nucleation provided that a negative line tension is taken into account. The drying pressure then provides a determination of this line tension with much higher precision than currently available methods. We find consistent values of the order of  $-30$  pN in a variety of hydrophobic materials.**

drying transition | hydrophobicity | kinetics | nanobubbles | mesoporous silica

A remarkable property of water is its ability to form nanosize bubbles, or cavities, on hydrophobic bodies (1). Since their first direct observations through atomic force microscopy about a decade ago (2, 3), surface nanobubbles on hydrophobic surfaces have raised considerable interest, and they are believed to play a major role in surface-driven phenomena, such as boundary slip-page of water flows, heat transfer at walls, vaporization and boiling, surface cleaning, etc. (4, 5). In a different context, the evaporation of water in the vicinity of hydrophobic bodies has been studied as a core mechanism for the hydrophobic interaction mediated by water (6–8), which plays a central role in biological matter. The formation of cavities able to bridge hydrophobic units provides a driving force for protein folding and supermolecular aggregation (9). Simulation examples of such drying-induced phenomena include the collapse of a polymer chain, multidomain proteins, and hydrophobic particles (9–13).

Despite their direct observation, the easy formation and the high stability of nanobubbles on hydrophobic bodies still raise fundamental questions (5, 14, 15). Because of significant theoretical work, it is now established that, at the scale of the nanometer, macroscopic concepts apply: hydrophobicity is described by interfacial energies, and the drying transition in hydrophobic confinement is a first-order transition triggered by the nucleation of a critical vapor bubble (1). The energy barrier limiting the kinetics of this transition is a strong signature of nanobubbles properties. Evaporation kinetics has also been pointed out as the most direct measure of the importance of hydrophobic collapse in protein folding (9). However, rate effects in the drying transition have not received much attention. A few numerical studies have addressed the rate of evaporation of liquid water confined between hydrophobic plates (16–19). The nucleation barrier has

been measured with different methods, and it has been shown to increase strongly with the slit separation. The classical theory of capillarity has been shown to overestimate the numerical findings (17, 18). The classical capillarity is a key framework to understand nucleation phenomena, but it is based on macroscopic considerations and does not include specific features, like fluctuations or line energies that can affect interfaces at nanometric scales. There is, however, no consensus about the leading effect at these scales. Fluctuations are invoked in ref. 18 to explain the observed nucleation barrier reduction, whereas line tension is shown to account for the observed deviations in ref. 19. Experimental studies are scarce, because the rate or time variable is generally ignored in studies of adsorption and desorption of confined liquids.

Here, we use highly ordered nanoporous silicas to study the dynamics of water evaporation in hydrophobic confinement. Molecule-templated silicas (MTSs) have quasi-1D mesopores shaped in the form of cylinders of monodisperse radius adjustable from 1 to 5 nm. These model materials have been used as nanoscale laboratory to study the phase diagram of confined liquids (20, 21). In previous works (22, 23), we used silane-grafted MCM-41 (Mobil Crystalline Material 41) to study water confined by hydrophobic walls. Liquid water penetrates into the nanopores at high pressure, reaching 500 bars for nanometer-sized pores. The intrusion pressure of water in the cylindrical pores scales as the inverse of their radius down to radii of 1.3 nm, according to the Laplace law of capillarity (Eq. 1):

$$P_{\text{int}} = -\frac{2\gamma_{\text{lv}}\cos\theta}{R_{\text{p}}} = 2\frac{\gamma_{\text{sl}} - \gamma_{\text{sv}}}{R_{\text{p}}}, \quad [1]$$

with  $\gamma_{\text{sl}}$ ,  $\gamma_{\text{sv}}$ , and  $\gamma_{\text{lv}}$  being the solid/liquid, solid/vapor and liquid/vapor surface tensions, respectively. This intrusion law shows the model character of hydrophobized MTS to provide a geometrically and energetically well-defined confinement. The drying transition is obtained by lowering the pressure. Liquid water becomes metastable and finally, empties the nanopores at a pressure  $P_{\text{ext}}$  lower than the intrusion pressure (24). The drying pressure  $P_{\text{ext}}$  is not described by the Young–Laplace law (1) and increases with temperature (23). Those features are in good qualitative agreement with a drying triggered by the nucleation of a critical vapor bubble on the pore walls.

Author contributions: G.V. and É.C. designed research; L.G. and T.B. performed research; T.B. and A.G. contributed new reagents/analytic tools; L.G., G.V., and É.C. analyzed data; and É.C. wrote the paper.

The authors declare no conflict of interest.

This article is a PNAS Direct Submission.

<sup>1</sup>To whom correspondence should be addressed. E-mail: elisabeth.Charlaix@ujf-grenoble.fr.

This article contains supporting information online at [www.pnas.org/lookup/suppl/doi:10.1073/pnas.1207658109/-DCSupplemental](http://www.pnas.org/lookup/suppl/doi:10.1073/pnas.1207658109/-DCSupplemental).


We report here investigations of the drying kinetics of the hydrophobic nanopores. For this study, we have developed a device that allows us to perform intrusion–extrusion cycles at finite rates ranging from 0.1 to 100 s<sup>-1</sup> (25). The dynamic study allows us to get quantitative access to the volume of the critical vapor bubbles initiating the drying and the energy barrier. Although the volume of the critical bubbles is remarkably well-predicted by the classical theory of capillarity, the latter overestimates considerably the energy barrier for their formation. We show that the low energy barrier observed is a strong support of a negative line tension of water on the silane monolayer. The drying pressure provides a measurement of this line tension, completely independent from other experimental methods and with a much higher precision.

## Results


We use here three different MTSs: MCM-41 (26, 27), SBA-15 (Santa Barbara Amorphous 15) (28, 29), and HMS (Hexagonal Mesoporous Silica) (30, 31), which are all shaped in the form of cylindrical pores with a narrow size distribution. Their synthesis, silanization with octyldimethylsilane, and pore size determination with nitrogen sorption at 77 K are described in *SI Text, section I*. The materials exhibit some differences in their organization and internal pore surface. The pore radii of the grafted materials are 1.34 ± 0.1 nm (MCM-41), 1.54 ± 0.1 nm (HMS), and 2.15 ± 0.25 nm (SBA-15) (Table 1). An instrumented, deformable cell is filled under vacuum with the degassed material and pure water, and water is forced in the pores up to full saturation (Fig. 1). The cell volume  $V$  is then increased at a constant rate until water empties the nanopores, and the initial cell volume is recovered. The intrusion and drying transitions appear as quasiplateaus on the pressure–volume (P–V) curves (Fig. 1).

Fig. 2 shows the typical behavior of the drying pressure as a function of the time  $t_{\text{ext}}$  of the drying process. The latter is defined and measured as the time spent on the drying plateau (Fig. 1). A logarithmic growth is obtained for all of the MTSs at all of the temperatures investigated. In contrast, the intrusion pressure exhibits much smaller kinetic effect.

This logarithmic kinetics is a strong signature of the activated processes that govern the drying transition. We argue that the mechanism limiting the drying process is the nucleation in each pore of a vapor bubble extending across the section and forming

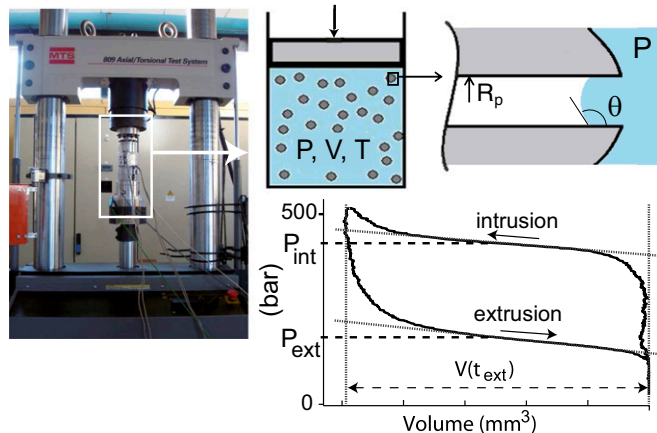

**Fig. 1.** Intrusion/extrusion of water in hydrophobic mesoporous silicas. A thermally regulated cell containing water and the material is placed in a traction machine (Left) to measure the pressure–volume isotherms (Lower Right). The volume change is driven at a constant velocity in the range of 0.08–80 mm/s. The intrusion and extrusion pressures,  $P_{\text{int}}$  and  $P_{\text{ext}}$ , respectively, are determined as the average pressure in the corresponding plateaus of the P–V isotherms (24).

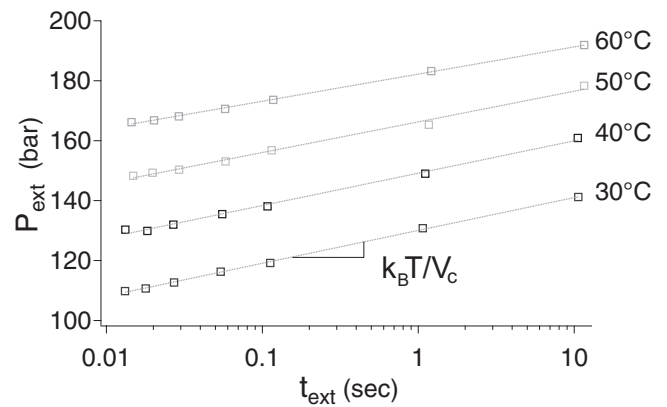

**Fig. 2.** Variation of the extrusion pressure  $P_{\text{ext}}$  with the logarithm of the time  $t_{\text{ext}}$  during which extrusion occurs for the MCM-41 material at different temperatures. The other materials show similar logarithmic growth of  $P_{\text{ext}}$  with  $t_{\text{ext}}$ .

two disconnected menisci (Fig. 3). The drying time, in each independent pore of average length  $L$ , is then related to the rate of nucleation of a spanning bubble:  $I = (\nu L/b)e^{-\Delta\Omega_c/k_B T}$ , by  $I t_{\text{ext}} \cong 1$ . Here,  $\Delta\Omega_c$  is the energy of the critical vapor nucleus,  $b$  and  $\nu$  are microscopic length scale and frequency, respectively, and  $k_B T$  is the thermal energy. This rate leads to a classical nucleation law (Eq. 2):

$$\Delta\Omega_c = k_B T \ln(L\nu t_{\text{ext}}/b). \quad [2]$$

Dimensionally, we expect that  $\Delta\Omega_c$  depends on the pressure only through a term  $P V_c$  involving the volume of the critical nucleus  $V_c$ . Hence, the drying pressure should express as (Eq. 3):

$$P_{\text{ext}} = \frac{k_B T}{V_c} \ln \frac{t_{\text{ext}}}{t_0} + P_{\text{ext}}^0(T), \quad [3]$$

with  $P_{\text{ext}}^0(T)$  being the extrusion pressure measured at some reference extrusion time  $t_0$ . If the volume of the vapor nucleus does not depend on the liquid pressure,  $P_{\text{ext}}$  is expected to grow logarithmically with  $t_{\text{ext}}$ . This result describes our data very well. We get values of  $V_c$  from the inverse of the slope of the experimental  $P_{\text{ext}}$  vs.  $\log(t_{\text{ext}})$  plots for each material and temperature. We obtain  $V_c = 10.2 \pm 1.5 \text{ nm}^3$  for the MCM-41,  $V_c = 17.8 \pm 2.7 \text{ nm}^3$  for the HMS, and  $V_c = 51 \pm 17 \text{ nm}^3$  for the SBA-15 (Fig. 3). The drying of SBA-15 shows a weaker dynamical behavior than the two others, and therefore, the uncertainty on  $V_c$  is much larger.

Because classical capillarity describes successfully the intrusion pressure, we compare  $V_c$  to the macroscopic calculation in the work by Lefevre et al. (22) for the nucleation of a bubble in a cylinder. The energy barrier is given within 5% by the approximate expression (Eq. 4):

$$\Delta\Omega_c \simeq P_L K_1(\theta) R_p^3 + K_2(\theta) \gamma_{\text{LV}} R_p^2, \quad [4]$$

where  $P_L$  is the liquid pressure, and  $K_1$  and  $K_2$  are functions of the Young's contact angle  $\theta$  (detailed in *SI Text, section I*). Note here that, in contrast to bulk nucleation, the critical volume  $V_c = R_p^3 K_1(\theta)$  does not depend on the applied pressure. The reason for this lack of dependence is that the formation of two disconnected menisci from a bubble growing at the wall of a cylinder occurs through a capillary instability, which is explained in Fig. 4. The theoretical volume  $R_p^3 K_1(\theta)$  of the critical nucleus can be calculated by taking the contact angle obtained from the





quoted in Table 1 are calculated using the microscopic quantities  $b = 1 \text{ \AA}$ ,  $\nu = 10^{12} \text{ s}^{-1}$ , and  $L = 10 \text{ \mu m}$ . Changing the ratio  $b/\nu L$  by a factor 10 or 0.1 changes  $\tau$  by less than  $\pm 0.6 \text{ pN}$  (that is, 1 to 2.5%). The line tension found has consistent values for the three materials ranging from  $-23 \text{ pN}$  in MCM-41 to  $-35 \text{ pN}$  in SBA-15. To account fully for the temperature variation of  $P_{\text{ext}}^0$ , we have allowed a small thermal variation  $\tau(T) = \tau_0[1 + \alpha(T - T_0)]$  (Fig. 7 and Table 1). The absolute value  $|\alpha|$  of the thermal coefficient is less than  $10^{-3} \text{ K}^{-1}$ , to be compared with the thermal coefficient of water surface tension in the same range,  $-2.4 \cdot 10^{-3} \text{ K}^{-1}$ .

The values that we find here are of the same amplitude but opposite sign to the line tension of water measured on hydrophilic surfaces, such as quartz (43) and silica (39). On strongly hydrophobic surfaces, measurements have focused on the shape of nanobubbles. State-of-the-art investigations have not evidenced a variation of the contact angle with the bubble size (40, 44, 45), corresponding to an upper amplitude of about 100 pN for the line tension of water. Therefore, we compare our results with the systematic study by Weijs et al. (42) performed for Lennard-Jones fluids, although the water/silane/silica system investigated here is chemically different. The (negative) line tension is characterized by the ratio of the tension length  $l = -\tau/\gamma_{\text{IV}}$  to the molecular size  $a$ . The ratios found here (with  $a = 2.7 \text{ \AA}$ ) are from 1.2 to 1.9, which is in good agreement with thermodynamic expectations and in qualitative agreement with the work by Weijs et al. (42) ( $l/a = 0.82$  at contact angle  $117^\circ$ ).

Finally, we find a difference of about  $-20\%$  (respectively,  $+20\%$ ) for the line tension in MCM-41 (respectively, SBA-15) with respect to HMS. This difference could be because of the topography of the pore walls (SBA-15 is known to have a rougher surface than MCM-41) or a systematic trend with the solid surface curvature, such as described in ref. 46.

### Conclusion

In summary, we have shown here that the drying of water brought into metastable equilibrium inside hydrophobic cavities is a dynamical process with slow logarithmic dynamics. This finding illustrates the importance of carrying out dynamical rate-dependent study of adsorption and desorption phenomena. Such studies are a sensitive probe of the specific mechanisms that control the formation and dynamics of nanobubbles on hydrophobic surfaces. Here, we find that the mechanism that allows one to interpret quantitatively the rate dependence of the extrusion pressure is the thermally activated appearance of a critical vapor nucleus that can be well-described by the macroscopic theory of capillarity, if a negative line tension of water is taken into account. Our approach provides an accurate independent estimate of this line tension, which is consistent with what can be

**Table 1. Nucleation volume and line tension in the various materials**

	MCM-41	SBA-15	HMS
$R_p^*$	$1.34 \pm 0.1$	$2.16 \pm 0.25$	$1.54 \pm 0.1$
$\theta_{50^\circ\text{C}}^\dagger$	$114.8^\circ$	$119.1^\circ$	$115^\circ$
$\delta\theta(^\circ\text{C}^{-1})$	0.036	0.077	0.059
$V_c^\ddagger$	$10.2 \pm 1.5$	$51 \pm 17$	$17.8 \pm 2.7$
$P_{\text{ext}}^0(50^\circ\text{C})^\S$	178	60.2*	109.4
$\tau_{50^\circ\text{C}}^\P$	-23.3	-35.5	-30.1
$\alpha(^\circ\text{C}^{-1})$	$-1.0 \cdot 10^{-3}$	$-0.8 \cdot 10^{-3}$	$-0.7 \cdot 10^{-3}$

\*Pore size (nm).

†Intruding contact angle at  $50^\circ\text{C}$ ;  $\theta(T) = \theta_{50^\circ\text{C}} + \delta\theta(T - 50)$ .

‡Nucleation volume ( $\text{nm}^3$ ).

§Reference extrusion pressure at  $50^\circ\text{C}$  (bar;  $t_0 = 1 \text{ s}$ ).

¶Line tension at  $50^\circ\text{C}$  ( $10^{-12} \text{ N}$ );  $\tau(T)/\tau_{50^\circ\text{C}} = 1 + \alpha(T - 50)$ .

**Table 2. Other characteristics of the materials**

	MCM-41	SBA-15	HMS
$R_{\text{BJH}} - R_{\text{BDB}}$ (nm)	1.25 – 1.43	1.91 – 2.40	1.44 – 1.64
$R_p$ (nm)	$1.34 \pm 0.1$	$2.15 \pm 0.25$	$1.54 \pm 0.1$
$P_{\text{int}}$ ( $50^\circ\text{C}$ ; bar)	432.1	291.1	325.5
$\theta_{50^\circ\text{C}}$	$114.8^\circ$	$119.1^\circ$	$115^\circ$
$\delta\theta(^\circ\text{C}^{-1})$	0.036	0.077	0.059
$K_1(\theta_{50^\circ\text{C}}) - K_2(\theta_{50^\circ\text{C}})$	4.27 – 3.24	4.28 – 2.614	4.27 – 3.21
$K_3(\theta_{50^\circ\text{C}})$	12.366	12.422	12.37

inferred from simulation data or atomic force measurements of droplet shapes. The existence of a negative line tension is an important ingredient for understanding the very high stability of nanobubbles on hydrophobic surfaces and the vaporization of water from repellent cavities, and it has wide implications for heterogeneous cavitation, hydrophobic interactions in biological matter, and more generally, properties of very small liquid objects. Additional work is under progress to study the compressibility of the water/silane hydrophobic interface in the mesopores (47).

### Materials and Methods

The MCM-41 was synthesized from the structuring agent octadecyltrimethylammonium bromide ( $\text{C}_{18}\text{NMe}_3\text{Br}$ ) as described in ref. 27. MCM-41 is a model material presenting independent cylindrical pores that are hexagonally ordered and have a smooth internal surface. SBA-15 was synthesized from the triblock copolymer poly(ethylene oxide)-poly(propylene oxide)-poly(ethylene oxide)  $\text{EO}_{20}\text{PO}_{70}\text{EO}_{20}$  as a structuring agent under acidic medium at  $60^\circ\text{C}$  for 24 h (29). SBA-15 also has a hexagonal arrangement of cylindrical pores, but depending on the synthesis temperature, these mesopores can be connected by a secondary network of smaller micropores. We chose a temperature of  $60^\circ\text{C}$ , which prevents the micropores from growing and creating interconnections (29). The HMS was prepared with  $\text{C}_{16}\text{NH}_2$  as the structuring agent, with a ratio  $\text{EtOH}/\text{H}_2\text{O} = 0.19$  at an ambient temperature for 24 h (31). The HMS has a smooth internal surface but is less ordered than MCM-41, and the pore network can be randomly connected in few locations. The three mesoporous silicas are silanized by grafting chlorodimethylsilyl silane as described in ref. 48. Before and after silanization, the MTS was characterized by nitrogen adsorption at 77 K (49). The pore size determination was done using two methods: the Barret–Joyner–Halenda method (50), which is classically used but has been shown to underestimate the pore size of hydrophilic silica (49), and the Broekhoff–de Boer method. The pore size of the hydrophobic materials is taken as the average of the two results  $R_p = (R_{\text{BDB}} + R_{\text{BJH}})/2$ , and the uncertainty is taken as their difference  $\Delta R_p = (R_{\text{BDB}} - R_{\text{BJH}})/2$ . The values are gathered in Table 2.

The experimental device, cell preparation, and obtention of the P-V isotherms of water in the hydrophobic materials are detailed in ref. 25. The intrusion (respectively, drying) pressure is defined as the average pressure value on the corresponding plateau. The intrusion pressure depends weakly on the intrusion rate, and we use quasistatic values obtained at a rate of  $0.1 \text{ s}^{-1}$ . It also depends very weakly on temperature, because  $P_{\text{int}} = P_{\text{int}}(T_0) + \Delta P_{\text{int},T}(T - T_0)$ . The Young contact angle derived from Eq. 1 also changes with temperature, because  $\theta = \theta(T_0) + \delta\theta(T - T_0)$ . Values for the three materials are summarized in Table 2.

In the data analysis, we use the following expressions to interpolate the functions  $K_1$ ,  $K_2$ , and  $K_3$  with  $90^\circ \leq \theta \leq 135^\circ$ :

$$K_1(\theta) = 4.1661 + 0.11242 \times \sin(0.11819 \times \theta + 0.16478),$$

$$K_2(\theta) = 20.32 - 0.14879 \times \theta, \text{ and}$$

$$K_3(\theta) = 3.355 + 0.14136 \times \theta - 0.00054762 \times \theta^2.$$

The theoretical calculation of the shape and energy of a vapor bubble in a cylinder in the presence of a line tension is performed with a finite element method and a relaxation algorithm.

**ACKNOWLEDGMENTS.** We thank Thierry Abensur and the European Aeronautic Defence and Space-Astrium Space Transportation Companies for supporting this research.

- Lum K, Chandler D, Weeks JD (1999) Hydrophobicity at small and large length scales. *J Phys Chem B* 103(22):4570–4577.
- Ishida N, Inoue T, Miyahara M, Higashitani K (2000) Nano bubbles on a hydrophobic surface in water observed by tapping-mode atomic force microscopy. *Langmuir* 16(16):6277–6380.
- Tyrrell JW, Attard P (2001) Images of nanobubbles on hydrophobic surfaces and their interactions. *Phys Rev Lett* 87(17):176104.
- Meyer EE, Rosenberg KJ, Israelachvili JN (2006) Recent progress in understanding hydrophobic interactions. *Proc Natl Acad Sci USA* 103(43):15739–15746.
- Seddon JRT, Lohse D (2011) Nanobubbles and micropancakes: Gaseous domains on immersed substrates. *J Phys Condens Matter* 23(13):133001.
- Christenson HK, Claesson PM (2001) Direct measurements of the force between hydrophobic surfaces in water. *Adv Colloid Interface Sci* 91(3):391–436.
- Chandler D (2002) Hydrophobicity: Two faces of water. *Nature* 417(6888):491.
- Berne BJ, Weeks JD, Zhou R (2009) Dewetting and hydrophobic interaction in physical and biological systems. *Annu Rev Phys Chem* 60:85–103.
- ten Wolde PR, Chandler D (2002) Drying-induced hydrophobic polymer collapse. *Proc Natl Acad Sci USA* 99(10):6539–6543.
- Patel AJ, et al. (2011) Extended surfaces modulate hydrophobic interactions of neighboring solutes. *Proc Natl Acad Sci USA* 108(43):17678–17683.
- Zhou R, Huang X, Margulis CJ, Berne BJ (2004) Hydrophobic collapse in multidomain protein folding. *Science* 305(5690):1605–1609.
- Giovambattista N, Lopez CF, Rossky PJ, Debenedetti PG (2008) Hydrophobicity of protein surfaces: Separating geometry from chemistry. *Proc Natl Acad Sci USA* 105(7):2274–2279.
- Mittal J, Hummer G (2008) Static and dynamic correlations in water at hydrophobic interfaces. *Proc Natl Acad Sci USA* 105(51):20130–20135.
- Borkent BM, Dammer SM, Schönherr H, Vansco GJ, Lohse D (2007) Superstability of surface nanobubbles. *Phys Rev Lett* 98(20):204502.
- Ducker WA (2009) Contact angle and stability of interfacial nanobubbles. *Langmuir* 25(16):8907–8910.
- Bolhuis PG, Chandler D (2000) Transition path sampling of cavitation between molecular scale solvophobic surfaces. *J Chem Phys* 113(18):8154–8160.
- Leung K, Luzar A, Bratko D (2003) Dynamics of capillary drying in water. *Phys Rev Lett* 90(6):065502.
- Luzar A (2004) Activation barrier scaling for the spontaneous evaporation of confined water. *J Phys Chem B* 108(51):19859–19866.
- Sharma S, Debenedetti PG (2012) Evaporation rate of water in hydrophobic confinement. *Proc Natl Acad Sci USA* 109(12):4365–4370.
- Liu D, et al. (2007) Observation of the density minimum in deeply supercooled confined water. *Proc Natl Acad Sci USA* 104(23):9570–9574.
- Zhang Y, et al. (2011) Density hysteresis of heavy water confined in a nanoporous silica matrix. *Proc Natl Acad Sci USA* 108(30):12206–12211.
- Lefevre B, et al. (2004) Intrusion and extrusion of water in hydrophobic mesopores. *J Chem Phys* 120(10):4927–4938.
- Lefevre B, et al. (2004) Intrusion and extrusion of water in highly hydrophobic mesoporous materials: Effect of the pore texture. *Coll and Surf A Physicochem Eng Asp* 241:265–272.
- Eroschenko VA, Regis RC, Souillard M, Patarin J (2001) Energetics: A new field of applications for hydrophobic zeolites. *J Am Chem Soc* 123(33):8129–8130.
- Guillemot L, Galarneau A, Vigier G, Abensur T, Charlaix E (2012) New device to measure dynamic intrusion/extrusion cycles of lyophobic heterogeneous systems. *Rev Sci Instrum* 83(10):105105.
- Kresge CT, Leonowicz ME, Roth WJ, Vartuli JC, Beck JS (1992) Ordered mesoporous molecular sieves synthesized by a liquid-crystal template mechanism. *Nature* 359:710–712.
- Martin T, Galarneau A, Di Renzo F, Brunel D, Fajula F (2004) Great improvement of chromatographic performance using MCM-41 spheres as stationary phase in HPLC. *Chem Mater* 16(9):1725–1731.
- Zhao D, et al. (1998) Triblock copolymer syntheses of mesoporous silica with periodic 50 to 300 angstrom pores. *Science* 279(5350):548–552.
- Galarneau A, et al. (2003) Microporosity and connections between pores in SBA-15 mesostructured silicas as a function of the temperature of synthesis. *New J Chem* 27(1):73–79.
- Tanev PT, Pinnavaia TJ (1996) Mesoporous silica molecular sieves prepared by ionic and neutral surfactant templating: A comparison of physical properties. *Chem Mater* 8(8):2068–2079.
- Di Renzo F, et al. (1999) Textural control of micelle-templated mesoporous silicates: The effects of co-surfactants and alkalinity. *Microporous Mesoporous Mater* 28(3):437–446.
- Huang DM, Geissler PL, Chandler D (2001) Scaling of hydrophobic solvation free energies. *J Phys Chem B* 105(28):6704–6709.
- Dzubiella J, Swanson JMJ, McCammon JA (2006) Coupling hydrophobicity, dispersion, and electrostatics in continuum solvent models. *Phys Rev Lett* 96(8):087802.
- Fisher LR, Israelachvili JN (1981) Direct measurement of the effect of meniscus force on adhesion: A study of the applicability of macroscopic thermodynamics to microscopic liquid interfaces. *Colloids Surf* 3(4):303–319.
- Christenson HK (1988) Adhesion between surfaces in undersaturated vapors - A re-examination of the influence of meniscus curvature and surface forces. *J Colloid Interface Sci* 121(1):170–178.
- Gibbs JW (1957) *The Scientific Papers* (Dover, New York), Vol. I.
- Drelich J (1996) The significance and magnitude of the line tension in three-phase (solid-liquid-fluid) systems. *Colloids Surf A Physicochem Eng Asp* 116:43–54.
- Amirfazli A, Neumann AW (2004) Status of the three-phase line tension: A review. *Adv Colloid Interface Sci* 110(3):121–141.
- Pompe T, Herminghaus S (2000) Three-phase contact line energetics from nanoscale liquid surface topographies. *Phys Rev Lett* 85(9):1930–1933.
- Borkent BM, de Beer S, Mugele F, Lohse D (2010) On the shape of surface nanobubbles. *Langmuir* 26(1):260–268.
- Checco A, Guenoun P, Daillant J (2003) Nonlinear dependence of the contact angle of nanodroplets on contact line curvature. *Phys Rev Lett* 91(18):186101.
- Weijss JH, Marchand A, Andreotti B, Lohse D, Snoeijer JH (2011) Origin of line tension for a Lennard-Jones nanodroplet. *Phys Fluids* 23(2):022001.
- Zorin Z, Platikanov D, Kolarov T (1987) The transition region between aqueous wetting films on quartz and the adjacent meniscus. *Colloids Surf* 22:147–159.
- Zhang XH, Maeda N, Craig VSJ (2006) Physical properties of nanobubbles on hydrophobic surfaces in water and aqueous solutions. *Langmuir* 22(11):5025–5035.
- Zhang XH, Quinn A, Ducker WA (2008) Nanobubbles at the interface between water and a hydrophobic solid. *Langmuir* 24(9):4756–4764.
- Bauer C, Dietrich S (2000) Shapes, contact angles, and line tensions of droplets on cylinders. *Phys Rev E Stat Phys Plasmas Fluids Relat Interdiscip Topics* 62(2):2428–2438.
- Sarupria S, Garde S (2009) Quantifying water density fluctuations and compressibility of hydration shells of hydrophobic solutes and proteins. *Phys Rev Lett* 103(3):037803.
- Martin T, et al. (2001) Towards total hydrophobisation of MCM-41 type silica surface. *Stud Surf Sci Catal* 135:4621–4628.
- Galarneau A, Desplandier D, Dutartre R, Di Renzo F (1999) Micelle-templated silicates as a test-bed for methods of mesopore size evaluation. *Microporous Mesoporous Mater* 27:297–308.
- Barrett EP, Joyner LG, Halenda PP (1951) The determination of pore volume and area distributions in porous substances. I. Computations from nitrogen isotherms. *J Am Chem Soc* 73(11):373–380.