

ORIGINAL ARTICLE

The importance of measuring toothpaste abrasivity in both a quantitative and qualitative way

GUNNAR JOHANNSEN¹, GEORG TELLEFSEN², ANNSOFI JOHANNSEN² & ANDERS LILJEBORG³

¹Department of Periodontology, Danakliniken, Danderyd, Sweden, ²Department of Dental Medicine, Division of Periodontology, Karolinska Institutet, Sweden, and ³KTH-Albanova, Nanostructure Physics, Stockholm

Abstract

Objective. To evaluate the relative abrasivity of different toothpastes and polishing pastes both qualitatively and quantitatively. **Materials and methods.** Acrylic plates were exposed to brushing in a brushing machine with a toothpaste/water slurry for 1 and 6 h. Twelve different toothpastes were used and also four different polishing pastes. The results were evaluated using a profilometer after 1 and 6 h of brushing (corresponding to 2000 and 12 000 double strokes, respectively). A surface roughness value (Ra-value) and also a volume loss value were calculated from the profilometer measurements. These values were then correlated to each other. An unpaired *t*-test for the difference in the abrasion values between the toothpastes and the abrasion values over time was used. **Results.** The polishing paste RDA[®] 170 yielded higher Ra-values than RDA 250[®], both after 1 and 6 h of brushing (1.01 ± 0.22 and 8.99 ± 1.55 compared to 0.63 ± 0.26 and 7.83 ± 5.89 , respectively) as well as volume loss values (3.71 ± 0.17 and 20.20 ± 2.41 compared to 2.15 ± 1.41 and 14.79 ± 11.76 , respectively), thus poor correlations between the RDA and Ra and Volume loss values were shown. Among the toothpastes, Apotekets[®] showed the highest Ra value after 1 h of brushing and Pepsodent[®] whitening after 6 h of brushing. Pepsodent[®] whitening also showed the highest volume loss values, both after 1 and 6 h of brushing. **Conclusion.** This study emphasizes the importance of not only considering the RDA value, but also a roughness value, when describing the abrasivity of a toothpaste. Furthermore, it can be concluded that so called 'whitening' toothpastes do not necessarily have a higher abrasive effect than other toothpastes.

Key Words: *abrasivity, dentifrice, profilometer*

Introduction

Toothpastes and different polishing pastes have during the years been used in order to increase whiteness of the teeth. The wear produced by toothpastes, toothbrushes and polishing pastes is defined as abrasion in contrast to the tooth-to-tooth contact wear which is defined as attrition. The acid-mediated softening of a tooth is defined as erosion [1]. The wear due to abrasion can be reduced by the presence of a pellicle [2], but the wear can also be reduced by adding silicone oil to the toothpaste [3]. It was demonstrated that the addition of silicone oil to a toothpaste decreased the abrasion rate and made the surface of the treated material smoother than after brushing with the original toothpaste. Abrasion and erosion can also be somewhat prevented by high

fluoride concentration gel [4]; however, it was concluded that fluoridated toothpaste provided very little protection.

To evaluate toothpaste abrasivity, many different techniques have been used, e.g. the RDA method, weight and volume loss techniques which are quantitative techniques, measuring the amount of abraded material removed [5,6] as well as profilometer and light reflexion techniques, which are qualitative techniques measuring the roughness of the abraded material [7,8].

The purposes have been to evaluate if toothpastes with higher abrasive content cause more damage to the tooth surface and to investigate the relation between abrasivity and cleaning-whitening [9,10].

Abrasion studies have been performed *in vitro* using various specimens of enamel and dentine. Bovine dentine specimens have been shown to act as an

Table I. Twelve commercially available toothpastes and four polishing pastes containing the following abrasives were used.

| Toothpaste | Abrasive | RDA |
|--------------------------|---|-------|
| Acta original | Natriummetafosfat | 45–60 |
| Apoliva | Silica | 70 |
| Apotekets classic | Silica | 71 |
| Colgate Total | Hydrated silicon dioxide | 44 |
| Opalescence | Silica | 66 |
| Oral B advantage | Hydrated silica | 65 |
| Zendium | Hydrated silica | 80 |
| Pepsodent white naturals | Silicon dioxide | 142 |
| Pepsodent xylitol | Silicon dioxide | 50 |
| Clinomyn | Calcium carbonate Silicon dioxide, aluminium silicate | 124 |
| Aloe Vera | Hydrated silica low | |
| Colgate whitening | Hydrated silica | 96 |
| RDA 250 | Pumice | 250 |
| RDA 170 | Pumice | 170 |
| RDA 120 | Hydrated silica | 120 |
| RDA 40 | Hydrated silica | 40 |

appropriate substitute for human dentine [11]. Acrylic plates with the same hardness as dentine have also been used and been shown to be appropriate for comparative studies of dentifrice abrasivity [12]. *In vivo* investigations have been performed in order to be able to translate the *in vitro* results into a clinical reality [13]. The abrasive component in toothpastes differs, but the most common abrasives used

today are derivatives of silica. The abrasivity of a toothpaste depends on the amount of abrasive, particle size, surface structure of the particle and on the chemical influence of other types of ingredients in the product [14].

It is difficult to distinguish the effect of the toothbrush on the abrasivity from that of the toothpaste and it is probably dependent on the interaction between the two [15]. During the years the toothbrush has only been considered to contribute to the abrasivity indirectly through harboring the toothpaste across the surface and in itself only having a negligible effect [5,16].

Since toothpaste manufacturers change the composition of the toothpastes on a regular basis also regarding the abrasive part and since the RDA value is the only measurement of abrasivity that is being tested, it is important to measure also a roughness value of the abraded material. Increased RDA value doesn't necessarily mean an increased roughness, which implies that a toothpaste with a low RDA value still can create a rougher surface than a toothpaste with a higher RDA value [12].

The aim of the present study was, therefore, to evaluate the relative abrasivity *in vitro* of different toothpastes and polishing pastes using the same method for both qualitative and quantitative evaluation.

Materials and methods

Twelve commercially-available toothpastes and four polishing pastes containing the following abrasives are included in the study and presented in Table I. All toothpastes were provided from a Swedish pharmacy. The RDA values were obtained from the manufacturer.

Table II. Ra and volume loss values after 1 and 6 h.

| Toothpaste | Ra, $\mu\text{m} \pm \text{SD}$ (1 h) | Ra, $\mu\text{m} \pm \text{SD}$ (6 h) | Vol mm^3 (1 h) | Vol mm^3 (6 h) |
|---------------|---------------------------------------|---------------------------------------|-------------------------|-------------------------|
| Opalescence | 1.30 \pm 0.53 | 6.67 \pm 2.71 | 3.26 \pm 0.89 | 10.61 \pm 6.60 |
| RDA 170 | 1.01 \pm 0.22 | 8.99 \pm 1.55 | 3.71 \pm 0.17 | 20.20 \pm 2.41 |
| RDA 250 | 0.63 \pm 0.26 | 7.83 \pm 5.89 | 2.15 \pm 1.41 | 14.79 \pm 11.76 |
| RDA 120 | 0.33 \pm 0.12 | 1.70 \pm 0.56 | 0.52 \pm 0.40 | 3.42 \pm 1.63 |
| Apotekets | 0.33 \pm 0.12 | 1.41 \pm 0.33 | 0.53 \pm 0.31 | 2.16 \pm 1.20 |
| Pepsodent W | 0.31 \pm 0.10 | 2.37 \pm 1.30 | 1.32 \pm 0.25 | 5.25 \pm 3.56 |
| RDA 40 | 0.27 \pm 0.20 | 0.65 \pm 0.34 | 0.34 \pm 0.08 | 1.42 \pm 1.06 |
| Apolivia | 0.27 \pm 0.09 | 1.46 \pm 0.46 | 0.53 \pm 0.32 | 2.72 \pm 0.90 |
| Colgate W | 0.20 \pm 0.10 | 0.97 \pm 0.31 | 0.58 \pm 0.32 | 2.32 \pm 0.86 |
| Oral B | 0.19 \pm 0.06 | 1.13 \pm 0.65 | 0.45 \pm 0.32 | 2.45 \pm 2.17 |
| Colgate Tot | 0.19 \pm 0.07 | 0.97 \pm 0.56 | 0.62 \pm 0.19 | 1.82 \pm 1.41 |
| Pepsodent Xyl | 0.18 \pm 0.08 | 1.44 \pm 1.00 | 0.44 \pm 0.31 | 1.73 \pm 0.69 |
| Aloe Vera | 0.13 \pm 0.09 | 1.11 \pm 0.62 | 0.34 \pm 0.21 | 1.76 \pm 1.27 |
| Clinomyn | 0.13 \pm 0.08 | 1.15 \pm 0.24 | 0.35 \pm 0.35 | 1.76 \pm 0.76 |
| Acta | 0.10 \pm 0.03 | 0.50 \pm 0.19 | 0.29 \pm 0.16 | 1.10 \pm 0.25 |
| Zendium | 0.08 \pm 0.05 | 0.81 \pm 0.54 | 0.19 \pm 0.14 | 0.99 \pm 0.89 |

Table III. Ra values after 1 h.

| | RDA 170 | RDA 250 | RDA 120 | Apotekets | PepsodentW | RDA 40 | Apoliva | Colgate W | Oralb Sens | Colgate Tot | Pepsodent Xyl | Aloe Vera | Clinomyn | Acta | Zendium |
|---------------|---------|---------|---------|-----------|------------|--------|---------|-----------|------------|-------------|---------------|-----------|----------|------|---------|
| RDA 170 | | | | | | | | | | | | | | | |
| RDA 250 | ** | | | | | | | | | | | | | | |
| RDA 120 | *** | ** | | | | | | | | | | | | | |
| Apotekets | *** | ** | NS | | | | | | | | | | | | |
| Pepsodent W | *** | ** | NS | NS | | | | | | | | | | | |
| RDA 40 | *** | ** | NS | NS | NS | | | | | | | | | | |
| Apoliva | *** | ** | NS | NS | NS | NS | | | | | | | | | |
| Colgate W | *** | *** | * | * | * | NS | NS | | | | | | | | |
| Oralb Sens | *** | *** | ** | * | ** | NS | * | NS | | | | | | | |
| Colgate Tot | *** | *** | ** | * | ** | NS | * | NS | NS | | | | | | |
| Pepsodent Xyl | *** | *** | ** | * | ** | NS | * | NS | NS | NS | | | | | |
| Aloe Vera | *** | *** | ** | ** | ** | NS | ** | NS | NS | NS | NS | | | | |
| Clinomyn | *** | *** | ** | ** | ** | NS | ** | NS | NS | NS | NS | NS | | | |
| Acta | *** | *** | *** | *** | *** | * | *** | * | *** | ** | * | NS | NS | | |
| Zendium | *** | *** | *** | *** | *** | * | *** | * | ** | * | * | NS | NS | NS | NS |

* $p < 0.01$, ** $p < 0.001$, *** $p < 0.0001$.

Table IV. Ra values after 6 h.

| | RDA 170 | RDA 250 | Peps W | RDA 120 | Apolivia | Peps X | Apotekets | Clinomyn | Oral B | Aloe Vera | Colgate W | Colgate T | Zendium | RDA 40 | Acta |
|--------------------|---------|---------|--------|---------|----------|--------|-----------|----------|--------|-----------|-----------|-----------|---------|--------|------|
| <i>Toothpastes</i> | | | | | | | | | | | | | | | |
| RDA 170 | | | | | | | | | | | | | | | |
| RDA 250 | NS | | | | | | | | | | | | | | |
| Peps W | * | * | | | | | | | | | | | | | |
| RDA 120 | *** | ** | NS | | | | | | | | | | | | |
| Apolivia | *** | ** | NS | NS | | | | | | | | | | | |
| Peps X | *** | ** | NS | NS | NS | | | | | | | | | | |
| Apotekets | *** | ** | * | NS | NS | NS | | | | | | | | | |
| Clinomyn | *** | ** | * | * | NS | NS | NS | | | | | | | | |
| Oral B | *** | ** | * | NS | NS | NS | NS | NS | | | | | | | |
| Aloe Vera | *** | ** | * | NS | NS | NS | NS | NS | NS | | | | | | |
| Colgate W | *** | ** | ** | ** | * | NS | * | NS | NS | NS | | | | | |
| Colgate T | *** | ** | ** | * | NS | NS | NS | NS | NS | NS | NS | | | | |
| Zendium | *** | ** | ** | ** | * | NS | * | NS | NS | NS | NS | NS | | | |
| RDA 40 | *** | ** | ** | *** | *** | * | *** | ** | NS | NS | * | NS | NS | | |
| Acta | *** | ** | *** | *** | *** | * | *** | *** | * | * | ** | * | NS | NS | |

* $p < 0.01$, ** $p > 0.001$, *** $p > 0.0001$.

Table V. Volume loss values after 1 h of brushing (mm³).

| | RDA 170 | RDA 250 | Peps W | Colgate T | Colgate W | Apolivia | Apotekets | RDA 120 | Oral B | Peps Xyl | Clinomyn | RDA 40 | Aloe Vera | Acta | Zendium |
|--------------------|---------|---------|--------|-----------|-----------|----------|-----------|---------|--------|----------|----------|--------|-----------|------|---------|
| <i>Toothpastes</i> | | | | | | | | | | | | | | | |
| RDA 170 | | | | | | | | | | | | | | | |
| RDA 250 | ** | | | | | | | | | | | | | | |
| Peps W | *** | NS | | | | | | | | | | | | | |
| Colgate T | *** | ** | *** | | | | | | | | | | | | |
| Colgate W | *** | ** | *** | NS | | | | | | | | | | | |
| Apolivia | *** | ** | *** | NS | NS | | | | | | | | | | |
| Apotekets | *** | ** | *** | NS | NS | NS | | | | | | | | | |
| RDA 120 | *** | ** | *** | NS | NS | NS | NS | | | | | | | | |
| Oral B | *** | ** | *** | NS | NS | NS | NS | NS | | | | | | | |
| Peps Xyl | *** | ** | *** | NS | NS | NS | NS | NS | NS | | | | | | |
| Clinomyn | *** | ** | *** | NS | NS | NS | NS | NS | NS | NS | | | | | |
| RDA 40 | *** | ** | *** | *** | NS | NS | NS | NS | NS | NS | NS | | | | |
| Aloe Vera | *** | ** | *** | ** | NS | NS | NS | NS | NS | NS | NS | NS | | | |
| Acta | *** | ** | *** | ** | * | NS | NS | NS | NS | NS | NS | NS | NS | | |
| Zendium | *** | *** | *** | *** | ** | * | ** | * | * | * | NS | * | NS | NS | NS |

p* < 0.01, *p* < 0.001, ****p* < 0.0001.

Table VI. Volume loss values after 6 h brushing (mm³).

| | RDA 170 | RDA 250 | Peps W | RDA 120 | Apolivia | Oral B | ColgateW | Apotekets | Colgate T | Aloe Vera | Clinomyn | Peps X | RDA 40 | Acta | Zendium |
|--------------------|---------|---------|--------|---------|----------|--------|----------|-----------|-----------|-----------|----------|--------|--------|------|---------|
| <i>Toothpastes</i> | | | | | | | | | | | | | | | |
| RDA 170 | | | | | | | | | | | | | | | |
| RDA 250 | NS | | | | | | | | | | | | | | |
| Peps W | *** | * | | | | | | | | | | | | | |
| RDA 120 | *** | * | NS | | | | | | | | | | | | |
| Apolivia | *** | ** | NS | NS | | | | | | | | | | | |
| Oral B | *** | ** | NS | NS | NS | | | | | | | | | | |
| Colgate W | *** | ** | * | NS | NS | NS | | | | | | | | | |
| Apotekets | *** | ** | * | NS | NS | NS | NS | | | | | | | | |
| Colgate T | *** | ** | * | * | NS | NS | NS | NS | | | | | | | |
| Aloe Vera | *** | ** | * | * | NS | NS | NS | NS | NS | | | | | | |
| Clinomyn | *** | ** | * | * | * | NS | NS | NS | NS | NS | | | | | |
| Peps X | *** | ** | * | * | * | NS | NS | NS | NS | NS | NS | | | | |
| RDA 40 | *** | ** | ** | ** | * | NS | NS | NS | NS | NS | NS | NS | | | |
| Acta | *** | ** | ** | *** | *** | NS | *** | * | NS | NS | * | * | NS | | |
| Zendium | *** | ** | ** | ** | *** | NS | ** | * | NS | NS | NS | NS | NS | NS | |

p* < 0.01, *p* < 0.001, ****p* < 0.0001.

Acrylic plates with the following specifications were used as substrate: Polymethylmetacrylate (PMMA) type Plexiglas XT. Dimensions $115 \times 25 \times 3$ mm. Density 1.18 g/m^3 , ball hardness HD 10 s (DIN 53.456) 190 MPa.

Brushing machine

Reciprocating movement of 85 mm, 2000 double strokes per hour. Load 2.35 N. The apparatus had six brush sites and each brush site had a trough for the toothpaste water slurry in which the test plates were placed. Between each test, new brushes were mounted in the machine.

Test procedure

Three plates were mounted in the brushing machine and toothpaste water slurry, containing 25 g of toothpaste mixed with 50 ml of water, was added. Every hour the plates were removed and rinsed in luke-warm water and the slurry was refilled. The total brushing time was 6 h, corresponding to 12 000 double strokes, but the plates were also analyzed after 1 h brushing (2000 double strokes). This procedure was repeated with the 12 different toothpastes and the four polishing pastes.

The plates were then analyzed using a surface profilometer (P15, KLA Tencor Corp., San Jose, CA) For detailed characteristics see Liljeborg et al. [12].

A low-force scanhead equipped with a diamond stylus (tip radius of $2 \mu\text{m}$) was used to scan the surface

profile across the sample. The force of the tip can be finely controlled between 0.05 mg up to 50 mg, as well as the scanning speed and the sampling interval of the depth values.

The vertical repeatability is $0.03 \mu\text{m}$ for a range of $30 \mu\text{m}$. The maximum vertical range of the profilometer is $130 \mu\text{m}$, which was enough for all the samples. Three profiles were collected for each sample, one at mid-point of the plate and two profiles 20 mm above and 20 mm below the mid-point. Roughness average (Ra) values were computed for each profile. Ra is defined as the arithmetic average deviation of the absolute values of the roughness profile from the mean line or the center line. Since all the measurements started and ended outside of the abraded area, it was also possible to compute the volume of removed material.

Statistical methods

The difference in the abrasion values between the toothpastes and also the abrasion values over time were calculated using the statistical package (SPSS 18.0 Statistical Package for the Social Services), using an unpaired *t*-test for calculating equality between means.

Results

The results are shown in Tables II,III,IV,V,VI and illustrated in Figures 1,2,3. The volume loss and the Ra measurements (Table II) are presented after 1 and 6 h along with the standard deviation. In Tables III,IV,V,VI the statistical significance of

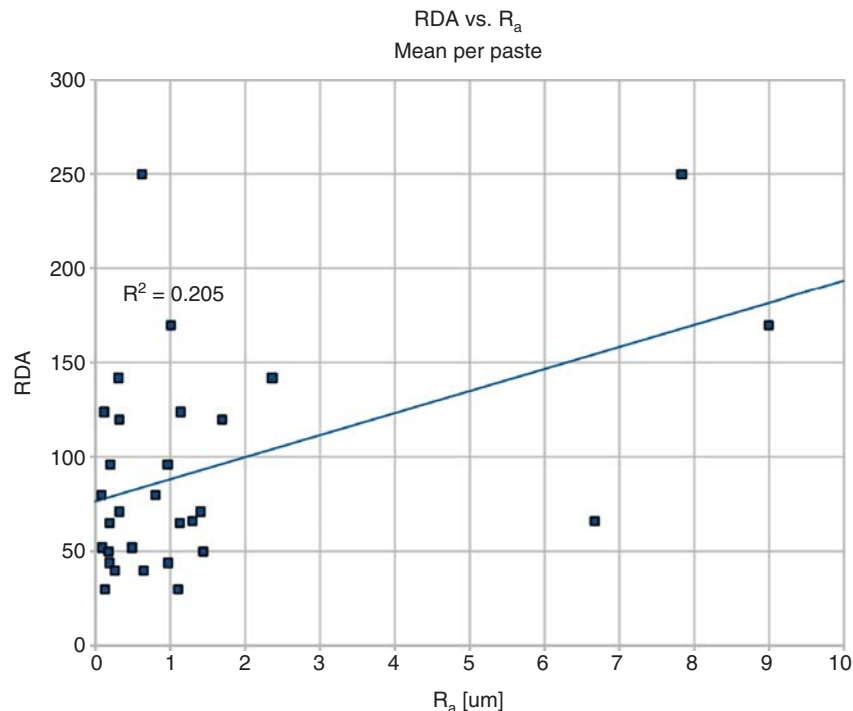


Figure 1. RDA values vs R_a (roughness average) for brushing both at 1 and 6 h. Correlation coefficient is 0.45 (equal the square root of the regression coefficient, R^2 , shown in the diagram).

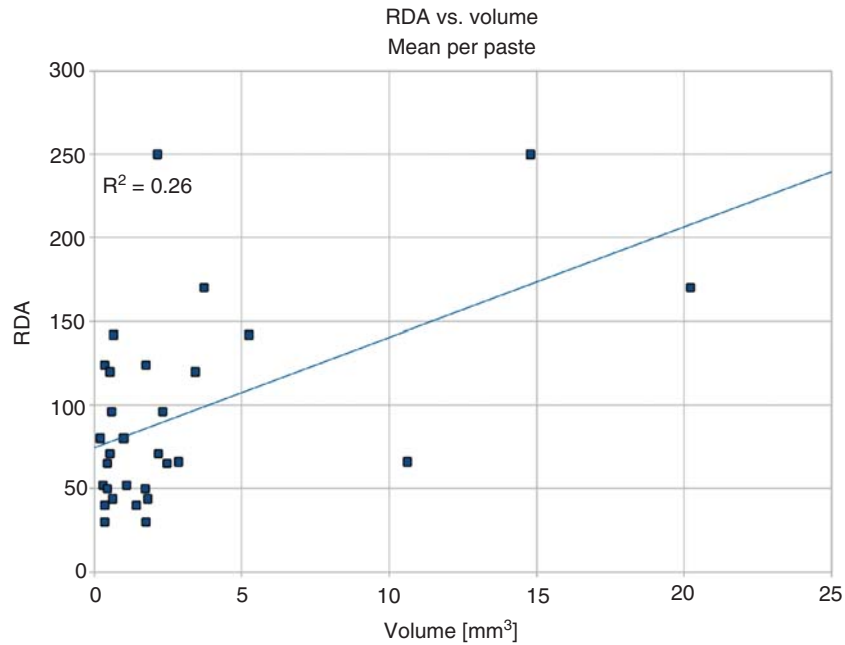


Figure 2. RDA values vs volume for brushing both at 1 and 6 h. Correlation coefficient is 0.51.

the differences between the toothpastes is presented. The highest Ra value and also Volume loss value was shown by the polishing pastes RDA 170[®] and RDA 250[®], respectively, both after 1 and 6 h brushing. The correlation coefficient between RDA and Ra was 0.45 (Figure 1), between RDA and Volume loss 0.51 (Figure 2) and between Ra and Volume loss 0.98 (Figure 3).

Among the toothpastes, the highest Ra values were shown by Apotekets[®] followed by Pepsodent whitening[®] after 1 h of brushing and by Pepsodent whitening[®] followed by Apolivia[®] after 6 h of

brushing. Regarding the volume loss values the highest were created by Pepsodent whitening[®] followed by Colgate total[®] after 1 h of brushing and Pepsodent[®] followed by Apolivia[®] after 6 h of brushing.

Zendium[®] followed by Acta[®] showed the lowest Volume loss values both after 1 and 6 h and also the lowest Ra values after 1 h brushing, while after 6 h Acta[®] showed the lowest Ra value followed by RDA 40[®] and Zendium[®].

The values for Opalescence[®] were excluded from the study due to the reasons given below.

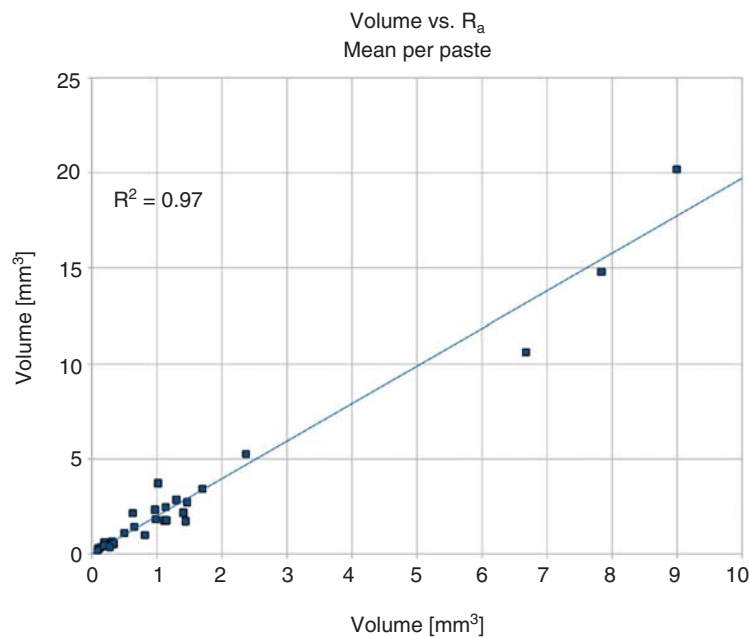


Figure 3. Volume vs R_a (roughness average) for brushing both at 1 and 6 h. Correlation coefficient is 0.98.

Discussion

The present study revealed a poor correlation between the Ra, Volume loss and RDA values, which is clearly shown in Figures 1,2,3, and also when comparing the values for the polishing pastes RDA 170[®] and RDA 250[®]. Both after 1 and 6 h of brushing RDA 170[®] yielded higher Ra and Volume loss values than RDA 250[®]. This is also in line with the results earlier obtained by Liljeborg et al. [12], which emphasizes the importance of considering both a qualitative (roughness) value and a quantitative (volume loss) value when describing a toothpaste abrasivity.

Another interesting finding in the present study was that the ranking order between the toothpastes was not the same after 1 and 6 h of brushing, indicating that the abrasion was not linear to the number of strokes, Colgate total[®] was ranked as number 5 regarding volume loss values after 1 h but as number 10 after 6 h brushing. Regarding Ra values, RDA 40[®] was ranked as number 7 after 1 h but as number 15 after 6 h of brushing. Other investigators have found similar results [17].

When discussing the abrasivity of whitening toothpaste vs conventional toothpaste results are varying. Some studies indicate that a whitening toothpaste does not cause more wear than a conventional toothpaste [18,19], but another study [10] concluded that the highest wear was caused by the whitening toothpastes compared to conventional toothpastes. In the present study no significant differences between the two whitening toothpastes (Pepsodent whitening[®] and Colgate whitening[®]) and conventional toothpastes regarding abrasivity were found.

The polishing pastes used in the present study were pastes used in the dental practice. As expected RDA 170[®] and RDA 250[®] yielded the highest abrasion values, both regarding the Volume loss and Ra value, after 1 and 6 h. Among the toothpastes, Clinomyn[®] (RDA = 124) revealed much lower values than the polishing paste RDA 120[®], especially concerning the Ra values both after 1 and 6 h. One of the reasons can be that Clinomyn[®] contains silicon oil which makes the surface of the abraded material smoother and reduces the abrasive effect [3].

Opalescence[®], a whitening toothpaste, somewhat influenced the acrylic surface chemically. It contains carbomer and acrylic acid which might have the ability to interact and dissolve acrylic. This must be taken into consideration if and when Opalescence[®] is being used on other acrylic replacements in the mouth. Therefore, the Ra and Volume loss value for Opalescence[®] was excluded from this study.

The wear process due to abrasion can also be influenced by erosion. This interaction has been studied by Hooper et al. [20], who used two

toothpastes with different RDA values *in vivo*. The test persons wore a removable acrylic appliance holding one piece of polished enamel and one piece of polished dentine during 10 days (8 h per day). Five different treatment regimens were tried with drinking water or orange juice before brushing to influence the surface. Synergetic effects on enamel were directional but not statistically significant. The synergetic effect on dentine could not be measured due to the exceeded measurement range of the profilometer; however, they found that dentine was more susceptible than enamel to erosion and abrasion alone or combined. This was also in line with findings of Voronets and Lussi [21], who compared softened enamel (by citric acid and orange juice) to non-softened enamel after brushing with a toothpaste water slurry. They found that the softened enamel showed an increase in abrasion, which also has been shown by Kielbasa et al. [22]. Also, detergents can modify the abrasivity [17]. They compared brushing with water, detergent slurries and toothpaste detergent slurries and found that brushing with detergents alone also caused loss of dentine. Furthermore, they found that the different silicas used as abrasives differed in abrasion properties, despite similar particle size.

One limitation of the present study was that the brushing was carried out on acrylic plates. The reason for choosing acrylic plates instead of dentin specimen was to get an homogenous surface with the same hardness as dentin that would be equal for all the experiments. Therefore, we only claim the relative comparisons between the toothpastes.

To transform these results into a clinical reality is difficult, but a rough estimate would be that 12 000 double strokes equals 2 years with twice daily brushing [23]. The clinical relevance of these results is obvious, since today the abrasivity of toothpaste is often only based on the RDA value and, since toothpastes with low RDA values are recommended to patients, especially in situations with recession defects, periodontal cases and hypersensitive teeth. Furthermore, the risk for damaging the tooth surface by using whitening toothpastes may be exaggerated. This expresses the need for an *in vivo* investigation to confirm these results.

Conclusion

From the present study it can be concluded that it is important to consider not only the RDA value, but also a roughness value, when describing the abrasivity of toothpastes. Furthermore, this study supports the theory that one toothpaste can cause a higher volume loss value but still create a smoother surface than another toothpaste and that 'whitening' toothpastes may very well be used as 'every day' toothpastes.

Acknowledgments

This study was supported by Praktikertjänst AB and Karolinska Institutet, Huddinge, Sweden.

Declaration of interest: The authors report no conflicts of interest. The authors alone are responsible for the performance and evaluation of the study protocol as well as for the content and writing of the paper.

References

- [1] Barbour ME, Rees GD. The role of erosion, abrasion and attrition in tooth wear. *J Clin Dent* 2006;7:88–93.
- [2] Joiner A, Schwartz A, Philpotts CJ, Cox TF, Huber K, Hannig M. The protective nature of pellicle towards toothpaste abrasion on enamel and dentine. *J Dent* 2008;36:360–8.
- [3] Johannsen G. The influence of silicone oil in toothpastes on abrasion *in vitro*. *Swed Dent J* 1993;17:117–22.
- [4] Lagerweij MD, Buchalla W, Kohnke S, Becker K, Lennon AM, Attin T. Prevention of erosion and abrasion by a high fluoride concentration gel applied at high frequencies. *Caries Res* 2006;40:148–53.
- [5] Harrington JH, Terry IA. Automatic and handbrushing abrasion studies. *J Am Dent Ass* 1964;68:43–50.
- [6] Hefferen JJ. A laboratory method for assessment of dentifrice abrasivity. *J Dent Res* 1976;55:563–73.
- [7] Addy M, Hughes J, Pickles MJ, Joiner A, Huntington E. Development of a method *in situ* to study toothpaste abrasion of dentine. Comparison of 2 products. *J Clin Periodontol* 2002;29:896–900.
- [8] Redmalm G, Ryden H. Dentifrice abrasivity. The use of laser beams for comparative studies *in vitro* of surface changes. *Swed Dent J* 1979;3:91–100.
- [9] Joiner A, Philpotts CJ, Ashcroft AT, Laucello M, Salvador A. *In vitro* cleaning, abrasion and fluoride efficacy of a new silica based whitening toothpaste containing blue covarine. *J Dent* 2008;36(Suppl 1):32–7.
- [10] Vincentini BC, Braga SR, Sobral MA. The measurement *in vitro* of dentine abrasion by toothpastes. *Int Dent J* 2007;57:314–18.
- [11] Wegehaupt FJ, Widmer R, Attin T. Is bovine dentine an appropriate substitute in abrasion studies? *Clin Oral Investig* 2010;14:201–5.
- [12] Liljeborg A, Tellefsen G, Johannsen G. The use of a profilometer for both quantitative and qualitative measurements of toothpaste abrasivity. *Int J Dent Hygiene* 2010;8:237–43.
- [13] Johannsen G. Cleaning effect of toothbrushing with three different toothpastes and water. *Swed Dent J* 1993;17:111–16.
- [14] Forward GC. Role of toothpastes in the cleaning of teeth. *Int Dent J* 1991;41:164–70.
- [15] Dyer D, Addy M, Newcombe RG. Studies *in vitro* of abrasion by different manual toothbrush heads and a standard toothpaste. *J Clin Periodontol* 2000;27:99–103.
- [16] Absi EG, Addy M, Adams D. Dentine hypersensitivity: uptake of toothpastes onto dentine and effects of brushing, washing and dietary acids. *J Oral Rehab* 1995;22:175–82.
- [17] Moore C, Addy M. Wear of dentine *in vitro* by toothpaste abrasives and detergents alone and combined. *J Clin Periodontol* 2005;32:242–6.
- [18] Joiner A. Review of the extrinsic stain removal and enamel/dentine abrasion by a calcium carbontae and perlite containing whitening toothpaste. *Int Dent J* 2006;56:175–80.
- [19] Joiner A, Pickles MJ, Lynch S, Cox TF. The measurement of enamel wear by for toothpastes. *Int Dent J* 2008;58:23–8.
- [20] Hooper S, West NX, Pickles MJ, Joiner A, Newcombe RG, Addy M. Investigation of erosion and abrasion on enamel and dentine: a model *in situ* using toothpastes of different abrasivity. *J Clin Periodontol* 2003;30:802–8.
- [21] Voronets J, Lussi A. Thickness of softened human enamel removed by toothbrush abrasion: an *in vitro* study. *Clin Oral Investig* 2010;14:251–6.
- [22] Kielbasa AM, Gillman L, Zantner C, Meyer-Lueckel H, Hellwig E, Schulte-Monting J. Profilometric and microradiographic studies on the effects of toothpaste and acidic gel abrasivity on sound and demineralized bovine dental enamel. *Caries Res* 2005;39:380–6.
- [23] Sexson JC, Phillips RW. Studies on the effect of abrasives on acrylic resins. *J Prosthet Dent* 1951;1:454–71.