

Open Access

High activity of Ag-doped Cd_{0.1}Zn_{0.9}S photocatalyst prepared by the hydrothermal method for hydrogen production under visible-light irradiation

Leny Yuliati*1,§, Melody Kimi^{2,3} and Mustaffa Shamsuddin²

Full Research Paper

Address:

¹Ibnu Sina Institute for Fundamental Science Studies, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia, ²Department of Chemistry, Faculty of Science, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia and ³Centre for Pre-University Studies, Universiti Malaysia Sarawak, 94300 Kota Samarahan, Sarawak, Malaysia

Email:

Leny Yuliati* - leny@ibnusina.utm.my

* Corresponding author

§ Tel: +60-7-5536272; Fax: +60-7-5536080

Keywords:

Ag doping; $Cd_{0.1}Zn_{0.9}S$; hydrogen production; hydrothermal; visible light

Beilstein J. Nanotechnol. **2014,** *5,* 587–595.

doi:10.3762/bjnano.5.69

Received: 31 December 2013 Accepted: 14 April 2014 Published: 07 May 2014

This article is part of the Thematic Series "Photocatalysis".

Guest Editor: R. Xu

© 2014 Yuliati et al; licensee Beilstein-Institut. License and terms: see end of document.

Abstract

Background: The hydrothermal method was used as a new approach to prepare a series of Ag-doped $Cd_{0.1}Zn_{0.9}S$ photocatalysts. The effect of Ag doping on the properties and photocatalytic activity of $Cd_{0.1}Zn_{0.9}S$ was studied for the hydrogen production from water reduction under visible light irradiation.

Results: Compared to the series prepared by the co-precipitation method, samples prepared by the hydrothermal method performed with a better photocatalytic activity. The sample with the optimum amount of Ag doping showed the highest hydrogen production rate of 3.91 mmol/h, which was 1.7 times higher than that of undoped Cd_{0.1}Zn_{0.9}S. With the Ag doping, a red shift in the optical response was observed, leading to a larger portion of the visible light absorption than that of without doping. In addition to the larger absorption in the visible-light region, the increase in photocatalytic activity of samples with Ag doping may also come from the Ag species facilitating electron—hole separation.

Conclusion: This study demonstrated that Ag doping is a promising way to enhance the activity of $Cd_{0.1}Zn_{0.9}S$ photocatalyst.

Introduction

The development of clean and renewable hydrogen energy through a sustainable production process is still a big issue to be addressed. Solar energy is a very attractive option as it is the most abundant energy. The conversion of solar energy to chemical energy by photocatalytic processes, such as photocatalytic water reduction in the presence of semiconductor photocata-

lysts, would be an opportunity to produce clean hydrogen energy. Recently, special attention has been paid to the use of visible light-driven photocatalysts [1-4]. One of the promising photocatalysts is $\operatorname{Cd}_{1-x}\operatorname{Zn}_x\operatorname{S}$ solid solution [5-8]. The successful formation of a solid solution of ZnS and CdS resulted in an absorption shift of ZnS to the visible-light range, while maintaining the high conduction band energy required for hydrogen production. However, in order to utilize solar energy in the future, a further red shift to a range of even longer wavelengths is still highly desired.

The modification of $Cd_{1-x}Zn_xS$ photocatalyst with metal ions, such as Cu [9-13], Ni [14,15], Sn [16], and Sr [17] has been a good attempt to increase the visible-light absorption of the $Cd_{1-x}Zn_xS$ photocatalyst. The use of Ag species as a good dopant for various types of photocatalysts has been also reported [18-20], including its use to modify Cd_{1-x}Zn_xS [21-23]. Cd_{1-x}Zn_xS modified by Ag₂S was reported to show activity for hydrogen production from water [21] and hydrogen sulfide [22]. On the other hand, the properties of Ag⁺-doped Cd_{1-x}Zn_xS have been investigated by spectroscopic and photochemical studies [23]. It was proposed that the Ag⁺ might act as a hole trapping site. Since the electron-hole recombination rate may increase as a result of defect sites created by the doping element, reducing electron-hole recombination and promoting interfacial charge transfer should be optimized in order to improve the efficiency of the photocatalysts.

The most widely used method to prepare Ag-doped $Cd_{1-x}Zn_xS$ is the co-precipitation method [21]. However, the co-precipitation method usually produces materials with low crystallinity. Since high crystallinity is beneficial for photocatalytic hydrogen production [1-4], it is worth to further investigate an alternative method to prepare the Ag-doped $Cd_{1-x}Zn_xS$ with high crystallinity. It has been reported that compared to the co-precipitation method, the hydrothermal method produced sulfide photocatalysts with better crystallinity, which gave higher activity for hydrogen production [9,16]. In the present work, the Ag(x)-doped $Cd_{0.1}Zn_{0.9}S$ samples were prepared by both hydrothermal and co-precipitation methods. The superior activity of Ag(x)-doped $Cd_{0.1}Zn_{0.9}S$ prepared by hydrothermal method is discussed.

Results and Discussion

Figure 1 shows the X-ray diffraction (XRD) patterns of $Cd_{0.1}Zn_{0.9}S$ and Ag(x)-doped $Cd_{0.1}Zn_{0.9}S$ samples prepared by using the hydrothermal method. The diffraction peaks for all samples, except for Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$, were in good agreement with the diffraction peaks of ZnS cubic zinc-blende phase (JCPDS No. 772100) with major diffraction peaks at 20 of 28.6, 32.5, 47.6 and 56.3°, corresponding to the (111), (200),

(220) and (311) planes respectively. On the other hand, in addition to the cubic zinc blende phase, the Ag(0.05)-doped Cd_{0.1}Zn_{0.9}S also showed the presence of small diffraction peaks of the hexagonal phase at 2θ of ca. 27 and 31° (Figure 1d). A similar phenomenon was also reported when Cu was used as a dopant [9]. There are no diffraction peaks corresponding to Ag or other crystal phases. This could be due to the fact that the content of Ag might be too small to be detected or Ag was well dispersed in Cd_{0.1}Zn_{0.9}S. This result also indicated that no detectable impurity phases existed in the prepared samples. The small amount of Ag dopant increased remarkably the intensity of the diffraction peaks compared to the undoped Cd_{0.1}Zn_{0.9}S (Figure 1a,b), which suggests that a small amount of Ag might induce the crystal growth. However, further increase of the Ag dopant did not further increase the intensity of the diffraction peaks. With increasing amount of Ag dopant, the peaks became slightly broader (Figure 1b-d) since Ag might be clustered and in turn gave a slightly increased disorder. As the diffraction peaks were only slightly shifted to higher values of 20 with increasing amount of Ag, it can be suggested that Ag could be doped into the lattice without causing much crystal distortion.

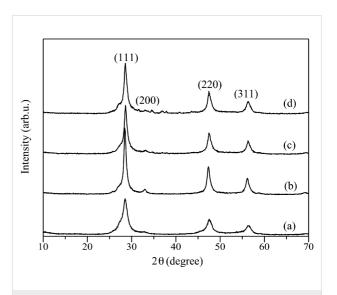


Figure 1: XRD patterns of (a) $Cd_{0.1}Zn_{0.9}S$, (b) Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$, (c) Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$, and (d) Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ prepared by the hydrothermal method.

The XRD patterns for $Cd_{0.1}Zn_{0.9}S$ and Ag(x)-doped $Cd_{0.1}Zn_{0.9}S$ samples prepared by the co-precipitation method are shown in Figure 2. For all samples, only diffraction peaks of ZnS cubic zinc-blende phase could be observed and no other phases could be detected. Different from the series prepared by hydrothermal method, there was no obvious change in the intensities of diffraction peaks after Ag was doped into the $Cd_{0.1}Zn_{0.9}S$. Broadening and shifting of the diffraction peaks were not observed, suggesting that Ag might not be doped


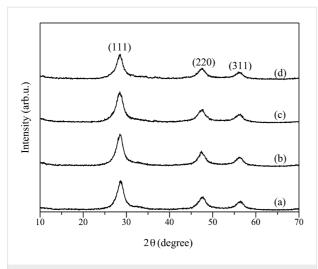



Figure 2: XRD patterns of (a) $Cd_{0.1}Zn_{0.9}S$, (b) Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$, (c) Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$, and (d) Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ prepared by the co-precipitation method.

inside but existed on the surface of Cd_{0.1}Zn_{0.9}S. Samples prepared by the co-precipitation method showed less intense and broader diffraction peaks than those prepared by the hydrothermal method, suggesting the less crystallinity and/or less crystallite size. This result was reasonable since co-precipitation method did not involve crystal growth by heating process.

Figure 3 and Figure 4 show field emission scanning electron microscopy (FESEM) images of $Cd_{0.1}Zn_{0.9}S$ and Ag(x)-doped $Cd_{0.1}Zn_{0.9}S$ samples prepared by hydrothermal and co-precipitation methods, respectively. For samples prepared by the hydrothermal method, all samples have a spherical shape with particle sizes in the range of 20–120 nm that are further agglomerated into bigger particles with no uniform size. The samples prepared by the co-precipitation method also have spherical shapes with slightly lower particle sizes in the range of 10–70 nm. For all samples, the morphology of $Cd_{0.1}Zn_{0.9}S$ was not affected by the added Ag.

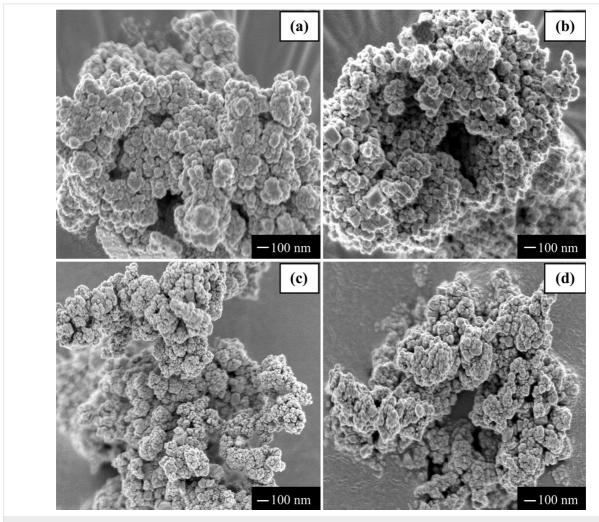

 $\textbf{Figure 3:} \ \textbf{FESEM} \ \text{images of (a)} \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S}, \ \textbf{(b)} \ \textbf{Ag} (0.01) \text{-doped } \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S}, \ \textbf{(c)} \ \textbf{Ag} (0.03) \text{-doped } \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \textbf{(d)} \ \textbf{Ag} (0.05) \text{-doped } \textbf{Ag} (0.05) \text{-doped } \textbf{Ag} (0.05) \text{-doped } \textbf{Ag} (0.05) \text{-doped } \textbf{$

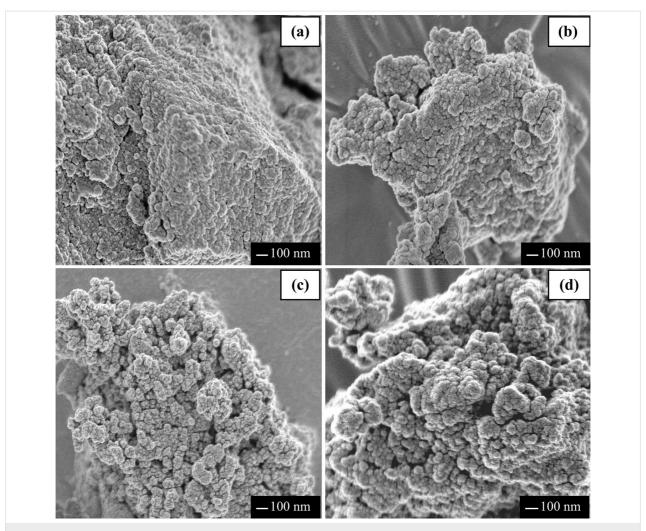

 $\textbf{Figure 4:} \ \ \textbf{FESEM} \ \ \text{images of (a)} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S}, \ \ \textbf{(b)} \ \ \textbf{Ag}(0.01) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S}, \ \ \textbf{(c)} \ \ \textbf{Ag}(0.03) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{(d)} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Cd}_{0.1}\textbf{Zn}_{0.9}\textbf{S} \ \ \textbf{Ag}(0.05) - \textbf{doped} \ \ \textbf{Ag}(0$

Figure 5 shows the diffuse reflectance UV-visible (DR UV-vis) spectra of samples prepared by the hydrothermal method. The Cd_{0.1}Zn_{0.9}S showed a shoulder peak around 400-500 nm (Figure 5a), similar to previous studies [9,16]. The addition of Ag shifted the absorption edge toward longer wavelengths, suggesting the formation of Ag-doped Cd_{0.1}Zn_{0.9}S samples. The values of the band gap energy for the samples are listed in Table 1. The band gap energy was determined by taking the intersection between the linear tangent line with the x-axis from a plot of $F(\%R)hv^{1/n}$ versus hv, in which F(%R) is the Kubelka-Munk function, h is Planck's constant, v is the frequency of vibration, and n is 1/2 for a direct allowed transition. As shown in Table 1, the addition of a small amount of Ag decreased the band gap energy of the Cd_{0.1}Zn_{0.9}S samples (Table 1, entries 1 and 2). A further increase of Ag did not give a monotonous decrease in the band gap energy, even though these samples still showed lower band gap energy than the Cd_{0.1}Zn_{0.9}S sample (Table 1, entries 3 and 4).

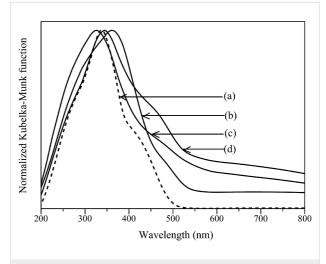


Figure 5: DR UV–visible spectra of (a) $Cd_{0.1}Zn_{0.9}S$, (b) Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$, (c) Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$ (d) Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ prepared by the hydrothermal method.

entry	sample	band gap energy/eV	preparation method
1	Cd _{0.1} Zn _{0.9} S	3.11	hydrothermal
2	Ag(0.01)-doped Cd _{0.1} Zn _{0.9} S	2.81	
3	Ag(0.03)-doped Cd _{0.1} Zn _{0.9} S	3.01	
4	Ag(0.05)-doped Cd _{0.1} Zn _{0.9} S	2.88	
5	Cd _{0.1} Zn _{0.9} S	2.94	co-precipitation
6	Ag(0.01)-doped Cd _{0.1} Zn _{0.9} S	3.06	
7	Ag(0.03)-doped Cd _{0.1} Zn _{0.9} S	2.99	
8	Ag(0.05)-doped Cd _{0.1} Zn _{0.9} S	2.66	

In addition to the shifted absorption edge and the decreased band gap energy, Ag doping caused an absorption tail in the range of 600-800 nm. The absorption in this area has been assigned to the formation of Ag₂S [21,24]. Even though the Ag₂S formation could not be detected by XRD owing to the low sensitivity, it can be suggested that the added Ag was not completely doped in the Cd_{0.1}Zn_{0.9}S. The addition of Ag also caused a new absorption appearing at about 295 nm for Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ and Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$ (Figure 5b,c), corresponding to the presence of Ag metal nanoparticles [25] that can be formed catalytically through the reduction of Ag⁺ by the Ag₂S as the catalyst [26]. On the other hand, even though Ag(0.05)-doped Cd_{0.1}Zn_{0.9}S did not show such an absorption at 295 nm (Figure 5d), its maximum peak was shifted to longer wavelengths, which might occur due to the increase in the particle size of the formed Ag metal [26]. Even though the mechanism could not be revealed in this paper, these results showed that the addition of Ag was not only simply doped into the Cd_{0.1}Zn_{0.9}S, but also was used to form other Ag species such as Ag metal and Ag₂S. The formation of the later species was obviously increased with the increase of the added Ag amount. Various possible formations of Ag species mentioned above led to the non-monotonous red shift and non-monotonous decrease in the band gap energy with the increase of Ag doping.

The absorption spectra of samples synthesized by co-precipitation method are shown in Figure 6. The $Cd_{0.1}Zn_{0.9}S$ sample showed a smooth absorption edge around 450 nm (Figure 6a). The addition of Ag shifted the absorption edge toward longer wavelengths when the amount of Ag was large (Figure 6d). As shown in Table 1, a small amount of Ag slightly increased the band gap energy of $Cd_{0.1}Zn_{0.9}S$ sample (Table 1, entries 5–7), while a large amount of Ag decreased the band gap energy (Table 1, entry 8). The increase in Ag doping also gave an increase in the absorption level above 600 nm due to the formation of Ag_2S [21,24]. The formation of Ag_2S on the samples prepared by the co-precipitation method was found to be larger

than that on the samples prepared by the hydrothermal method. Even though the formation of a new absorption below 300 nm was not as clear as those observed on the samples prepared by the hydrothermal method, it could be observed that the peak maximum of Cd_{0.1}Zn_{0.9}S was shifted from 348 to 325–326 nm (Figure 6b,c), which would be due to formation of Ag metal on Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S and Ag(0.03)-doped Cd_{0.1}Zn_{0.9}S. A further increase of the amount of added Ag caused the peak maximum to be shifted from 326 to 339 nm (Figure 6d), owing to the formation of larger particles of Ag metal, similar to the samples prepared by hydrothermal method mentioned above.

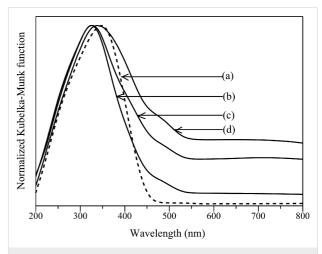


Figure 6: DR UV–visible spectra of (a) $Cd_{0.1}Zn_{0.9}S$, (b) Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$, (c) Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$ (d) Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ prepared by the co-precipitation method.

The photocatalytic performances of Cd_{0.1}Zn_{0.9}S and Ag(x)-doped Cd_{0.1}Zn_{0.9}S samples prepared by the hydrothermal method were examined for hydrogen production under visible-light irradiation as shown in Figure 7. All samples showed visible-light activity for hydrogen production. The undoped Cd_{0.1}Zn_{0.9}S sample produced hydrogen at a rate of 2.49 mmol/h. The Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S showed an increased rate of hydrogen production of 3.68 mmol/h.

However, unfortunately, when the amount of Ag increased, the activity was not improved. After 5 h of reaction, Ag(0.03)doped $Cd_{0.1}Zn_{0.9}S$ and Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ even showed a lower rate than that obtained from the undoped Cd_{0.1}Zn_{0.9}S. The enhancement in the photocatalytic activity of Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S might be attributed to the better crystallinity, the improved absorption in the visible-light region, as well as the presence of Ag species. Regarding the latter it has been proposed that both Ag⁰ and Ag⁺ played an important role in facilitating the charge separation and suppressing the recombination of photoexcited charge carries [18,19], while the Ag₂S could also act as a hole-transfer catalyst [21,24] for the oxidation of sulfide ions, which in turn promoted the activity. As shown in the DR UV-vis spectra (Figure 5), the formation of Ag₂S could not be avoided and it increased with the increase of Ag amount. However, since the activity did not increase but decreased with the increase of Ag amount, the Ag₂S would not be the main species responsible for the high activity on Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S. Indeed, the decrease of the activity of Ag(0.03)-doped Cd_{0.1}Zn_{0.9}S and Ag(0.05)-doped Cd_{0.1}Zn_{0.9}S showed that the Ag₂S might block the incident light, reduce the reaction sites for oxidation, and thus suppress the photocatalytic reaction [24].

The stability of the samples prepared by the hydrothermal method was investigated by reusing the samples for two consecutive runs. The photocatalytic activity results for first and second runs are also shown in Figure 7. The undoped $Cd_{0.1}Zn_{0.9}S$ showed a lower photocatalytic activity in the second run due to poor stability. On the other hand, all Ag-doped $Cd_{0.1}Zn_{0.9}S$ samples showed a relatively stable

activity. This result suggested that the presence of Ag was important to maintain the stability of the photocatalysts. Among the samples, the Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S sample showed the highest activity for hydrogen production. The rate for hydrogen production was slightly increased in the second run, suggesting that the Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S sample might experience a photochemical activation process. The similar phenomenon was also reported to occur on CdS/ZnFe₂O₄ photocatalyst during the photocatalytic hydrogen production [27]. In order to understand the possible photochemical activation process occurred on the Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S sample, the used sample was characterized by DR UV-visible spectroscopy. As shown in Figure 8, the absorption peak of the

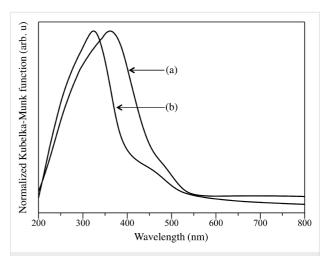


Figure 8: DR UV–visible spectra of (a) fresh and (b) used Ag(0.01)–doped $Cd_{0.1}Zn_{0.9}S$ prepared by the hydrothermal method after second run

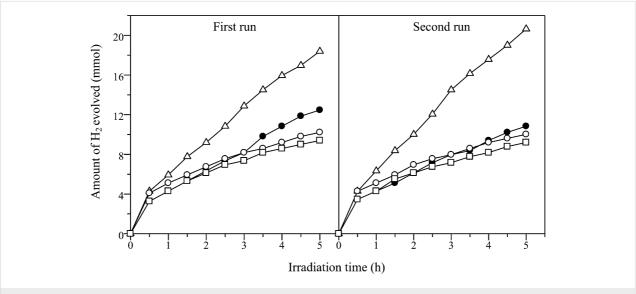


Figure 7: Photocatalytic hydrogen evolution on $Cd_{0.1}Zn_{0.9}S$ (filled circles), Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ (empty triangles), Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$ (empty circles), and Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ (empty squares) prepared by the hydrothermal method under visible-light irradiation.

Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ sample was shifted to lower wavelengths centred around 323 nm and the absorption intensity above 550 nm was decreased after the second run. These changes showed that the amount of Ag metal on the surface might be increased via photoreduction during the reaction. As a result, the photocatalytic activity of the Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ sample increased within the reaction time. The average hydrogen production rate from both runs was determined to be 3.91 mmol/h and the value was 1.7 times better than the average rate observed on the undoped $Cd_{0.1}Zn_{0.9}S$.

Figure 9 shows the photocatalytic activities of Cd_{0.1}Zn_{0.9}S and Ag(x)-doped $Cd_{0.1}Zn_{0.9}S$ samples prepared by co-precipitation method. The Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ and Ag(0.03)-doped Cd_{0.1}Zn_{0.9}S showed a higher activity than the undoped Cd_{0.1}Zn_{0.9}S. The highest photocatalytic activity was recorded for the Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S with a hydrogen production rate of 2.19 mmol/h. As for Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$, the activity was higher than that of the undoped compound in the first 3.5 hours, but the activity decreased over time. The samples prepared by the co-precipitation method showed less activity than those prepared by the hydrothermal method, which might be due to the lower crystallinity as discussed above. The stability of the samples was also tested for the second run. It was observed that undoped Cd_{0.1}Zn_{0.9}S and Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S showed a slightly decreased photocatalytic activity as compared to activity obtained in the first run. The decrease in the activity is stronger in Ag(0.03)-doped Cd_{0.1}Zn_{0.9}S and Ag(0.05)-doped Cd_{0.1}Zn_{0.9}S. Both samples showed a lower activity than the undoped one in the second run. The Ag(x)doped Cd_{0.1}Zn_{0.9}S samples prepared by the co-precipitation

method were found to be less stable than those prepared by the hydrothermal method that might be due to the formation of more Ag₂S and less doping of Ag.

Conclusion

Two series of Ag-doped $Cd_{0.1}Zn_{0.9}S$ samples were prepared by hydrothermal and co-precipitation methods, respectively. The Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ prepared by the hydrothermal method showed the highest photocatalytic activity and stability under visible light irradiation with a hydrogen production rate of 3.91 mmol/h, which was 1.7 times higher than that of the undoped $Cd_{0.1}Zn_{0.9}S$. The better photocatalytic activity observed for the Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ was proposed due to higher crystallinity, better absorption of visible light, and the formation of an optimum amount of Ag species, which facilitates the electron–hole separation and increase the stability of the catalyst, and the formation of less Ag_2S , which would suppress the reaction.

Experimental

Preparation of Ag-doped Cd_{0.1}Zn_{0.9}S. Hydrothermal and co-precipitation methods were used to prepare the Ag-doped Cd_{0.1}Zn_{0.9}S samples, which were labeled as Ag(x)-doped Cd_{0.1}Zn_{0.9}S, with x showed the doping amount of Ag (x = 0.01, 0.03, or 0.05 mol). For the hydrothermal method, a series of Ag(x)-doped Cd_{0.1}Zn_{0.9}S samples was synthesized similarly to the previous studies [9,16]. In a typical synthesis for Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S, AgNO₃ (Unilab, 99.9%), Cd(NO₃)₂·4H₂O (Aldrich, 98%), Zn(CH₃COO)₂·2H₂O (GCE chemicals, 98%) and CH₃CSNH₂ (Merck, 99%) with molar ratios of 0.01:0.1:0.9:1 were dissolved in distilled water at room

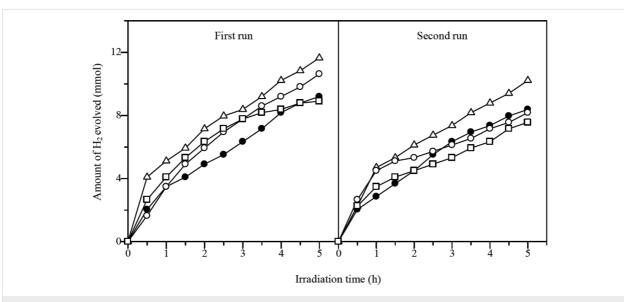


Figure 9: Photocatalytic hydrogen evolution on $Cd_{0.1}Zn_{0.9}S$ (filled circles), Ag(0.01)-doped $Cd_{0.1}Zn_{0.9}S$ (empty triangles), Ag(0.03)-doped $Cd_{0.1}Zn_{0.9}S$ (empty circles), and Ag(0.05)-doped $Cd_{0.1}Zn_{0.9}S$ (empty squares) prepared by the co-precipitation method under visible-light irradiation.

temperature. The solution was then transferred into an autoclave with an inner Teflon lining, sealed and heated in an oven at 433 K for 8 h. The solution was left to reach room temperature naturally. The precipitate was separated by using a centrifuge and washed by using distilled water. The sample was then dried at room temperature under vacuum conditions. For the co-precipitation method, the series of Ag(x)-doped Cd_{0.1}Zn_{0.9}S was prepared similarly to the previous studies [9,16]. Typically, to synthesize Ag(0.01)-doped Cd_{0.1}Zn_{0.9}S, Na₂S·xH₂O (QRëc, 98%) solution was added dropwise to an aqueous solution containing AgNO₃ (Unilab, 99.9%), Cd(NO₃)₂·4H₂O (Aldrich, 98%) and Zn(CH₃COO)₂·2H₂O (GCE chemicals, 98%) with molar ratios of 0.01:0.1:0.9. The solution was stirred for 12 h at room temperature. The resulting precipitate was filtered and washed several times with distilled water. The product then was dried in air at 343 K for 12 h.

Characterizations. XRD patterns were obtained on an X-ray diffractometer (Bruker Advance D8) using Cu Kα radiation (40 kV, 40 mA). The morphologies and size of the samples were observed by using field emission scanning electron microscopy (FESEM) with JEOL JSM 6701F at an accelerating voltage of 2 kV with platinum coating prior to analysis. DR UV–vis spectra were recorded at room temperature using a UV–visible spectrometer (Perkin Elmer Lambda 900). BaSO₄ was used as a reflectance standard.

Photocatalytic testing. As described in the previous studies [9,16], photocatalytic hydrogen evolution was performed in a closed side irradiated-Pyrex cell equipped with a water condenser to maintain the temperature constant during the reaction. A 500 W halogen lamp was used as the visible-light source. Hydrogen gas evolved was identified by an online system with thermal conductivity detector (TCD) gas chromatography (GC, Agilent 7890A) using Supelco 13X molecular sieves and argon carrier gas, which amount was measured by volumetric method. In all experiments, the powder sample (0.2 g) was dispersed by magnetic stirring in an aqueous solution (50 mL) containing 0.25 M Na₂SO₃ and 0.35 M Na₂S as the sacrificial agents. Nitrogen gas was flushed through the reaction cell for 30 min before reaction to remove air. In order to check the photocatalytic stability, the sample was reused without washing or drying. Before another 5 h irradiation in the second run, the reactor containing the tested sample was purged with nitrogen gas for 30 min to ensure that there was no residual hydrogen in the reactor.

Acknowledgements

This work was financially supported by the Ministry of Higher Education (MOHE, Malaysia) and the Universiti Teknologi Malaysia (UTM, Malaysia) through a Tier-1 Research University Grant (cost center code: Q.J130000.2526.02H95). Financial support from the Ministry of Science, Technology and Innovation through the National Science Fellowship is greatly acknowledged (MK).

References

- Navarro, R. M.; Alvarez-Galván, M. C.; Villoria de la Mano, J. A.; Al-Zahrani, S. M.; Fierro, J. L. G. *Energy Environ. Sci.* 2010, 3, 1865–1882. doi:10.1039/c001123a
- Maeda, K. J. Photochem. Photobiol., C: Photochem. Rev. 2011, 12, 237–268. doi:10.1016/j.jphotochemrev.2011.07.001
- Zhang, K.; Guo, L. Catal. Sci. Technol. 2013, 3, 1672–1690. doi:10.1039/c3cy00018d
- Abe, R. J. Photochem. Photobiol., C: Photochem. Rev. 2010, 11, 179–209. doi:10.1016/j.jphotochemrev.2011.02.003
- Xing, C.; Zhang, Y.; Yan, W.; Guo, L. Int. J. Hydrogen Energy 2006, 31, 2018–2024. doi:10.1016/j.ijhydene.2006.02.003
- del Valle, F.; Ishikawa, A.; Domen, K.; Villoria de la Mano, J. A.; Sánchez-Sánchez, M. C.; González, I. D.; Herreras, S.; Mota, N.; Rivas, M. E.; Álvarez Galván, M. C.; Fierro, J. L. G.; Navarro, R. M. Catal. Today 2009, 143, 51–56. doi:10.1016/j.cattod.2008.09.024
- Wang, L.; Wang, W.; Shang, M.; Yin, W.; Sun, S.; Zhang, L. Int. J. Hydrogen Energy 2010, 35, 19–25. doi:10.1016/i.iihvdene.2009.10.084
- Liu, M.; Wang, L.; Lu, G. (M.); Yao, X.; Guo, L. Energy Environ. Sci. 2011, 4, 1372–1378. doi:10.1039/c0ee00604a
- Kimi, M.; Yuliati, L.; Shamsuddin, M. J. Photochem. Photobiol., A: Chem. 2012, 230, 15–22. doi:10.1016/j.jphotochem.2012.01.004
- Zhang, W.; Zhong, Z.; Wang, Y.; Xu, R. J. Phys. Chem. C 2008, 112, 17635–17642. doi:10.1021/jp8059008
- Liu, G.; Zhao, L.; Ma, L.; Guo, L. Catal. Commun. 2008, 9, 126–130. doi:10.1016/j.catcom.2007.05.036
- Zhang, W.; Xu, R. Int. J. Hydrogen Energy 2009, 34, 8495–8503. doi:10.1016/j.ijhydene.2009.08.041
- Liu, G.; Zhou, Z.; Guo, L. Chem. Phys. Lett. 2011, 509, 43–47. doi:10.1016/j.cplett.2011.04.073
- Zhang, X.; Jing, D.; Liu, M.; Guo, L. Catal. Commun. 2008, 9, 1720–1724. doi:10.1016/j.catcom.2008.01.032
- Zhang, X.; Jing, D.; Guo, L. Int. J. Hydrogen Energy 2010, 35, 7051–7057. doi:10.1016/j.ijhydene.2009.12.132
- Kimi, M.; Yuliati, L.; Shamsuddin, M. Int. J. Hydrogen Energy 2011, 36, 9453–9461. doi:10.1016/j.ijhydene.2011.05.044
- Zhang, K.; Jing, D.; Chen, Q.; Guo, L. Int. J. Hydrogen Energy 2010, 35, 2048–2057. doi:10.1016/j.ijhydene.2009.12.143
- Liao, L.; Ingram, C. W. Appl. Catal., A: Gen. 2012, 433–434, 18–25. doi:10.1016/j.apcata.2012.04.033
- Li, Y.; Ma, M.; Chen, W.; Li, L.; Zen, M. Mater. Chem. Phys. 2011, 129, 501–505. doi:10.1016/j.matchemphys.2011.04.055
- Lin, Y.-J.; Chang, Y.-H.; Chen, G.-J.; Chang, Y.-S.; Chang, Y.-C. J. Alloys Compd. 2009, 479, 785–790. doi:10.1016/j.jallcom.2009.01.061
- Reber, J. F.; Rusek, M. J. Phys. Chem. 1986, 90, 824–834. doi:10.1021/j100277a024
- Khan, M. M. T.; Bhardwaj, R. C.; Bhardwaj, C. Int. J. Hydrogen Energy 1988, 13, 7–10. doi:10.1016/0360-3199(88)90003-1

- Dzhagan, V. M.; Stroyuk, O. L.; Rayevska, O. E.; Kuchmiy, S. Y.; Valakh, M. Y.; Azhniuk, Y. M.; von Borczyskowski, C.; Zahn, D. R. T. J. Colloid Interface Sci. 2010, 345, 515–523. doi:10.1016/j.jcis.2010.02.001
- Shen, S.; Guo, L.; Chen, X.; Ren, F.; Mao, S. S.
 Int. J. Hydrogen Energy 2010, 35, 7110–7115.
 doi:10.1016/j.ijhydene.2010.02.013
- Zhou, Z.; Long, M.; Cai, W.; Cai, J. J. Mol. Catal. A: Chem. 2012, 353–354, 22–28. doi:10.1016/j.molcata.2011.10.025
- 26. Kryukov, A. I.; Stroyuk, A. L.; Zin'chuk, N. N.; Korzhak, A. V.; Kuchmii, S. Y. *J. Mol. Catal. A: Chem.* **2004**, *221*, 209–221. doi:10.1016/j.molcata.2004.07.009
- 27. Yu, T.-H.; Cheng, W.-Y.; Chao, K.-J.; Lu, S.-Y. *Nanoscale* **2013**, *5*, 7356–7360. doi:10.1039/c3nr02658b

License and Terms

This is an Open Access article under the terms of the Creative Commons Attribution License (http://creativecommons.org/licenses/by/2.0), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

The license is subject to the *Beilstein Journal of Nanotechnology* terms and conditions: (http://www.beilstein-journals.org/bjnano)

The definitive version of this article is the electronic one which can be found at: doi:10.3762/bjnano.5.69