



Published in final edited form as:

*Cell Transplant.* 2015 ; 24(2): 235–245. doi:10.3727/096368913X676204.

## Engineering a Fibrocartilage Spectrum Through Modulation of Aggregate Redifferentiation

Meghan K. Murphy<sup>a</sup>, Taylor E. Masters<sup>a</sup>, Jerry C. Hu<sup>a</sup>, and Kyriacos A. Athanasiou<sup>a,b,\*</sup>

<sup>a</sup> Department of Biomedical Engineering, University of California Davis Davis, CA 95616, USA

<sup>b</sup> Department of Orthopaedic Surgery, University of California Davis Davis, CA 95616, USA

### Abstract

Expanded costochondral cells provide a clinically relevant cell source for engineering both fibrous and hyaline articular cartilage. Expanding chondrocytes in monolayer results in a shift toward a proliferative, fibroblastic phenotype. Three-dimensional aggregate culture may, however, be used to recover chondrogenic matrix production. This study sought to engineer a spectrum of fibrous to hyaline neocartilage from a single cell source by varying the duration of three-dimensional culture following expansion. In third passage porcine costochondral cells, the effects of aggregate culture duration were assessed after 0, 8, 11, 14, and 21 days of aggregate culture and after 4 subsequent weeks of neocartilage formation. Varying the duration of aggregate redifferentiation generated a spectrum of fibrous to hyaline neocartilage. Within 8 days of aggregation, proliferation ceased, and collagen and glycosaminoglycan production increased, compared with monolayer cells. In self-assembled neocartilage, type II to I collagen ratio increased with increasing aggregate duration, yet glycosaminoglycan content varied minimally. Notably, 14 days of aggregate redifferentiation increased collagen content by 25%, tensile modulus by over 110%, and compressive moduli by over 50%, compared with tissue formed in the absence of redifferentiation. A spectrum of fibrous to hyaline cartilage was generated using a single, clinically relevant cell source, improving the translational potential of engineered cartilage.

### Keywords

Costal chondrocytes; Monolayer expansion; Three-dimensional culture; Self-Assembly; Hyaline cartilage

### Introduction

Articular cartilage degeneration affects a number of load bearing joints including the knee, hip, shoulder, facet, and temporomandibular joint (TMJ). Based on the 2007-2009 National Health Interview Survey, 50M Americans reported doctor-diagnosed arthritis and 21M experienced arthritis-related activity limitations (11). However, existing clinical approaches

\* Corresponding author: K. A. Athanasiou One Shields Ave, Davis, CA 95616, USA Phone: 530 754 6645, Fax: 530 754 5739 athanasiou@ucdavis.edu.

Author Disclosure Statement

The authors have no conflicts of interest to disclose.

for articular cartilage degeneration seldom provide long-term repair or restoration to a non-destructive loading environment (14,29,33). In the case of hyaline cartilage lesions, such approaches include debridement, in which the joint is arthroscopically cleaned of loose debris and surfaces are smoothed, microfracture, in which defects are created to initiate bleeding from the subchondral bone, and mosaicplasty, in which cartilage biopsies are removed from non-arthritic regions and pieced together to resurface the load-bearing regions. In the case of fibrocartilage degeneration, partial or total discectomy or meniscectomy may be used to remove a portion of the meniscus or the entire structure. Engineering a replacement tissue may present an alternate approach to replace degenerated tissues, circumventing the negative side effects and short comings of current standards of care (25).

Hyaline and fibrous cartilages are two distinctly different articular structures, both of which contribute to a healthy loading environment in diarthrodial joints. Hyaline cartilage, which lines the ends of long bones, plays a key role in the distribution of forces borne by the joint, and reduces the coefficient of friction during motion. The predominant type of collagen in hyaline cartilage is type II collagen (~90%), accompanied by an abundance of glycosaminoglycans (GAGs) (3). Unlike hyaline cartilage, fibrocartilage consists of predominantly type I collagen with minimal GAG content (3). Fibrocartilage is found in the knee meniscus, intervertebral disc, TMJ disc, and mandibular condyle. Fibrocartilage functions to distribute loads experienced by the surrounding structures. The collagen is highly organized, resisting strains along the functional axes. Though hyaline- and fibrocartilages differ in their composition and structure, both are essential to joint function while lacking sufficient capacity for self-repair.

Tissue engineering has the potential to produce functional replacement tissue for addressing hyaline and fibrocartilage degeneration. The self-assembling process has been developed to engineer robust scaffold-free constructs (22). The self-assembling process entails seeding chondrocytes at high density ( $10^7$  cells/mL) in non-adherent wells. The cells demonstrate cell-cell interactions within 24 hours of seeding, and begin producing extracellular matrix (38). This process is reminiscent of cartilage development and results in neocartilage with mechanical properties approaching those of native tissue (38). Moreover, manipulating cell source, culture conditions, and exogenous stimuli can enhance functional properties of engineered tissues. Efforts to engineer hyaline cartilage using articular chondrocytes in the self-assembling process have shown significant promise. In the presence of exogenous stimuli, tissue rich in type II collagen and GAGs, with tensile moduli over 3.5 MPa and an aggregate modulus of approximately 100 kPa has been developed (36). Separately, efforts have shown that articular chondrocyte and meniscus cell co-cultures may be used to engineer meniscus-shaped fibrocartilage with anisotropic tensile properties (Young's modulus over 3 MPa circumferentially, 2 MPa radially) (24). Common among these is the reliance on differentiated, articular chondrocytes, whose scarcity limits their use in autologous therapy. The ability to generate both hyaline and fibrous cartilage from a single, clinically relevant cell source would greatly improve the translational potential of tissue engineering efforts.

Costal cartilage exhibits notable potential as a cell source for tissue engineering. It is used in reconstructive surgeries, demonstrating isolation feasibility (35,47), and it is unaffected by pathologies of the diarthrodial joints (39). Expansion of chondrocytes has previously been shown to induce a shift toward a more fibrous phenotype (13,41). Compared with a spherical, chondrocyte-like morphology, cells exhibit a spread, fibroblast-like morphology with passage. This is accompanied by changes in matrix synthesis from type II collagen and aggrecan to fibroblastic matrices such as type I collagen (7,9,13). If methods are developed to direct and control this shift from one phenotype to the other, costal chondrocytes might hold the potential to be engineered into both hyaline cartilage and fibrocartilage.

Informed by the articular cartilage literature, aggregate culture duration may present a method for manipulating costochondral cell phenotype, in terms of matrix production, following monolayer expansion. Expanded chondrocytes have previously shown the potential to re-express a chondrogenic phenotype upon reintroduction into three-dimensional environment, which is valuable in engineering hyaline cartilage (5-7,26). Pellet cultures, polymer gels, and rotational cultures have all resulted in marked increases in cartilage-specific matrix expression following expansion (5-7,17,23,26,40). One such system, aggregate culture, employs a single cell suspension ( $\sim 10^6$  cells/mL) in a nonadherent dish, in rotation, allowing the cells to form suspended aggregates. In fourth passage articular chondrocytes, aggregate culture for 1 wk significantly increased collagen and GAG content, and tensile properties, compared with no aggregation and with pellet culture (23). Thus, varying the duration of aggregate culture may provide a useful means of engineering a spectrum of fibrous to hyaline cartilage using costal chondrocytes.

The present study sought to assess the effects of aggregate culture duration in third passage expanded costochondral cells. Using a one-factor analysis of variance study design, the effects of aggregate duration were assessed after 0, 8, 11, 14, and 21 days of aggregate culture, and after 4 weeks of neocartilage formation. It was hypothesized that 1) in aggregates, increasing aggregate duration would increase type II to type I collagen ratio and GAG content, 2) in constructs, there is a beneficial aggregate culture duration that would increase overall collagen content, type II to type I collagen ratio, GAG content, and resulting mechanical properties, and 3) different types of cartilages may be obtained from differing aggregate durations. This work builds upon previous efforts to identify expansion conditions to enhance proliferation and maintain chondrogenic potential in third passage costochondral cells (34). The present study seeks to extend this effort by developing methods to manipulate the re-expression of the chondrogenic phenotype following monolayer. This may allow for the development of a fibrocartilaginous spectrum of engineered tissues.

## Materials and Methods

### Cell Isolation and Expansion

Costal cartilage from crossbred Hampshire porcine approximately 6 mos of age (n=4, female, UC Davis Dept. Animal Sciences Meat Laboratory, Davis, CA, USA) were obtained within 24 hrs of death. A porcine model was selected based on translational efforts in the use of large animal models. Anatomically, there are notable similarities between the pig and the human, especially in the temporomandibular joint, as both are omnivores (27). Such

similarities point to the pig as a model for allogeneic tissue replacements. Advantages include availability of skeletally mature tissue, though one disadvantage is variations in biomechanical loading in quadrupeds compared with bipedal humans.

Costal cartilage was isolated from the four caudal asternal ribs and the perichondrium was discarded. Remaining cartilage was minced into ~ 1 mm pieces and digested in 0.2% collagenase type II (Worthington, Lakewood, NJ, USA) in chemically defined chondrogenic culture medium (CHG) [Dulbecco's modified Eagle medium (DMEM) with 4.5g/L-glucose and GlutaMAX (Gibco, Grand Island, NY, USA), 1% penicillin-streptomycin-fungizone (BD Biosciences, Bedford, MA, USA), 1% ITS+ premix (BD Biosciences), 1% non-essential amino acids (Gibco), 100 nM dexamethasone (Sigma, St. Louis, MO, USA), 50 µg/mL ascorbate-2-phosphate (Sigma), 40 µg/mL L-proline (Sigma), and 100 µg/mL sodium pyruvate (Sigma)] containing 3% FBS (Atlanta Biologicals, Lawrenceville, GA, USA) for 18 hrs at 37°C. After digestion, the cell suspension was filtered, counted, and seeded in T-225 flasks (BD Biosciences) at  $2.5 \times 10^4$  cells/cm<sup>2</sup>. Cells were expanded in CHG supplemented with 1 ng/mL TGF-β1 (PeproTech, Rocky Hill, NJ, USA), 5 ng/mL bFGF (PeproTech), and 10 ng/mL PDGF (PeproTech) based on increases in proliferation and chondrogenic potential previously demonstrated by the authors in a study utilizing a separate costochondral cell batch (34). At 80-90% confluence, cells were passaged with 0.5% Trypsin-EDTA (Gibco) 3 times (P3). P3 was selected based on previous work investigating collagen and GAG synthesis in primary, P1, P3 and P5 costochondral cells. P3 cells demonstrated significantly greater GAG content with no significant differences in total collagen content compared with primary cells (1).

### Chondrocyte Aggregation

Following monolayer expansion and prior to construct self-assembly, costochondral cells were redifferentiated in aggregate culture. The cells were seeded in a single cell suspension into 100 mm × 20 mm petri dishes (BD Biosciences) coated with 1% molecular biology grade agarose (Fisher Scientific, Fair Lawn, NJ, USA) at  $10^6$  cells/mL CHG supplemented with 10 ng/mL TGF-β1. Dishes were placed on an orbital shaker at 72 rpm for 8 days, 11 days, 14 days, or 21 days. In the case of 0 days (no aggregation), cells were immediately seeded into constructs following the last passage. At the conclusion of the specified aggregation treatment, several aggregates were evaluated histologically. Remaining aggregates were digested for 45 mins in 0.5% Trypsin-EDTA, followed by 45 mins in 0.2% collagenase type II on an orbital shaker at 37°C. Cell viability was assessed by Trypan blue exclusion assay (Sigma). The methods employed throughout the tissue engineering process are depicted in Figure 1.

### Construct Formation

Constructs were self-assembled following aggregate digestion. A sterile, custom-made stainless steel mold consisting of 5 mm diameter cylindrical prongs was constructed in-house to fit in 6 wells of a 48 well plate (Corning Inc., Corning, NY, USA). The wells were filled with 800 µL of sterile molten 2% molecular biology grade agarose (Fisher Scientific) in phosphate buffered saline (PBS, Sigma) and allowed to solidify at room temperature. Once the agarose solidified, the mold was removed and CHG was used to saturate the wells

prior to seeding. Cells were then seeded at  $2 \times 10^7$  cells/mL in 100  $\mu$ L aliquots. Thus,  $2 \times 10^6$  cells were seeded into each 5 mm diameter well. After 8 days of culture in the agarose wells, constructs were unconfined and placed in wells coated with a thin layer of 2% agarose to prevent adhesion. Unconfinement was intended to prevent radial growth restriction. Eight constructs were formed in each treatment. Constructs were cultured in CHG for a total of 4 weeks from seeding.

## Histology

Both aggregates and constructs were analyzed histologically. Aggregate samples from each group were collected at the end of the specified treatment duration and construct samples were taken after 4 weeks of construct culture. Samples were frozen in HistoPrep Frozen Tissue Embedding Media (Fisher Scientific) and cryosectioned to 14  $\mu$ m. Sections were fixed in formalin (EMD Chemicals, Gibbstown, NJ, USA) and stained with Safranin-O (Sigma)/fast-green (Sigma) for GAGs and with picosirius red (Spectrum Chemical, Gardena, CA, USA) for collagen. Immunohistological staining techniques were used to detect the presence of types I and II collagen. Mouse anti-type I collagen monoclonal antibody at 1:600 dilution (Accurate Chemical, Westbury NY, USA) was used to detect type I collagen and rabbit anti-human type II collagen polyclonal antibody at 1:200 dilution (Cedarlane Labs, Burlington, NC, USA) was used to detect type II collagen.

## Biochemical Evaluation

Samples were analyzed for biochemical content after 4 weeks of construct culture. Samples were massed before and after 48 hrs of lyophilization and digested in 125  $\mu$ g/mL papain (Sigma) in PBS (pH 6.5) containing 2mM N-acetyl cysteine (Sigma) and 2 mM EDTA (ACROS organics, Geel, Belgium) for 18 hrs at 60°C. GAG content was quantified using a Blyscan GAG assay (Bicolor, Westbury, NY, USA), based on 1,9-dimethylmethyl blue binding. Total collagen was quantified after hydrolyzing samples with 2 N NaOH for 20 min at 110°C using chloramine-T hydroxyproline assay with Sircol collagen standards (Bicolor). Cellularity was quantified using Quant-iT Picrogreen double stranded deoxyribonucleic acid (DNA) assay kit (Invitrogen, Carlsbad, CA, USA).

Sandwich enzyme-linked immunosorbent assays (ELISA) were used to detect types I and II collagen. Lyophilized samples were resuspended in 0.05 M acetic acid containing 0.5 M NaCl (pH 3.0) and digested with constant agitation in 10 mg/mL pepsin in 0.05 M acetic acid at 4°C for 4 days, followed by 1 mg/mL pancreatic elastase (Sigma) in 1x tris buffered saline at 4°C for 24 hrs. Capture antibodies (monoclonal mouse anti-porcine type I and II collagen, respectively, Chondrex Redmond, WA, USA) were incubated overnight at 4°C, 2% bovine serum albumin was used to block wells, samples/standards were added and incubated overnight, and detection antibodies (biotinylated monoclonal mouse anti-porcine type I and II collagen, respectively, Chondrex) were incubated overnight. Streptavidin Peroxidase solution was added, followed by tetramethylbenzidine, and HCl was used to stop the reaction.

## Mechanical Evaluation

Constructs were evaluated after 4 weeks of culture in unconfined compression and uniaxial tension. A 2 mm diameter punch was taken from the center of each construct for compression testing. Using an Instron 5565 (Instron, Norwood, MA, USA), samples were preconditioned with 15 cycles of 5% compressive strain and then strained sequentially at 10% and 20% in a stress-relaxation test. A Kelvin solid viscoelastic model was fit to the data to quantify instantaneous modulus ( $E_i$ ), relaxation modulus ( $E_r$ ), and coefficient of viscosity ( $\mu$ ) at each strain level, using a custom Matlab program (MathWorks, Natick, MA, USA). Tensile testing was conducted using a Test Resources 840L (Test Resources, Shakopee, MN, USA). A second 2 mm diameter punch was taken to form a dog-bone shaped tensile specimen. Paper tabs were used to grip the sample and to establish a consistent gauge length of 1.3 mm. Samples were elongated at a rate of 1% strain per second. Stress-strain curves were developed from the load-displacement curve and Young's modulus ( $E_Y$ ) was quantified using a custom Matlab program (MathWorks).

## Statistics

To determine if aggregate duration was a significant factor, data were analyzed using one-way analysis of variance (ANOVA). Tukey's *post hoc* test was performed to determine specific effects of each treatment, when indicated by the F-test ( $p < 0.05$ ). Data are reported as mean  $\pm$  standard deviation. Groups not sharing a common character are considered significantly different ( $p < 0.05$ ).

## Results

As depicted in Figure 1, morphology was characterized and histology was performed in monolayer, aggregates, and self-assembled neocartilage. Additionally, biochemical content and mechanical properties of self-assembled neocartilage was characterized after 4 weeks of culture.

### Monolayer, Aggregate, and Self-Assembled Neocartilage Morphology

Figure 2 demonstrates the morphology of costochondral cells throughout the tissue engineering process: in monolayer, aggregates, and self-assembled constructs. In monolayer, costochondral cells demonstrated a flattened, cobblestone morphology (Figure 2a). Morphology was consistent across passage number. Within 48 hrs of aggregation, cell aggregates formed in the range of 0.3-0.7 mm in diameter (Figure 2b). At the conclusion of each aggregate duration period, dissociated cells were self-assembled. Construct morphology varied within 48 hrs of self-assembly (Figure 2c). Cells that did not undergo redifferentiation (0 day treatment) contracted, demonstrating a decreased construct diameter, unlike the 8, 11, 14, and 21 day treatments.

### Monolayer and Aggregate Histology

Histology was performed in monolayer at confluence, prior to final passage, and at the conclusion of each aggregate duration (Figure 3a,b). Cells in monolayer stained minimally for intracellular collagen while GAG staining was not detectable (Figure 3a). Aggregate histology demonstrated the presence of collagen and GAGs for all treatments (Figure 3b).



Collagen staining increased with duration, while GAG staining remained generally consistent. Immunohistochemistry demonstrated the presence of type I and II collagen in all aggregates. With increasing aggregate duration, type I collagen decreased. Cell viability was quantified following aggregation (Figure 3c). Viability remained generally consistent. It was greatest after 11 days (95%) and lowest after 21 days (90%).

### Neocartilage Geometry and Hydration

Diameter, wet weight, hydration, and cellularity are presented in Table 1. The 0 day treatment led to the smallest average diameter ( $4.0 \pm 0.1$  mm), while 11 day treatment showed the largest average diameter ( $5.9 \pm 0.2$  mm). The morphology of representative constructs is depicted in Figure 2. Zero day treatment yielded a cyst in the central region of the tissue, while 8 days yielded smaller diffuse regions in the periphery. Homogeneous, disc-shaped neocartilage was observed with 11, 14, and 21 day treatments. The hydration of constructs paralleled the morphology; 11, 14 and 21 day treatments showed decreased tissue hydration, compared with 0 and 8 days.

### Neocartilage Histology and Biochemical Content

Histology reflected the presence of GAGs and collagen across all treatment groups (Figure 4a). Picrosirius red staining in neocartilage increased as aggregate duration increased. Safranin-O staining in 8, 11, 14 and 21 day treatments was increased compared with 0 days treatment. Immunohistochemistry demonstrated decreased type I collagen as aggregate duration increased. Notably type I collagen dropped off from 0 day treatment to 8 days, and again from 11 days to 14 days. Type II collagen staining remained generally consistent. .

Biochemical analysis of engineered constructs quantitatively reflected trends observed in collagen and GAG staining (Figure 4b). Collagen content increased with aggregate duration, showing significantly greater content in the 14 ( $0.8 \pm 0.09$  %) and 21 ( $0.9 \pm 0.08$  %) day treatments, compared with the 0 ( $0.7 \pm 0.03$  %), 8 ( $0.7 \pm 0.05$  %), and 11 ( $0.6 \pm 0.05$  %) day treatments. No significant differences were observed in GAG content between 0, 8, 11 and 14 day treatments. A significant decrease was observed in the 21 day treatment. ELISA was used to quantify types I and II collagen content. Type I collagen content was below the limit of detection of the assay. Type II collagen per DNA is reported in Figure 4b, reflecting phenotypic alterations. The 14 day treatment significantly increased type II collagen per cell, compared with 0 day treatment. Furthermore, a trending increase was observed from 8 days to 14 days and a trending decrease was observed from 14 days to 21 days.

### Neocartilage Mechanical Properties

The tensile and compressive properties of engineered neocartilage are reported in Figure 5. Generally, the mechanical properties of the engineered tissue improved as aggregate duration increased, with no significant differences between 14 and 21 day treatments. Young's modulus was significantly greater in the 14 ( $1.3 \pm 0.4$  MPa) and 21 day treatments ( $1.3 \pm 0.3$  MPa) compared with the 0, 8, and 11 day treatments (Figure 5a). The relaxation and instantaneous moduli in the 8 ( $73.2 \pm 22.1$  kPa,  $250.0 \pm 93.5$  kPa), 14 ( $79.8 \pm 31.8$  kPa,  $279.8 \pm 65.7$  kPa), and 21 ( $77.8 \pm 19.5$  kPa,  $347.3 \pm 80.7$  kPa) day treatments were significantly greater than the 0 day treatments. The lowest moduli were observed in the 0

and 11 day treatments (Figure 5b,c). Coefficient of viscosity increased with increasing aggregate duration (Figure 5d). Both viscosity and instantaneous moduli peaked after 21 days in aggregate culture.

## Discussion

Articular cartilages, fibrous and hyaline, are essential to load transmission throughout joint motion, and in the case of pathology, tissue engineering may present a promising therapeutic approach (25). The translational potential of tissue engineering may be improved if a spectrum of fibrous to hyaline cartilage may be engineered using a single, clinically relevant cell source. Importantly, chondrocyte expansion is associated with increased proliferation and matrix production similar to that of fibrocartilage, specifically type I collagen (13). In contrast, three-dimensional culture, following expansion, is associated with restoration of type II collagen production and matrix characteristic of hyaline cartilage (7). In the present study, the duration of aggregate culture was investigated with an objective of generating a spectrum of fibrous to hyaline self-assembled cartilage using clinically relevant costochondral cells. First, the hypothesis that increasing aggregate culture duration would increase type II to type I collagen ratio in aggregates was confirmed. Second, the hypothesis that there is a beneficial aggregate culture duration that would increase overall collagen content, type II to type I collagen ratio, and resulting mechanical properties in neocartilage was also confirmed. However, GAG content varied only minimally with duration in both aggregates and constructs. Overall, confirming the third hypothesis, varying aggregate duration yielded a spectrum of fibrocartilaginous tissues.

Aggregate redifferentiation of costochondral cells for 8 days yielded chondrogenic matrix production as evidenced by deposition of type II collagen and GAGs and no apparent proliferation. These observations are in agreement with other aggregate culture systems. In a system utilizing aggregate culture to precondition expanded articular chondrocytes for chondrogenesis, aggregated cells demonstrated significantly decreased proliferation and increased type II collagen mRNA expression after 6 days in culture, compared with monolayer cells (44). Similarly, aggregated fourth passage chondrocytes maintained in spinner-flasks demonstrated increased type II collagen and aggrecan mRNA expression within 3 days and type II collagen increased further after 5 days (30). Eight days in aggregate culture was sufficient to initiate the transition of costochondral cells from proliferation to chondrogenic matrix production.

Two weeks in aggregate culture further enhanced redifferentiation compared with 8 days, and the resulting cell population generated cartilage more reminiscent of hyaline cartilage. In aggregates, the most notable finding was that after 14 days, type I collagen synthesis was reduced appreciably, compared with 8 or 11 days. Previously in pellet culture, type II collagen mRNA expression peaked after 2 weeks in pellet culture and type I collagen mRNA expression dropped appreciably from 1 wk to 2 weeks and remained reduced out to 4 weeks (8). In agarose culture, it was similarly observed that after 2 weeks, only 5% of collagen peptides present were type I collagen and the switch from type I to type II collagen was essentially complete (7). These studies demonstrate 2 weeks in three-dimensional culture is particularly suitable for inducing a chondrogenic phenotype. Employing this



regimen to engineer neocartilage significantly increased collagen content (Figure 4) and led to a 70% increase in tensile modulus (Figure 5). Quantified by ELISA, type II collagen synthesis increased significantly with 14 day treatment compared with 0 days and trended higher compared with 8 days (Figure 4). The increase in type II collagen, however, did not parallel further increases in GAG content. Both engineered cartilage and articular cartilage explants cultured *in vitro* have historically demonstrated abundant glycosaminoglycan production (2). It is postulated that in this *in vitro* culture system, chondrocytes are maintaining high levels of GAG production. Extending the aggregate culture to 21 days seemed to reverse the beneficial effects seen with 14 days. After 21 days in aggregate culture, aggregates showed an increase in type I collagen staining. In constructs, decreased GAG content and type II collagen were detected quantitatively. Such results demonstrate 21 days of aggregate culture exceeds the beneficial effects of redifferentiation toward a hyaline cartilage phenotype observed in the 14 day treatment.

Regulators of cell shape and cytoskeletal dynamics likely play an important role in the shift in costochondral cell phenotype observed from monolayer to three-dimensional aggregate culture. As described, a phenotypic transition was observed from proliferation in monolayer, with minimal matrix secretion, to cartilage-specific matrix production in aggregate culture. Mediated by cytoskeletal organization and interactions with the extracellular matrix (ECM), cell shape has been indicated in regulation of proliferation, differentiation, and gene expression (10,12). In both mesenchymal precursors (48) and differentiated chondrocytes (37,43), cytoskeletal modulators affect chondrogenic differentiation and cartilage-specific matrix production (19). Specifically, the RhoA/ROCK signaling pathway and actin dynamics have been shown to play an important role in chondrocyte phenotype (45). RhoA overexpression in the chondrogenic cell line ATDC5 has been associated with cell spreading, stress fiber formation, and increased proliferation (43,46). In micromass, RhoA/ROCK signaling inhibition resulted in increased Sox9 mRNA expression and glycosaminoglycan content. Considering the change in cell morphology from adherent monolayer to non-adherent aggregate culture, it is likely cell shape and cytoskeletal mediators contributed to the decreased proliferation and increased chondrogenic matrix production observed in aggregates.

The morphology of fibrocartilage self-assembled in the 0 day and 8 day treatments may result from a heterogeneous population of chondrocytes and fibroblasts segregating based on the differential adhesion hypothesis. In constructs self-assembled from the 0 day treatment, an acellular cyst was observed in the central region that stained intensely for type I collagen, while type II collagen staining was more concentrated in the tissues periphery. In the 8 day treatment, smaller acellular regions were present and type I collagen was localized to the acellular regions while type II collagen was more diffuse throughout the tissue. It is suggested that a nonhomogeneous cell population is present resulting from progressive dedifferentiation in monolayer and redifferentiation in three-dimensional culture. Assessment of phenotypic changes in sequential passage of chondrocytes demonstrates a progressive decrease in Col2 to Col1 gene expression with increasing passage number, commencing as early as first passage (13). Similarly, this work demonstrates progressive, time-dependent redifferentiation in aggregate culture. The non-uniform matrix distribution

in these two groups suggests that the chondrocytes and fibroblastic cells migrate and segregate during self-assembly, through cadherin mediated processes. Cadherins modulate cell sorting, migration, and adhesion during morphogenesis (18), and N-cadherin expression has been shown to peak within the first 4 days of the self-assembling process. Based upon the differential adhesion hypothesis, it is conceivable that inhomogeneous cell populations migrate and segregate, reducing the free-energy associated with the cadherin-based cell-cell interactions (16). Increasing redifferentiation beyond 8 days yielded dense, homogeneous tissues, likely resulting from a more uniform chondrocyte population for self-assembly. The morphology of fibrocartilage self-assembled without redifferentiation may result from cell migration and segregation, guided by the differential adhesion hypothesis.

Aggregate culture duration may be manipulated to develop a spectrum of cartilage from a single cell source. It was found that constructs with 0 day treatment demonstrated the most intense type I collagen staining. Inversely, constructs with the 14 day treatment had the greatest amount of type II collagen. Total collagen and tensile modulus also increased significantly with increasing aggregate duration. From 11 to 14 days, a 30% increase in total collagen and a 75% increase in tensile modulus were observed. Based upon minimal variability in cell viability, it is suggested that this transition results from progressively more cells chondrodifferentiating with time. In previous efforts to develop a fibrocartilaginous spectrum, co-cultures of articular chondrocytes (AC) and meniscus fibrochondrocytes (MC) have demonstrated similar results. Seeding constructs with a greater proportion of articular chondrocytes (50:50 MC:AC compared with 75:25 MC:AC) increased collagen content and tensile properties (32). Additionally, in the differentiation of human embryonic stem cells (hESCs), fibrochondrocyte co-cultures have been used in conjunction with growth factors to engineer fibrocartilage. Combining TGF- $\beta$ 3 and BMP-4 with differentiation cues from hESCs/fibrochondrocyte co-culture resulted in a trend of increased GAG and collagen synthesis over growth factor, or co-culture stimulation alone (21). In the present study, a single cell population was expanded and redifferentiated for variable durations to engineer a spectrum of fibrous to hyaline cartilage.

Neocartilage engineered in the present study demonstrated ECM content and mechanical properties approaching those of native cartilage. Neocartilage self-assembled following 8 days in aggregate culture was more fibrous in nature. The tissue demonstrated a greater proportion of type I collagen within the matrix (Figure 4). Mechanical properties and tissue morphology were enhanced compared with neocartilage self-assembled without redifferentiation (0 days) (Figure 5). The 8 day redifferentiation yielded a fibrocartilage similar to TMJ condylar cartilage, which demonstrates the presence of both types I and II collagen, depending upon the zone. Previously, porcine condylar cartilage has demonstrated anisotropic tensile properties with Young's modulus in the range of 6-9 MPa (28) and an apparent aggregate modulus of 75 kPa (31), compared with a Young's modulus of 0.8 MPa and a relaxation modulus of 73 kPa measured here in the 8 day treatment. In contrast, hyaline bovine articular cartilage has previously demonstrated predominantly type II collagen, tensile properties in the range of 5-8 MPa (15), and aggregate moduli in the range of 400-500 kPa (4), similar to tissue self-assembled following 14 days in aggregate redifferentiation, which demonstrated predominantly type II collagen, a tensile modulus of 1.5 MPa, and a compressive relaxation modulus of 80 kPa (Figure 4, 5). Engineering a

spectrum of fibrocartilage additionally depends upon phenotype stability with long-term *in vitro* culture and upon *in vivo* implantation. Investigation of long-term phenotypic stability in three-dimensional culture *in vitro* has demonstrated that primary bovine articular chondrocytes maintain their phenotype, continuing to produce type II collagen and aggrecan after 8 months of alginate encapsulation (20). Additionally, in an investigation of chondrocyte phenotype following 28 days of *in vivo* subcutaneous implantation, primary chondrocytes seeded in agarose gels continued to produce primarily type II collagen. No significant differences were observed in total collagen or GAG content following 28 days of implantation (42). Literature suggests the stability of the chondrocyte phenotype in extended three-dimensional *in vitro* culture, and upon *in vivo* implantation, enhancing the translational potential of the neocartilage spectrum engineered here.

## Conclusion

A range of fibrous to hyaline neocartilage was generated using a single, clinically relevant cell source: costochondral cells. Within 8 days in aggregate redifferentiation, proliferation ceased and chondrogenic matrix production increased, compared with monolayer cells. Neocartilage formed following 14 days of redifferentiation demonstrated a 25% increase in collagen content, 100% increase in tensile modulus, and over 50% increase in compressive moduli, compared with tissue formed in the absence of redifferentiation. Increasing the aggregate duration from 8 days to 14 days yielded a spectrum of robust tissue with ECM paralleling that of fibrous TMJ condylar cartilage and hyaline femoral cartilage, respectively. Further work may turn toward approaches in tendon and ligament engineering to improve the strategy for developing homogeneous type I collagen-rich fibrocartilage, for example, the knee meniscus and TMJ disc. Additionally, future efforts to engineer hyaline cartilage may combine 14 days of aggregate redifferentiation with anabolic or catabolic stimuli in the self-assembling process to improve maturational growth.

## Acknowledgements

This material is based upon work supported by the National Science Foundation Graduate Research Fellowship [DGE- 1148897] to M.M. Additionally, the authors acknowledge support from the National Institutes of Health [R01DE019666 and R01DE015038].

## References


1. Anderson DE, Athanasiou KA. Passaged goat costal chondrocytes provide a feasible cell source for temporomandibular joint tissue engineering. *Ann. Biomed. Eng.* 2008; 36(12):1992–2001. [PubMed: 18830818]
2. Asanbaeva A, Masuda K, Thonar EJ, Klisch SM, Sah RL. Mechanisms of cartilage growth: modulation of balance between proteoglycan and collagen in vitro using chondroitinase ABC. *Arthritis and rheumatism.* 2007; 56(1):188–198. [PubMed: 17195221]
3. Athanasiou, KA. *Articular cartilage.* CRC Press/Taylor & Francis; Boca Raton, FL: 2013.
4. Athanasiou KA, Rosenwasser MP, Buckwalter JA, Malinin TI, Mow VC. Interspecies comparisons of in situ intrinsic mechanical properties of distal femoral cartilage. *Journal of orthopaedic research : official publication of the Orthopaedic Research Society.* 1991; 9(3):330–340. [PubMed: 2010837]

5. Aulthouse AL, Beck M, Griffey E, Sanford J, Arden K, Machado MA, Horton WA. Expression of the human chondrocyte phenotype in vitro. *In Vitro Cell Dev. Biol.* 1989; 25(7):659–668. [PubMed: 2666386]
6. Barbero A, Grogan S, Schafer D, Heberer M, Mainil-Varlet P, Martin I. Age related changes in human articular chondrocyte yield, proliferation and post-expansion chondrogenic capacity. *Osteoarthritis Cartilage.* 2004; 12(6):476–484. [PubMed: 15135144]
7. Benya PD, Shaffer JD. Dedifferentiated chondrocytes reexpress the differentiated collagen phenotype when cultured in agarose gels. *Cell.* 1982; 30(1):215–224. [PubMed: 7127471]
8. Bernstein P, Dong M, Corbeil D, Gelinsky M, Gunther KP, Fickert S. Pellet culture elicits superior chondrogenic redifferentiation than alginate-based systems. *Biotechnol. Prog.* 2009; 25(4):1146–1152. [PubMed: 19572391]
9. Binette F, McQuaid DP, Haudenschild DR, Yaeger PC, McPherson JM, Tubo R. Expression of a stable articular cartilage phenotype without evidence of hypertrophy by adult human articular chondrocytes in vitro. *Journal of orthopaedic research : official publication of the Orthopaedic Research Society.* 1998; 16(2):207–216. [PubMed: 9621895]
10. Bissell MJ, Hall HG, Parry G. How does the extracellular matrix direct gene expression? *J. Theor. Biol.* 1982; 99(1):31–68. [PubMed: 6892044]
11. Centers for Disease Control and Prevention. Prevalence of doctor-diagnosed arthritis and arthritis-attributable activity limitation --- United States, 2007-2009. *MMWR Morb Mortal Wkly Rep.* 2010; 59(39):1261–1265. [PubMed: 20930703]
12. Daniels K, Solorush M. Modulation of chondrogenesis by the cytoskeleton and extracellular matrix. *J. Cell Sci.* 1991; 100(Pt 2):249–254. [PubMed: 1757484]
13. Darling EM, Athanasiou KA. Rapid phenotypic changes in passaged articular chondrocyte subpopulations. *Journal of orthopaedic research : official publication of the Orthopaedic Research Society.* 2005; 23(2):425–432. [PubMed: 15734258]
14. Dolwick MF. The role of temporomandibular joint surgery in the treatment of patients with internal derangement. *Oral Surg. Oral Med. Oral Pathol. Oral Radiol. Endod.* 1997; 83(1):150–155. [PubMed: 9007939]
15. Eleswarapu SV, Responde DJ, Athanasiou KA. Tensile properties, collagen content, and crosslinks in connective tissues of the immature knee joint. *PLoS One.* 2011; 6(10):e26178. [PubMed: 22022553]
16. Foty RA, Steinberg MS. The differential adhesion hypothesis: a direct evaluation. *Dev. Biol.* 2005; 278(1):255–263. [PubMed: 15649477]
17. Furukawa KS, Imura K, Tateishi T, Ushida T. Scaffold-free cartilage by rotational culture for tissue engineering. *J. Biotechnol.* 2008; 133(1):134–145. [PubMed: 17913274]
18. Gonsalves, KE. *Biomedical nanostructures.* Wiley-Interscience; Hoboken, N.J.: 2008.
19. Haudenschild DR, Chen J, Steklov N, Lotz MK, D'Lima DD. Characterization of the chondrocyte actin cytoskeleton in living three-dimensional culture: response to anabolic and catabolic stimuli. *Mol. Cell Biomech.* 2009; 6(3):135–144. [PubMed: 19670824]
20. Hauselmann HJ, Fernandes RJ, Mok SS, Schmid TM, Block JA, Aydelotte MB, Kuettner KE, Thonar EJ. Phenotypic stability of bovine articular chondrocytes after long-term culture in alginate beads. *J. Cell Sci.* 1994; 107(Pt 1):17–27. [PubMed: 8175906]
21. Hoben GM, Willard VP, Athanasiou KA. Fibrochondrogenesis of hESCs: growth factor combinations and cocultures. *Stem cells and development.* 2009; 18(2):283–292. [PubMed: 18454697]
22. Hu JC, Athanasiou KA. A self-assembling process in articular cartilage tissue engineering. *Tissue Eng.* 2006; 12(4):969–979. [PubMed: 16674308]
23. Huey DJ, Athanasiou KA. Alteration of the Fibrocartilaginous Nature of Scaffoldless Constructs Formed from Leporine Meniscus Cells and Chondrocytes through Manipulation of Culture and Processing Conditions. *Cells, tissues, organs.* 2013; 197(5):360–371. [PubMed: 23406714]
24. Huey DJ, Athanasiou KA. Maturation growth of self-assembled, functional menisci as a result of TGF-beta1 and enzymatic chondroitinase-ABC stimulation. *Biomaterials.* 2011; 32(8):2052–2058. [PubMed: 21145584]


25. Huey DJ, Hu JC, Athanasiou KA. Unlike bone, cartilage regeneration remains elusive. *Science*. 2012; 338(6109):917–921. [PubMed: 23161992]
26. Jakob M, Demarteau O, Schafer D, Hintermann B, Dick W, Heberer M, Martin I. Specific growth factors during the expansion and redifferentiation of adult human articular chondrocytes enhance chondrogenesis and cartilaginous tissue formation in vitro. *J. Cell Biochem*. 2001; 81(2):368–377. [PubMed: 11241676]
27. Kalpakci KN, Willard VP, Wong ME, Athanasiou KA. An interspecies comparison of the temporomandibular joint disc. *J. Dent. Res*. 2011; 90(2):193–198. [PubMed: 21118792]
28. Kang H, Bao G, Dong Y, Yi X, Chao Y, Chen M. [Tensile mechanics of mandibular condylar cartilage]. *Hua Xi Kou Qiang Yi Xue Za Zhi*. 2000; 18(2):85–87. [PubMed: 12539336]
29. Kurosawa H, Fukubayashi T, Nakajima H. Load-bearing mode of the knee joint: physical behavior of the knee joint with or without menisci. *Clin. Orthop. Relat. Res*. 1980; (149):283–290. [PubMed: 7408313]
30. Lee TJ, Bhargava SH, La WG, Yang HS, Seong JY, Lee H, Im GI, Lee SH, Kim BS. Spinner-flask culture induces redifferentiation of de-differentiated chondrocytes. *Biotechnol. Lett*. 2011; 33(4):829–836. [PubMed: 21125413]
31. Lu XL, Mow VC, Guo XE. Proteoglycans and mechanical behavior of condylar cartilage. *J. Dent. Res*. 2009; 88(3):244–248. [PubMed: 19329458]
32. MacBarb RF, Makris EA, Hu JC, Athanasiou KA. A chondroitinase-ABC and TGF-beta1 treatment regimen for enhancing the mechanical properties of tissue-engineered fibrocartilage. *Acta biomaterialia*. 2013; 9(1):4626–4634. [PubMed: 23041782]
33. Minas T, Nehrer S. Current concepts in the treatment of articular cartilage defects. *Orthopedics*. 1997; 20(6):525–538. [PubMed: 9195635]
34. Murphy MK, Huey DJ, Reimer AJ, Hu JC, Athanasiou KA. Enhancing post-expansion chondrogenic potential of costochondral cells in self-assembled neocartilage. *PLoS One*. 2013; 8(2):e56983. [PubMed: 23437288]
35. Nagata S. Modification of the stages in total reconstruction of the auricle: Part I. Grafting the three-dimensional costal cartilage framework for lobule-type microtia. *Plast. Reconstr. Surg*. 1994; 93(2):221–230. [PubMed: 8310014]
36. Natoli RM, Responde DJ, Lu BY, Athanasiou KA. Effects of multiple chondroitinase ABC applications on tissue engineered articular cartilage. *Journal of orthopaedic research : official publication of the Orthopaedic Research Society*. 2009; 27(7):949–956. [PubMed: 19123232]
37. Newman P, Watt FM. Influence of cytochalasin D-induced changes in cell shape on proteoglycan synthesis by cultured articular chondrocytes. *Exp. Cell Res*. 1988; 178(2):199–210. [PubMed: 3169129]
38. Ofek G, Revell CM, Hu JC, Allison DD, Grande-Allen KJ, Athanasiou KA. Matrix development in self-assembly of articular cartilage. *PLoS One*. 2008; 3(7):e2795. [PubMed: 18665220]
39. Ontell FK, Moore EH, Shepard JA, Shelton DK. The costal cartilages in health and disease. *Radiographics*. 1997; 17(3):571–577. [PubMed: 9153697]
40. Stewart MC, Saunders KM, Burton-Wurster N, Macleod JN. Phenotypic stability of articular chondrocytes in vitro: the effects of culture models, bone morphogenetic protein 2, and serum supplementation. *J. Bone Miner. Res*. 2000; 15(1):166–174. [PubMed: 10646126]
41. Takigawa M, Shirai E, Fukuo K, Tajima K, Mori Y, Suzuki F. Chondrocytes dedifferentiated by serial monolayer culture form cartilage nodules in nude mice. *Bone Miner*. 1987; 2(6):449–462. [PubMed: 2851342]
42. Vinardell T, Sheehy EJ, Buckley CT, Kelly DJ. A comparison of the functionality and in vivo phenotypic stability of cartilaginous tissues engineered from different stem cell sources. *Tissue Eng Part A*. 2012; 18(11-12):1161–1170. [PubMed: 22429262]
43. Wang G, Woods A, Sabari S, Pagnotta L, Stanton LA, Beier F. RhoA/ROCK signaling suppresses hypertrophic chondrocyte differentiation. *J. Biol. Chem*. 2004; 279(13):13205–13214. [PubMed: 14726536]
44. Wolf F, Candrian C, Wendt D, Farhadi J, Heberer M, Martin I, Barbero A. Cartilage tissue engineering using pre-aggregated human articular chondrocytes. *Eur. Cell Mater*. 2008; 16:92–99. [PubMed: 19101892]

45. Woods A, Beier F. RhoA/ROCK signaling regulates chondrogenesis in a context-dependent manner. *J Biol Chem.* 2006; 281(19):13134–13140. [PubMed: 16565087]
46. Woods A, Wang G, Beier F. RhoA/ROCK signaling regulates Sox9 expression and actin organization during chondrogenesis. *J. Biol. Chem.* 2005; 280(12):11626–11634. [PubMed: 15665004]
47. Zalzal GH, Cotton RT, McAdams AJ. The survival of costal cartilage graft in laryngotracheal reconstruction. *Otolaryngol. Head Neck Surg.* 1986; 94(2):204–211. [PubMed: 3083336]
48. Zanetti NC, Solorsh M. Induction of chondrogenesis in limb mesenchymal cultures by disruption of the actin cytoskeleton. *J. Cell Biol.* 1984; 99(1 Pt 1):115–123. [PubMed: 6539780]



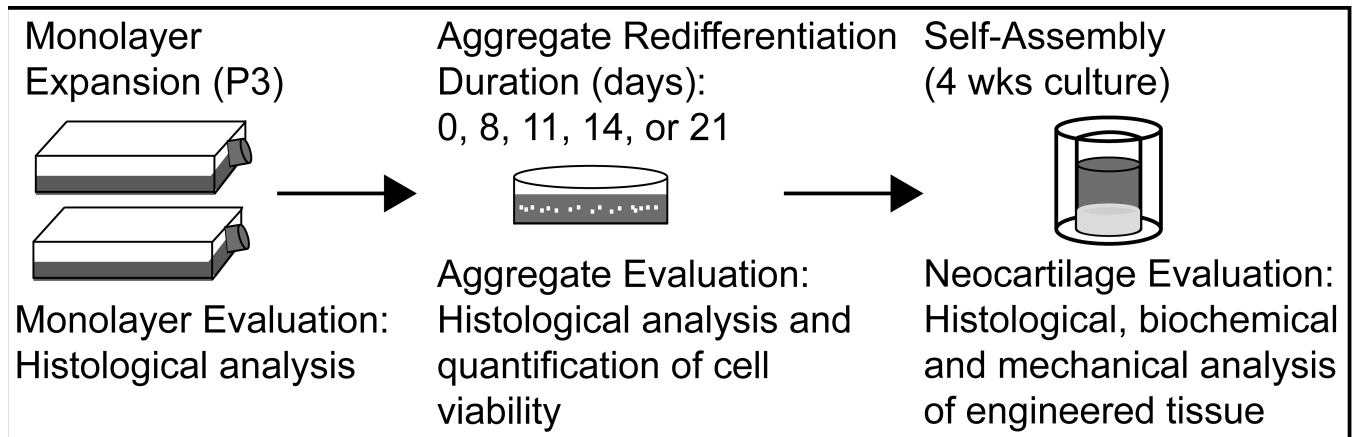


**Figure 1.** Neocartilage Formation Schematic. Costochondral cells were expanded to third passage, and redifferentiated for 0 (immediately self-assembled), 8, 11, 14, or 21 days. Following redifferentiation, aggregates were digested, and cells were self-assembled.

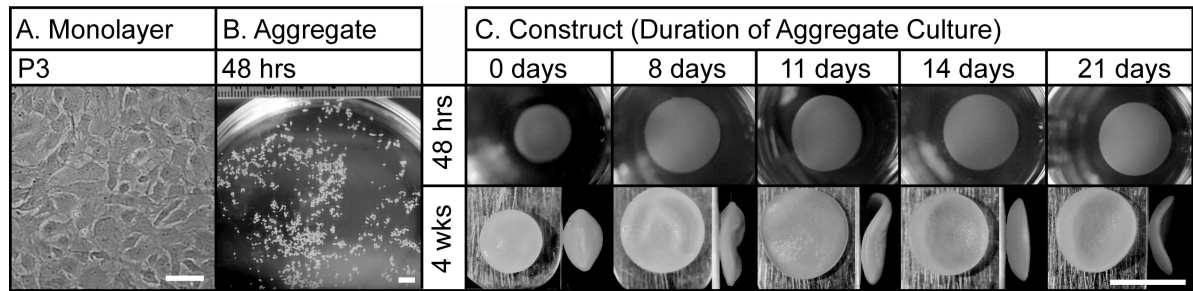


**Figure 2.**


Gross Morphology Throughout Neocartilage Formation. (A) Cell morphology at confluence prior to P3 expansion. Scale bar = 100  $\mu$ m. (B) Aggregate morphology after 48 hrs in aggregate culture. Scale bar = 5 mm. (C) Self-assembled neocartilage morphology after 48 hrs and 4 weeks in culture. Scale bar = 5 mm.

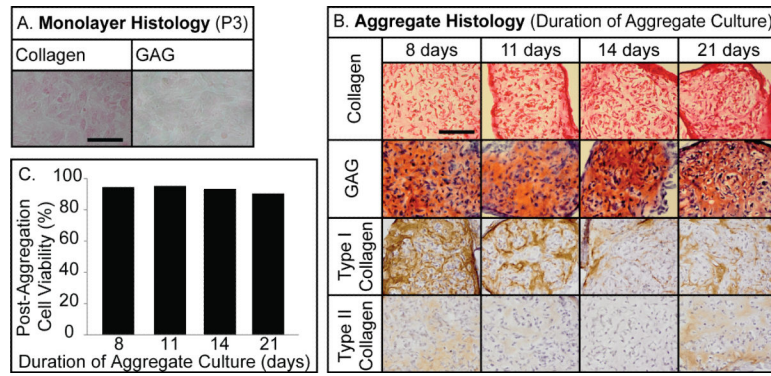

**Figure 3.** Monolayer and Aggregate Histology and Cell Viability. (A) Third passage monolayer stained minimally with Picrosirius red for intracellular collagen, while Safranin-O staining for GAGs was undetectable. Scale bar = 100  $\mu$ m. (B) Picrosirius red and Safranin-O/fast-green staining demonstrated the presence of extracellular collagen and GAGs, respectively, for each treatment. Immunohistochemistry for type I and II collagen demonstrated type I collagen staining decreased with increasing aggregate duration, and type II collagen presence was minimal. Scale bar = 100  $\mu$ m. (C) Cell viability varied minimally across treatments.

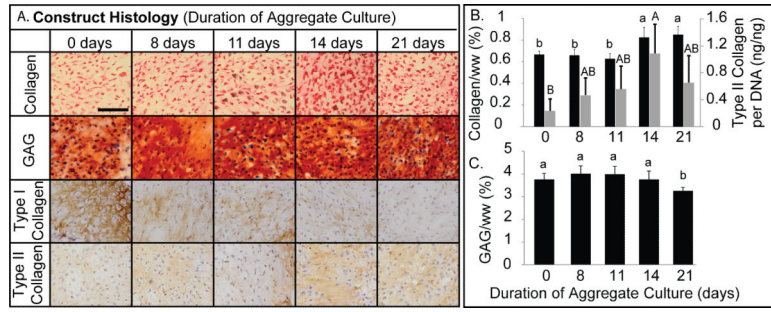

**Figure 4.** Self-Assembled Neocartilage ECM Analysis. (A) Neocartilage from each treatment group was analyzed histologically for total collagen, GAGs, type I collagen, and type II collagen. Notably, GAG content varied minimally. With increasing aggregation duration, type I collagen decreased. Scale bar = 100  $\mu$ m. (B) Neocartilage formed following 14 and 21 days aggregation had the greatest total collagen content, and 14 days significantly increased type II collagen synthesis per cell compared with 0 days. (C) GAG content did not vary appreciably up to 14 days but decreased after 21 days of aggregation. Data are reported as mean  $\pm$  standard deviation. All groups not connected by a common letter are significantly different ( $p < 0.05$ ).

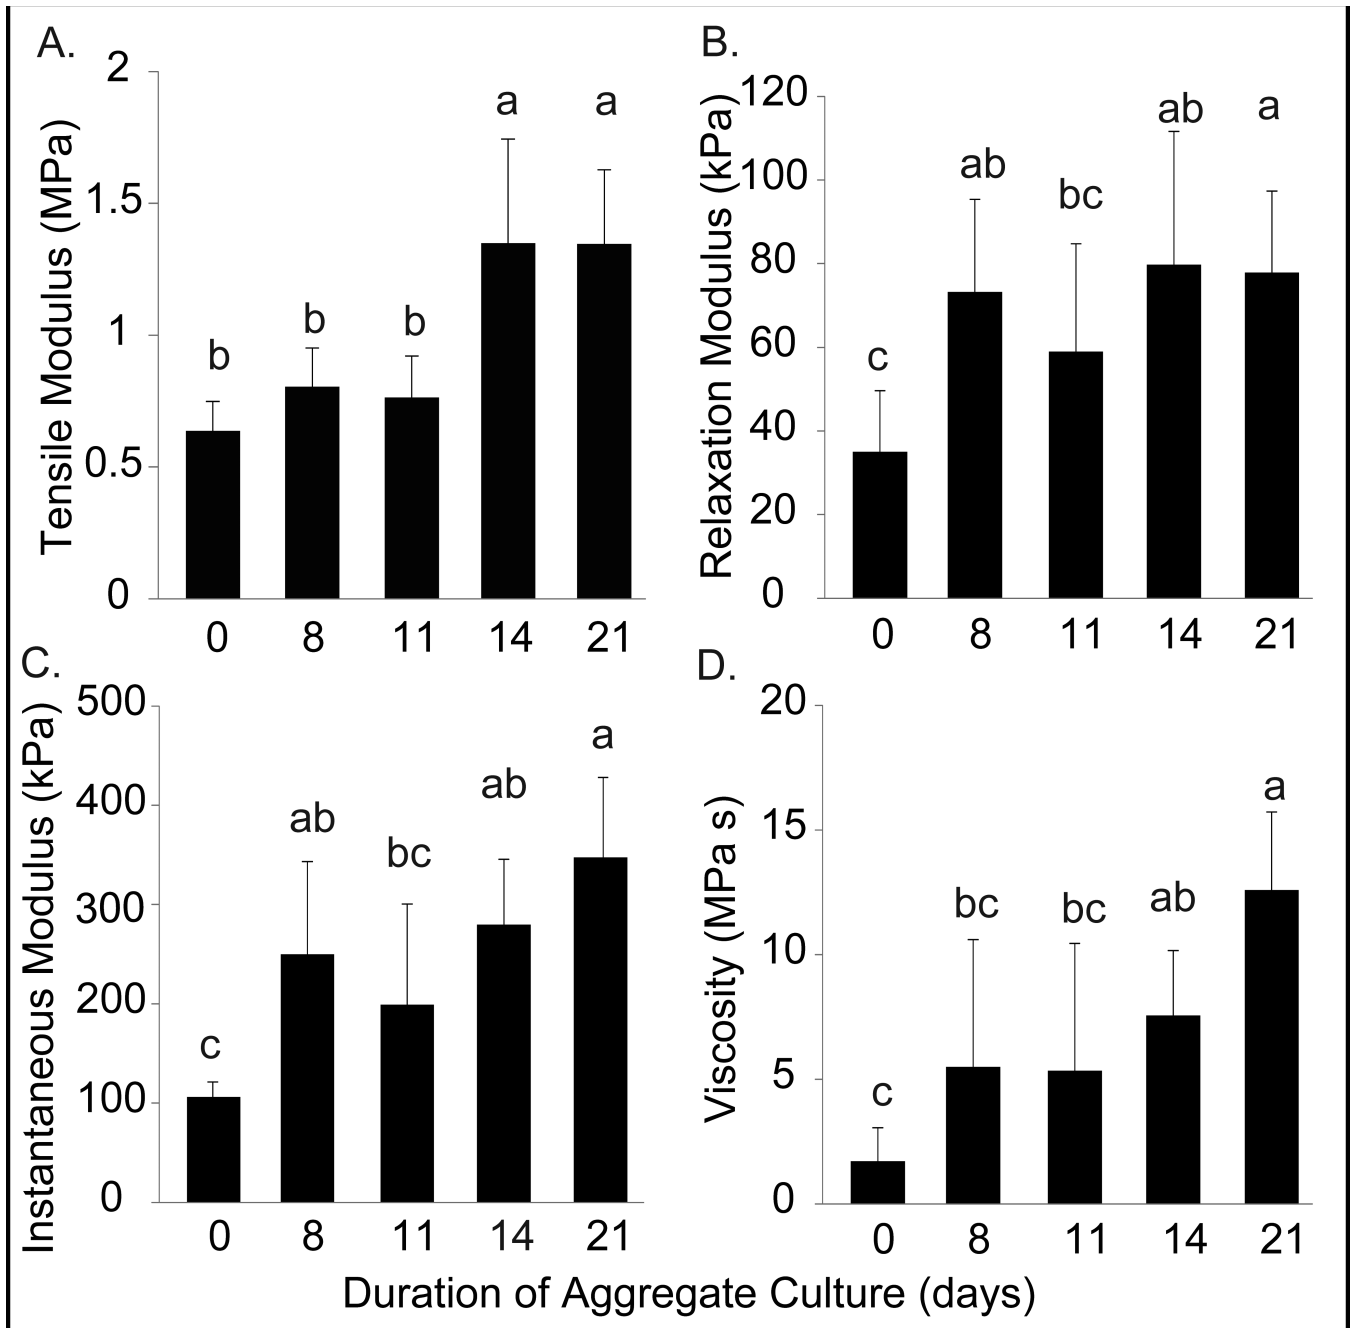

**Figure 5.** Self-Assembled Neocartilage Mechanical Properties. (A) Tensile modulus, (B-C) compressive relaxation and instantaneous moduli, and (D) coefficient of viscosity were measured after 4 weeks culture. Tensile stiffness increased significantly in neocartilage with 14 and 21 days aggregation. Compressive properties increased over control in all treatments. Coefficient of viscosity was greatest with 21 days aggregation. Data are reported as mean  $\pm$  standard deviation. All groups not connected by a common letter are significantly different ( $p < 0.05$ ).

**Table 1**

## Neocartilage Properties.

Duration of Aggregate Culture	0 day	8 days	11 days	14 days	21 days
Diameter (mm)	4.0±0.1 <sup>c</sup>	5.6±0.1 <sup>b</sup>	5.9±0.2 <sup>a</sup>	5.5±0.1 <sup>b</sup>	5.5±0.2 <sup>b</sup>
Wet weight (mg)	19.6±0.7 <sup>b</sup>	21.8±2.3 <sup>a</sup>	17.1±0.9 <sup>c</sup>	13.3±1.3 <sup>d</sup>	12.4±0.7 <sup>d</sup>
Hydration (%)	88.3±0.8 <sup>abc</sup>	88.7±0.6 <sup>a</sup>	88.5±0.3 <sup>ab</sup>	87.4±0.8 <sup>c</sup>	87.4±0.8 <sup>bc</sup>
Cells/construct (10 <sup>6</sup> )	1.7±0.1 <sup>a</sup>	1.8±0.2 <sup>a</sup>	1.4±0.1 <sup>b</sup>	1.3±0.1 <sup>b</sup>	1.7±0.2 <sup>a</sup>

Data are reported mean ± standard deviation. All groups not connected by a common letter are significantly different (p<0.05).