

**NANO EXPRESS**

**Open Access**

# Sensory properties of hybrid composites based on poly(3,4-ethylenedioxythiophene)-porous silicon-carbon nanotubes

Igor B Olenych<sup>1\*</sup>, Olena I Aksimentyeva<sup>2</sup>, Liubomyr S Monastyrskii<sup>1</sup>, Yulia Yu Horbenko<sup>2</sup> and Lidia I Yarytska<sup>3</sup>

**Abstract:** In this work, we have prepared film sensor elements based on a hybrid system poly(3,4-ethylenedioxythiophene)-porous silicon nanocrystals-carbon nanotubes on flexible polymer substrates. Our FTIR spectroscopy-based studies for the molecular structure of the materials obtained suggest some interaction of their components in the hybrid layer. The influence of adsorption of water molecules on the conductivity and capacitance of the hybrid composites has been investigated in the temperature range of 20°C to 40°C. We have detected essential changes in the electrical conductivity and capacitance which depend on the humidity of the surrounding atmosphere. For estimating the sensing properties of our composites, we have analyzed the sensing abilities of the hybrid systems and their dynamic characteristics. The hybrid composites as working materials for the sensors provide improved performance of the latter. In particular, the response time is reduced by 3 to 5 times.

**PACS:** 73.63.-b, 73.61.Ph, 82.35.Np, 81.05.Rm

**Keywords:** Porous silicon; Poly(3,4-ethylenedioxythiophene); Carbon nanotubes; Composite film sensors; Sensing ability

## Background

The development of flexible electronic, optical, and sensory devices requires novel composite materials which combine the properties of polymers and inorganic nanoparticles of different natures, such as semiconductor nanocrystals, metallic, silicon, and carbon nanoclusters [1-6]. Incorporation of low-dimensional components in composites is needed to maximize the size effects and large specific surface areas of nanoparticles.

It is known that conducting polymers with conjugated backbone and controlled electron characteristics represent promising components of organic-inorganic composites [7,8]. Novel organic materials for sensors and molecular electronics have been developed on the basis of those polymers [9-12]. The conducting polymers manifest electron delocalization arising from conjugated double bonds in a polymer backbone. They reveal electrical conductivity in the doped states (*p*- or *n*-doping) though remain insulators when undoped (a neutral state).

Protonic acids, electron donors (Na(naphthalide), Li, K, etc.), and electron acceptor substances ( $J_2$ ,  $Cl_2$ ,  $FeCl_3$ , etc.) have been widely used as dopants [7-10]. Due to doping-dedoping processes, the electronic properties (e.g., the bandgap) of the conjugated polymers can be varied substantially [7-9]. Among the conducting polymers, poly(3,4-ethylenedioxythiophene) abbreviated hereafter as PEDOT is of particular interest owing to its remarkable optical, electrical, and electrochemical properties. To obtain PEDOT-based films deposited on almost any surfaces (e.g., conductive or dielectric, flexible, and polymeric), aqueous dispersion of polymeric complex of PEDOT doped by poly(styrenesulfonate) (PSS) is often used. A polymeric anion PSS acts simultaneously as an acid dopant and an anionic surfactant which stabilizes the dispersion of the polymer [13-15]. High enough processing ability and conductivity of the polymer complex PEDOT:PSS make it one of the most promising conducting polymers. Recently, it has been shown that adsorption of gas molecules such as CO [16] and  $NH_3$  [17], as well as vapors of organic solvents [15] or water molecules [18,19], can strongly affect different physical characteristics of PEDOT:PSS and the relevant composites. This suggests

\* Correspondence: iolenych@gmail.com

<sup>1</sup>Radioelectronics and Computer Systems Department, Ivan Franko National University of Lviv, 50 Dragomanov Street, 79005 Lviv, Ukraine  
Full list of author information is available at the end of the article

some ground for employing PEDOT:PSS in gas-sensing devices, e.g., humidity sensors.


Perhaps, one can use silicon and/or silica nanoparticles, which have high abilities to adsorb water molecules, for enhancing the performance of humidity sensors [1,20]. Silicon nanoclusters can be prepared using a straightforward procedure of electrochemical etching of single-crystalline silicon, with further formation of a layer of 'porous silicon' (PS). Ever since the intense visible photoluminescence of the PS has been detected at the room temperature by Canham in 1990 [21], the PS is regarded as a promising active element for optoelectronics. This includes applications associated with light-emitting diodes, phosphors, and optical transmission [22-24]. An essential point which limits the applications of PS in optoelectronics is its high surface sensitivity. On the one hand, this is a negative factor that imposes instability of the PS in air though, on the other hand, one can use this material for fabricating various sensors. An increase in the electrical resistance of the composites induced by silicon nanoparticles can be diminished basing on conductive admixtures such as carbon nanotubes (CNTs).

Notice that the CNTs are considered as a very promising material in the field of nanotechnology and sensor-related applications [5,17,25-27]. So, a network of single-walled CNTs shows good enough sensitivity to different gases ( $\text{NO}_2$  and  $\text{NH}_3$  [28,29] and vapors of organic solvents [28]). Multi-walled CNTs are sensitive to, e.g.,  $\text{H}_2$  and  $\text{CH}_4$  [30]. They have already found applications in ammonia and water vapor gas sensors [31] due to larger effective surface areas, with many sites allowing the adsorption of the gas molecules.

We expect that the composites based on poly(3,4-ethylenedioxythiophene) combined with the PS nanocrystals and the CNTs should enhance the sensitivity and the operating speed of thin-film sensors fabricated with relatively simple and inexpensive technologies. As a consequence, the aim of the present work is to study the effect of adsorption of  $\text{H}_2\text{O}$  molecules on the electrical parameters of film sensory systems based on hybrid composites PEDOT:PSS-PS-CNT.

## Methods

The hybrid composites were prepared from 1.5% aqueous polymer suspension PEDOT:PSS purchased from Sigma-Aldrich Co, St. Louis, MO, USA. Figure 1 (inset) shows a chemical formula of PEDOT:PSS. The other component of our hybrid composite was PS nanoparticles. The PS was manufactured by means of electrochemical etching performed in galvanostatic mode on single-crystalline silicon substrates, with had the typical thicknesses of 400  $\mu\text{m}$  and the crystallographic orientation (100). The silicon substrates had the *n*-type conductivity (*n*-Si), with the specific resistance of 4.5  $\Omega$  cm. Ethanol

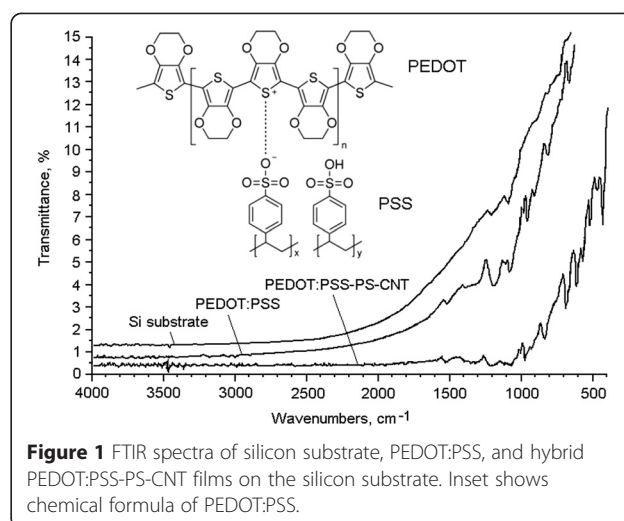

**Figure 1** FTIR spectra of silicon substrate, PEDOT:PSS, and hybrid PEDOT:PSS-PS-CNT films on the silicon substrate. Inset shows chemical formula of PEDOT:PSS.

solution of hydrofluoric acid (the volume ratio of the components  $\text{HF}:\text{C}_2\text{H}_5\text{OH} = 1:1$ ) was used as an electrolyte. The anodic current (the density of 30  $\text{mA cm}^{-2}$ ) passed during all the etching time (about 20 min). To ensure the availability of holes in the surface layer of *n*-Si, which were necessary for occurrence of anodic reactions and formation of the PS, the working surface of a silicon plate was irradiated with white light during the whole process of electrochemical etching. After cleaning our samples with distilled water and drying in air, a resulting porous layer has been taken off from the surface of the plate. It had the shape of a finely dispersed powder. The sizes of silicon particle ranged from a few tens of nanometers to several microns.

The third component of our composite was the multi-walled CNTs purchased from Sigma-Aldrich Co, St. Louis, MO, USA, with the diameters of 8 to 15 nm and the average length of 30  $\mu\text{m}$ . The nanotubes were dispersed using ultrasonic processing in the mixture of nitric and sulfuric acids taken according to the ratio 3:1. The concentration of the CNTs was 0.5 mg per 1 ml. After multiple washing of the CNTs with distilled water, they were mixed with the nanoparticles of PS and the PEDOT:PSS solution and subjected to ultrasonic processing for 8 h. The suspension thus obtained was deposited onto a 0.4-mm-thick fluoroplastic substrate and then dried at the room temperature during 48 h. Eventually, a monolithic film of the hybrid PEDOT:PSS-PS-CNT nanocomposite was obtained. The thickness of the film was about 20  $\mu\text{m}$ . The composite films PEDOT:PSS containing approximately 5% of CNTs and approximately 40% of PS were tested in our further experiments.

The molecular structure of the PEDOT:PSS-PS-CNT composite was explored using FTIR spectroscopy. The transmittance spectra were measured with an 'Avatar' spectrometer in the wave number region of 400 to

4,000  $\text{cm}^{-1}$ . To obtain the infrared (IR) spectra of the hybrid films, the composite PEDOT:PSS-PS-CNT was deposited, using the method described above, on a silicon wafer with the thickness of 400  $\mu\text{m}$ . The absorption bands of the silicon substrate were easily identified (see [32]). To identify the absorption bands of the PEDOT:PSS-PS-CNT films, the literature data [13,32,33] may be considered.

For studying the sensory properties of the hybrid composite films, silver contacts were thermally deposited onto the surfaces of the films. The thickness of the contacts was about 0.5  $\mu\text{m}$ . The adsorption processes in the hybrid PEDOT:PSS-PS-CNT films were studied in an airtight chamber, of which the gas medium can be changed. The water vapor concentration in the air was determined experimentally with a Honeywell HIH-4000-004 humidity sensor (Morristown, NJ, USA). The electrical parameters of our composite films were measured in the both DC and AC (1 kHz) regimes at two different temperatures, 20°C and 40°C.

## Results and discussion

To identify the components of the hybrid systems PEDOT:PSS-PS-CNT, we have measured their FTIR spectra. A comparative analysis of those spectra for the PEDOT:PSS system and the hybrid films deposited on the silicon substrates reveals a decreasing transmittance of the hybrid films, which has to be caused by the additional absorption and scattering of light by the nanotubes and the PS nanoparticles (see Figure 1).

The absorption bands located at 660 and 1,100  $\text{cm}^{-1}$  correspond respectively to deformational Si-H mode and valence vibrations Si-O-Si of the silicon substrate (see [32]). In general, the bands observed are due to the oxidation of the silicon surface and adsorption of the water molecules from the atmosphere. The absorption bands observed in the FTIR spectra of the PEDOT:PSS-PS-CNT composite, which are located in the regions 1,080 to 1,200 and 1,500 to 1,550  $\text{cm}^{-1}$ , are characteristic for C-O-C complexes and C=C, C-C vibrations of thiophene rings


[13,33]. The absorption band at 700  $\text{cm}^{-1}$  can be ascribed to valence vibrations C-S. The band with the maximum located at 860  $\text{cm}^{-1}$  and the peaks in the region of 950 to 1,000  $\text{cm}^{-1}$  may originate from deformational vibrations Si-OH and C-H, respectively [13]. A new band at 470 to 520  $\text{cm}^{-1}$  can appear due to the carbon bonds available in the CNTs.

Note that the hybrid PEDOT:PSS-PS-CNT films show more intense absorption bands, as compared to the polymer. Moreover, they manifest different absorption profiles in the regions of 620 to 800  $\text{cm}^{-1}$  and 1,300 to 1,420  $\text{cm}^{-1}$ . This can be readily explained by the interactions among the structural parts of the polymer and the CNTs, and the PS surface. In the spectral interval 3,400 to 4,000  $\text{cm}^{-1}$ , we have observed the absorption bands induced by the hydroxyl groups from Si-OH and by the adsorbed water molecules. It is worthwhile noting that the hydrophilic properties of the hybrid composites PEDOT:PSS-PS-CNT expand their prospects as working elements for the humidity sensors.


We have found experimentally that the electrical characteristics of our thin-film sensor elements are strongly dependent on the surrounding atmosphere. In particular, the increasing relative humidity results in significant decrease of the electrical resistance and increase of the capacitance of the hybrid PEDOT:PSS-PS-CNT films (see Figure 2).

The dependences mentioned above can be explained by the interaction of water molecules with the surface of the composite, which leads to changing electric parameters of the PS nanocrystals (see [20]). As a result, one observes increasing conductivity of the hybrid film. On the other hand, water impurities might induce additional (or 'secondary') doping of the conjugated polymer PEDOT:PSS. This manifests itself in change of the chain shape to an 'unfolded spiral' and, therefore, stimulates increase in the conductivity [15].

Besides the influence on the electronic structure of silicon nanocrystals, the effective dielectric permittivity of the hybrid film also varies due to the adsorption of

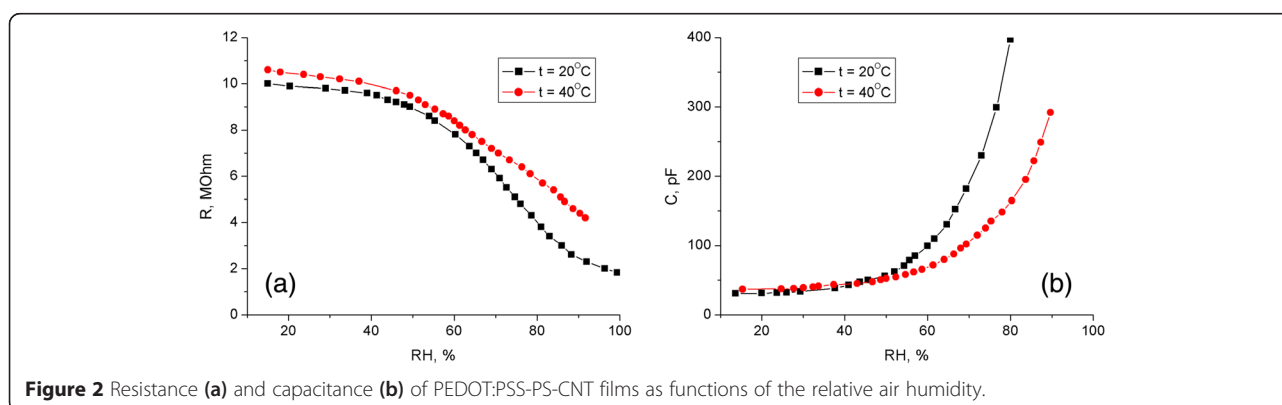

**Figure 2** Resistance (a) and capacitance (b) of PEDOT:PSS-PS-CNT films as functions of the relative air humidity.

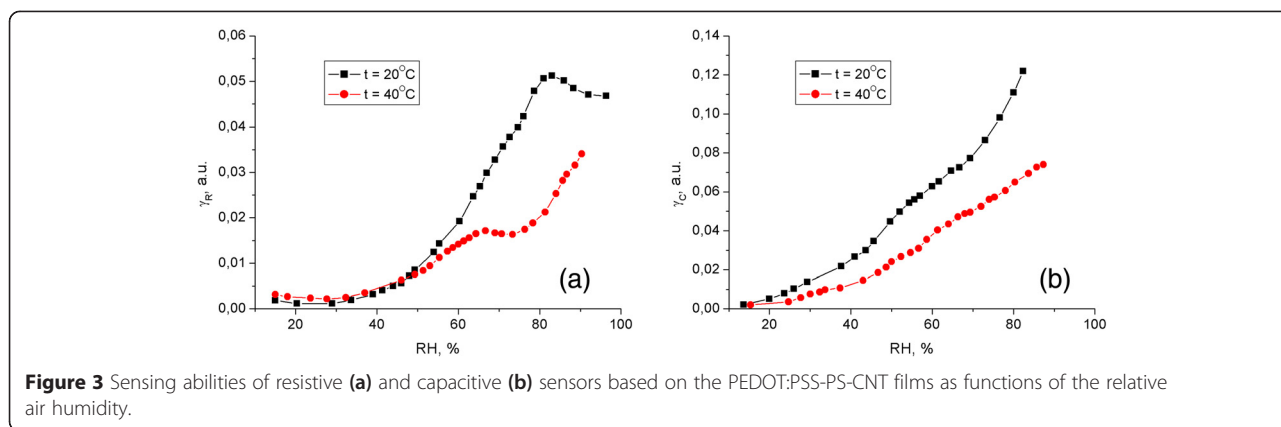

the water molecules, which have large dielectric constant ( $\epsilon = 81$ ) as compared to the silicon. This is why increasing relative humidity of the air causes a noticeable increase of the capacitance of the hybrid nanocomposites PEDOT:PSS-PS-CNT.

An important factor of studying the mechanisms of variation of the physical parameters of sensor materials under adsorption-desorption interactions with gaseous media is the determination of the sensing ability of the material. To estimate the sensing (i.e., gas-sensitive) properties of the hybrid composite PEDOT:PSS-PS-CNT films, we have calculated their ‘sensing ability’ using the known relation [34]  $\gamma_G = \frac{1}{S} \frac{\Delta S}{\Delta p}$ .


Here  $\Delta S/S$  denotes the relative change in the electrical resistance or the capacitance of the structure, and  $\Delta p$  is the change in the relative air humidity. The calculated dependences of sensitivity for the two different film sensor elements on the humidity are shown in Figure 3.

The sensory properties of the composite film are better within the humidity region 80% to 100%. Such a behavior observed at large concentrations of the water vapor, when the pores of the nanocomposite contain a significant amount of condensed water, might be related

to the change in the water adsorption mechanism (from monomolecular to polymolecular). The latter mechanism is mainly governed by the intermolecular interactions inside the film [35,36]. The ambient temperature also affects the electrical resistance and the capacitance of the sensing elements. Although the increase in the temperature up to 40°C does not change a general character of the dependences, it decreases the sensitivity of our structures to the water vapor concentration variations.

The kinetics of the sensor response to varying relative air humidity has a two-stage shape. The dynamic dependences for the sensor elements based on the PEDOT:PSS-PS-CNT film are shown in Figure 4.

The interaction with the water vapor has a character of physical adsorption. It represents an inverse process with low activation threshold. This hypothesis is substantiated by the fact that the initial conductivity and capacitance of the hybrid films are restored after scavenging and pumping off the water vapor from the experimental chamber. The time of response of the sensory elements to changing gas concentration is about 30 s, which is quite sufficient for microelectronic humidity sensors. When compared with the moisture-sensitive

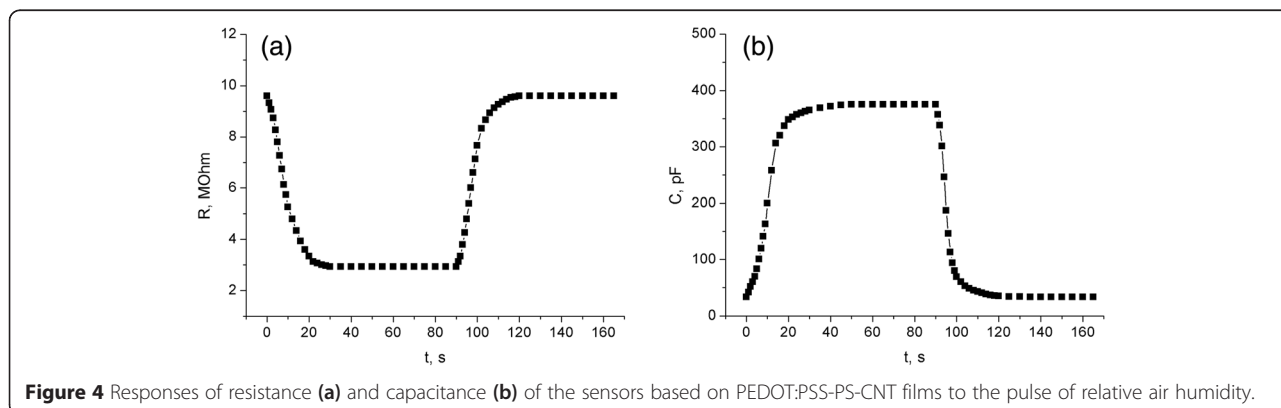



structures PS-silicon substrate [20], the response of our hybrid film sensors is much more (3 to 5 times) faster.

## Conclusions

We have created flexible sensory elements based on the PEDOT:PSS-PS-CNT composite films. Using the FTIR spectroscopy, we have determined the components present in the hybrid layer. In particular, we have found the main IR absorption bands related to the structural chains of the polymer. The changes in the IR absorption observed by us may be due to some interactions of the polymer complexes with the PS nanocrystals and the CNT, as well as due to the adsorption of water molecules and hydroxyl groups.

It has been revealed experimentally that the adsorption of water molecules changes the electrophysical properties of the composites under test. The analyses of dependences of the electrical conductivity, the capacitance, and the sensing ability on the concentration of water vapor point to a notable increase in the sensitivity of the composite at the relative humidity approximately 80%. This may be associated with changing conductivity mechanisms. The kinetics of the response of the hybrid composites PEDOT:PSS-PS-CNT to the changing water vapor concentration is fast enough to be employed in various microelectronic humidity sensors. Finally, the results obtained in the present study would allow further optimization of flexible film sensors.

## Competing interests

The authors declare that they have no competing interests.

## Authors' contributions

IBO designed the experiment, participated in the investigations of sensory properties of the samples and drafted the manuscript. OIA supervised the work and finalized the manuscript. LSM analyzed sensory properties of the samples. YYH synthesized the nanocomposites. LIY participated in the FTIR measurements and structure refinements. All the authors read and approved the final manuscript.

## Author details

<sup>1</sup>Radioelectronics and Computer Systems Department, Ivan Franko National University of Lviv, 50 Dragomanov Street, 79005 Lviv, Ukraine. <sup>2</sup>Physical and Colloidal Chemistry Department, Ivan Franko National University of Lviv, 6 Kyrylo and Mefodiy Street, 79005 Lviv, Ukraine. <sup>3</sup>Thermodynamics and Physics Department, Lviv State University of Live Safety, 35 Kleparivska Street, 79000 Lviv, Ukraine.

Received: 20 October 2014 Accepted: 7 April 2015

Published online: 18 April 2015

## References

- Francis R, Joy N, Aparna P, Vijayan R. Polymer grafted inorganic nanoparticles, preparation, properties, and applications: a review. *Polymer Rev.* 2014;54:268–347.
- Das TK, Prusty S. Graphene-based polymer composites and their applications. *Polym-Plast Technol Eng.* 2013;52:319–31.
- Svrcek V. Hybrid optoelectronic and photovoltaic materials based on silicon nanocrystals and conjugated polymers. InTech: Optoelectronic Devices and Properties; 2011. p. 197–214.
- Bai H, Gong G. Toward high performance inverted polymer solar cells. *Polymer.* 2012;53:5437–48.
- Ma PC, Tang BZ, Kim J-K. Effect of CNT decoration with silver nanoparticles on electrical conductivity of CNT-polymer composites. *Carbon.* 2008;46:1497–505.
- Davies J, Hamada H. Flexural properties of a hybrid polymer matrix composite containing carbon and silicon carbide fibers. *Adv Composite Mater.* 2001;10:77–96.
- Heeger AJ. Semiconducting and metallic polymers: the fourth generation of polymeric materials. *Synth Metals.* 2002;123:23–42.
- Kohlman RS, Joo J, Epstein AJ. In: Mark JE, editor. Conducting polymers: electrical conductivity, Physical properties of polymers handbook. New York: Amer. Inst. Phys. Woodbury; 1996. p. 453–78.
- Leclere P, Surin M, Brocorens P, Cavallini M, Biscarini F, Lazzaroni R. Supramolecular assembly of conjugated polymers: from molecular engineering to solid-state properties. *Mater Sci Engin R.* 2006;55:1–56.
- Martin J, Maiz J, Sacristan J, Mijangos C. Tailored polymer-based nanorods and nanotubes by "template synthesis": from preparation to applications. *Polymer.* 2012;53:1149–66.
- Bai H, Shi G. Gas sensors based on conducting polymers. *Sensors.* 2007;7:267–307.
- Saxena V, Malhotra BD. Prospects of conducting polymers in molecular electronics. *Curr App Phys.* 2003;3:293–305.
- Pyshkina O, Kubarkov A, Sergeev V. Poly(3,4-ethylenedioxythiophene): synthesis and properties. *Mater Sci App Chem.* 2010;21:51–4.
- Na S-I, Kim S-S, Jo J, Kim D-Y. Efficient and flexible ITO-free organic solar cells using. *Adv Mater.* 2008;20:4061–7.
- Ouyang J, Xu Q, Chu C-W, Yang Y, Li G, Shinar J. On the mechanism of conductivity enhancement in poly(3,4-ethylenedioxythiophene): poly(styrene sulfonate) film through solvent treatment. *Polymer.* 2004;45:8443–50.
- Latessa G, Brunetti F, Reale A, Saggio G, Di Carlo A. Piezoresistive behaviour of flexible PEDOT:PSS based sensor. *Sensor Actuator B.* 2009;139:304–9.
- Jian J, Guo X, Lin L, Cai Q, Cheng J, Li J. Gas-sensing characteristics of dielectrophoretically assembled composite film of oxygen plasma-treated SWCNTs and PEDOT/PSS polymer. *Sensor Actuator B.* 2013;178:279–88.
- Kuş M, Okur S. Electrical characterization of PEDOT:PSS beyond humidity saturation. *Sensor Actuator B.* 2009;143:177–81.
- Saxena K, Nanda O, Gupta N, Kumar P, Jain VK. Humidity sensing response of poly(3,4-ethylene dioxythiophene)-poly(styrene sulphonate) and its nanocomposites. *Environmental Science and Engineering: Physics of Semiconductor Devices*; 2014. p. 417–9. doi:10.1007/978-3-319-03002-9\_104.
- Olenych IB, Monastyrskii LS, Aksimentyeva OI, Sokolovskii BS. Humidity sensitive structures on the basis of porous silicon. *Ukr J Phys.* 2011;56:1198–202.
- Canham LT. Silicon quantum wire array fabrication by electrochemical and chemical dissolution of wafers. *Appl Phys Lett.* 1990;57:1046–8.
- Bisi O, Ossicini S, Pavesi L. Porous silicon: a quantum sponge structure for silicon based optoelectronics. *Surf Sci Rep.* 2000;38:1–126.
- Monastyrskii LS, Aksimentyeva OI, Olenych IB, Sokolovskii BS. Photosensitive structures of conjugated polymer—porous silicon. *Mol Cryst Liq Cryst.* 2014;589:124–31.
- Olenych IB, Aksimentyeva OI, Monastyrskii LS, Pavlyk MR. Electrochromic effect in photoluminescent porous silicon—polyaniline hybrid structures. *J Appl Spectrosc.* 2012;79:495–8.
- Ajayan PM. Nanotubes from carbon. *Chem Rev.* 1999;99:1787–800.
- Kymakis E, Amarantunga GAJ. Optical properties of polymer-nanotube composites. *Synth Met.* 2004;142:161–7.
- Tahhan M, Truong V-T, Spinks GM, Wallace GG. Carbon nanotube and polyaniline composite actuators. *Smart Mater Struc.* 2003;12:626–32.
- Li CJ, Lu Y, Ye Q, Cinke M, Han J, Meyyappan M. Nanotube sensors for gas and organic vapor detection. *Nano Lett.* 2003;3:929–33.
- Wang LC, Tang KT, Teng IJ, Kuo TC, Ho CL, Kuo HW, et al. A single-walled carbon nanotube network gas sensing devices. *Sensors.* 2011;11:7763–72.
- Samarasekara P. Hydrogen and methane gas sensors synthesis of multi-walled carbon nanotubes. *Chin J Phys.* 2009;47:361–9.
- Varghese OK, Kichambre PD, Gong D, Ong KG, Dickey EC, Grimes CA. Gas sensing characteristics of multi-wall carbon nanotubes. *Sensor Actuator B.* 2001;81:32–41.
- Niwano M. In-situ IR observation of etching and oxidation processes of Si surfaces. *Surf Sci.* 1999;427–428:199–207.

33. Han MG, Foulger SH. Preparation of poly(3,4-ethylenedioxythiophene) (PEDOT) coated silica core-shell particles and PEDOT hollow particles. *Chem Commun.* 2004;19:2154–5.
34. Vashpanov YA, Smyntyna VA. Adsorption sensitivity of semiconductors. Astropoint: Odessa; 2005 (in Russian).
35. Gregg SJ, Sing KSW. Adsorption, surface area and porosity. London: Academic; 1982.
36. Tutov EA, Bormontov EN, Kashkarov VM, Pavlenko MN, Domashevskaya EP. Influence of water vapor adsorption on the C-V characteristics of heterostructures containing porous silicon. *Tech Phys.* 2003;73:1442–8.

**Submit your manuscript to a SpringerOpen<sup>®</sup> journal and benefit from:**

- ▶ Convenient online submission
- ▶ Rigorous peer review
- ▶ Immediate publication on acceptance
- ▶ Open access: articles freely available online
- ▶ High visibility within the field
- ▶ Retaining the copyright to your article

---

Submit your next manuscript at ▶ [springeropen.com](http://springeropen.com)

---