

Research



Cite this article: Makoveeva EV, Alexandrov DV. 2019 Effects of nonlinear growth rates of spherical crystals and their withdrawal rate from a crystallizer on the particle-size distribution function. *Phil. Trans. R. Soc. A* **377**: 20180210.
<http://dx.doi.org/10.1098/rsta.2018.0210>

Accepted: 7 November 2018

One contribution of 17 to a theme issue 'Heterogeneous materials: metastable and non-ergodic internal structures'.

Subject Areas:

complexity, mathematical modelling, applied mathematics, solid-state physics

Keywords:

nucleation, evolution of particulate assemblage, metastable liquid, removal of crystals, phase transformation

Author for correspondence:

Dmitri V. Alexandrov
e-mail: dmitri.alexandrov@urfu.ru

Effects of nonlinear growth rates of spherical crystals and their withdrawal rate from a crystallizer on the particle-size distribution function

Eugenia V. Makoveeva and Dmitri V. Alexandrov

Department of Theoretical and Mathematical Physics, Laboratory of Multi-Scale Mathematical Modeling, Ural Federal University, Ekaterinburg 620000, Russian Federation

EVM, 0000-0002-2499-3196; DVA, 0000-0002-6628-745X

In this paper, we show that the nonlinear growth rate of particles in a supersaturated solution or supercooled melt, as well as the rate of removal of crystals from the metastable liquid of a crystallizer, significantly change the size-distribution function of crystals. Taking these rates into account, we present a complete analytical solution of the integro-differential model describing the transient nucleation of solid particles and their evolution in a metastable liquid. The distribution function and metastability degree (supersaturation or supercooling) are found by means of the separation of variables and saddle-point methods. The nonlinear growth rates of crystals in supersaturated solutions and supercooled melts (single-component and binary) are summarized and compared with experimental data.

This article is part of the theme issue 'Heterogeneous materials: metastable and non-ergodic internal structures'.

1. Introduction

In actual practice, the nucleation and evolution of a polydisperse ensemble of crystals are complicated by their removal from a metastable liquid as well as by the presence of mass sources or heat sinks [1–4]. In addition, the growth rate of crystals in supersaturated solutions and supercooled melts is a nonlinear function of the supersaturation (supercooling) of the metastable liquid

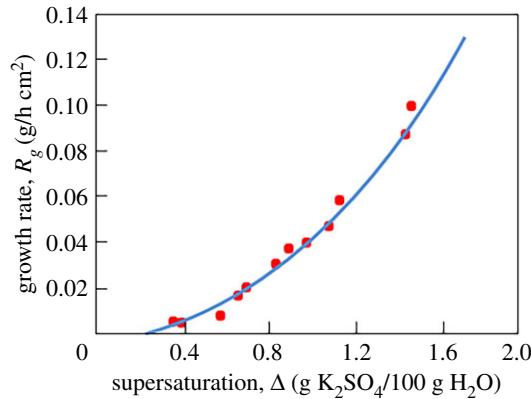


Figure 1. Growth rate R_g of potassium sulfate crystals in a fluidized bed crystallizer (symbols designate the experimental data [6] and the solid curve is plotted in accordance with expression (1.2)). Here $\chi_3 = 0.049 \text{ h}^{-1}[\Delta]^{-1}$, $\kappa = 0.082 \text{ g}/(\text{h cm}^2[\Delta])$ and $[\Delta]$ denotes the dimension of supersaturation shown on the horizontal axis.

[5–11]. Namely, experimental works [5–8] demonstrate that the growth rate V of crystals is close to parabolic with increasing the supersaturation Δ . In other words, the frequently used linear approximation $V(\tau) = \beta_* \Delta(\tau)$ does not well describe the real experiments (here β_* and τ represent the kinetic coefficient and time). The analytical theory recently developed for supercooled single-component and binary melts [9,10] as well as for supersaturated solutions [11] shows that the crystal growth rate represents the following nonlinear function of metastability degree Δ and time τ

$$V(\tau) = \beta_* \Delta(\tau) \begin{cases} (1 - \chi_1 \tau \Delta(\tau)), & \text{supercooled single-component melts [9]} \\ (1 - \chi_2 \tau \Delta(\tau)), & \text{supercooled binary melts [10]} \\ (1 - \chi_3 \tau \Delta(\tau)), & \text{supersaturated solutions [11]} \end{cases} \quad (1.1)$$

and

$$\chi_1 = \frac{\beta_*^2 \rho_s L}{\lambda_l}, \quad \chi_2 = \frac{\beta_*^2 \rho_s L}{\lambda_l} \left(1 + \frac{m(1-k)C_0 \lambda_l}{D \rho_s L} \right), \quad \chi_3 = \frac{\beta_*^2 (k-1)C_p}{D},$$

where λ_l is the thermal conductivity, ρ_s is the density of the solid phase, L is the latent heat of phase transition, m is the liquidus slope, k is the equilibrium partition coefficient, C_0 is the solute concentration far from the growing crystal, D is the diffusion coefficient, and C_p is the concentration at saturation. To find the rate R_g ($\text{g}/\text{h cm}^2$) of the increase in the mass of growing crystals per unit time per unit area, let us write out the mass of crystals as $M = \rho_s N \nu$, where N is the total number of crystals and ν is the volume of a single particle. Next considering the case of spherical crystals $\nu = 4\pi r^3/3$ one can find the mass growth rate as $dM/d\tau = 4\pi \rho_s N r^2 V(\tau)$, where $V(\tau)$ is given by expressions (1.1). Now introducing $R_g = (4\pi r^2 N)^{-1} dM/d\tau = \rho_s V(\tau)$, we come to

$$R_g = \kappa \Delta (1 - \chi_3 \tau \Delta), \quad \kappa = \rho_s \beta_*, \quad (1.2)$$

where the third line of expression (1.1) is taken into account. As the growth rate (1.2) depends on Δ and τ one can use a desupersaturation curve $\Delta(\tau)$ or its inverse function $\tau(\Delta)$ to plot the growth rate (1.2) as a function of a single variable $V(\tau)$ or $V(\Delta)$. Using such a curve experimentally found by Garside *et al.* [6] (see their fig. 5), we compare in figure 1 the nonlinear growth rates (1.1) and (1.2) with experimental data on the nucleation and evolution of potassium sulfate in a laboratory scale fluidized bed crystallizer.

Taking into account the aforesaid, we note that the evolution of a polydisperse ensemble of particles in a metastable liquid should be described by means of an integro-differential model of kinetic and balance equations, which includes the nonlinear growth rates of spherical

crystals (1.1). In addition, this model is complicated by the presence of mass sources (heat sinks) and the removal of product crystals in the case of the industrial crystallizer. With that in mind, we develop a new theoretical approach for analytical description of the evolution of a particulate assemblage in a supersaturated solution or a supercooled melt of the industrial crystallizer.

2. The model of nonlinear dynamics of crystals in a crystallizer

Consider the process of evolution of a polydisperse ensemble of particles in the metastable liquid (supersaturated solution or supercooled melt) of a crystallizer. Owing to the mass flux $Q_C(\tau)$ introduced from outside (or the heat flux $Q_\theta(\tau)$ removed from the system) the supersaturation (supercooling) necessary for crystal growth is maintained in the liquid. Taking into account the withdrawal rate of product crystals from the metastable liquid of a crystallizer, let us write down the kinetic equation for the particle-radius distribution function $f(r, \tau)$ describing the evolution of a polydisperse assemblage of particles

$$\frac{\partial f}{\partial \tau} + V(\tau) \frac{\partial f}{\partial r} + h(r)f(r, \tau) = \frac{\partial}{\partial r} \left(D(\tau) \frac{\partial f}{\partial r} \right), \quad r > r_*, \tau > 0, \quad (2.1)$$

where $V(\tau) = dr/d\tau$ is determined by expression (1.1), r is the radial coordinate, $h(r)$ is the crystal withdrawal rate (h represents the inverse of the mean residence time of particles of radius r in the metastable liquid), r_* is the radius of critical nuclei that are capable to appear in a supersaturated or supercooled system, and D is the coefficient of mutual Brownian diffusion. For the sake of simplicity, we consider the case of constant rate h and $D(\tau) = d_1 V(\tau)$, where d_1 stands for a pertinent factor [4,12–14].

The mass (heat) balance equation for supersaturated (supercooled) liquids reads as

$$\left. \begin{aligned} \frac{dC}{d\tau} &= Q_C - 4\pi C_p \int_{r_*}^{\infty} r^2 \left(V(\tau)f(r, \tau) - D(\tau) \frac{\partial f}{\partial r} \right) dr, & \tau > 0 \\ \text{and} \quad \rho_m C_m \frac{d\theta}{d\tau} &= Q_\theta + 4\pi L_V \int_{r_*}^{\infty} r^2 \left(V(\tau)f(r, \tau) - D(\tau) \frac{\partial f}{\partial r} \right) dr, & \tau > 0, \end{aligned} \right\} \quad (2.2)$$

where C is the solute concentration of the supersaturated solution, θ is the temperature of the supercooled melt, ρ_m and C_m are the density and specific heat of the mixture, respectively, and $L_V = \rho_s L$. Note that the first line of expression (2.2) corresponds to supersaturated solutions, whereas the second line describes a phase transformation in supercooled melts.

The initial distribution function $f_0(r)$ as well as the initial metastability degree $\Delta_0 = \Delta C_0$ ($\Delta\theta_0$) should be known, i.e.

$$f(r, 0) = f_0(r), \quad \Delta_0 = \begin{cases} \Delta C_0, & \text{supersaturated solutions} \\ \Delta\theta_0, & \text{supercooled melts.} \end{cases} \quad (2.3)$$

The flux of crystals overcoming the critical nucleation barrier and the distribution function of withdrawn crystals determine the boundary conditions

$$V(\tau)f(r_*, \tau) - D(\tau) \frac{\partial f}{\partial r} = I(\Delta), \quad r = r_*; \quad f(r_p, \tau) = 0, \quad r = r_p, \quad (2.4)$$

where I is the rate of nucleation, r_p is the radius of withdrawn crystals (product crystals), and Δ designates the current metastability degree $\Delta = \Delta C = C - C_p$ or $\Delta = \Delta\theta = \theta_p - \theta$ in cases of supersaturated or supercooled liquids. Here C and θ stand for the current values of solute concentration and temperature, and θ_p represents the phase transition temperature of a supercooled melt.

Our further analysis is devoted to the study of the influence of the nonlinear contribution to the growth rate of individual crystals (which is proportional to $\tau \Delta(\tau)$ in (1.1)) on the evolution of a polydisperse ensemble of particles in a metastable liquid of a crystallizer.

3. Analytical solution

For the convenience of further analysis, the mathematical model (2.1)–(2.4) can be rewritten in dimensionless form as (parameter χ plays the role of χ_1 , χ_2 or χ_3 introduced in expression (1.1))

$$\begin{aligned} \frac{\partial F}{\partial t} + w(1 - \chi\tau_0\Delta C_0wt) \frac{\partial F}{\partial x} + \gamma F \\ = u_0w(1 - \chi\tau_0\Delta C_0wt) \frac{\partial^2 F}{\partial x^2}, \quad t > 0, \quad 0 < x < x_0, \end{aligned} \quad (3.1)$$

$$\frac{dw}{dt} = Q(t) - b_1w(1 - \chi\tau_0\Delta C_0wt) \int_0^{x_0} (x + s_*)^2 \left(F - u_0 \frac{\partial F}{\partial x} \right) dx, \quad t > 0 \quad (3.2)$$

and

$$\begin{aligned} w = 1, \quad F = F_0(x), \quad t = 0, \quad F = u_0 \frac{\partial F}{\partial x} = J(w), \\ x = 0; \quad F = 0, \quad x = x_0, \end{aligned} \quad (3.3)$$

where $J = w^{-1}(1 - \chi\tau_0\Delta C_0wt)^{-1} \exp(p\phi(w))$ (p and $\phi(w)$ are given in §2 in [15] for supersaturated solutions and supercooled melts for the Meirs and Weber–Volmer–Frenkel–Zeldovich kinetics), x and t represent the dimensionless coordinate and time, respectively, $F(x, t)$ and $w(t)$ are the dimensionless distribution function and supersaturation (supercooling), respectively, x_0 is the reduced radius of withdrawn crystals, Q is the dimensionless mass (heat) flux, and all the rest parameters are introduced in [15] (in the case of supercooled liquids the initial supersaturation ΔC_0 should be replaced by the initial supercooling $\Delta\theta_0$).

To use the method of separation of variables to solve equation (3.1), we make the boundary conditions for the distribution function homogeneous by means of the following substitution:

$$F_1(x, t) = F(x, t) - \frac{J(w(t))(x_0 - x)}{x_0 + u_0}. \quad (3.4)$$

After that, the problem (3.1), (3.3) takes the form

$$\frac{\partial F_1}{\partial t} + w(1 - \chi\tau_0\Delta C_0wt) \frac{\partial F_1}{\partial x} + \gamma F_1 - u_0w(1 - \chi\tau_0\Delta C_0wt) \frac{\partial^2 F_1}{\partial x^2} = v(x, t), \quad (3.5)$$

$$F_1 = F_0(x) - \frac{x_0 - x}{x_0 + u_0}, \quad t = 0; \quad F_1 - u_0 \frac{\partial F_1}{\partial x} = 0, \quad x = 0; \quad F_1 = 0, \quad x = x_0 \quad (3.6)$$

and

$$v(x, t) = \frac{J(w(t))}{x_0 + u_0} [w(t)(1 - \chi\tau_0\Delta C_0wt) - \gamma(x_0 - x)] - \frac{x_0 - x}{x_0 + u_0} \frac{dJ}{dt}. \quad (3.7)$$

Now representing the reduced distribution function $F_1(x, t)$ as a product of two functions solely dependent on x and t , $F_1(x, t) = X(x)T(t)$, and taking into account that $X(0) - u_0X'(0) = 0$ and $X(x_0) = 0$, we obtain the eigenvalues n_k and eigenfunctions $X_k(x)$ in the form

$$\left. \begin{aligned} X_k(x) &= \exp\left(\frac{x}{2u_0}\right) [2n_k u_0 \cos(n_k x) + \sin(n_k x)], \\ 2n_k u_0 \cos(n_k x_0) + \sin(n_k x_0) &= 0, \quad k = 0, 1, 2, \dots \end{aligned} \right\} \quad (3.8)$$

Expanding functions $v(x, t)$ and $F_1(x, 0)$ in series in the eigenfunctions $X_k(x)$

$$v(x, t) = \sum_{k=0}^{\infty} v_k(t) X_k(x), \quad F_1(x, 0) = \sum_{k=0}^{\infty} F_{0k} X_k(x),$$

and substituting (3.8) into (3.5), we get

$$F_1(x, t) = \sum_{k=0}^{\infty} \left[F_{0k} + \int_0^t v_k(t_1) \exp(\xi_k(t_1)) dt_1 \right] \exp(-\xi_k(t)) X_k(x), \quad (3.9)$$

where $v_k(t)$ and F_{0k} are determined by expressions (3.9) and (3.10) in [15], and

$$\xi_k(t) = \frac{S_k(t)}{4u_0}, \quad S_k = (1 + 4u_0^2 n_k^2) \int_0^t w(t_1)(1 - \chi \tau_0 \Delta C_0 w t) dt_1 + 4u_0 \gamma t. \quad (3.10)$$

Now taking into account that the derivative $S'(t) > 0$ ($S(t)$ reaches a maximum at the upper limit of integration), we estimate the integral contribution in (3.9) on the basis of the saddle-point method for a Laplace-type integral as [16] ($u_0 \ll 1$)

$$\int_0^t v_k(t_1) \exp\left(\frac{S_k(t_1)}{4u_0}\right) dt_1 \approx \frac{4u_0 v_k(t) \exp[S_k(t)/(4u_0)]}{S'_k(t)}. \quad (3.11)$$

Combining (3.9) and (3.11), we have

$$F_1 \approx \sum_{k=0}^{\infty} X_k(x) \left[F_{0k} \exp(-\xi_k(t)) + \frac{4u_0 v_k(t)}{(1 + 4u_0^2 n_k^2) U'(t)(1 - \chi \tau_0 \Delta C_0 w t) + 4u_0 \gamma} \right], \quad (3.12)$$

where we introduced a new unknown function

$$U(t) = \int_0^t w(t_1) dt_1. \quad (3.13)$$

Now substituting (3.12) into the mass (heat) balance equation (3.2) and keeping in mind expression (3.4), we arrive at the following Cauchy problem for the determination of the integral function $U(t)$

$$\left. \begin{aligned} U'' &= M_0(U', U, t), \\ \tilde{f}'(t) &= U'(1 - \chi \tau_0 \Delta C_0 U'(t)t) \\ \text{and} \quad U &= 0, \quad U' = 1, \quad \tilde{f} = 0, t = 0. \end{aligned} \right\} \quad (3.14)$$

Here the following notations are introduced

$$\begin{aligned} M_0(U', U, t) &= \{Q(t) + b_1(U')^p \Psi - b_1 U'(1 - \chi \tau_0 \Delta C_0 U' t) S_2 - b_1 U'(1 - \chi \tau_0 \Delta C_0 U' t) 4u_0 S_3 \\ &\quad + \delta_1 (U')^p\} [1 - b_1 U'(1 - \chi \tau_0 \Delta C_0 U' t) 4u_0 S_1]^{-1}, \\ \Psi &= \frac{(x_0 + s_*)^4 - 4s_*^3(x_0 + s_*) + 3s_*^4}{12(x_0 + u_0)}, \quad \delta_1 = \frac{b_1 u_0 [s_*^3 - (x_0 + s_*)^3]}{3(x_0 + u_0)}, \\ S_1 &= \frac{(p-1)(U')^{p-2}(1 - \chi \tau_0 \Delta C_0 U' t) + (U')^{p-1} \chi \tau_0 \Delta C_0 t}{(1 - \chi \tau_0 \Delta C_0 U' t)^2} \sum_{k=0}^{\infty} v_{k4} \frac{(Z_k - u_0 Y_k)}{\Phi_k(U')}, \\ S_2 &= \sum_{k=0}^{\infty} F_{0k} \exp(-\xi_k(t)) (Z_k - u_0 Y_k), \quad \xi_k(t) = \gamma t + \frac{(1 + 4u_0^2 n_k^2) \tilde{f}(t)}{4u_0}, \\ S_3 &= \sum_{k=0}^{\infty} \left[(U')^p v_{k1} - \frac{(U')^{p-1}}{1 - \chi \tau_0 \Delta C_0 U' t} v_{k2} - \frac{(U')^p}{(1 - \chi \tau_0 \Delta C_0 U' t)^2} v_{k3} \right] \frac{Z_k - u_0 Y_k}{\Phi_k(U')}, \\ Z_k &= \int_0^{x_0} (x + s_*)^2 X_k(x) dx, \quad Y_k = \int_0^{x_0} (x + s_*)^2 \frac{dX_k(x)}{dx} dx, \end{aligned}$$

$$\begin{aligned}\Phi_k(U') &= (1 + 4u_0^2 n_k^2) U'(1 - \chi \tau_0 \Delta C_0 U' t) + 4u_0 \gamma, \\ v_{k1} &= \frac{1}{I_k(x_0 + u_0)} \int_0^{x_0} X_k(x) \exp\left(\frac{-x}{u_0}\right) dx, \\ v_{k2} &= \frac{\gamma}{I_k(x_0 + u_0)} \int_0^{x_0} (x_0 - x) X_k(x) \exp\left(\frac{-x}{u_0}\right) dx, \\ v_{k3} &= \frac{1}{I_k(x_0 + u_0)} \int_0^{x_0} (x_0 - x) \chi \tau_0 \Delta C_0 X_k(x) \exp\left(\frac{-x}{u_0}\right) dx, \\ v_{k4} &= \frac{1}{I_k(x_0 + u_0)} \int_0^{x_0} (x_0 - x) X_k(x) \exp\left(\frac{-x}{u_0}\right) dx.\end{aligned}$$

Let us especially note that the solution of the Cauchy problem (3.14) determines the integral function $U(t)$. Then the metastability degree $w(t)$ can be easily found as a derivative of this function, i.e. $w(t) = U'(t)$. It means that the dimensionless particle size distribution function $F(x, t)$ is also known by means of expressions (3.4) and (3.12) and takes the form

$$F(x, t) = \frac{J(w(t))(x_0 - x)}{x_0 + u_0} + \sum_{k=0}^{\infty} X_k(x) \left[F_{0k} \exp(-\xi_k(t)) + \frac{4u_0 v_k(t)}{(1 + 4u_0^2 n_k^2) U'(t)(1 - \chi \tau_0 \Delta C_0 w t) + 4u_0 \gamma} \right]. \quad (3.15)$$

4. Summary and conclusion

Figures 2–4 illustrate the particle-size distribution function plotted in accordance with the analytical solution (3.15) (physical parameters of the system under consideration are given in [15], $Q(t) = A(1 - \sin(\omega t)/2)$, $A = 0.005$, and $\omega = \pi/15$). The first important conclusion is the fact that the size distribution of crystals strongly depends on the parameter χ (compare curves at different χ in figures 2 and 3*a,b*). It is easily seen that the nonlinear growth rate of particles in a metastable liquid of crystallizer (expressions (1.1)) substantially changes the particle-size distribution. Our calculations show that the relative error may exceed tens of per cent in the course of time for real metastable liquids. As this takes place, the greatest difference of nonlinear growth law occurs for sufficiently small particles at a fixed time (figures 2*a* and 3*a*) and at essentially large times for particles of a given size (figures 2*b* and 3*b*). From the physical point of view, the nonlinear growth law (1.1) with non-zero χ means that the growth rates of evolving crystals become lower as compared with the case $\chi = 0$. In other words, we have more crystals in the supercooled (supersaturated) liquid of a crystallizer, which grow longer until they are removed from the system (until they reach a given size x_0).

The second important conclusion is the influence of the crystal withdrawal rate h (which is proportional to the parameter γ) on the distribution of growing crystals. Indeed, with an increase in the rate of removal of crystals (γ increases), the number of large particles decreases and the number of small particles increases. Note that this effect takes place in both cases of linear and nonlinear growth rates (figure 4*a,b*). In other words, with the evolution of a metastable system with the same supercooling (supersaturation), when the number of larger crystals decreases, the number of smaller crystals increases and vice versa. Therefore, the distribution functions shown in figure 4 at various γ have a point of intersection. In addition, the three-dimensional dependencies F of x and t plotted in figure 5 show that the surface of the distribution function is inverted with an increase in the rate of removal of crystals (with increasing γ and h). In this case, the mean residence time of crystals in the metastable liquid of a crystallizer decreases and the surface of the distribution function bends in the direction of smaller times.

In summary, the particle-size distribution function strongly depends on two principal effects influencing the evolution of particulate assemblages in metastable liquids: (i) the nonlinear growth laws of crystals (expressions (1.1)) and (ii) the crystal withdrawal rate from a crystallizer. The theory under consideration, which takes into account these important physical effects should be used for a more precise description of similar phase transition phenomena when the

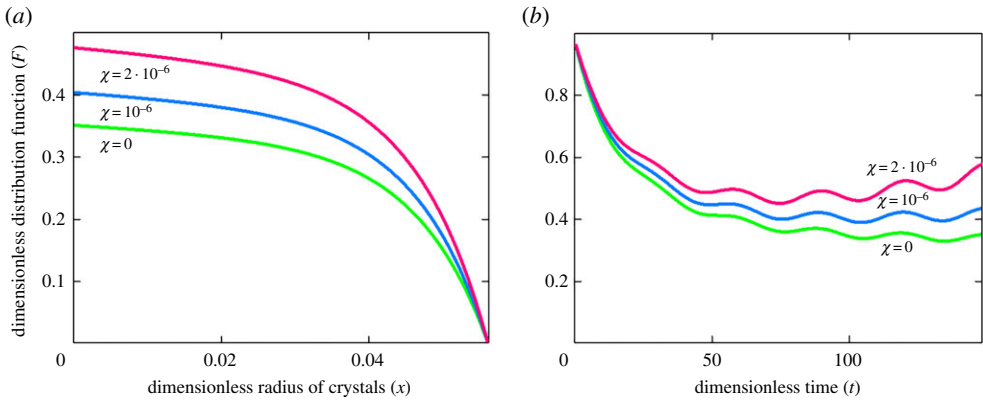


Figure 2. Dimensionless distribution function versus dimensionless coordinate x ((a) $t = 100$) and time t ((b) $x = 0.01$) for $\gamma = 0.711$.

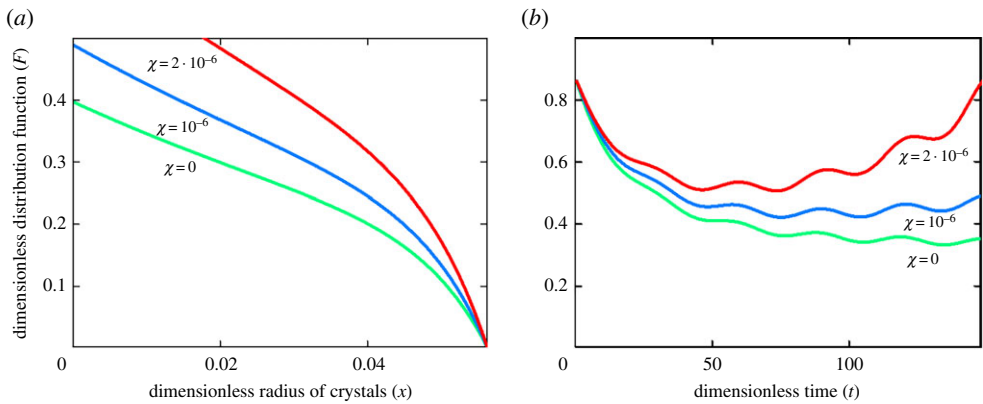


Figure 3. Dimensionless distribution function versus dimensionless coordinate x ((a) $t = 100$) and time t ((b) $x = 0.01$) for $\gamma = 7.11$.

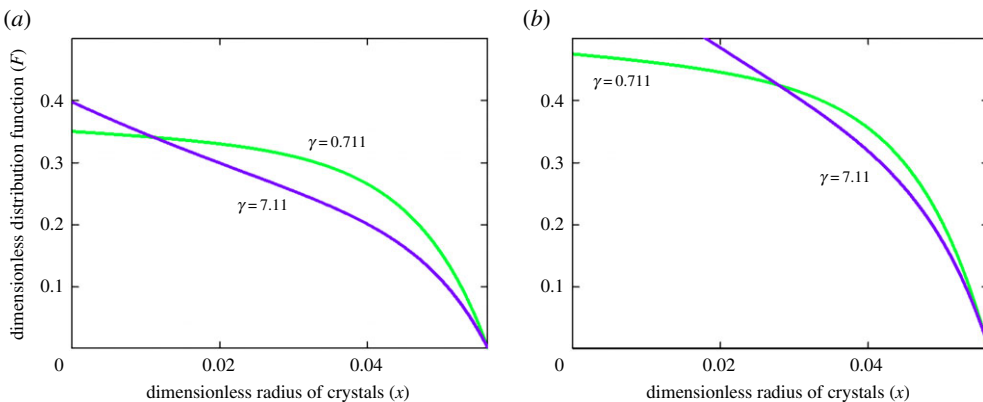


Figure 4. Dimensionless distribution function versus dimensionless coordinate x at time $t = 100$ for $\chi = 0$ (a) and $\chi = 2 \cdot 10^{-6}$ (b).

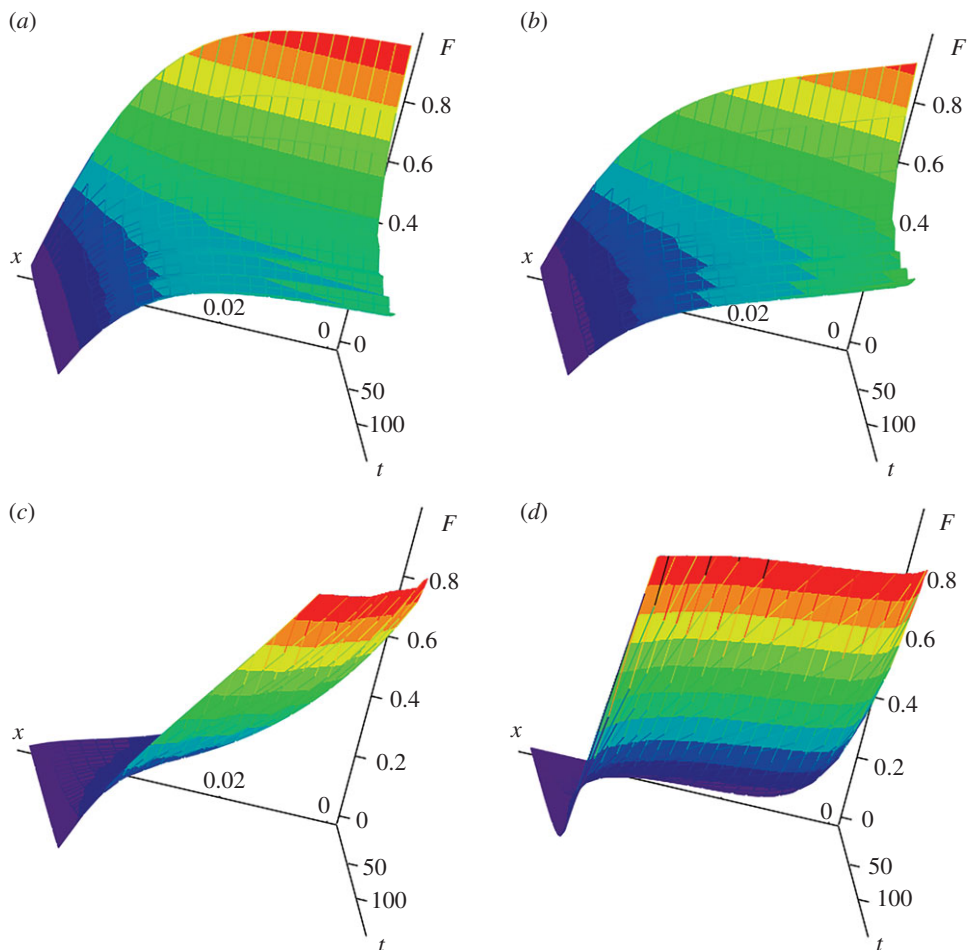


Figure 5. Dimensionless distribution function versus dimensionless coordinate x and time t for $\chi = 10^{-6}$ and $\gamma = 0.711$ (a), $\gamma = 7.11$ (b), $\gamma = 71.1$ (c) and $\gamma = 711$ (d).

evolution of crystals or other aggregates plays a decisive role. Such processes and phenomena as polymerization and crystallization in continuous apparatuses [17], evolution of protein and insulin crystals [18–20], evolution of aggregates in colloids and magnetic fluids [21–23], crystal growth in mushy layers [24–26], dissolution of dispersed solids, evaporation of a polydisperse mist, combustion of a solid dispersed fuel [27–29] may be mentioned among others.

Data accessibility. This article has no additional data.

Authors' contributions. All authors contributed equally to the present research article.

Competing interests. We declare we have no competing interests.

Funding. This work was supported by the Russian Science Foundation (grant no. 18-19-00008).

References

1. Buyevich YuA, Natalukha IA. 1994 Unsteady processes of combined polymerization and crystallization in continuous apparatuses. *Chem. Eng. Sci.* **49**, 3241–3247. (doi:10.1016/0009-2509(94)E0052-R)
2. Volmer U, Raisch J. 2001 H_∞ -Control of a continuous crystallizer. *Control Eng. Practice* **9**, 837–845. (doi:10.1016/S1474-6670(17)38528-2)
3. Rachah A, Noll D, Espitalier F, Baillon F. 2015 A mathematical model for continuous crystallization. *Math. Meth. Appl. Sci.* **39**, 1101–1120. (doi:10.1002/mma.3553)

4. Alexandrov DV. 2014 Nucleation and crystal growth kinetics during solidification: the role of crystallite withdrawal rate and external heat and mass sources. *Chem. Eng. Sci.* **117**, 156–160. (doi:10.1016/j.ces.2014.06.012)
5. Mullin JW, Gaska C. 1969 The growth and dissolution of potassium sulphate crystals in a fluidized bed crystallizer. *Can. J. Chem. Eng.* **47**, 483–489. (doi:10.1002/cjce.5450470514)
6. Garside J, Gaska C, Mullin JW. 1972 Crystal growth rate studies with potassium sulphate in a fluidized bed crystallizer. *J. Cryst. Growth* **13/14**, 510–516. (doi:10.1016/0022-0248(72)90290-4)
7. Mullin JW, Gaska C. 1973 Potassium sulfate crystal growth rates in aqueous solution. *J. Chem. Eng. Data* **18**, 217–220. (doi:10.1021/je60057a030)
8. Mullin JW, Osman MM. 1973 Nickel ammonium sulfate crystal growth rates in aqueous solution. *J. Chem. Eng. Data* **18**, 353–355. (doi:10.1021/je60059a035)
9. Alexandrov DV. 2018 Nucleation and evolution of spherical crystals with allowance for their unsteady-state growth rates. *J. Phys. A: Math. Theor.* **51**, 075102. (doi:10.1088/1751-8121/aaa5b7)
10. Alexandrov DV, Alexandrova IV. 2019 On the theory of the unsteady-state growth of spherical crystals in metastable liquids. *Phil. Trans. R. Soc. A* **377**, 20180209. (doi:10.1098/rsta.2018.0209)
11. Alexandrov DV, Nizovtseva IG, Alexandrova IV. 2019 On the theory of nucleation and nonstationary evolution of a polydisperse ensemble of crystals. *Int. J. Heat Mass Trans.* **128**, 46–53. (doi:10.1016/j.ijheatmasstransfer.2018.08.119)
12. Alexandrov DV. 2014 Nucleation and crystal growth in binary systems. *J. Phys. A: Math. Theor.* **47**, 125102. (doi:10.1088/1751-8113/47/12/125102)
13. Alexandrov DV, Malygin AP. 2014 Nucleation kinetics and crystal growth with fluctuating rates at the intermediate stage of phase transitions. *Modelling Simul. Mater. Sci. Eng.* **22**, 015003. (doi:10.1088/0965-0393/22/1/015003)
14. Alexandrov DV, Nizovtseva IG. 2014 Nucleation and particle growth with fluctuating rates at the intermediate stage of phase transitions in metastable systems. *Proc. R. Soc. A* **470**, 20130647. (doi:10.1098/rspa.2013.0647)
15. Makoveeva EV, Alexandrov DV. 2018 A complete analytical solution of the Fokker-Planck and balance equations for nucleation and growth of crystals. *Phil. Trans. R. Soc. A* **376**, 20170327. (doi:10.1098/rsta.2017.0327)
16. Fedoruk MV. 1977 *Saddle-point method*. Moscow, Russia: Nauka.
17. Ivanov AA, Alexandrova IV, Alexandrov DV. 2019 Phase transformations in metastable liquids combined with polymerization. *Phil. Trans. R. Soc. A* **377**, 20180215. (doi:10.1098/rsta.2018.0215)
18. Barlow DA. 2009 Theory of the intermediate stage of crystal growth with applications to protein crystallization. *J. Cryst. Growth* **311**, 2480–2483. (doi:10.1016/j.jcrysgro.2009.02.035)
19. Barlow DA. 2017 Theory of the intermediate stage of crystal growth with applications to insulin crystallization. *J. Cryst. Growth* **470**, 8–14. (doi:10.1016/j.jcrysgro.2017.03.053)
20. Alexandrov DV, Nizovtseva IG. 2019 On the theory of crystal growth in metastable systems with biomedical applications: protein and insulin crystallization. *Phil. Trans. R. Soc. A* **377**, 20180214. (doi:10.1098/rsta.2018.0214)
21. Buyevich YA, Ivanov AO. 1993 Kinetics of phase separation in colloids: I. Formation of initial aggregates. *Physica A* **192**, 375–390. (doi:10.1016/0378-4371(93)90044-5)
22. Buyevich YA, Ivanov AO. 1993 Kinetics of phase separation in colloids II. Non-linear evolution of a metastable colloid. *Physica A* **193**, 221–240. (doi:10.1016/0378-4371(93)90027-2)
23. Ivanov AO, Zubarev AY. 1998 Non-linear evolution of a system of elongated drop-like aggregates in a metastable magnetic fluid. *Physica A* **251**, 348–367. (doi:10.1016/S0378-4371(97)00561-X)
24. Alexandrov DV, Ivanov AA. 2009 Solidification of a ternary melt from a cooled boundary, or nonlinear dynamics of mushy layers. *Int. J. Heat Mass Trans.* **52**, 4807–4811. (doi:10.1016/j.ijheatmasstransfer.2009.05.029)
25. Alexandrov DV, Malygin AP. 2011 Convective instability of directional crystallization in a forced flow: the role of brine channels in a mushy layer on nonlinear dynamics of binary systems. *Int. J. Heat Mass Trans.* **54**, 1144–1149. (doi:10.1016/j.ijheatmasstransfer.2010.11.008)
26. Alexandrov DV, Ivanov AA, Alexandrova IV. 2018 Analytical solutions of mushy layer equations describing directional solidification in the presence of nucleation. *Phil. Trans. R. Soc. A* **376**, 20170217. (doi:10.1098/rsta.2017.0217)

27. Buyevich YuA, Korolyova NA, Natalukha IA. 1993 Modelling of unsteady combustion regimes for polydisperse fuels I. Instability and auto-oscillations. *Int. J. Heat Mass Trans.* **36**, 2223–2231. (doi:10.1016/S0017-9310(05)80153-X)
28. Buyevich YuA, Korolyova NA, Natalukha IA. 1993 Modelling of unsteady combustion regimes for polydisperse fuels II. Parametrically controlled combustion. *Int. J. Heat Mass Trans.* **36**, 2233–2238. (doi:10.1016/s0017-9310(05)80154-1)
29. Buyevich YuA, Goldobin YuM, Yasnikov GP. 1994 Evolution of a particulate system governed by exchange with its environment. *Int. J. Heat Mass Trans.* **37**, 3003–3014. (doi:10.1016/0017-9310(94)90354-9)