

DABCOonium: An Efficient and High-Voltage Stable Singlet Oxygen Quencher for Metal–O₂ Cells

Yann K. Petit, Christian Leypold, Nika Mahne, Eléonore Mourad, Lukas Schafzahl, Christian Slugovc, Sergey M. Borisov, and Stefan A. Freunberger*


Abstract: Singlet oxygen (¹O₂) causes a major fraction of the parasitic chemistry during the cycling of non-aqueous alkali metal–O₂ batteries and also contributes to interfacial reactivity of transition-metal oxide intercalation compounds. We introduce DABCOonium, the mono alkylated form of 1,4-diazabicyclo[2.2.2]octane (DABCO), as an efficient ¹O₂ quencher with an unusually high oxidative stability of ca. 4.2 V vs. Li/Li⁺. Previous quenchers are strongly Lewis basic amines with too low oxidative stability. DABCOonium is an ionic liquid, non-volatile, highly soluble in the electrolyte, stable against superoxide and peroxide, and compatible with lithium metal. The electrochemical stability covers the required range for metal–O₂ batteries and greatly reduces ¹O₂ related parasitic chemistry as demonstrated for the Li–O₂ cell.

Oxides are the backbone of most cathodes for alkali-ion batteries and their interfacial reactivity key for battery lifetime. Candidates include traditional Li-stoichiometric transition-metal oxides (TMOs) and the two intensely investigated directions of TMOs with oxygen redox and metal–O₂ batteries, which both promise significantly higher energy storage.^[1] The metal–O₂ batteries critically rely on reversibly forming/decomposing Li, Na, or K peroxide or superoxide at the cathode.^[1a,f,2] However, practically realizing such cells requires inhibition of the severe parasitic reactions, which compromise rechargeability, efficiency, and cycle life.

Reactivity of (su)peroxides has been perceived to be responsible for the parasitic reactions that decompose cell components in metal–O₂ cells into alkali carbonates and carboxylates, which are hard to oxidize and accumulate on

cycling.^[1a,b,f,2b–e,3] (Su)peroxide's reactivities as strong nucleophiles and bases could, however, not fully explain the parasitic reactions.^[1f,2b,3b,d] Recently, the highly reactive singlet oxygen (¹Δ_g or ¹O₂) was shown to cause a large fraction of the parasitic reactions; it forms at all stages of cycling at rates that resemble the rates of parasitic reactions.^[4] Superoxide disproportionation to Li₂O₂ was suggested as the source of ¹O₂, which has been shown to react with electrolyte and carbon.^[4a,5] Furthermore, ¹O₂ is now also recognized to contribute to interfacial reactivity of TMO intercalation materials.^[6] Fighting parasitic chemistry in batteries requires therefore neutralizing the ¹O₂.

Singlet oxygen is found in biological systems that use O₂ reduction and evolution for energy storage.^[7] Life has evolved strategies to protect itself against this harmful chemical using chemical trapping and physical quenching agents, such as tocopheroles and carotenes. Analogous agents also work for man-made systems.^[8] Traps uptake ¹O₂ into stable, innocuous adducts and are hence gradually consumed.^[4a,7–9] For example, 9,10-dimethylanthracene (DMA) has been shown to selectively form its endoperoxide (DMA–O₂).^[10] However, at the rate of ¹O₂ formation in batteries the DMA is quickly consumed. Physically deactivating (quenching) ¹O₂ to triplet oxygen (³O₂) is preferred since the quencher is not consumed and no new products accumulate. Radiationless physical quenching follows three mechanisms that convert the excess energy of ¹O₂ into heat:^[7,10] electronic-to-vibrational (e–v) energy transfer (¹O₂ quenching by solvents, slow), charge transfer (CT) induced quenching (ca. 10⁷ times faster than e–v), and electronic energy transfer (even faster, e.g., carotenes, unsuitable for electrochemical systems). Quenching suitable for electrochemical systems proceeds efficiently via a charge transfer (CT) mechanism. The quencher Q and ¹O₂ form a singlet encounter complex ¹(Q¹Δ)_{EC}, followed by a singlet charge transfer complex ¹(Q¹Δ)_{CT}, in which electronic charge is partially transferred to the oxygen. Energy is then released during the intersystem crossing (isc) to the triplet ground state complex ³(Q³Σ)_{CT}, which dissociates to Q and ³O₂ [Eq. (1)]




This mechanism applies to electron-rich quenchers, such as amines, and has first been suggested for 1,4-diazabicyclo[2.2.2]octane (DABCO, **1**; Scheme 1), which has also been shown to be effective in aprotic media.^[4a,6] Amines have been widely investigated and it was found that the partial charge transfer causes the quenching efficiency to correlate logarithmically

[*] Y. K. Petit, Dr. C. Leypold, Dr. N. Mahne, Dr. E. Mourad, Dr. L. Schafzahl, Prof. C. Slugovc, Dr. S. A. Freunberger
Institute for Chemistry and Technology of Materials
Graz University of Technology
Stremayrgasse 9, 8010 Graz (Austria)
E-mail: freunberger@tugraz.at

Prof. S. M. Borisov
Institute for Analytical Chemistry and Food Chemistry
Graz University of Technology
Stremayrgasse 9, 8010 Graz (Austria)

Supporting information and the ORCID identification number(s) for the author(s) of this article can be found under:
<https://doi.org/10.1002/anie.201901869>.

© 2019 The Authors. Published by Wiley-VCH Verlag GmbH & Co. KGaA. This is an open access article under the terms of the Creative Commons Attribution Non-Commercial NoDerivs License, which permits use and distribution in any medium, provided the original work is properly cited, the use is non-commercial, and no modifications or adaptations are made.

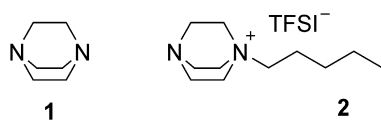

Scheme 1. Structures of the used quenchers DABCO (1) and PeDTFSI (pentyl DABCONium TFSI) (2). Synthesis and IUPAC Names are given in the Supporting Information.

mically with the ionization potential and hence oxidation potential.^[7] The efficiency drops by a factor of approximately 10^4 per volt increased oxidation potential. DABCO as one of the best known quenchers gets oxidized at approximately 3.6 V vs. Li/Li⁺ whereas approximately 4.2 V are typically required to recharge Li–O₂ cells.^[1a,3b,11] Furthermore, cation interactions with strongly Lewis basic amines are known to impair quenching.^[7] The challenge for suitable amine quenchers is therefore to lower Lewis basicity, to raise the oxidation stability to around 4.2 V, and to counterbalance for the inevitably lower molar quenching efficiency by high concentrations. It should also be compatible with a lithium-metal anode. Herein we show that monoalkylating the diamine DABCO to its onium salt (DABCONium) achieves all these goals. Applied to a Li–O₂ cell, it significantly reduces side reactions on discharge and charge.

We prepared a pentyl DABCONium species bearing a bis(trifluoromethanesulfonyl)imide (TFSI[−]) anion (1-pentyl-1,4-diazabicyclo[2.2.2]octan-1-ium TFSI **2**, in the following abbreviated as PeDTFSI) according to a literature procedure as detailed in the Supporting Information.^[12] It is an ionic liquid with a melting point of 43 °C (Figure S3 in the Supporting Information) and widely miscible with glymes (oligo ethylene glycol dimethyl ether), which are frequently used for metal–O₂ cells. As a proxy for Lewis basicity, we measured the donor number (DN) and obtained a value of 12.5 kcal mol^{−1} (see Supporting Information for details). This is similar to tetraethyleneglycol dimethylether (TEGDME), which has a DN of 12, but is much lower than that of tertiary amines, such as triethylamine (DN = 61).^[13] PeDTFSI is, like DABCO, stable against superoxide, peroxide and ¹O₂ as determined by ¹H NMR spectroscopy (Figure S5, S6).

Linear sweep voltammetry was used to determine the electro-chemical stability window of the quenchers (Figures 1 and Figure S7). Onset of reduction is in either case at around 0.5 V vs. Li/Li⁺ and hence sufficient for the O₂ cathode (Figure S7). PeDTFSI is compatible with a metal lithium anode, which sustains low overpotentials on cycling (Figure S8). Monoalkylating DABCO raises the oxidation stability of the remaining tertiary amine moiety from around 3.6 V in DABCO by approximately 0.6 V to an onset potential of about 4.2 V in PeDTFSI (Figure 1).

We measured the quenching efficiency by monitoring the disappearance rate of the ¹O₂ trap DMA in presence of the quenchers during continuous photochemical ¹O₂ generation, an approach frequently used in the literature and detailed in the Supporting Information.^[10] In short, ¹O₂ was generated photochemically at a constant rate by illuminating (643 nm) O₂ saturated TEGDME containing the photosensitizer Pd^{II} *meso*-tetra(4-fluorophenyl)tetrabenzoporphyrin,^[8] DMA,

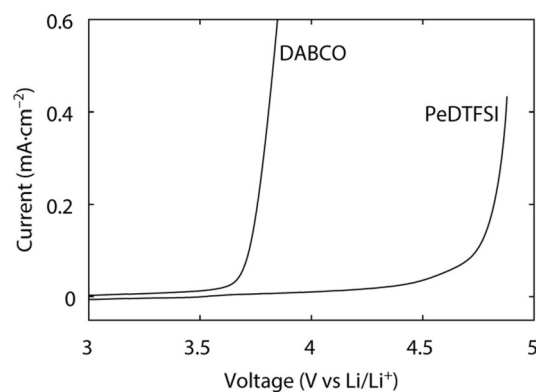


Figure 1. Linear sweep voltammetry of **1** and **2** at a glassy carbon disc electrode in 0.1 M LiTFSI/TEGDME containing 2 mM of the quencher. The scan rate was 50 mV s^{−1}.

and either no other additive or the quencher. The DMA concentration was measured by means of the UV/Vis absorbance at 379 nm. The quenching efficiency was then obtained by comparing the DMA consumption rate with and without quencher.^[10] A prerequisite of the method is that the quencher does not significantly affect the ¹O₂ generation rate by reducing the lifetime of the excited sensitizer T₁ state, which goes on to convert ³O₂ into ¹O₂. Measuring the T₁ lifetimes in presence of various quencher concentrations shows negligible influence of the quencher on ¹O₂ generation rate (see Figure S9 and S10 and discussion in the Supporting Information).

Figure 2a shows the decay of DMA concentration with various PeDTFSI concentrations. Since DMA and the quencher compete to react with/quench ¹O₂, a slower decay of the DMA concentration indicates better a quenching efficiency and hence a larger ¹O₂ fraction quenched. Figure 2b shows the thus obtained DMA decay rates without and with the quenchers and the quenched ¹O₂ fraction. 40 μM DABCO roughly halved the DMA decay rate, indicating that around 50% of the ¹O₂ was quenched. The PeDTFSI concentration had to be increased to the mM range for a strong effect. With 0.01, 0.05, 0.1, and 0.38 M, the quenched ¹O₂ fractions were 9, 23, 56, and 86%, respectively. PeDTFSI has a lower molar quenching efficiency than DABCO as expected from the higher oxidation potential. However, the high solubility of PeDTFSI allows for quenching the vast majority of the ¹O₂.

Ultimately, a suitable quencher needs to effectively decrease the amount of ¹O₂ related parasitic chemistry. Key measures for the extent of parasitic chemistry are deviations of the ratio of O₂ consumed/evolved and (su)peroxide formed/decomposed per electron passed on discharge/charge from the ideal cell reaction $O_2 + xe^- + xM^+ \rightleftharpoons M_xO_2$ (M = Li, Na, K). We chose the Li–O₂ cell to demonstrate the impact of PeDTFSI as a quencher since amongst Li-, Na-, and K–O₂ cells, Li–O₂ shows the most severe side reactions.^[1b,2c,e,3a,b,11,14] Li–O₂ cells were constructed as detailed in the Supporting Information with carbon black/PTFE cathodes and TEGDME electrolytes containing 1 M LiTFSI, 30 mM DMA and either no quencher, DABCO, or PeDTFSI. Cells were cycled at constant current and the O₂

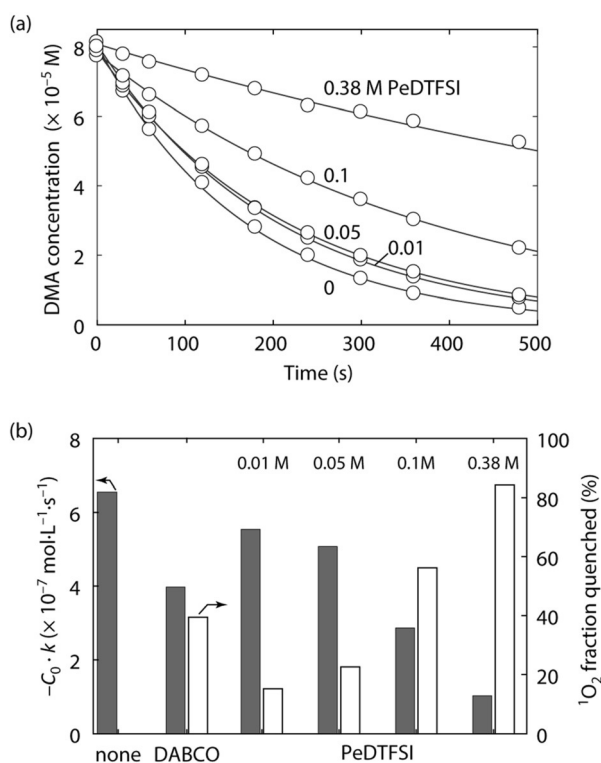


Figure 2. a) 9,10-dimethylanthracene (DMA) concentration versus time during ¹O₂ generation in the presence of various PeDTFSI concentrations to determine quenching efficiency. 80 μM DMA and the noted concentration of PeDTFSI in O₂ saturated TEGDME containing 1 μM of the sensitizer palladium(II) *meso*-tetra(4-fluorophenyl)tetrabenzoporphyrin (Pd₄F) were illuminated at 643 nm and the DMA concentration measured via the absorbance at 379 nm. b) Quenching efficiency expressed as DMA decay kinetics and fraction of ¹O₂ quenched for 40 μM DABCO and various PeDTFSI concentrations. DMA decay curves DABCO are given in Figure S11.

consumption/evolution monitored using a pressure transducer connected to the cell head space. After discharge, the electrolyte was extracted and analysed for the degree of DMA into DMA-O₂ conversion as a measure for unquenched ¹O₂, and the electrodes were analysed for the amount of Li₂O₂ and carbonaceous side products using the established procedures of photometry of the [Ti(O₂)OH]⁺ complex and CO₂ evolution upon adding acid and Fenton's reagent.^[15]

For the first discharge, we ran cells without quencher, with 60 mM DABCO, or 60, 120, or 380 mM PeDTFSI. The e⁻/O₂ ratio was within 2% of the ideal value of 2 (Figure S12), which is in accord with previous reports for similar cells without quencher.^[3a,b,4a,11,15] Li₂O₂ yields were around 95 to 96% without a significant trend with regard to the presence of a quencher (white bars in Figure 3). This result is in accord with the expectation that deactivating already formed ¹O₂ would not be expected to influence the Li₂O₂ yield, but rather the amount of side products. Consequently, the amount of unquenched ¹O₂ directly correlates with the amount of carbonaceous side products formed (black and grey bars in Figure 3). Presence of 60 mM DABCO cuts the side products by a factor of 4. The same concentration of PeDTFSI cuts the side products by half in accord with the lower molar

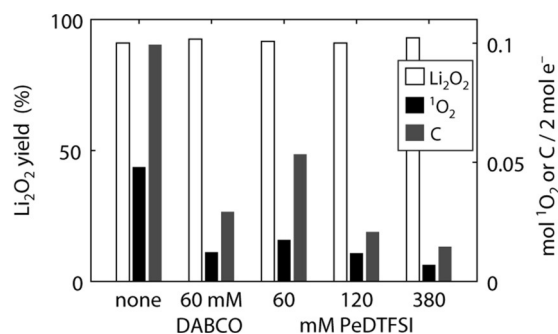


Figure 3. Li₂O₂ yield, unquenched ¹O₂ (as obtained from DMA conversion), and total carbonaceous side products (labelled with C) in Super P/PTFE (9/1, m/m) composite electrodes after discharge at 100 mA g⁻¹ to 1000 mAh g⁻¹ in 1 M LiTFSI/TEGDME containing the given quenchers.

quenching efficiency. With 380 mM PeDTFSI, however, the side products were cut to 14% of the value without quencher. PeDTFSI hence effectively reduces ¹O₂ related parasitic chemistry on discharge.

Turning to cell charge, we assessed the effect of a quencher on the O₂ evolution rate as measured by the pressure in the cell head space. DABCO has already been shown to reduce ¹O₂ related parasitic chemistry on charge within the limited oxidative stability of 3.6 V.^[4a] We hence focus on the quencher-free cell in comparison to a cell with electrolyte containing 380 mM PeDTFSI. Cells were first discharged at 100 mA g⁻¹ to 1000 mAh g⁻¹ and then recharged to a cut-off voltage of 4.6 V (Figure 4). For the quencher-free cell, the voltage rises to within a few percent of the recharge capacity towards a plateau at around 4.2 V before it further rises steeply close to the end of recharge. The O₂ evolution remains from the onset of charge, significantly below the value required for 2e⁻/O₂, indicating e⁻ extraction from side products and the reaction of released O₂ species with cell components rather than evolving as O₂.^[3a,b,d] A similar behaviour has frequently been observed in similar quencher-free Li-O₂ cells.^[1a,3a,b,d] The quickly increasing voltage was partly related to increasingly difficult electron transfer as the Li₂O₂ decrease on charging,^[2d,3c] and mainly to the increasing oxidation potential caused by newly formed parasitic products.^[1a,3]

In contrast, the cell with PeDTFSI evolves O₂ at the ideal rate of 2e⁻/O₂ up to approximately 4.2 V, which confirms that a) all the electrons are extracted from Li₂O₂ rather than partly from side products and b) any ¹O₂ is quenched to ³O₂ rather than forming side products. We have previously shown that Li₂O₂ oxidation evolves considerable fractions of ¹O₂ from the onset of charge, causing the O₂ evolution rate to be below that expected for 2e⁻/O₂.^[4a] Since a quencher cannot suppress ¹O₂ formation, the observed rate of 2e⁻/O₂ hence means that PeDTFSI effectively quenches ¹O₂ into ³O₂. Together with the much lower amounts of side products at the end of discharge (Figure 3), the eliminated ¹O₂ on charging also avoids more side products forming on recharging. This is reflected in the slower rise of the voltage compared to the quencher-free cell. Nevertheless rising voltage can be related to increasingly difficult electron transport from Li₂O₂ remote from the

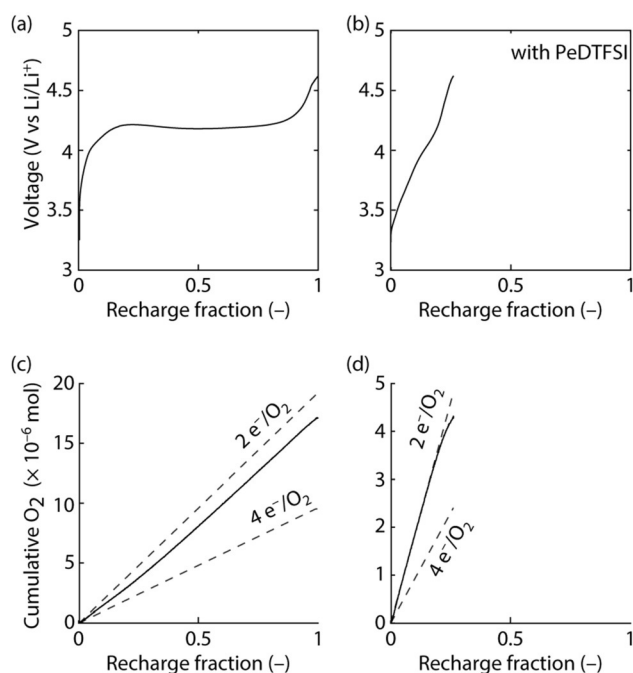


Figure 4. a),b) Voltage profiles during recharge of Super P/PTFE (9/1, m/m) composite electrodes after discharge to 1000 mAhg^{-1} at 100 mA g^{-1} in O_2 saturated $1 \text{ M LiTFSI/TEGDME}$ without (a) and with 380 mM PeDTFSI (b). c),d) Cumulative O_2 evolution in the cells in (a) and (b), respectively, as determined by measuring the pressure in the cell head space in comparison to the theoretical value based on current.

electrode surface as charging proceeds.^[2d,3c] That this is the reason for rising voltage is further supported by comparing the amount of oxidized Li_2O_2 with the charge passed. Charge capacity at cut-off corresponds to 23% of the formed Li_2O_2 , which balances with 77% left as measured by Li_2O_2 titration. Electron flux overwhelmingly oxidizing Li_2O_2 further corroborates that rising voltage is not caused by side-product formation but rather by loss of contact.^[16] PeDTFSI is amphoteric, Lewis basic at the tertiary N atom and Lewis acidic at the quaternary N atom, which could possibly solubilize the LiO_2 intermediate. Difficulties in recharging cells using additives favouring the solution mechanism are widely recognized and similarly the impeded recharge under conditions that favour solution processes have been discussed analogously.^[1f,16b,17] Such cells are now recognized to require mediators for full charge.^[1f]

In conclusion, we show that DABCONium, the mono alkylated form of the diamine 1,4-diazabicyclo[2.2.2]octane (DABCO), is an efficient $^1\text{O}_2$ quencher with high voltage stability suitable for non-aqueous battery cathodes and the Li anode. Quaternizing one of the nitrogen atoms raises the oxidation stability of the remaining tertiary nitrogen from $3.6 \text{ V vs. Li/Li}^+$ to approximately 4.2 V . We demonstrate the efficiency of DABCONium by means of the $\text{Li}-\text{O}_2$ cathode, where $^1\text{O}_2$ related parasitic chemistry is particularly severe and where the quencher greatly reduces the parasitic chemistry. On a wider perspective, partly quaternizing diamines is suitable to tune the oxidation potential of $^1\text{O}_2$ quenchers. $^1\text{O}_2$ is now also known to evolve from layered

transition-metal cathodes and upon oxidizing Li_2CO_3 , a common impurity of cathode materials. Quenchers stable under high-voltage are hence relevant to control $^1\text{O}_2$ related interfacial reactivity and long-term cyclability of many currently studied cathodes.

Acknowledgements

S.A.F. is indebted to the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation program (grant agreement no. 636069). We thank A. Samojlov and D. Schuster for support with measurements. We thank EL-Cell GmbH (Hamburg, Germany) for the PAT-Cell-Press test cells.

Conflict of interest

The authors declare no conflict of interest.

Keywords: DABCONium · electrochemistry · lithium batteries · quenchers · singlet oxygen

How to cite: *Angew. Chem. Int. Ed.* **2019**, *58*, 6535–6539
Angew. Chem. **2019**, *131*, 6605–6609

- [1] a) Y.-C. Lu, B. M. Gallant, D. G. Kwabi, J. R. Harding, R. R. Mitchell, M. S. Whittingham, Y. Shao-Horn, *Energy Environ. Sci.* **2013**, *6*, 750–768; b) C. L. Bender, P. Hartmann, M. Vračar, P. Adelhelm, J. Janek, *Adv. Energy Mater.* **2014**, *4*, 1301863; c) L. Croguennec, M. R. Palacin, *J. Am. Chem. Soc.* **2015**, *137*, 3140–3156; d) S. E. Renfrew, B. D. McCloskey, *J. Am. Chem. Soc.* **2017**, *139*, 17853–17860; e) G. Assat, J.-M. Tarascon, *Nat. Energy* **2018**, *3*, 373–386; f) D. Aurbach, B. D. McCloskey, L. F. Nazar, P. G. Bruce, *Nat. Energy* **2016**, *1*, 16128; g) K. Luo, M. R. Roberts, R. Hao, N. Guerrini, D. M. Pickup, Y.-S. Liu, K. Edström, J. Guo, A. V. Chadwick, L. C. Duda, P. G. Bruce, *Nat. Chem.* **2016**, *8*, 684–691.
- [2] a) S. Ganapathy, B. D. Adams, G. Stenou, M. S. Anastasaki, K. Goubitz, X.-F. Miao, L. F. Nazar, M. Wagemaker, *J. Am. Chem. Soc.* **2014**, *136*, 16335–16344; b) Z. Liang, Y.-C. Lu, *J. Am. Chem. Soc.* **2016**, *138*, 7574–7583; c) T. Liu, G. Kim, M. T. L. Casford, C. P. Grey, *J. Phys. Chem. Lett.* **2016**, *7*, 4841–4846; d) J. Wang, Y. Zhang, L. Guo, E. Wang, Z. Peng, *Angew. Chem. Int. Ed.* **2016**, *55*, 5201–5205; *Angew. Chem.* **2016**, *128*, 5287–5291; e) W. Wang, N.-C. Lai, Z. Liang, Y. Wang, Y.-C. Lu, *Angew. Chem. Int. Ed.* **2018**, *57*, 5042–5046; *Angew. Chem.* **2018**, *130*, 5136–5140.
- [3] a) B. D. McCloskey, A. Valery, A. C. Luntz, S. R. Gowda, G. M. Wallraff, J. M. Garcia, T. Mori, L. E. Krupp, *J. Phys. Chem. Lett.* **2013**, *4*, 2989–2993; b) B. D. McCloskey, D. S. Bethune, R. M. Shelby, T. Mori, R. Scheffler, A. Speidel, M. Sherwood, A. C. Luntz, *J. Phys. Chem. Lett.* **2012**, *3*, 3043–3047; c) J. Højberg, B. D. McCloskey, J. Hjelm, T. Vegge, K. Johansen, P. Norby, A. C. Luntz, *ACS Appl. Mater. Interfaces* **2015**, *7*, 4039–4047; d) B. D. McCloskey, J. M. Garcia, A. C. Luntz, *J. Phys. Chem. Lett.* **2014**, *5*, 1230–1235.
- [4] a) N. Mahne, B. Schafzahl, C. Leypold, M. Leypold, S. Grumm, A. Leitgeb, G. A. Strohmeier, M. Wilkening, O. Fontaine, D. Kramer, C. Slugovc, S. M. Borisov, S. A. Freunberger, *Nat. Energy* **2017**, *2*, 17036; b) L. Schafzahl, N. Mahne, B. Schafzahl, M. Wilkening, C. Slugovc, S. M. Borisov, S. A. Freunberger, *Angew. Chem. Int. Ed.* **2017**, *56*, 15728–15732; *Angew. Chem.*

- 2017, 129, 15934–15938; c) J. Wandt, P. Jakes, J. Granwehr, H. A. Gasteiger, R.-A. Eichel, *Angew. Chem. Int. Ed.* **2016**, 55, 6892–6895; *Angew. Chem.* **2016**, 128, 7006–7009.
- [5] a) K. Chaisiwamongkhol, C. Batchelor-McAuley, R. G. Palgrave, R. G. Compton, *Angew. Chem. Int. Ed.* **2018**, 57, 6270–6273; *Angew. Chem.* **2018**, 130, 6378–6381; b) M. Carboni, A. G. Marrani, R. Spezia, S. Brutti, *J. Electrochem. Soc.* **2018**, 165, A118–A125.
- [6] a) T. Hatsukade, A. Schiele, P. Hartmann, T. Brezesinski, J. Janek, *ACS Appl. Mater. Interfaces* **2018**, 10, 38892–38899; b) J. Wandt, A. T. S. Freiberg, A. Ogrodnik, H. A. Gasteiger, *Mater. Today* **2018**, 21, 825–833; c) N. Mahne, S. E. Renfrew, B. D. McCloskey, S. A. Freunberger, *Angew. Chem. Int. Ed.* **2018**, 57, 5529–5533; *Angew. Chem.* **2018**, 130, 5627–5631.
- [7] C. Schweitzer, R. Schmidt, *Chem. Rev.* **2003**, 103, 1685–1758.
- [8] S. M. Borisov, G. Nuss, W. Haas, R. Saf, M. Schmuck, I. Klimant, *J. Photochem. Photobiol. A* **2009**, 201, 128–135.
- [9] S. Miyamoto, G. R. Martinez, M. H. G. Medeiros, P. Di Mascio, *J. Am. Chem. Soc.* **2003**, 125, 6172–6179.
- [10] F. Wilkinson, W. P. Helman, A. B. Ross, *J. Phys. Chem. Ref. Data* **1995**, 24, 663–1021.
- [11] B. D. Adams, R. Black, Z. Williams, R. Fernandes, M. Cuisinier, E. J. Berg, P. Novak, G. K. Murphy, L. F. Nazar, *Adv. Energy Mater.* **2015**, 5, 1400867.
- [12] M. Yoshizawa-Fujita, K. Johansson, P. Newman, D. R. MacFarlane, M. Forsyth, *Tetrahedron Lett.* **2006**, 47, 2755–2758.
- [13] V. Gutmann, *Coord. Chem. Rev.* **1976**, 18, 225–255.
- [14] a) R. Black, A. Shyamsunder, P. Adeli, D. Kundu, G. K. Murphy, L. F. Nazar, *ChemSusChem* **2016**, 9, 1795–1803; b) S. Y. Sayed, K. P. C. Yao, D. G. Kwabi, T. P. Batcho, C. V. Amanchukwu, S. Feng, C. V. Thompson, Y. Shao-Horn, *Chem. Commun.* **2016**, 52, 9691–9694; c) N. Xiao, R. T. Rooney, A. A. Gewirth, Y. Wu, *Angew. Chem. Int. Ed.* **2018**, 57, 1227–1231; *Angew. Chem.* **2018**, 130, 1241–1245.
- [15] B. Schafzahl, E. Mourad, L. Schafzahl, Y. K. Petit, A. R. Raju, M. O. Thotiyl, M. Wilkening, C. Slugovc, S. A. Freunberger, *ACS Energy Lett.* **2018**, 3, 170–176.
- [16] a) X. Gao, Y. Chen, L. Johnson, P. G. Bruce, *Nat. Mater.* **2016**, 15, 882; b) X. Gao, Z. P. Jovanov, Y. Chen, L. R. Johnson, P. G. Bruce, *Angew. Chem. Int. Ed.* **2017**, 56, 6539–6543; *Angew. Chem.* **2017**, 129, 6639–6643.
- [17] a) C. M. Burke, V. Pande, A. Khetan, V. Viswanathan, B. D. McCloskey, *Proc. Natl. Acad. Sci. USA* **2015**, 112, 9293–9298; b) Y. Zhang, L. Wang, X. Zhang, L. Guo, Y. Wang, Z. Peng, *Adv. Mater.* **2018**, 30, 1705571.

Manuscript received: February 12, 2019

Accepted manuscript online: March 18, 2019

Version of record online: April 9, 2019