

MATERIALS SCIENCE

Room-temperature skyrmion lattice in a layered magnet ($\text{Fe}_{0.5}\text{Co}_{0.5}\text{Fe}_5\text{GeTe}_2$)

Hongrui Zhang^{1*†}, David Raftrey^{2,3†}, Ying-Ting Chan^{4†}, Yu-Tsun Shao^{5†}, Rui Chen^{1,2}, Xiang Chen^{2,6}, Xiaoxi Huang¹, Jonathan T. Reichanadter^{7,8}, Kaichen Dong^{1,2}, Sandhya Susarla^{1,2}, Lucas Caretta¹, Zhen Chen⁵, Jie Yao^{1,2}, Peter Fischer^{2,3}, Jeffrey B. Neaton^{2,6,9}, Weida Wu⁴, David A. Muller^{5,10}, Robert J. Birgeneau^{2,6}, Ramamoorthy Ramesh^{1,2,6*}

Novel magnetic ground states have been stabilized in two-dimensional (2D) magnets such as skyrmions, with the potential next-generation information technology. Here, we report the experimental observation of a Néel-type skyrmion lattice at room temperature in a single-phase, layered 2D magnet, specifically a 50% Co-doped Fe_5GeTe_2 (FCGT) system. The thickness-dependent magnetic domain size follows Kittel's law. The static spin textures and spin dynamics in FCGT nanoflakes were studied by Lorentz electron microscopy, variable-temperature magnetic force microscopy, micromagnetic simulations, and magnetotransport measurements. Current-induced skyrmion lattice motion was observed at room temperature, with a threshold current density, $j_{\text{th}} = 1 \times 10^6 \text{ A/cm}^2$. This discovery of a skyrmion lattice at room temperature in a noncentrosymmetric material opens the way for layered device applications and provides an ideal platform for studies of topological and quantum effects in 2D.

INTRODUCTION

Two-dimensional van der Waals (2D vdW) magnets offer an excellent platform for exploring fascinating magnetic and quantum topological phases, owing to their unique layered structure and crystal symmetries. (1–5). Magnetic skyrmions, which are topologically protected spin textures, are often observed in chiral (6–8) and polar (9–14) magnets and are usually stabilized by an antisymmetric exchange interaction, the Dzyaloshinskii-Moriya interaction (DMI). Recent investigations of 2D vdW magnets have led to the discovery and manipulation of skyrmions, a promising new frontier for future spintronic devices (15–19). Néel-type skyrmions supported by interfacial DMI energy were found in the $\text{WTe}_2/\text{Fe}_3\text{GeTe}_2$ (17) and $\text{O-Fe}_3\text{GeTe}_2/\text{Fe}_3\text{GeTe}_2$ (18) heterostructures. In addition, zero-field Néel-type skyrmions were stabilized by interlayer exchange coupling between Fe_3GeTe_2 and Co/Pd multilayers (19). However, these previously reported vdW skyrmions were all achieved below room temperature, limiting the further investigation of their formation mechanism and subsequent potential developments toward room-temperature applications. The discovery of an intrinsic magnetic ground state, especially a topological skyrmion state, at room temperature in layered materials provides an ideal platform to study the interfacial coupling between spin and other degrees of freedom, which may give rise to novel quantum behaviors at room temperature. Here, we report the realization of a room-temperature Néel-type

skyrmion lattice in 50% Co-doped Fe_5GeTe_2 (FCGT), which is a layered polar ferromagnetic metal. Its static properties and dynamic behavior of ~85- to 2100-nm-thick nanoflakes were characterized using Lorentz (scanning) transmission electron microscopy [L(S)TEM], variable-temperature magnetic force microscopy (MFM) for domain imaging supported by micromagnetic simulations. Magnetotransport measurements were performed to understand the spin dynamics of the skyrmion lattice. Our studies demonstrate the dependence of skyrmion size and stability of the skyrmion lattice as a function of sample thickness, applied magnetic field, and temperature, as well as the current-induced skyrmion formation and motion at room temperature.

RESULTS AND DISCUSSION

Structure and room-temperature skyrmions of the FCGT system

The AA'-stacked FCGT is a polar ferromagnetic metal that belongs to the $P6_3mc$ space group and C_{6v} point group. Figure 1A shows a schematic of FCGT with the wurtzite structure. High-angle annular dark-field-based STEM (HAADF-STEM) images (Fig. 1B and fig. S1) show the atomic-scale structure of FCGT and the high quality of our single-crystalline FCGT nanoflakes. Similar to Fe_5GeTe_2 , the FCGT unit cell nominally features three unique Fe Wyckoff positions: Fe1, Fe2, and Fe3; Fe1 is further split by fractional occupation between the Fe1a and Fe1b sites (Fig. 1, A and B). Unlike the undoped Fe_5GeTe_2 system where the partially occupied Fe1 positions are disordered (20–23), Fe1 atoms in the AA'-stacked FCGT system are ordered, and six layers [Fe/Co (Fe1a site), Fe/Co (Fe3 site), Fe/Co (Fe2 site), Ge, Fe/Co (Fe2), and Fe/Co (Fe3)] are separated by two adjacent Te layers. The crystal structure sublayers exhibit an ordered zigzag arrangement along the c axis (and hence the notation of AA') as viewed from the [100] projection. In addition, Co (Fe) atoms prefer to occupy the Fe2 (Fe3) site in the AA'-stacked FCGT (45%) (22); however, most of the Co (Fe) atoms still occupy the Fe2 (Fe3) site, but a fraction of Co (Fe) atoms occupy the Fe3 (Fe2) site in the AA'-stacked FCGT (see Fig. 1B and fig. S2). Thus, the AA'-stacked

¹Department of Materials Science and Engineering, University of California, Berkeley, Berkeley, CA, USA. ²Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA, USA. ³Physics Department, University of California, Santa Cruz, Santa Cruz, CA, USA. ⁴Department of Physics and Astronomy, Rutgers University, Piscataway, NJ, USA. ⁵School of Applied and Engineering Physics, Cornell University, Ithaca, NY, USA. ⁶Department of Physics, University of California, Berkeley, Berkeley, CA, USA. ⁷Department of Electrical Engineering, University of California, Berkeley, Berkeley, CA, USA. ⁸Department of Chemistry, University of California, Berkeley, Berkeley, CA, USA. ⁹Kavli Energy Nanosciences Institute at Berkeley, Berkeley, CA, USA. ¹⁰Kavli Institute at Cornell for Nanoscale Science, Cornell University, Ithaca, NY, USA.

*Corresponding author. Email: hongruizhang@berkeley.edu (H.Z.); rramesh@berkeley.edu (R.R.)

†These authors contributed equally to this work.

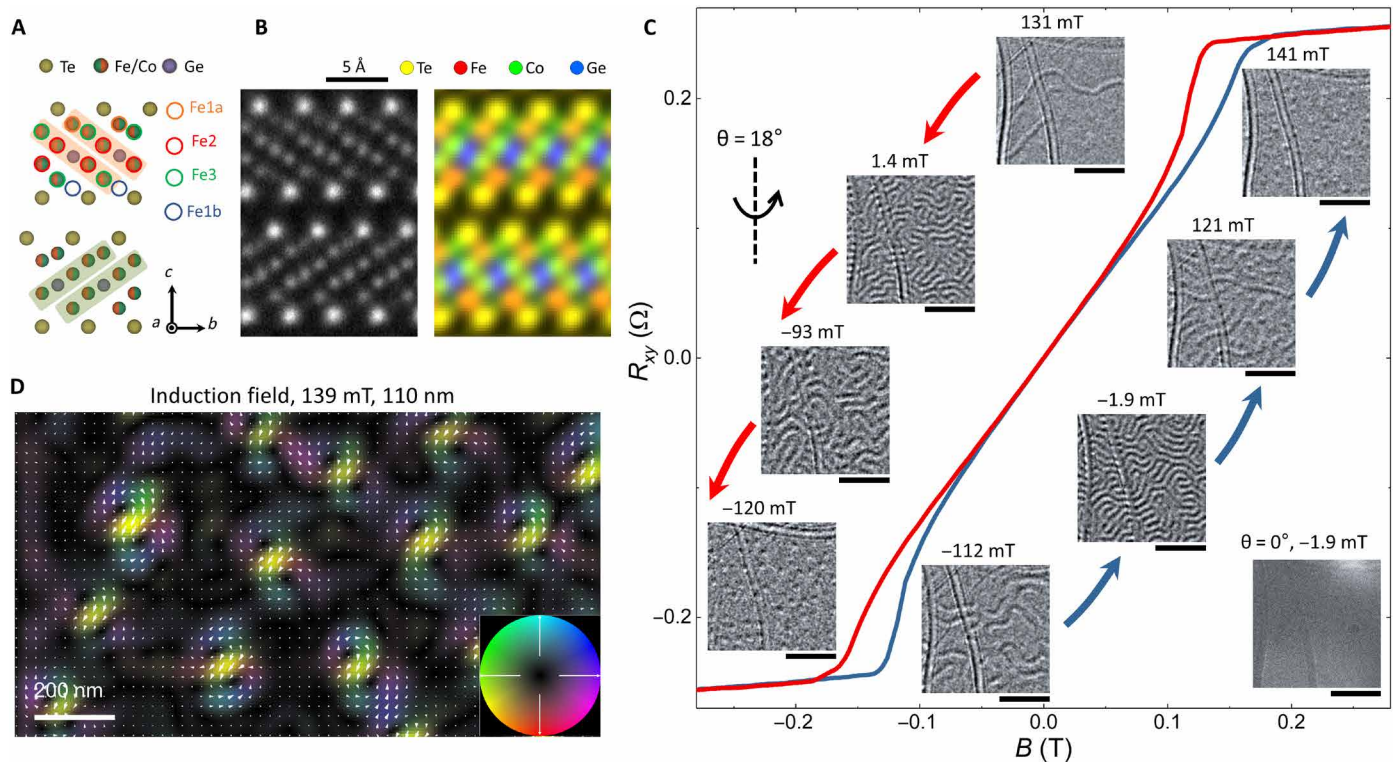


Fig. 1. Skymion creation as a function of the out-of-plane magnetic field at room temperature. (A) Structural model of FCGT viewed along the *a* axis. Fe1a site, Fe2 site, Fe3 site, and Fe1b site are marked by orange, red, green, and blue circles, respectively. (B) Experimental atomic resolution HAADF-STEM image (left) and the corresponding STEM–energy-dispersive x-ray spectroscopy (EDS) map (right). The STEM-EDS map is shown as a composite overlay of Fe, Co, Ge, and Te with red, green, blue, and yellow color maps, respectively. (C) Hysteresis curve of a 110-nm-thick FCGT flake and the corresponding Lorentz TEM images at various applied fields. The red (blue) curve indicates the direction for decreasing (increasing) magnetic fields. The contrast change between 0° and 18° tilt reveals the Néel character. Scale bars, 500 nm. (D) Magnetic induction field map of isolated skyrmions in a 110-nm-thick flakes obtained using 4D-LSTEM along with an EMPAD, with applied fields of 139 mT. The color and arrows indicate induction field components perpendicular to the beam propagation direction of Néel skyrmions at an 18° tilt.

FCGT system is a unique noncentrosymmetric structure in the Fe_NGeTe_2 ($N = 3, 4, \text{ and } 5$) system (22, 24, 25). A notable feature arising as a result of the pronounced order of the two Fe1 sites in the AA' phase is the absence of an inversion center located at the Ge site that is observed in the bulk AA-stacked Fe_5GeTe_2 . While the inversion point disallows any cumulative DM vector beyond the unit cell, thus restricting any long-range chiral spin texture in Fe_3GeTe_2 (26), the DM interactions in the AA' FCGT are far less constrained and become sensitive to the extent of the ordering of two Fe1 site occupancies. Application of Moriya's symmetry rules (27) to the nearest-neighbor spins in the AA' FCGT system restricts all antisymmetric interactions to be oriented in plane and transverse to the pair axis, yet in contrast to the AA phase, the AA' phase with ordered Fe1 site occupation allows for an uncompensated DMI vector to persist beyond the atomic scale. Given the broken inversion symmetry and the expected in-plane DMI of the AA' phase, one expects to observe Néel-type skyrmions in this system, in contrast to most bulk DMI systems (such as the B20 compounds), which exhibit only Bloch-type skyrmions (28, 29).

The temperature dependence of magnetization and magneto-transport (see figs. S3 and S4) reveals an unexpectedly high Curie temperature for this FCGT system, up to ~350 K. The sheared out-of-plane anomalous Hall transport curves at room temperature indicate a multidomain state at remanence (13), which hints that a skyrmion might be stabilized under a suitable magnetic field in this

polar magnet. L(S)TEM measurements were carried out at room temperature to resolve the nanoscale spin texture of FCGT. Magnetic field-dependent L(S)TEM images are shown in Fig. 1C, superimposed on the anomalous Hall resistance plot from a sample of similar thickness. At $B = -1.9$ mT, no contrast in the L(S)TEM image is observed for the 110-nm-thick FCGT nanoflake when the sample is not tilted; that is, the electron beam direction is collinear with the normal to the sample's surface. Once the sample is slightly tilted (for example, by 18°) along the direction labeled in Fig. 1C, the labyrinthine domain is observed, which suggests a Néel-type character of the domain wall (30–32). The absence of contrast in the L(S)TEM image for the nontilted sample is due to the symmetric distribution of magnetization in the Néel-type domain wall, leading to an electron deflection that cancels out. At field magnitudes beyond 200 mT, no contrast can be observed, which is indicative of a uniform (single domain) magnetized state. As the magnetic field is progressively decreased toward zero field (red curve), stripe domains start to appear (131 mT) and progressively aggregate to form worm-like features (1.4 mT), but skyrmions are hardly observed under this field. However, with a further decrease of the magnetic field and the subsequent change of the field direction, the stripe domains turn into a mixture of short stripe domains and bubbles (–93 mT) and then evolve into bubbles (–120 mT). The bubbles show a dark/bright contrast along the direction perpendicular to the tilted axis, which further confirms the Néel-type spin texture in this

system. For field magnitudes beyond ~ 200 mT, the image contrast is uniform, indicating a uniform magnetic state. Recovering a skyrmionic bubble state requires that the field be progressively increased in the positive direction to about 130 to 140 mT (see also movie S1). Figure 1D shows a magnetic induction map obtained using 4D Lorentz STEM (4D-LSTEM) in conjunction with an electron microscope pixel array detector (EMPAD) (33). The theoretical simulations and experimental results demonstrate that the Néel-type skyrmion can be described by a magnetic induction composed of clockwise and counterclockwise spin curls in the induction field map (31, 34), which also agrees well with our experimental observation in Fig. 1D and the corresponding simulation in fig. S5.

Thickness controlled skyrmion size and ordering

For Bloch-type skyrmions, the lateral size is independent of the sample thickness, as exemplified in the B20 compound (35, 36). By contrast, Néel-type skyrmion sizes can be extensively manipulated by the thickness of the sample owing to magnetostatic interactions (37). FCGT, as a layered material, can be systematically exfoliated into nanoflakes with varying thickness, starting from few unit cells. To study the evolution of the skyrmions as a function of sample thickness, MFM measurements were performed at room temperature and zero magnetic field. The nanoflakes were prepared by mechanical exfoliation from bulk crystals and were capped with a 3-nm-thin Au layer to prevent degradation. Figure 2 (A to G) depicts MFM images of the FCGT nanoflakes with various thicknesses, where yellow (blue) contrast corresponds to spin up (down) regions. Stripe domains were observed in a 58-nm-thick nanoflake (Fig. 2A). As the thickness of the FCGT nanoflake increases to ~ 114 nm (Fig. 2B), isolated patches of bubbles (skyrmions) emerge in the stripe domains. As the thickness is increased to ~ 128 nm, an ordered hexagonal skyrmion lattice emerges (Fig. 2C). The skyrmion lattice is stable over a broad thickness range until the nanoflake is thicker than ~ 300 nm. For thicknesses greater than ~ 300 nm, a mixture of isolated skyrmion and labyrinthine domains was observed (Fig. 2E), and a further thickness increase gradually stabilizes the labyrinthine domain state, as exemplified in the 482-nm-thick (Fig. 2F) and 2.2- μm -thick (Fig. 2G) nanoflakes. No magnetic

contrast was observed in a nanoflake of thickness below ~ 40 nm; however, it is likely that the magnetic signal falls below the MFM sensitivity because of the reduced stray field in thin nanoflakes (38). Figure 2H shows the thickness-dependent domain width and skyrmion size, which are determined from the line profile of the stripes and bubbles. The domain size diminishes with smaller thickness, following Kittel's law ($d \propto t^{1/2}$, where d is the domain size and t is the sample thickness). This is also verified by micromagnetic simulations illustrated in Fig. 2H. From these measurements and simulations, we estimated a DMI energy of $D = 0.76 \pm 0.02$ mJ/m² (see section S1).

Metastable zero-field skyrmions

We now discuss the possible mechanisms that lead to the observation of a zero-field skyrmion lattice in the FCGT nanoflakes. In previous works, zero-field Néel-type skyrmions have been stabilized by an exchange bias field (39), stray fields from MFM tips (40, 41), and Joule heating (42–44) in multilayer ferromagnetic metal films. The exchange bias scenario can be eliminated because anomalous Hall measurements on zero-field skyrmion samples exhibit no measurable shift after either positive or negative field cooling (see fig. S4). A metastable skyrmion lattice can be stabilized at low temperature by quenching from a thermally equilibrated skyrmion lattice phase near the transition temperature (T_c) (42, 43). It is worth noting that the T_c of bulk FCGT is just above room temperature, and thus, it is ideal to stabilize skyrmions at room temperature. The reduced M_s near T_c favors the formation of skyrmion due to the reduced energy barriers from stray fields in nanoflakes (43). Last, local fields from the scanning MFM tip can also be the driving force to create the nominally zero-field skyrmion lattice (45). To investigate the origin of the creation of a zero-field skyrmion lattice in FCGT, a series of MFM measurements under different conditions were carried out. Figure 3 demonstrates that the metastable skyrmion lattice phase can be stabilized in zero field through field training. At zero field, the stripe domain phase (which is the ground state) is observed after zero field cooling through T_c (Fig. 3A). So, the free energy of the skyrmion lattice phase is higher, likely because of the positive energy cost of domain walls (see the 'Micromagnetic simulations' section).

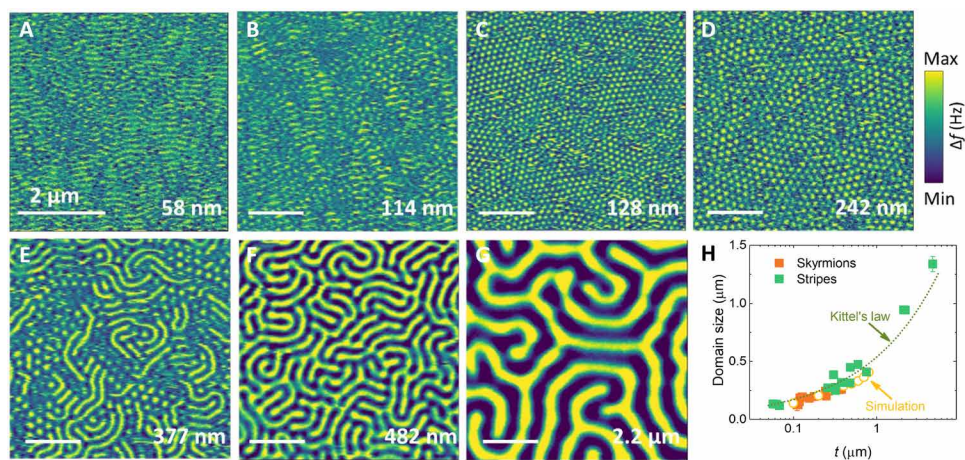


Fig. 2. MFM measurements at room temperature. (A to G) MFM images of an FCGT nanoflake on a SiO₂/Si substrate with different thicknesses (scale bar, 2 μm). The thickness was measured by atomic force microscopy. (H) Domain size as a function of the FCGT thickness. The skyrmion size strongly depends on flake thickness. The dotted line is a fit to Kittel's law. The micromagnetic simulation results also follow Kittel's law (yellow circles).

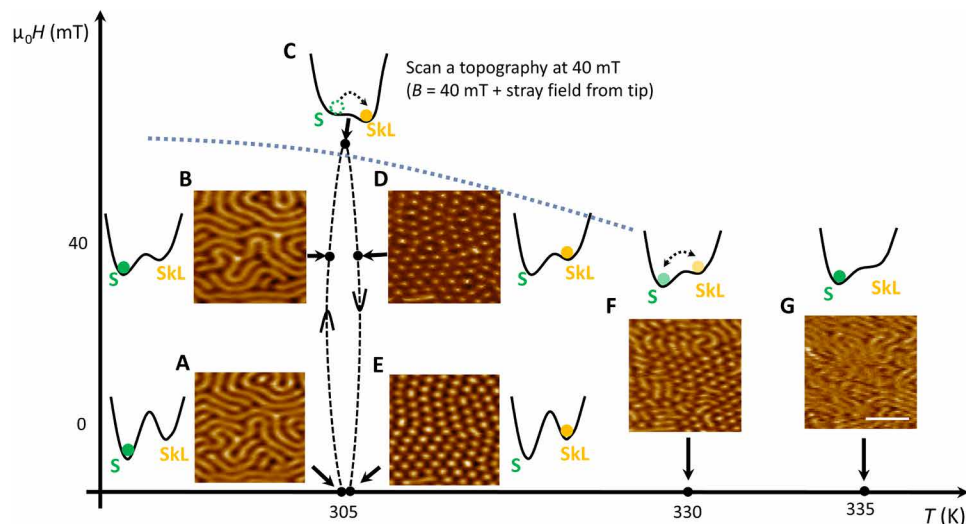


Fig. 3. Metastable zero-field skyrmions. MFM images in the 261-nm FCGT nanoflake and the corresponding schematic H - T energy landscape diagram of the stripe domain state (S) and skyrmion lattice state (SkL). (A and B) Stripe domain state at 0 and 40 mT, at 305 K. (C) The skyrmion lattice phase was induced by the combination of the external field (40 mT) and the stray field from the MFM tip. (D and E) Skyrmion lattice state persists as a metastable state at 40 and 0 mT. (F) Coexistence of stripes and skyrmions at 330 K. (G) Fully recovered stripe domain state at 335 K. No magnetic contrast was observed above 340 K. The dotted line is the phase boundary between stripe domain and skyrmion lattice. Scale bar, 1 μm .

The Zeeman energy gain of the skyrmion lattice phase due to a finite, out-of-plane magnetic field lowers its free energy, resulting in a transition from stripe domains to a skyrmion lattice. At room temperature, the transition field to induce skyrmion lattice is >100 mT (see Lorentz TEM results in Fig. 1C). For the same reason, the stray field from the MFM tip (several tens of milliteslas as shown in fig. S6) by itself is not sufficient to induce a skyrmion lattice phase at room temperature (see fig. S7). At 305 K (slightly above room temperature), the stripe phase is stable in a 40-mT external field (Fig. 3B). This, in combination with the several tens of milliteslas field from the MFM tip, can induce a skyrmion lattice (Fig. 3D), further validating that the combined field is above the transition field (Fig. 3C). The induced skyrmion lattice is stable in a 40-mT field at 305 K as shown in Fig. 3D, suggesting a substantial energy barrier between the two phases. Furthermore, the skyrmion lattice phase persists as a metastable state even after removing the external field (Fig. 3E), corroborating the substantial energy barrier. The skyrmion lattice phase is robust against a mild temperature increase (up to 312 K). A mild thermal annealing even improves the correlation length of the metastable skyrmion lattice (see fig. S8). However, further increases in temperature destabilize the skyrmion lattice phase, which gradually returns to the stripe domains through a mixed state (Fig. 3F), indicating the gradual decrease of the energy barrier due to the reduction of M_s and magnetic anisotropy with T_c . The stripe phase completely recovers at ~ 335 K in zero field (Fig. 3G).

Micromagnetic simulations

To better understand the stabilization of the zero-field skyrmion lattice and its evolution as a function of key magnetic parameters [DMI constant D , effective perpendicular magnetic anisotropy (PMA) energy K , and exchange stiffness constant A] in the FCGT system, micromagnetic simulations were performed as a function of thickness at room temperature (see Methods). During the simulation process, a temporary 100-mT out-of-plane magnetic field was

applied to nucleate the skyrmion lattice at room temperature. The skyrmion lattice remains even after removing the field, which is consistent with the MFM experimental results. Figure 4 summarizes the micromagnetic simulations that demonstrate a metastable skyrmion lattice in the 200-nm FCGT nanoflake for certain combinations of A , K , and D . These simulations reveal that the skyrmionic spin texture results from the competition between the magnetic dipolar energy and domain wall energy. For a fixed thickness of the nanoflake and temperature, the domain pattern tends to be progressively dependent on the domain wall energy (46) ($\sigma_w = 4\sqrt{AK} - \pi|D|$). In the high- D and low- A (K) regime, i.e., $\sigma_w < 0$, a labyrinthine domain pattern with a small domain width is observed at zero field. An external magnetic field is needed to stabilize the skyrmion lattice. In contrast, large bubbles and stripe domains were obtained in the high- A (K) and low- D regime (high σ_w). For σ_w in the range of ~ 0 to 1.62 mJ/m², a skyrmion lattice can be stabilized in a 200-nm-thick nanoflake, as confirmed by experimental data (see section S1). Similar to the results with 200-nm-thick nanoflakes, the domain pattern in 50- and 100-nm-thick nanoflakes also transforms from a labyrinthine domain pattern to a skyrmion lattice and returns to a labyrinthine domain with a large width, and lastly to a single domain with increasing σ_w . The skyrmion lattice phase was observed only in a very narrow range of σ_w for the relative thin nanoflake, which is attributed to a larger dipolar energy (see fig. S11). Even under a magnetic field, the skyrmions are more difficult to be stabilized in the thinner nanoflake as evidenced by the L(S)TEM measurement. With increasing field, the labyrinthine domain at remanence in a 60-nm-thick nanoflake reverses via rapid domain wall motion through the entire sample (see fig. S12). On the other hand, when the nanoflakes are thick, the skyrmion lattice can be stabilized under a magnetic field (see fig. S13A). However, breaking up of the larger-width labyrinthine domain into bubbles requires overcoming a large energy barrier. Therefore, a metastable skyrmion lattice can be readily stabilized at zero magnetic field only for nanoflakes with thicknesses between 120 and 300 nm.

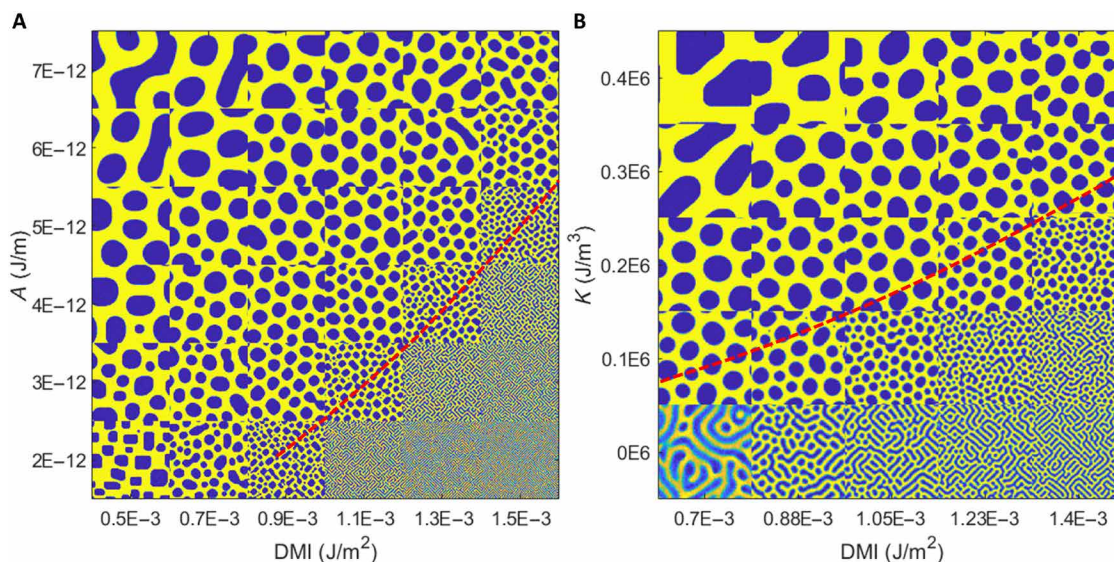


Fig. 4. Micromagnetic simulations. (A) Skymrion phase diagram as a function of DMI constant D and exchange stiffness constant A in 200-nm FCGT. (B) Skymrion phase diagram as a function of DMI constant D and effective PMA energy K . We have used a 4-nm maximum distance between unit cells, which is lower than the value of the exchange length $l_{ex} = \sqrt{\frac{2A}{\mu_0 M_s^2}} \sim 9.8$ nm. The image size is $1 \mu\text{m}$ by $1 \mu\text{m}$. The red dashed line follows the solution of $\sigma_w = 0$.

Current-driven spin dynamics of skyrmions

Now that the stabilization of a skyrmion lattice at room temperature is verified, to further demonstrate the potential of the FCGT system for skyrmionic devices, we performed the magnetotransport measurements to study the current-driven motion of skyrmions. Figure 5A shows Hall measurements at various current densities in a 136-nm-thick nanoflake at room temperature. The sample temperature was monitored by the longitudinal resistance of the sample itself to eliminate the heating effect (see fig. S14). The Hall resistance consists of the normal, anomalous, and topological Hall resistances. The topological Hall effect has been associated with a noncollinear spin texture that comprises the skyrmions (47). At low current density, the Hall effect curves show a sheared out-of-plane hysteresis loop with two distinct slopes, i.e., sharp (decreasing field) and slanted (increasing field) slopes (labeled by green and red arrows). From the L(S)TEM results (Fig. 1 and movie S1), the skyrmions are stabilized only when the field magnitude is increased from ~ 120 to ~ 140 mT. As the current density is increased, a suppression in the Hall effect curve (marked by a red arrow in Fig. 5A and a red box in Fig. 5B) is observed when increasing the field. In prior work, such a current-dependent suppression of the Hall resistance has been explained by the progressive decrease of the topological Hall resistance. The current-induced skyrmion motion is expected to cause an “emergent” electric field perpendicular to the direction of motion, which opposes the topological Hall field, leading to a reduction of the measured topological Hall resistance (48–50).

The topological Hall curve (see Methods) was calculated as shown in Fig. 5C. Using the peak value of the ρ^{THE} in Fig. 5C as a representative measure of the topological Hall component, its dependence on the current density, i.e., the differential topological Hall resistivity $|\Delta\rho^{\text{THE}}|$, was studied. This current density dependence of the $|\Delta\rho^{\text{THE}}|$ is shown in Fig. 5D. Focusing on the data plotted in red circles, one can see that below the threshold current density, j_{th} , of $\sim 1 \times 10^6$ A/cm² for skyrmion motion, the stationary skyrmions are pinned by defects, and therefore, the topological

Hall resistivity remains constant. Above j_{th} , the skyrmion starts to move, and the topological Hall resistivity decreases. Further increases in the current density do not significantly change $\Delta\rho^{\text{THE}}$. From this, the skyrmion drift velocity (v) can be estimated to be ~ 35.4 m/s at $j \sim 4.76 \times 10^6$ A/cm² (49) (see fig. S15 and section S2 for the details of this calculation).

When decreasing the field from saturation (labeled by a green arrow in Fig. 5A and a green box in Fig. 5B), there is no skyrmion phase from the L(S)TEM measurements. The sharp peak exhibits a positive value, similar to that in the increasing field regime. The sharp kink is not induced by a topological Hall effect associated with the skyrmions but by a different nucleation process (see Fig. 1C). As the current density increases, the sign of the resistivity in the peak position reverses and the absolute value is close to that when the field increases starting from zero (red circles) (Fig. 5D). This indicates that the skyrmion lattice can be induced by the applied current and the skyrmion density increases with increasing current density, as expected from $|\rho^{\text{THE}}| \propto n_{\text{sk}}$ (skyrmion density) (51).

To further probe the skyrmion dynamics, second-harmonic Hall measurements were performed. In a noncentrosymmetric ferromagnet (52, 53), the electrical resistance generally depends on the current and magnetic field direction (54) and thus a nonreciprocal magnetotransport signature is anticipated, originating from an emergent electromagnetic field induced by skyrmion motion (52). The spin dynamics of the vortex-like domain can be deduced by the phase diagram as a function of the second-harmonic resistance and the current density, where three distinct regimes were identified (52): (i) $j < j_{\text{th}}$ (threshold current density), the real part of the second-harmonic resistance ($\text{Re } R_{xy}^{2\omega}$) is essentially zero, which indicates that the skyrmion lattice is stationary; (ii) $j_{\text{th}} < j < j_{\text{CO}}$ (a crossover current density), the $\text{Re } R_{xy}^{2\omega}$ monotonically increases because of the disordered motion of the skyrmion lattice; and (iii) $j_0 > j_{\text{CO}}$, the $\text{Re } R_{xy}^{2\omega}$ decreases, the lattice state turns into a dynamical reordering due to the relative reduction of the pinning force at large current densities. Figure 5F shows the typical profiles of the second-harmonic

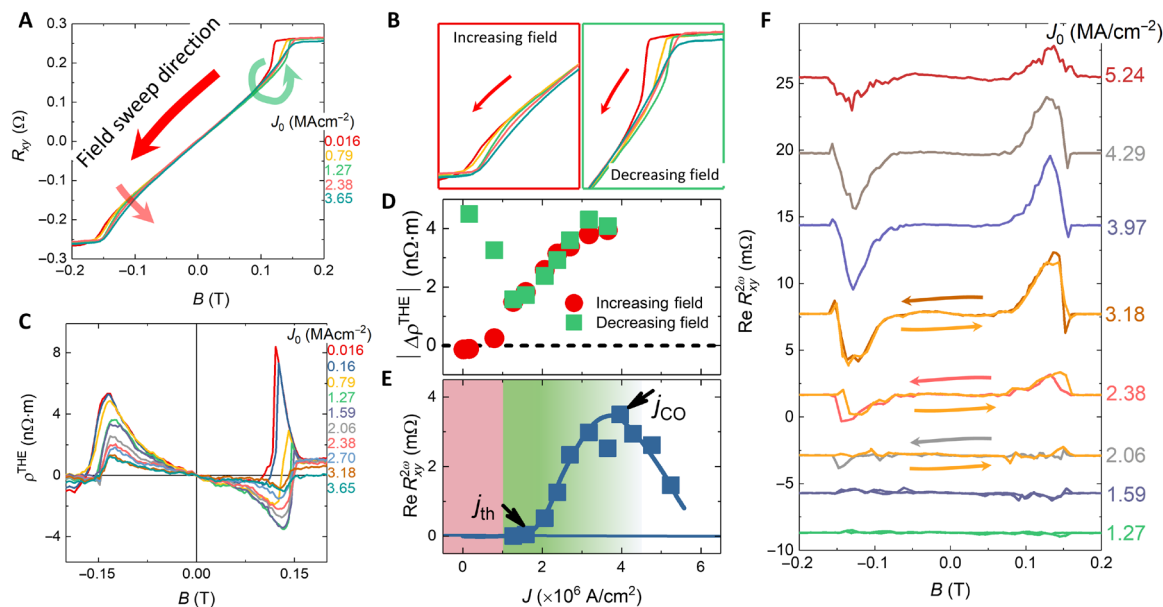


Fig. 5. Room-temperature current-driven spin dynamics of skyrmions of FCGT nanoflake. (A) Hall measurements at various current densities. (B) Zoom-in of the Hall curve near saturated field. (C) Magnetic field dependence of topological Hall resistivity at various current densities. Current density dependence of $|\Delta\rho^{\text{THE}}|$ (D) and $\text{Re } R_{xy}^{2\omega}$ (E). (F) Magnetic field-dependent $\text{Re } R_{xy}^{2\omega}$ at various current densities.

Hall effect measured at various current densities. The magnitude of $\text{Re } R_{xy}^{2\omega}$ measured with $j_0 = 1.27 \times 10^6 \text{ A/cm}^2$ is small and below the noise floor of the measurements. As the current density reaches $2.06 \times 10^6 \text{ A/cm}^2$, a peak occurs when increasing the field from zero, while $\text{Re } R_{xy}^{2\omega}$ is almost zero when decreasing the field from a saturated state. This indicates that the skyrmion motion when increasing the fields from zero exhibits a low j_{th} . In contrast, the back-and-forth curve overlaps well once the measured current density is raised up to $j = 2.4 \times 10^6 \text{ A/cm}^2$, indicating that the skyrmion dynamics are similar for both increasing and decreasing fields. The j_{th} is $\sim 2.06 \times 10^6 \text{ A/cm}^2$, which is also in agreement with the topological Hall effect results. When the current density is higher than j_{CO} ($3.97 \times 10^6 \text{ A/cm}^2$), $\text{Re } R_{xy}^{2\omega}$ begins to decrease. Figure 5E shows a room-temperature phase diagram as a function of current density and $\text{Re } R_{xy}^{2\omega}$ at peak position. The threshold current density for skyrmion lattice motion at room temperature in the FCGT system is smaller than for a traditional ferromagnetic metal (13, 55–58).

Phase diagram

Figure 6A exhibits magnetic field-dependent $\text{Re } R_{xy}^{2\omega}$ in the FCGT nanoflake with current densities $j_0 = 3.7 \times 10^6 \text{ A/cm}^2$ at various temperatures. Above 340 K, no measurable signal was observed, which is consistent with the temperature-dependent MFM measurements. A strong peak occurs at the temperature range of 270 to 340 K, which indicates that the skyrmion lattice can be stabilized in this temperature regime. As the temperature further decreases, the peak intensity abruptly decreases and hints at the existence of a few isolated skyrmions. This result is further confirmed by the field dependence of MFM measurements at 200 K (see Fig. 6B and fig. S16). At zero field, the MFM image shows a labyrinthine stripe domain structure with equal populations of domains with opposite magnetization; these stripes also show some small branches. With increasing magnetic field, the antiparallel stripe domains reverse one by one

rather than by breaking into bubbles. The PMA in the FCGT system rapidly increases as the temperature is decreased and plays a more dominant role compared to the DMI constant and A (59). A strong PMA helps in decreasing the skyrmion density (60), and thus, no skyrmion lattice phase was observed at 200 K under any magnetic field. Last, Fig. 6C compiles the phase stability diagram for the FCGT system as a function of temperature (T) and magnetic field (B).

In summary, we have demonstrated that the AA'-stacked FCGT is a new class of room-temperature Néel-type skyrmion hosting material with C_{6v} symmetry and that skyrmion lattices can be stabilized over a wide range of thickness, magnetic field, and temperature, specifically at zero field and room temperature. The skyrmion lattices can be easily manipulated by the stray field of an MFM tip and current density. Current-induced skyrmion lattice formation and motion were achieved at room temperature. We expect that by subtle tuning of the magnetic parameters using chemical doping, stacking with spin-orbit coupling material, ion radiation, etc., one can achieve small skyrmions with high mobility under a low current density. Therefore, our system provides a promising platform for 2D skyrmion-based logic and memory devices, notably at room temperature.

METHODS

Sample synthesis

Single crystals of $(\text{Fe}_{0.5}\text{Co}_{0.5})_{5-8}\text{GeTe}_2$ were grown by the chemical vapor transfer method. Iodine (I_2) were used as the transport agent to assist the growth of single crystals. Elemental Fe powder (99.99%), Co powder (99.99%), small Ge pieces (99.999%, 1 to 3 mm in size), and Te powder (99.999%) were used for the sample synthesis. The starting raw materials were fully mixed together with the nominal molar ratio $\text{Fe}:\text{Co}:\text{Ge}:\text{Te} = 3:3:1:2$ inside the glovebox. About 30 mg of iodine was added to the mixture. The starting mixture was then

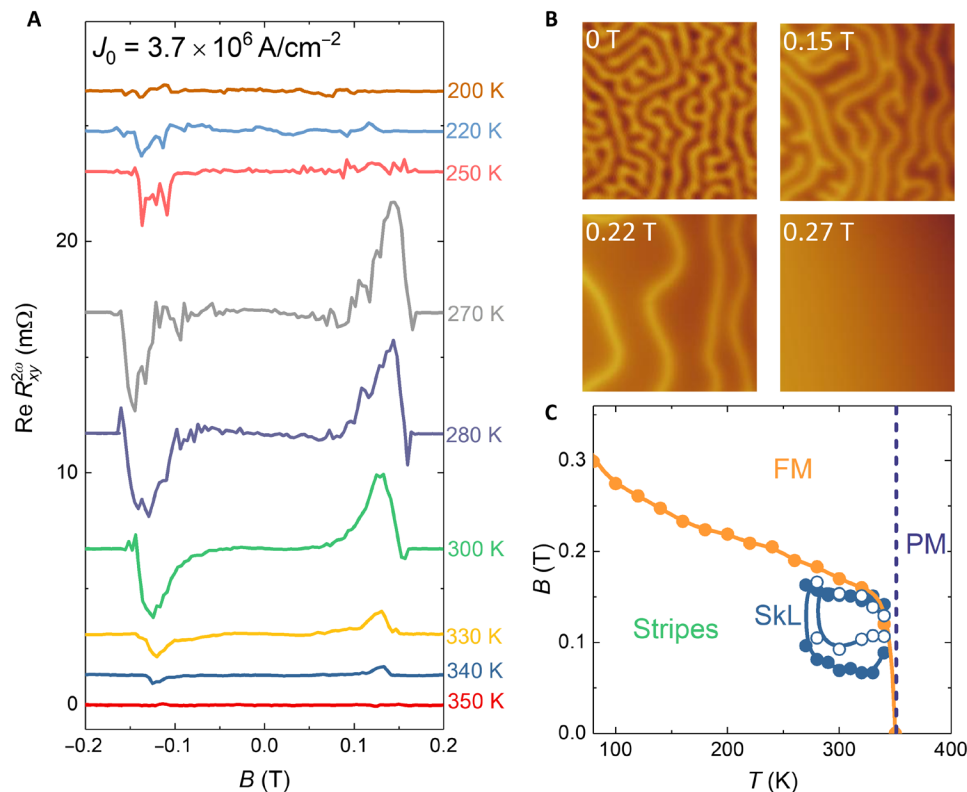


Fig. 6. Phase diagram. (A) Magnetic field dependence of the real part of second-harmonic Hall resistance at various temperatures. (B) MFM images on a 261-nm nano-flake were taken in 0, 0.15, 0.22, and 0.27 T at 200 K, respectively. The color scales of MFM images are 1.6, 5.5, 6, and 0.2 Hz, respectively. The size of the images is $5 \mu\text{m}$ by $5 \mu\text{m}$. The lift height is 150 nm. (C) Phase diagram of FCGT as a function of temperature and magnetic field obtained in 136-nm-thick nanoflakes. The blue, green, yellow, and purple areas represent skyrmion lattice (SkL), stripe, ferromagnetic (FM), and paramagnetic phases (PM), respectively. The solid and empty circles correspond to the results of the second-harmonic Hall resistance measured by 3.7×10^6 and $2.7 \times 10^6 \text{ A/cm}^2$, respectively.

vacuumed, back-filled with one-third volume of argon, and sealed inside the quartz tube with an inner diameter of 8 mm, an outer diameter of 12 mm, and a length of about 150 mm. The sealed quartz tube was placed horizontally inside a muffle furnace during the growth. The reaction temperature was set to 750°C under isothermal conditions for up to 7 or 10 days. Small single crystals were harvested by quenching the furnace at 750°C in air. Excess iodine was removed from the surfaces of the single crystals with ethanol.

Scanning transmission electron microscopy

Cross-sectional TEM specimens were prepared on the FCGT nanoflakes, using a Thermo Fisher Helios G4 UX focused ion beam with a Ga^+ ion beam of 30 and 5 keV, and followed by a final milling step of 2 keV to reduce damage. To protect the surface from ion beam damage, we deposited carbon and platinum layers before milling. The thickness of the cross-sectional TEM specimen was determined to be $\sim 10 \text{ nm}$ by convergent beam electron diffraction analysis. HAADF-STEM images were acquired by using a Cs-corrected FEI Titan operated at 300 keV, with a beam semiconvergence angle of 21.4 mrad and a beam current of 10 pA.

The atomic-resolution energy-dispersive x-ray spectroscopy (EDS) mapping was acquired with a Thermo Fisher Scientific “Kraken” Spectra 300 operated at 120 kV equipped with Dual-X EDS detectors with a collection solid angle of 1.76 sr. The STEM-EDS maps were acquired with a probe current of 120 pA and a semiconvergence angle of 30 mrad, continuously raster-scanned with drift correction with

a dwell time of $2 \mu\text{s}$ and over a total acquisition time of ~ 4 hours. The specimen thickness was $\sim 10 \text{ nm}$ estimated by convergent beam electron diffraction analysis. The elemental maps were first obtained by fitting the peak intensities above the background with the Cliff-Lorimer method. Nonlocal principal components analysis was used to reduce the Poisson noise in the obtained EDS elemental maps, which further revealed the low-frequency details of atomic features (61).

Micromagnetic simulation

Micromagnetic simulations were performed using the graphical processing unit-accelerated finite mesh package MuMax3 (62). To reproduce the experimentally observed spin textures, simulations were run over a phase space of material parameters close to the experimentally measured values. The parameter scans are presented in Fig. 4 as mosaics where each tile is a $1 \mu\text{m}$ by $1 \mu\text{m}$ rendering of the z component of magnetization from a single simulation.

Simulations incorporated the dipole-dipole interaction and finite temperature. Periodic boundary conditions were used because the simulated area $1 \mu\text{m}$ by $1 \mu\text{m}$ is smaller than the actual sample. The parameters in the Hamiltonian are exchange constant A , first-order uniaxial anisotropy K , saturation magnetization M_s , and interfacial DMI constant D . The cell size of 3.9 nm by 3.9 nm by 3.1 nm is below the exchange length $l_{\text{ex}} = \sqrt{\frac{2A}{\mu_0 M_s^2}} \sim 9.8 \text{ nm}$.

Figure 2H explores the Kittel effect in terms of skyrmion diameter dependence on sample thickness at zero field. The simulation area is $1 \mu\text{m}$ by $1 \mu\text{m}$ by (100 to 900) nm. A cell size of 3.9 nm by

3.9 nm by 3.1 nm is used. In these simulations $A = 4 \times 10^{-12}$ J/m, $K = 0.24 \times 10^6$ J/m³, $D = 0.9$ mJ/m², $M_s = 301$ kA/m, and $T = 293$ K. The M_s and K_u are estimated by the isothermal magnetization curves of the bulk FCGT at room temperature. The simulation is initialized in a skyrmion lattice state with a skyrmion diameter of 60 nm. The initial state is relaxed using the MuMax3 standard relax function. The simulation is then advanced using a time evolver for 10 ns to incorporate thermal effects.

Figure 4 explores the phase space of spin textures over varying material parameters. In Fig. 4, the simulation area is 1 μm by 1 μm by 200 nm. A cell size of 3.9 nm by 3.9 nm by 3.1 nm is used. In these simulations, $A = (2 \times 10^{-12}$ to $7 \times 10^{-12})$ J/m, $K = (0.0 \times 10^6$ to $0.4 \times 10^6)$ J/m³, $D = (0.5$ to $1.5)$ mJ/m², $M_s = 301$ kA/m, and $T = 293$ K. When held constant, $A = 4 \times 10^{-12}$ J/m and $K = 0.24 \times 10^6$ J/m³. The simulation is initialized in a random state with a 100-mT magnetic field oriented along the normal axis. The initial state is relaxed using the MuMax3 standard relax function. The field is then removed, and the simulation is advanced using a time evolver for 10 ns to reach the zero-field state and incorporate thermal effects.

Figure S11 explores the phase space of spin textures over varying material parameters and sample thicknesses. In fig. S11, the simulation area is 1 μm by 1 μm by (50 to 200) nm. A cell size of 3.9 nm by 3.9 nm by 3.1 nm is used. In these simulations, $A = (2 \times 10^{-12}$ to $7 \times 10^{-12})$ J/m, $K = (0.0 \times 10^6$ to $0.4 \times 10^6)$ J/m³, $D = (0.7$ to $1.4)$ mJ/m², $M_s = 301$ kA/m, and $T = 293$ K. When held constant, $A = 4 \times 10^{-12}$ J/m and $K = 0.24 \times 10^6$ J/m³. The simulation is initialized in a random state with a 100-mT magnetic field oriented along the normal axis. The initial state is relaxed in the applied field using the MuMax3 standard relax function. The field is then removed, and the simulation is advanced using a time evolver for 10 ns to reach the zero-field state and incorporate thermal effects.

MFM measurement

The thickness-dependent room-temperature MFM measurements were performed using an Asylum Research MFP-3D system. The MFM images (color bar, yellow and blue) were measured by typical tapping/lift mode. The lift height is fixed at 100 nm for scanning nanoflakes of thickness above 100 nm to reduce the influence of stray fields created by the MFM tips.

The temperature-dependent MFM measurements (Figs. 3 and 6B and fig. S16) (color bar, brown and white) were performed in a homebuilt variable-temperature MFM (Rutgers University) using commercial piezoresistive cantilevers with a spring constant $k \sim 3$ N/m and a resonant frequency $f_0 \sim 43$ kHz. The tips were coated with nominally 100-nm Co by using magnetron sputtering. The MFM signal (the shift of resonant frequency) is proportional to the out-of-plane stray field gradient, which was extracted by a phase-locked loop (SPECS). MFM images were taken with constant-height noncontact mode. The magnetic field was applied by clamping two permanent magnets on the side of MFM probe. The north poles of two magnets face each other to generate an out-of-plane field (max, ~ 0.04 T) with a tiny in-plane field component (< 0.003 T) due to misalignment, calibrated by a gauss meter. The cryogenic MFM measurements were performed inside a superconducting magnet.

Transport measurement

FCGT nanoflakes were exfoliated onto SiO₂/Si substrates using a scotch tape. Polymethyl methacrylate (PMMA) is spin-coated on the substrate, and then e-beam lithography is used to pattern the samples.

After development in a commercial solution (KAYAKU MIBK/IPA 1:3), we deposit 3-nm Cr/100-nm Au to form electrodes by means of e-beam evaporation. Acetone eventually removes the PMMA resist and the residual Cr/Au. Following the abovementioned process, high-quality Hall bar devices were fabricated on the basis of FCGT nanoflakes.

Magnetoresistance and Hall resistance were performed in a cryogen-free measurement system from Cryogenic Ltd. with the applied DC currents of 100 μA . The skyrmion dynamic measurements were obtained using the standard lock-in technique (SR-830, Stanford Research Systems) with AC modulated at 23 Hz. Given the increase in sample temperature owing to Joule heating, we did not use the temperature controller from the transport measurement system to monitor the temperature of the samples. We derived the temperature from the longitudinal resistance of the nanoflake sample itself and adjusted the environment temperature of the sample so that the sample temperature remained at room temperature. The topological Hall resistivity can be derived from the Hall resistance and isothermal magnetization curve; however, the magnetization of nanoflake is too small to measure via bulk magnetic characterization. Therefore, to obtain a rough estimate of the topological Hall resistance, we assume that the topological Hall resistivity is negligible under a large current density ($\sim 4 \times 10^6$ A/cm²). Under this assumption, the topological Hall resistivity can be estimated as the difference between the Hall resistivity under the measured current density and saturated current density.

SUPPLEMENTARY MATERIALS

Supplementary material for this article is available at <https://science.org/doi/10.1126/sciadv.abm7103>

REFERENCES AND NOTES

1. K. F. Mak, J. Shan, D. C. Ralph, Probing and controlling magnetic states in 2D layered magnetic materials. *Nat. Rev. Phys.* **1**, 646–661 (2019).
2. K. S. Burch, D. Mandrus, J.-G. Park, Magnetism in two-dimensional van der Waals materials. *Nature* **563**, 47–52 (2018).
3. Y. Deng, Y. Yu, Y. Song, J. Zhang, N. Z. Wang, Z. Sun, Y. Yi, Y. Z. Wu, S. Wu, J. Zhu, J. Wang, X. H. Chen, Y. Zhang, Gate-tunable room-temperature ferromagnetism in two-dimensional Fe₃GeTe₂. *Nature* **563**, 94–99 (2018).
4. Z. Fei, B. Huang, P. Malinowski, W. Wang, T. Song, J. Sanchez, W. Yao, D. Xiao, X. Zhu, A. F. May, W. Wu, D. H. Cobden, J. H. Chu, X. Xu, Two-dimensional itinerant ferromagnetism in atomically thin Fe₃GeTe₂. *Nat. Mater.* **17**, 778–782 (2018).
5. M. Gibertini, M. Koperski, A. F. Morpurgo, K. S. Novoselov, Magnetic 2D materials and heterostructures. *Nat. Nanotech.* **14**, 408–419 (2019).
6. S. Mühlbauer, B. Binz, F. Jonietz, C. Pfleiderer, A. Rosch, A. Neubauer, R. Georgii, P. Boni, Skyrmion lattice in a chiral magnet. *Science* **323**, 915–919 (2009).
7. X. Z. Yu, Y. Onose, N. Kanazawa, J. H. Park, J. H. Han, Y. Matsui, N. Nagaosa, Y. Tokura, Real-space observation of a two-dimensional skyrmion crystal. *Nature* **465**, 901–904 (2010).
8. K. Karube, J. S. White, N. Reynolds, J. L. Gavilano, H. Oike, A. Kikkawa, F. Kagawa, Y. Tokunaga, H. M. Ronnow, Y. Tokura, Y. Taguchi, Robust metastable skyrmions and their triangular-square lattice structural transition in a high-temperature chiral magnet. *Nat. Mater.* **15**, 1237–1242 (2016).
9. I. Kezsmarki, S. Bordacs, P. Milder, E. Neuber, L. M. Eng, J. S. White, H. M. Ronnow, C. D. Dewhurst, M. Mochizuki, K. Yanai, H. Nakamura, D. Ehlers, V. Tsurkan, A. Loidl, Néel-type skyrmion lattice with confined orientation in the polar magnetic semiconductor GaV₄S₈. *Nat. Mater.* **14**, 1116–1122 (2015).
10. T. Kurumaji, T. Nakajima, V. Ukleev, A. Feoktystov, T. H. Arima, K. Kakurai, Y. Tokura, Néel-Type skyrmion lattice in the tetragonal polar magnet VOSe₂O₅. *Phys. Rev. Lett.* **119**, 237201 (2017).
11. S. Heinze, K. von Bergmann, M. Menzel, J. Brede, A. Kubetzka, R. Wiesendanger, G. Bihlmayer, S. Blügel, Spontaneous atomic-scale magnetic skyrmion lattice in two dimensions. *Nat. Phys.* **7**, 713–718 (2011).
12. N. Romming, C. Hanneken, M. Menzel, J. E. Bickel, B. Wolter, K. von Bergmann, A. Kubetzka, R. Wiesendanger, Writing and deleting single magnetic skyrmions. *Science* **341**, 636–639 (2013).

13. S. Woo, K. Litzius, B. Krüger, M. Y. Im, L. Caretta, K. Richter, M. Mann, A. Krone, R. M. Reeve, M. Weigand, P. Agrawal, I. Lemesch, M. A. Mawass, P. Fischer, M. Kläui, G. S. D. Beach, Observation of room-temperature magnetic skyrmions and their current-driven dynamics in ultrathin metallic ferromagnets. *Nat. Mater.* **15**, 501–506 (2016).
14. R. Chen, Y. Gao, X. Zhang, R. Zhang, S. Yin, X. Chen, X. Zhou, Y. Zhou, J. Xia, Y. Zhou, S. Wang, F. Pan, Y. Zhang, C. Song, Realization of isolated and high-density skyrmions at room temperature in uncompensated synthetic antiferromagnets. *Nano Lett.* **20**, 3299–3305 (2020).
15. B. Ding, Z. Li, G. Xu, H. Li, Z. Hou, E. Liu, X. Xi, F. Xu, Y. Yao, W. Wang, Observation of magnetic skyrmion bubbles in a van der Waals ferromagnet Fe₃GeTe₂. *Nano Lett.* **20**, 868–873 (2020).
16. M.-G. Han, J. A. Garlow, Y. Liu, H. Zhang, J. Li, D. DiMarzio, M. W. Knight, C. Petrovic, D. Jariwala, Y. Zhu, Topological magnetic-spin textures in two-dimensional van der Waals Cr₂Ge₂Te₆. *Nano Lett.* **19**, 7859–7865 (2019).
17. Y. Wu, S. Zhang, J. Zhang, W. Wang, Y. L. Zhu, J. Hu, G. Yin, K. Wong, C. Fang, C. Wan, X. Han, Q. Shao, T. Taniguchi, K. Watanabe, J. Zang, Z. Mao, X. Zhang, K. L. Wang, Néel-type skyrmion in WTe₂/Fe₃GeTe₂ van der Waals heterostructure. *Nat. Commun.* **11**, 3860 (2020).
18. T.-E. Park, L. Peng, J. Liang, A. Hallal, F. S. Yasin, X. Zhang, K. M. Song, S. J. Kim, K. Kim, M. Weigand, G. Schütz, S. Finizio, J. Raabe, K. Garcia, J. Xia, Y. Zhou, M. Ezawa, X. Liu, J. Chang, H. C. Koo, Y. D. Kim, M. Chshiev, A. Fert, H. Yang, X. Yu, S. Woo, Néel-type skyrmions and their current-induced motion in van der Waals ferromagnet-based heterostructures. *Phys. Rev. B* **103**, 104410 (2021).
19. M. Yang, Q. Li, R. V. Chopdekar, R. Dhall, J. Turner, J. D. Carlström, C. Ophus, C. Klewe, P. Shafer, A. T. N'Diaye, J. W. Choi, G. Chen, Y. Z. Wu, C. Hwang, F. Wang, Z. Q. Qiu, Creation of skyrmions in van der Waals ferromagnet Fe₃GeTe₂ on (Co/Pd)_n superlattice. *Sci. Adv.* **6**, eabb5157 (2020).
20. A. F. May, D. Ovchinnikov, Q. Zheng, R. Hermann, S. Calder, B. Huang, Z. Fei, Y. Liu, X. Xu, M. A. McGuire, Ferromagnetism near room temperature in the cleavable van der Waals crystal Fe₃GeTe₂. *ACS Nano* **13**, 4436–4442 (2019).
21. H. Zhang, R. Chen, K. Zhai, X. Chen, L. Caretta, X. Huang, R. V. Chopdekar, J. Cao, J. Sun, J. Yao, R. Birgeneau, R. Ramesh, Itinerant ferromagnetism in van der Waals Fe_{3-x}GeTe₂ crystals above room temperature. *Phys. Rev. B* **102**, 064417 (2020).
22. A. F. May, M.-H. Du, V. R. Cooper, M. A. McGuire, Tuning magnetic order in the van der Waals metal Fe₃GeTe₂ by cobalt substitution. *Phys. Rev. Mater.* **4**, 074008 (2020).
23. C. Tian, F. Pan, S. Xu, K. Ai, T. Xia, P. Cheng, Tunable magnetic properties in van der Waals crystals (Fe_{1-x}Co_x)₅GeTe₂. *Appl. Phys. Lett.* **116**, 202402 (2020).
24. H.-J. Deiseroth, K. Aleksandrov, C. Reiner, L. Kienle, R. K. Kremer, Fe₃GeTe₂ and Ni₃GeTe₂ – Two new layered transition-metal compounds: Crystal structures, HRTEM investigations, and magnetic and electrical properties. *Eur. J. Inorg. Chem.* **2006**, 1561–1567 (2006).
25. J. Seo, D. Y. Kim, E. S. An, K. Kim, G.-Y. Kim, S.-Y. Hwang, D. W. Kim, B. G. Jang, H. Kim, G. Eom, S. Y. Seo, R. Stania, M. Muntwiler, J. Lee, K. Watanabe, T. Taniguchi, Y. J. Jo, J. Lee, B. I. Min, M. H. Jo, H. W. Yeom, S.-Y. Choi, J. H. Shim, J. S. Kim, Nearly room temperature ferromagnetism in a magnetic metal-rich van der Waals metal. *Sci. Adv.* **6**, eaay8912 (2020).
26. S. Laref, K.-W. Kim, A. Manchon, Elusive Dzyaloshinskii-Moriya interaction in monolayer Fe₃GeTe₂. *Phys. Rev. B* **102**, 060402 (2020).
27. T. Moriya, Anisotropic superexchange interaction and weak ferromagnetism. *Phys. Rev.* **120**, 91–98 (1960).
28. A. N. Bogdanov, D. A. Yablonskii, Thermodynamically stable ‘vortices’ in magnetically ordered crystals. The mixed state of magnets. *Zh. Eksp. Teor. Fiz.* **95**, 178–182 (1989).
29. A. N. Bogdanov, A. Hubert, The properties of isolated magnetic vortices. *Phys. Stat. Sol.* **186**, 527–543 (1994).
30. M. J. Benitez, A. Hrabec, A. P. Mihai, T. A. Moore, G. Burnell, D. McGrouther, C. H. Marrows, S. McVitie, Magnetic microscopy and topological stability of homochiral Néel domain walls in a Pt/Co/AlO_x trilayer. *Nat. Commun.* **6**, 8957 (2015).
31. S. D. Pollard, J. A. Garlow, J. Yu, Z. Wang, Y. Zhu, H. Yang, Observation of stable Néel skyrmions in cobalt/palladium multilayers with Lorentz transmission electron microscopy. *Nat. Commun.* **8**, 14761 (2017).
32. R. Streubel, C. H. Lambert, N. Kent, P. Ercius, A. T. N'Diaye, C. Ophus, S. Salahuddin, P. Fischer, Experimental evidence of chiral ferrimagnetism in amorphous GdCo films. *Adv. Mater.* **30**, 1800199 (2018).
33. M. W. Tate, P. Purohit, D. Chamberlain, K. X. Nguyen, R. Hovden, C. S. Chang, P. Deb, E. Turgut, J. T. Heron, D. G. Schlom, D. C. Ralph, G. D. Fuchs, K. S. Shanks, H. T. Philipp, D. A. Muller, S. M. Gruner, High dynamic range pixel array detector for scanning transmission electron microscopy. *Microsc. Microanal.* **22**, 237–249 (2016).
34. T. Denneulin, J. Caron, M. Hoffmann, M. Lin, H. K. Tan, A. Kovacs, S. Blügel, R. E. Dunin-Borkowski, Off-axis electron holography of Néel-type skyrmions in multilayers of heavy metals and ferromagnets. *Ultramicroscopy* **220**, 113155 (2021).
35. X. Z. Yu, N. Kanazawa, Y. Onose, K. Kimoto, W. Z. Zhang, S. Ishiwata, Y. Matsui, Y. Tokura, Near room-temperature formation of a skyrmion crystal in thin-films of the helimagnet FeGe. *Nat. Mater.* **10**, 106–109 (2011).
36. F. Zheng, F. N. Rybakov, A. B. Borisov, D. Song, S. Wang, Z. A. Li, H. du, N. S. Kiselev, J. Caron, A. Kovács, M. Tian, Y. Zhang, S. Blügel, R. E. Dunin-Borkowski, Experimental observation of chiral magnetic bobs in B20-type FeGe. *Nat. Nanotech.* **13**, 451–455 (2018).
37. A. K. Srivastava, P. Devi, A. K. Sharma, T. Ma, H. Deniz, H. L. Meyerheim, C. Felser, S. S. P. Parkin, Observation of robust Néel skyrmions in metallic PtMnGa. *Adv. Mater.* **32**, 1904327 (2020).
38. M. Bačani, M. A. Marioni, J. Schwenk, H. J. Hug, How to measure the local Dzyaloshinskii-Moriya interaction in skyrmion thin-film multilayers. *Sci. Rep.* **9**, 3114 (2019).
39. Y. Guang, I. Bykova, Y. Liu, G. Yu, E. Goering, M. Weigand, J. Gräfe, S. K. Kim, J. Zhang, H. Zhang, Z. Yan, C. Wan, J. Feng, X. Wang, C. Guo, H. Wei, Y. Peng, Y. Tserkovnyak, X. Han, G. Schütz, Creating zero-field skyrmions in exchange-biased multilayers through X-ray illumination. *Nat. Commun.* **11**, 949 (2020).
40. S. Zhang, J. Zhang, Q. Zhang, C. Barton, V. Neu, Y. Zhao, Z. Hou, Y. Wen, C. Gong, O. Kazakova, W. Wang, Y. Peng, D. A. Garanin, E. M. Chudnovsky, X. Zhang, Direct writing of room temperature and zero field skyrmion lattices by a scanning local magnetic field. *Appl. Phys. Lett.* **112**, 132405 (2018).
41. A. V. Ognev, A. G. Kolesnikov, Y. J. Kim, I. H. Cha, A. V. Sadovnikov, S. A. Nikitov, I. V. Soldatov, A. Talapatra, J. Mohanty, M. Mruczkiewicz, Y. Ge, N. Kerber, F. Dittrich, P. Virnau, M. Kläui, Y. K. Kim, A. S. Samardak, Magnetic direct-write skyrmion nanolithography. *ACS Nano* **14**, 14960–14970 (2020).
42. H. Oike, A. Kikkawa, N. Kanazawa, Y. Taguchi, M. Kawasaki, Y. Tokura, F. Kagawa, Interplay between topological and thermodynamic stability in a metastable magnetic skyrmion lattice. *Nat. Phys.* **12**, 62–66 (2016).
43. I. Lemesch, K. Litzius, M. Böttcher, P. Bassirian, N. Kerber, D. Heinze, J. Závorka, F. Büttner, L. Caretta, M. Mann, M. Weigand, S. Finizio, J. Raabe, M. Y. Im, H. Stoll, G. Schütz, B. Dupé, M. Kläui, G. S. D. Beach, Current-induced skyrmion generation through morphological thermal transitions in chiral ferromagnetic heterostructures. *Adv. Mater.* **30**, 1805461 (2018).
44. Z. Wang, M. Guo, H. A. Zhou, L. Zhao, T. Xu, R. Tomasello, H. Bai, Y. Dong, S. G. Je, W. Chao, H. S. Han, S. Lee, K. S. Lee, Y. Yao, W. Han, C. Song, H. Wu, M. Carpentieri, G. Finocchio, M. Y. Im, S. Z. Lin, W. Jiang, Thermal generation, manipulation and thermoelectric detection of skyrmions. *Nat. Electron.* **3**, 672–679 (2020).
45. A. Casiraghi, H. Corte-León, M. Vafeas, F. Garcia-Sanchez, G. Durin, M. Pasquale, G. Jakob, M. Kläui, O. Kazakova, Individual skyrmion manipulation by local magnetic field gradients. *Commun. Phys.* **2**, 145 (2019).
46. A. P. Malozemoff, J. C. Slonczewski, *Magnetic Domain Walls in Bubble Materials: Advances in Materials and Device Research* (Academic Press, 2016), vol. 1.
47. W. Wang, M. W. Daniels, Z. Liao, Y. Zhao, J. Wang, G. Koster, G. Rijnders, C. Z. Chang, D. Xiao, W. Wu, Spin chirality fluctuation in two-dimensional ferromagnets with perpendicular magnetic anisotropy. *Nat. Mater.* **18**, 1054–1059 (2019).
48. T. Schulz, R. Ritz, A. Bauer, M. Halder, M. Wagner, C. Franz, C. Pfleiderer, K. Everschor, M. Garst, A. Rosch, Emergent electrostatics of skyrmions in a chiral magnet. *Nat. Phys.* **8**, 301–304 (2012).
49. D. Liang, J. P. DeGrave, M. J. Stolt, Y. Tokura, S. Jin, Current-driven dynamics of skyrmions stabilized in MnSi nanowires revealed by topological Hall effect. *Nat. Commun.* **6**, 8217 (2015).
50. J. Zang, M. Mostovoy, J. H. Han, N. Nagaosa, Dynamics of skyrmion crystals in metallic thin films. *Phys. Rev. Lett.* **107**, 136804 (2011).
51. M. Raju, A. Yagil, A. Soumyanarayanan, A. K. C. Tan, A. Almoalem, F. Ma, O. M. Auslaender, C. Panagopoulos, The evolution of skyrmions in Ir/Fe/Co/Pt multilayers and their topological Hall signature. *Nat. Commun.* **10**, 696 (2019).
52. T. Yokouchi, S. Hoshino, N. Kanazawa, A. Kikkawa, D. Morikawa, K. Shibata, T.-H. Arima, Y. Taguchi, F. Kagawa, N. Nagaosa, Y. Tokura, Current-induced dynamics of skyrmion strings. *Sci. Adv.* **4**, eaat1115 (2018).
53. R. Aoki, Y. Kousaka, Y. Togawa, Anomalous nonreciprocal electrical transport on chiral magnetic order. *Phys. Rev. Lett.* **122**, 057206 (2019).
54. Y. Tokura, N. Nagaosa, Nonreciprocal responses from non-centrosymmetric quantum materials. *Nat. Commun.* **9**, 3740 (2018).
55. S. S. P. Parkin, M. Hayashi, L. Thomas, Magnetic domain-wall racetrack memory. *Science* **320**, 190–194 (2008).
56. W. Legrand, D. Maccariello, N. Reyren, K. Garcia, C. Moutafis, C. Moreau-Luchaire, S. Collin, K. Bouzehouane, V. Cros, A. Fert, Room-temperature current-induced generation and motion of sub-100 nm skyrmions. *Nano Lett.* **17**, 2703–2712 (2017).
57. R. Juge, S. G. Je, D. S. Chaves, L. D. Buda-Prejbeanu, J. Peña-García, J. Nath, I. M. Miron, K. G. Rana, L. Aballe, M. Foerster, F. Genuzio, T. O. Menteş, A. Locatelli, F. Maccheronzi, S. S. Dhesi, M. Belmeguenai, Y. Roussigné, S. Auffret, S. Pizzini, G. Gaudin, J. Vogel, O. Boulle, Current-driven skyrmion dynamics and drive-dependent skyrmion Hall effect in an ultrathin film. *Phys. Rev. Appl.* **12**, 044007 (2019).
58. K. Litzius, J. Leliaert, P. Bassirian, D. Rodrigues, S. Kromin, I. Lemesch, J. Závorka, K. J. Lee, J. Mulkers, N. Kerber, D. Heinze, N. Keil, R. M. Reeve, M. Weigand, B. van Waeyenberge,

- G. Schütz, K. Everschor-Sitte, G. S. D. Beach, M. Kläui, The role of temperature and drive current in skyrmion dynamics. *Nat. Electron.* **3**, 30–36 (2020).
59. M. Raju, A. P. Petrović, A. Yagil, K. S. Denisov, N. K. Duong, B. Göbel, E. Şaşıoğlu, O. M. Auslaender, I. Mertig, I. V. Rozhansky, C. Panagopoulos, Colossal topological Hall effect at the transition between isolated and lattice-phase interfacial skyrmions. *Nat. Commun.* **12**, 2758 (2021).
60. A. Soumyanarayanan, M. Raju, A. L. Gonzalez Oyarce, A. K. C. Tan, M. Y. Im, A. P. Petrović, P. Ho, K. H. Khoo, M. Tran, C. K. Gan, F. Ernult, C. Panagopoulos, Tunable room-temperature magnetic skyrmions in Ir/Fe/Co/Pt multilayers. *Nat. Mater.* **16**, 898–904 (2017).
61. A. B. Yankovich, C. Zhang, A. Oh, T. J. A. Slater, F. Azough, R. Freer, S. J. Haigh, R. Willett, P. M. Voyles, Non-rigid registration and non-local principle component analysis to improve electron microscopy spectrum images. *Nanotechnology* **27**, 364001 (2016).
62. A. Vansteenkiste, J. Leliaert, M. Dvornik, M. Helsen, F. Garcia-Sanchez, B. van Waeyenberge, The design and verification of MuMax3. *AIP Adv.* **4**, 107133 (2014).
63. Z. Malek, V. Kambersky, On the theory of the domain structure of thin films of magnetically uni-axial materials. *Czech. J. Phys.* **8**, 416–421 (1958).
64. S. Woo, K. M. Song, X. Zhang, Y. Zhou, M. Ezawa, X. Liu, S. Finizio, J. Raabe, N. J. Lee, S. I. Kim, S. Y. Park, Y. Kim, J. Y. Kim, D. Lee, O. J. Lee, J. W. Choi, B. C. Min, H. C. Koo, J. Chang, Current-driven dynamics and inhibition of the skyrmion Hall effect of ferrimagnetic skyrmions in GdFeCo films. *Nat. Commun.* **9**, 959 (2018).
65. M. Mansuripur, Computation of electron diffraction patterns in Lorentz electron microscopy of thin magnetic films. *J. Appl. Phys.* **69**, 2455–2464 (1991).
66. T. Xu, Z. Chen, H. A. Zhou, Z. Wang, Y. Dong, L. Aballe, M. Foerster, P. Gargiani, M. Valvidares, D. M. Bracher, T. Savchenko, A. Kleibert, R. Tomasello, G. Finocchio, S. G. Je, M. Y. Im, D. A. Muller, W. Jiang, Imaging the spin chirality of ferrimagnetic Néel skyrmions stabilized on topological antiferromagnetic Mn₃Sn. *Phys. Rev. Mater.* **5**, 084406 (2021).
67. N. Romming, A. Kubetzka, C. Hanneken, K. von Bergmann, R. Wiesendanger, Field-dependent size and shape of single magnetic skyrmions. *Phys. Rev. Lett.* **114**, 177203 (2015).
68. P. Huang, T. Schönenberger, M. Cantoni, L. Heinen, A. Magrez, A. Rosch, F. Carbone, H. M. Rønnow, Melting of a skyrmion lattice to a skyrmion liquid via a hexatic phase. *Nat. Nanotechnol.* **15**, 761–767 (2020).
69. J. Zázvorka, F. Dittrich, Y. Ge, N. Kerber, K. Raab, T. Winkler, K. Litzius, M. Veis, P. Virnau, M. Kläui, Skyrmion lattice phases in thin film multilayer. *Adv. Funct. Mater.* **30**, 2004037 (2020).

Acknowledgments: We thank C. Y. Zhang for the EDS data processing. **Funding:** H.Z., Y.-T.S., J.T.R., and L.C. are supported by the Department of Defense, Air Force Office of Scientific Research under award FA9550-18-1-0480. X.C., S.S., R.J.B., and R.R. acknowledge support from the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division under contract DE-AC02-05CH11231 [quantum materials program (KC2202)]. R.C. and J.Y. acknowledge the support by Intel Corporation under an award titled Valleytronics center. X.H. is supported by the SRC-ASCENT center, which is part of the SRC-JUMP program. L.C. acknowledges financial support from the University of California Office of the President and the Ford Foundation. The electron microscopy studies were performed at the Cornell Center for Materials Research, a National Science Foundation (NSF) Materials Research Science and Engineering Centers program (DMR-1719875). The Cornell FEI Titan Themis 300 was acquired through NSF-MRI-1429155, with additional support from the Cornell University, the Weill Institute, and the Kavli Institute at Cornell. The devices were fabricated in the University of California Berkeley Marvell Nanofabrication Laboratory. D.R. and P.F. are supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division under contract no. DE-AC02-05-CH11231 (nonequilibrium magnetic materials program MSMAG). This research used the Lawrence computational cluster resource provided by the IT Division at the Lawrence Berkeley National Laboratory, supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under contract no. DE-AC02-05CH11231. The MFM studies at Rutgers are supported by the Office of Basic Energy Sciences, Division of Materials Sciences and Engineering, U.S. Department of Energy under award no. DE-SC0018153. **Author contributions:** H.Z. and R.R. designed the experiments. X.C. synthesized the single crystals. R.C. performed nanoflake preparation, sample transfer, and device fabrication. D.R. performed micromagnetic simulation. Y.-T.C. performed the variable-temperature MFM. H.Z. and X.H. performed the Hall resistance and second-harmonic Hall resistance measurements. H.Z. performed the AFM and MFM measurements at room temperature. Y.-T.S. performed the STEM and L(S)TEM measurements with Z.C. under the supervision of D.A.M. H.Z. and R.R. wrote the manuscript. All authors discussed results and commented on the manuscript. **Competing interests:** The authors declare that they have no competing interests. **Data and materials availability:** All data needed to evaluate the conclusions in the paper are present in the paper and/or the Supplementary Materials.

Submitted 7 October 2021

Accepted 28 January 2022

Published 23 March 2022

10.1126/sciadv.abm7103