

Iron (Fe)-doped mesoporous 45S5 bioactive glasses: Implications for cancer therapy

Farzad Kermani^a, Arghavan Vojdani-Saghir^a, Sahar Mollazadeh Beidokhti^a,
 Simin Nazarnezhad^b, Zahra Mollaei^a, Sepideh Hamzehlou^{c,d}, Ahmed El-Fiqi^e,
 Francesco Baino^f, Saeid Kargozar^{b,*}

^a Department of Materials Engineering, Faculty of Engineering, Ferdowsi University of Mashhad (FUM), Azadi Sq., Mashhad 917794-8564, Iran

^b Tissue Engineering Research Group (TERG), Department of Anatomy and Cell Biology, School of Medicine, Mashhad University of Medical Sciences, Mashhad 917794-8564, Iran

^c Genetics Laboratory, Ghaem Hospital, Mashhad University of Medical Sciences, Mashhad, Iran

^d Hematology/Oncology and Stem Cell Transplantation Research Center, Tehran University of Medical Sciences, Tehran, Iran

^e Glass Research Department, National Research Centre, Cairo 12622, Egypt

^f Institute of Materials Physics and Engineering, Applied Science and Technology Department, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy

ARTICLE INFO

Keywords:

45S5 bioglass
 Mesoporous bioactive glasses (MBGs)
 Cancer treatment
 Fenton's reaction
 Bone tissue engineering

ABSTRACT

The utilization of bioactive glasses (BGs) in cancer therapy has recently become quite promising; herein, a series of Fe-doped mesoporous 45S5-based BGs (MBGs) were synthesized via the sol-gel method in the presence of Pluronic P123 as a soft template. The physico-chemical and biological properties of the prepared glasses were well-characterized through structural assessments, thermal analyses, and electron microscopic studies. Electrochemical analyses, including cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS), were also performed to investigate the actual potential of the Fe₂O₃-containing MBGs in modulating the Fenton's reaction. The XRD results confirmed the glassy state of the Fe-doped samples before immersion in simulated body fluid (SBF). The prepared Fe-doped MBGs exhibited a particle size in the range of 11–86 nm, surface charge of 27–30 mV, S_{BET} of 95–306 m²/g, and M_s of 0.08 to 0.2 emu/g. The incorporation of Fe₂O₃ led to a negligible decrease in the bioactivity of the glasses. The CV analysis indicated that the Fe-doped MBGs could generate H₂O₂ in a cathodic potential higher than -0.2 V (vs. Ag/AgCl) in the O₂-saturated Na₂SO₄ solution. Additionally, the data of the EIS test revealed that the Fe₂O₃-doped MBGs could increase the standard rate constant of Electro-Fenton's (EF) reaction up to 38.44 times as compared with the Fe-free glasses. In conclusion, Fe-doped 45S5-derived glasses may be useful in cancer therapy strategies due to their capability of activating Fenton's reaction and subsequent production of reactive oxygen species (ROS) such as *OH free radicals.

Introduction

Cancer is still the second leading cause of life-threatening human morbidity over the world, with an estimated number of nearly 10 million deaths in 2020 [1–3]. Among different types of cancer, bone tumors (e.g., osteosarcoma) form approximately 5% of childhood and 1% of adults' cancers [4]. Up to date, a huge number of attempts have been made to treat bone cancers, including chemotherapy, radiotherapy, and surgical excision. The mentioned therapeutic strategies have led to the enhanced survival rate of patients; however, novel therapies are required to simultaneously battle against cancer cells and

restore the lost bone tissue [5]. On this matter, designing and developing anticancer biomaterials, under the concept of tissue engineering, hold great promise in the biomedical setting [5,6].

As biocompatible materials, bioactive glasses (BGs) have been extensively applied for managing various bone lesions over the past 50 years. The first developed member of the BG family was a silicate-based glass, the so-called 45S5 (Bioglass®), with the composition of 45% SiO₂, 24.5% Na₂O, 24.5% CaO, and 6% P₂O₅ in weight% [7,8]. There is a long history of successful usage of 45S5 BG in the medical setting; other types and formulations of BGs have been developed over the years for different applications [9]. In fact, the reason for such achievement is

* Corresponding author at: Mashhad University of Medical Sciences, Mashhad, Iran.

E-mail address: kargozarsaeid@gmail.com (S. Kargozar).

<https://doi.org/10.1016/j.tranon.2022.101397>

Received 17 December 2021; Received in revised form 9 March 2022; Accepted 11 March 2022

1936-5233/© 2022 The Authors. Published by Elsevier Inc. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

associated with the excellent characteristics of BGs for hard tissue engineering, including their osteoconductive and osteoinductive properties. More importantly, BGs show a unique feature for regenerative medicine, i.e., their capability of bonding to human tissues, known as “bioactivity.” Over time, specific formulations of biocompatible glasses were developed to further expand and tune their biological properties for specific conditions in the body, such as cancer treatment [10–12]. In this regard, a series of metallic and non-metallic elements can be added to the basic composition of BGs to render anticancer activities [13–15]. For instance, iron (Fe) was successfully incorporated in glasses for rendering osteostimulatory multi-functions, such as improved bone metabolism through enhanced calcification, osteoblast proliferation, as well as apatite-forming ability [16–18]. Notably, Fe also shows significant anticancer activity in its oxide compounds (e.g., Fe₂O₃). In fact, this element may trigger specific chemical reactions (e.g., the Fenton’s reaction) which can eventually lead to tumor cell death.

ROS have widely been studied and utilized in cancer therapy; they comprise both oxygen-related free radicals (e.g., hydroxyl radical (*OH)) and non-radical species (e.g., singlet oxygen (¹O₂)) [19]. Although high amounts of ROS play roles in up-regulating pro-tumorigenic signals and improving tumor proliferation, they can also activate anti-tumorigenic signaling pathways to increase cancer cell death [20]. It has been demonstrated that Fe ions (Fe²⁺/Fe³⁺) under a redox mechanism can increase cancer cell death due to their ability to generate ROS, which is based on transforming less toxic H₂O₂ to cytotoxic *OH [16,21]. Therefore, there has been growing interest in utilizing Fe₂O₃-containing formulations in cancer therapy approaches [21] and, for example, adding Fe oxides to biocompatible glasses and glass-ceramics has become a highly-promising procedure in such kind of biomedical engineering settings [22].

In the present study, we, for the first time, synthesized a series of Fe-doped 45S5-based mesoporous BGs (MBGs) for potential applications in cancer therapy based on triggering Fenton’s reactions. For this aim, we utilized the sol-gel method for producing silicate-based MBGs in which Fe₂O₃ has been added in concentrations of 0, 1, 2.5, 5, and 7.5 mol%. The effects of Fe doping on the physicochemical properties of the glasses were studied through a complete series of tests (e.g., DTA-TG, XRD, FTIR, PSA, Zeta potential, FE-SEM, AFM, and VSM). More importantly, our study highlights the effect of Fe-doped MBGs on the properties and the rate of electro-Fenton’s (EF) reaction using a series of electrochemical analyses involving cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS).

Experimental

Synthesis of Fe-doped glasses

The Fe-doped 45S5-based MBGs were synthesized in a 46.14SiO₂-(26.91-X) CaO-XFe₂O₃-54.4Na₂O-2.55P₂O₅ (X = 0, 1, 2.5, 5, 7.5 mol%) multi-component system (Table 1). For this purpose, appropriate amounts of reagents, including tetraethyl orthosilicate (Si(OC₂H₅)₄, TEOS), Ca(NO₃)₂·4H₂O, Fe(NO₃)₃·9H₂O, NaNO₃, triethyl phosphate ((C₂H₅)₃PO₄, TEP) were defined using HSC chemistry® software (HSC chemistry® 9.4, Outotec, Espo, Finland) to obtain 10 g of each MBG. The reagents were purchased as an analytical grade substances (Sigma-Aldrich, USA). Experimentally, 2 g of P123 (EO20-PO70-EO20, M_w =

Table 1
Nominal compositions in mole % of the undoped and Fe-doped 45S5 MBGs.

Sample code	SiO ₂	CaO	Fe ₂ O ₃	Na ₂ O	P ₂ O ₅
Fe0	46.14	26.91	0	24.4	2.55
Fe1	46.14	25.91	1	24.4	2.55
Fe2.5	46.14	24.41	2.5	24.4	2.55
Fe5	46.14	21.91	5	24.4	2.55
Fe7.5	46.14	19.41	7.5	24.4	2.55

5800 g/mol) (Sigma-Aldrich, USA) was dissolved in 77 mL of absolute ethanol (Merck, Germany) in an acidic condition (0.5 mL of HCL (1 M)), named solution 1. Then TEOS and TEP were hydrolyzed in the presence of deionized water and HNO₃ for 60 min and separately added to solution 1. After that, the nitrate precursors were dissolved in deionized water and added to solution 1 every 45 min intervals. In the next step, the pH of solution 1 was increased up to 14 by adding ammonium hydroxide (25% NH₃ in H₂O) in order to immediately form the gels. The formed gels were stirred for 24 h and then aged in sealed bottles for 7 days at room temperature. Subsequently, the mentioned gels were rinsed 5 times with distilled water to remove residual ammonia solution and ethanol. The samples were then dried using the freeze-drying process for 48 h. Next to this step, the samples were initially treated at 250 °C for 24 h and, finally, heat-treated at 600 °C (heating rate of 1 °C/min) in the air for 30 h.

Characterizations

Thermal behavior

The thermal behavior of the freeze-dried samples was analyzed using thermogravimetric (TGA) and differential thermal (DTA) analyses (STA 503, Germany) with a heating rate of 10 °C/min in air. The glass transition temperatures (T_g) of Fe-containing silicate-based BGs were then calculated and compared with those reported in SciGlass database version 7.12 [23]. It is noted that we removed the dropped data (maximum 10%) in order to increase the analysis accuracy, and the resulting values were processed using SPSS Modeler (version 18.22, IBM, USA).

XRD analyses

The structure of the synthesized glass particles before and after immersion in simulated body fluid (SBF; see also section 2.3.1) was investigated using X-ray diffraction (XRD) analysis (D8-Advance Bruker, Germany). The instrument conditions were set as 2θ range of 20–80° with Cu-Kα radiation, a step size of 0.05°, and time per step of 2 s. The phase characteristics were studied using the Rietveld refinement method using Profex and BGMN packages [24].

The rate constant (K) of the phase transformation of the Fe-doped MBGs to hydroxyapatite during immersion in SBF was calculated using Equation 0.1 (Eq. (1)) [25].

$$K = -\ln(Ca / C0) / T \quad (1)$$

where C0 is the initial amount of the hydroxyapatite after the first incubation time (24 h or 86,400 s) and Ca is the amount of the crystalline phase after a time T.

FTIR study

The chemical bonding in the structure of Fe-doped MBGs before and after immersion in SBF was investigated using Fourier-transform infrared spectroscopy (FTIR) (Thermo Nicolet AVATAR 370, USA) over the range of 400–4000 cm⁻¹.

Particle size and zeta potential measurements

The glass particle size was determined by using dynamic light scattering (DLS) (Vasco3, Cordouan, France) analysis. The zeta (ζ) potential of the samples was measured using Zeta potential analyzer (NANO-flex® II, Thermo Fisher Scientific, USA). To do this, 0.01 g of the Fe-doped MBGs were dispersed in 10 mL of absolute ethanol with the aid of ultrasonic waves (FR USC 22 LQ, 400 w, 20%, Taiwan) for 5 min.

Morphological observations by electron microscopy

The surface morphology of gold-sputtered MBGs was observed using field-emission scanning electron microscopy (FESEM) analysis (MIRA3, TESCAN, CZ) before and after immersion in SBF. The effect of adding Fe₂O₃ on the particle size and morphology was also assessed using

transmission electron microscopy (TEM) (EM 208S, Philips, Netherland). The influence of Fe dopant concentrations on the surface topography and roughness was investigated by using atomic force microscopy (AFM) analysis (Nano Wizard II; JPK Instruments, Germany). In order to perform TEM and AFM analyses, 0.01 g of the glasses were first dispersed in 30 mL of absolute ethanol under the action of ultrasonic waves (FR USC 22 LQ, 400 w, 20%, Taiwan) for 10 min. Then, a drop of the prepared suspension was coated on the standard carbon-coated copper meshes grade for TEM and AFM analyses.

N₂ adsorption-desorption analysis

The textural properties of the glasses, including specific surface area (S_{BET}), pore size ranges, and pore volume, were determined by nitrogen adsorption-desorption measurement using the Brunauer-Emmett-Teller (BET) and Barrett-Joyner-Halenda (BJH) analysis (Quantachrome instrument, Japan). Prior to performing the analysis, the glass powder samples were degassed at 250 °C for 6 h in a vacuum process.

VSM analysis

Magnetic properties of the Fe-doped MBGs were measured by a vibrating sample magnetometer (VSM) analysis (Lake Shore Cryotronics, USA) using a magnetic field of 20 kOe at room temperature.

Electro-Fenton's reaction analysis

Preparation of working electrode. To prepare working electrode, MBG powders, polyvinylidene fluoride (PVDF, Sigma-Aldrich, USA), and carbon black (Sigma-Aldrich, USA) were mixed in the mass ratio of 75:22:3. To do this, 29.4 mg of polyvinylidene fluoride (PVDF) were dissolved in 1 mL of 1-methyl-2-pyrrolidinone (NMP) under constant stirring for 60 min (sol-A). Then, 100 mg of MBG particles and 4 mg of carbon black were separately added to sol-A every 45 min intervals. The obtained solution was sonicated using a sonication bath for 1 h. Subsequently, the solution was stirred for 24 h in order to reach the appropriate coating slurry. To prepare Ni foam ($1 \times 0.5 \text{ cm}^2$), a substrate for coating, first the oxidized layer was removed using HCl solution (3 M), and then it was carefully rinsed with alcohol and deionized water three times. Finally, the dip-coated foam in the slurry was dried using a vacuum process at 80 °C for 24 h. The schematic representation of synthesis steps and working electrode preparation is shown in [Scheme 1A](#) and [B](#).

Electro-Fenton properties. The electrochemical properties of the prepared working electrode were recorded using an electrochemical analyzer (Autolab PGSTAT302N). In the test, a platinum (Pt) wire, Ag/AgCl, and 1 M Na₂SO₄ solution were utilized as the counter electrode, reference electrode, and electrolyte reference for electrochemical measurements at room temperature, respectively. It is worth noting that the electrochemical analysis was recorded in O₂-saturated electrolyte using a portable oxygen concentrator.

Cyclic voltammetry (CV) analysis of the coated glasses was recorded at a scan rate of 50 mV·s⁻¹. It should be mentioned that the CV test was analyzed in N₂-purged and the O₂-saturated solutions. Electrochemical impedance spectroscopy (EIS) analysis was evaluated using alternating current (AC) at an amplitude of 10 mV in the frequency range of 0.1 Hz–10⁵ Hz. The solution resistance (R_s), constant phase element (CPE), and charge transfer resistance (R_{ct}) of the samples were derived using ZView® software (version 3.5) by fitting the EIS data and simulating impedance measurements.

In vitro bioactivity assessment

To evaluate the bioactivity, we first prepared the SBF according to

Kokubo's method [26]. Then 0.15 g of the synthesized MBGs were incubated in 100 mL of SBF. The solution was shaken at a speed of 20 rpm at the temperature of 37 °C for the periods of 1, 3, and 7 days. Meanwhile, pH values of the glass-containing SBF were recorded by using a digital pH-meter (AZ pH Meter 86,552, Taiwan) over the incubation periods. Besides, the release profile of ions from the glass into SBF was monitored via inductively coupled plasma atomic emission spectroscopy (ICP-AES, Spectro Arcos, Germany).

Statistical analysis

The particle size and ζ potential results were performed three times, and the obtained data were represented as mean \pm standard deviation. The outcomes were statistically analyzed via the one-way ANOVA analysis (GraphPad Prism, 8.4.3(686), USA) followed by post hoc analysis. (* $p \leq 0.05$, ** $p \leq 0.01$, *** $p \leq 0.001$, **** $p \leq 0.0001$).

Results

DTA/TGA analysis

[Fig. 1](#) shows the DTA and TGA results of the synthesized glasses after the freeze-drying process. In general, the peaks lower than 300 °C are attributed to physically adsorbed water in the compounds. The minor endothermic peaks around 700 °C could be related to the decomposition of nitrate groups, in good agreement with the results reported by other authors for gel-derived 45S5 glasses [27]. According to DTA data, the glass transition of the Fe-free MBG was around 713 °C while the values recorded for 1, 2.5, 5, and 7.5 mol% Fe₂O₃-containing MBGs were about 704, 700, 659, and 693 °C, respectively. It seems that the major weight loss observed in the samples is associated with the burning out of the Pluronic P123 template. Finally, increasing the weight in the TGA graphs can be related to the oxidation of the new phases [28].

[Fig. 2A](#) illustrates how we used the Sci-glass data for comparing the synthesized glasses' T_g with those reported results on Fe₂O₃-containing 45S5 composition. The frequency distribution histogram of SiO₂, Fe₂O₃, and T_g in the extracted data is shown in [Fig. 2B](#). According to the data, the T_g values have changed after incorporation of Fe₂O₃ into MBGs; it shows a decrease along with an increase in Fe₂O₃ concentrations (up to 10 mol%), and then it increased again [Fig. 2C](#) clarifies that the T_g values (y) are function of the Fe₂O₃ concentrations (x) as $y = 1.11618 x^2 - 22.826 x + 528.65$.

DLS and zeta potential characterization

The DLS characterization of the glass particles is represented in [Table 2](#). The Dv 90 value measured for the Fe-free MBG was 110 \pm 9 nm, while the values of 86 \pm 8, 39 \pm 6, 12 \pm 1, and 11 \pm 1 nm were recorded for 1, 2.5, 5, and 7.5 mol% Fe₂O₃-containing samples, respectively. According to the data, the particle size significantly decreased after the incorporation of Fe₂O₃ into the glass structure. The ζ potential of the Fe-free sample was about -27 \pm 4 mV, while the values of -27 \pm 5, -28 \pm 2, -30 \pm 4, and -27 \pm 3 mV were recorded for 1, 2.5, 5, and 7 mol% Fe₂O₃-doped glasses.

XRD patterns

The results of the XRD analysis are shown in [Fig. 3](#) before and after immersion in SBF. The figure shows the Rietveld analysis results of the SBF-immersed glasses after 7 days of incubation. Besides, the calculation of crystallinity, crystallite size, lattice constant, and rate of the glass phase transformation to hydroxyapatite (HAP) (i.e., the bioactive properties) are represented in [Table 3](#). According to the obtained data, all the glass samples were amorphous before incubation in SBF. The crystallinity values calculated for the Fe-free, 1, 2.5, 5, and 7.5 mol% Fe₂O₃-containing MBGs were 6, 6, 3, 3, and 2%, respectively. The HAP

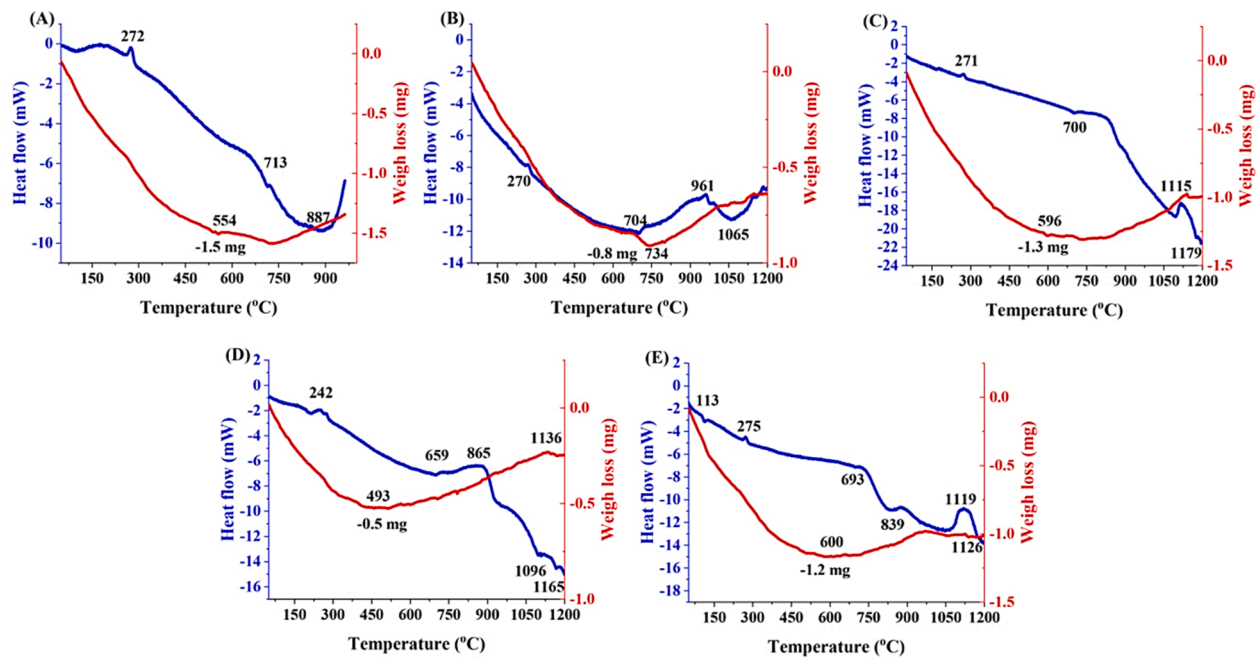


Fig. 1. DTA/TGA graphs of Fe₂O₃ free (A), 1% (B), 2.5% (C), 5% (D) and 7.5% (E) Fe₂O₃-containing MBGs.

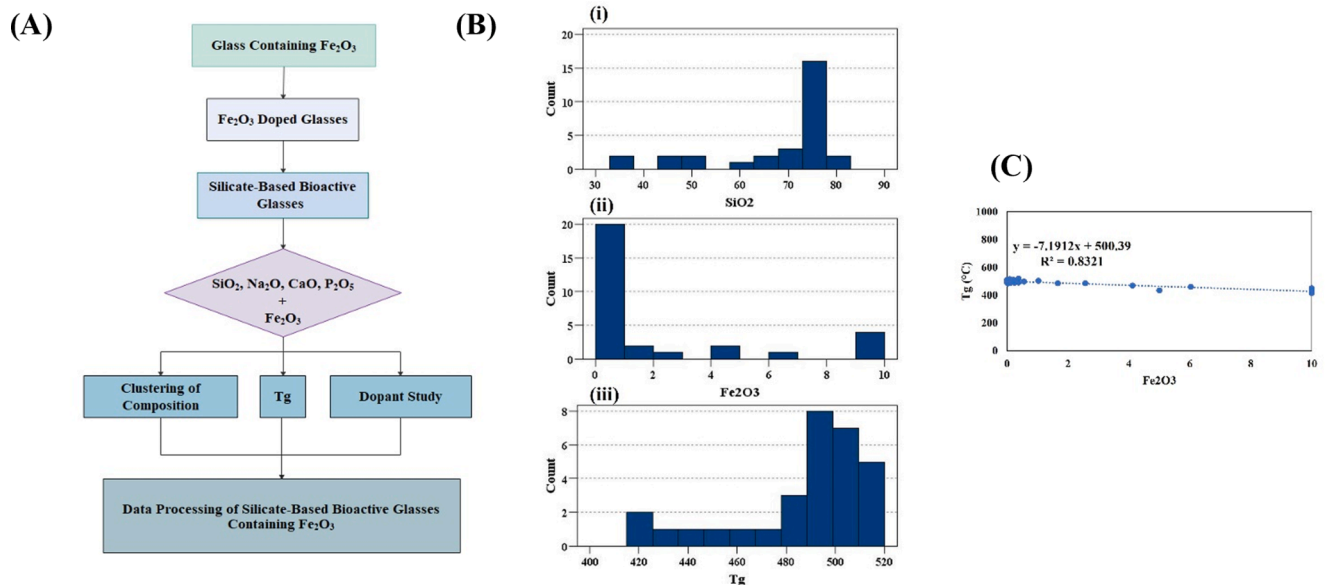


Fig. 2. (A) The decision tree of the Fe₂O₃-containing silicate glasses (A). The frequency distribution histogram of SiO₂, Fe₂O₃, and Tg (B). The dependency of the Tg values on the Fe₂O₃ amounts in the MBGs (C).

Table 2

Particle size and zeta potential values of the Fe free and Fe-doped 45S5 MBGs. (* $p \leq 0.05$, ** $p \leq 0.01$, *** $p \leq 0.001$, **** $p \leq 0.0001$).

Sample	Dv 50 (nm)	P value	Dv 90 (nm)	P value	Zeta (mV)	P value
Fe0	83 ± 4	-	110 ± 9	-	-27 ± 4	-
Fe1	59 ± 3	**	86 ± 8	**	-27 ± 5	$P > 0.05$
Fe2.5	20 ± 2	***	39 ± 6	***	-28 ± 2	$P > 0.05$
Fe5	6 ± 2	***	12 ± 1	***	-30 ± 4	$P > 0.05$
Fe7.5	6 ± 1	****	11 ± 1	****	-27 ± 3	$P > 0.05$

phase (ICDD ref. cod. 9-0432) was detected in all SBF-immersed samples as 27, 30, 24, 20, and 15%, respectively. According to the data, the lattice constant of the formed HAP is higher in the samples incubated for 7 days as compared to their counterparts after 3 days. The rate constant of glass to HAP transformation in the SBF were 6, 7, 9, 13, and $15 \times 10^{-7} \text{ s}^{-1}$ for the Fe-free, 1, 2.5, 5, and 7.5 mol% Fe-doped MBGs, respectively.

FTIR spectroscopy

Fig. 4 displays the FTIR spectra of the synthesized MBGs before and after immersion in SBF. The marked bands in the range of 553–680 cm^{-1} and the broadband around 1100 cm^{-1} are related to P-O bonds [29]. The

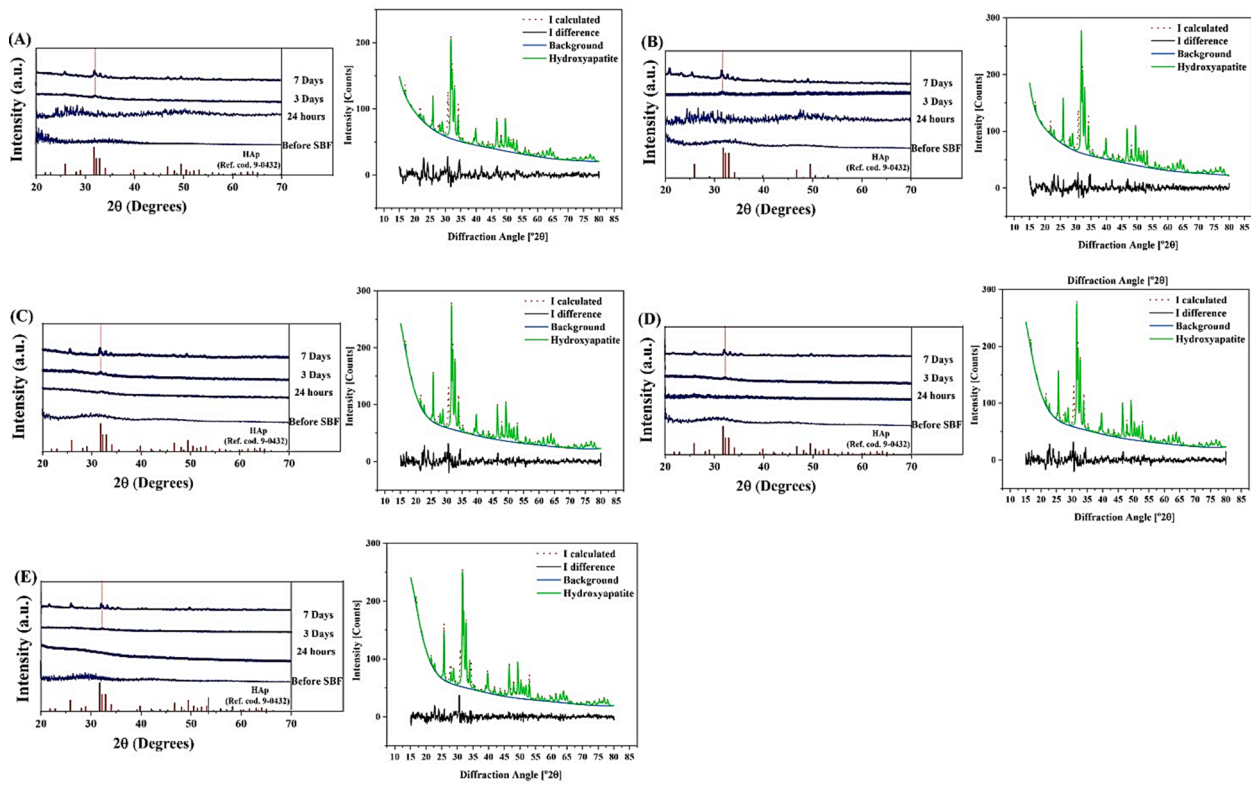


Fig. 3. The XRD patterns of Fe₂O₃ free (A), 1% (B), 2.5% (C), 5% (D) and 7.5% (E) Fe₂O₃-containing MBGs before and after immersion in the SBF. The Rietveld refinement results of the immersed samples after 7 days are illustrated in the figures.

Table 3

Summarized results of crystallite size, crystallinity, lattice constants of the formed HAp, and the average rate constant of glass to HAp transformation.

Sample	Crystallite size (nm)		Crystallinity (%)				a Å		c Å		Average rate constant ($K \times 10^{-7}$) s ⁻¹
Days	3	7	0	1	3	7	3	7	3	7	–
F0	8	48	6	5	8	27	9.418	9.422	6.881	6.883	6
F1	9	60	6	5	10	30	9.429	9.431	6.890	6.890	7
F2.5	5	51.4	3	3	6	24	9.432	9.434	6.895	6.898	9
F5	6	52.4	3	3	5	20	9.436	9.443	6.900	6.904	13
F7.5	6	49.6	4	2	4	15	9.430	9.432	6.893	6.893	15

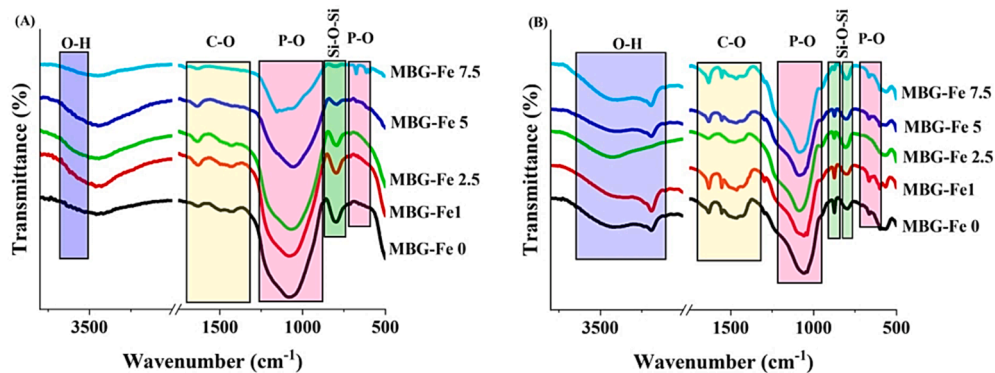


Fig. 4. FTIR spectra of the undoped and Fe₂O₃-doped MBGs before (A) and after 7 days of incubation in SBF (B).

bands around 800 cm⁻¹ and 870 cm⁻¹ are associated with structural groups of the silicate glass [28]. As it can be seen, the intensity of the Si-O-Si groups shows a reduction in the Fe-doped samples due to changes that occurred in the glass network. The observed broad bands in the range of 1460–1560 cm⁻¹ are attributed to carbonated groups. The increased intensity of the carbonated groups in the SBF-immersed MBGs

is correlated to the formation of the hydroxycarbonate apatite (HCA) layer.

FE-SEM observations

The surface morphology of the MBGs is presented in Fig. 5. The

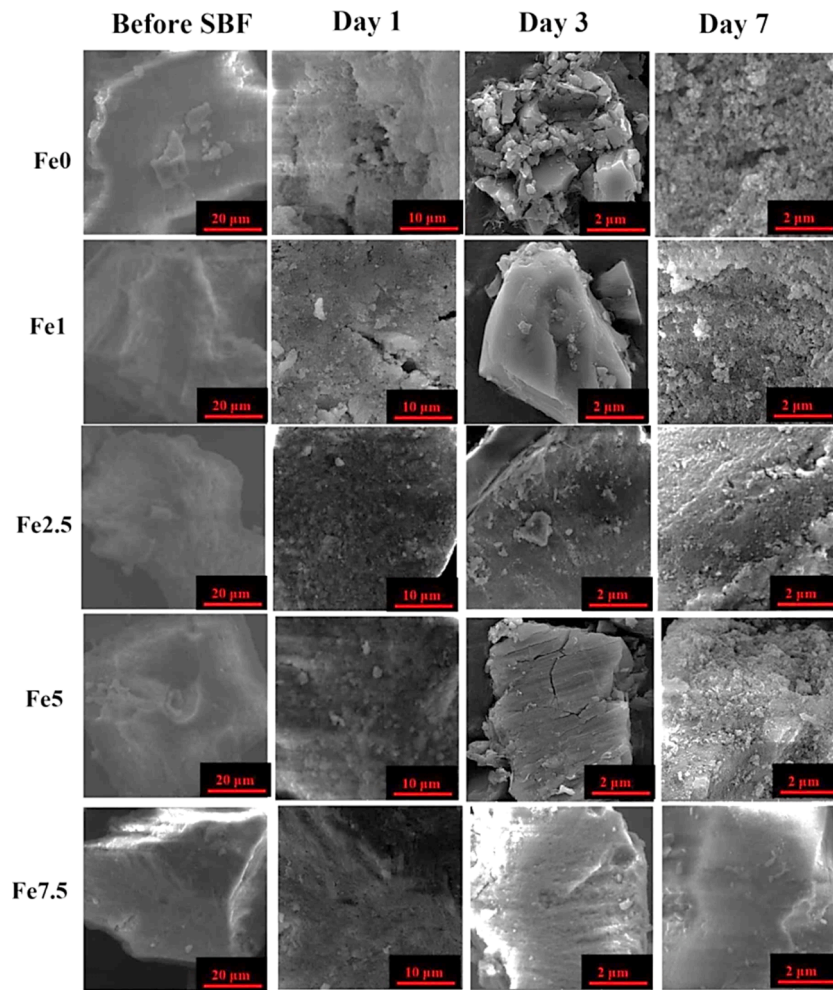


Fig. 5. SEM micrographs of the undoped and Fe₂O₃-doped MBGs before and after incubation in the SBF for time periods up to 7 days.

formation of typical HCA agglomerates onto the SBF-immersed samples can be clearly observed in the relative images, indicating the bioactive feature of all the samples.

TEM images

TEM micrographs of the un-doped and Fe-doped MBGs are shown in Fig. 6. A porous structure was observed in all the glass particles. As can be observed in the TEM images, the particle size of the Fe-doped samples was reduced, and its agglomeration was increased.

AFM micrographs

The surface roughness of the glass particles (Fig. 7) was monitored by using AFM microscopy. As shown, the addition of Fe₂O₃ to the parent 45S5 glass made significant changes in the surface roughness of the synthesized MBGs. The average value of surface roughness was 36 ± 14 nm for the Fe-free MBGs, while the values decreased to 112 ± 26 , 108 ± 10 , 4 ± 0.8 , and 25 ± 6 nm for 1, 2.5, 5, and 7.5 mol% Fe₂O₃-containing samples, respectively.

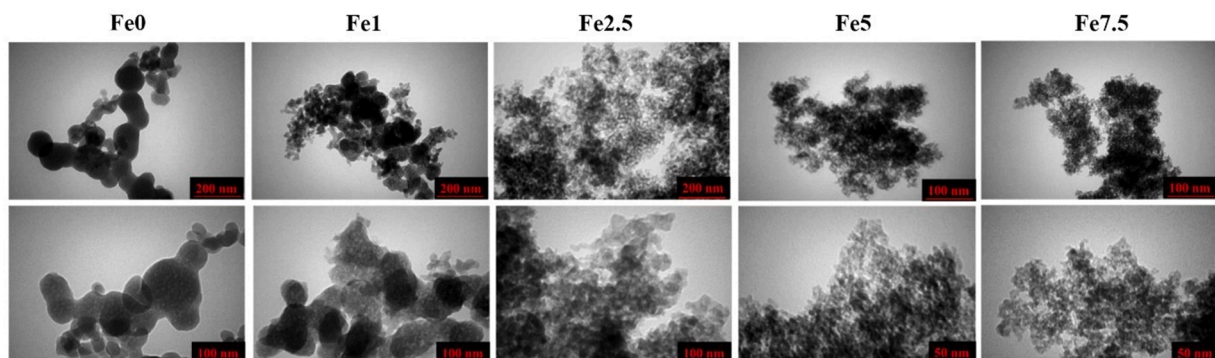


Fig. 6. TEM micrographs of the Fe₂O₃ free and Fe₂O₃-doped MBGs.

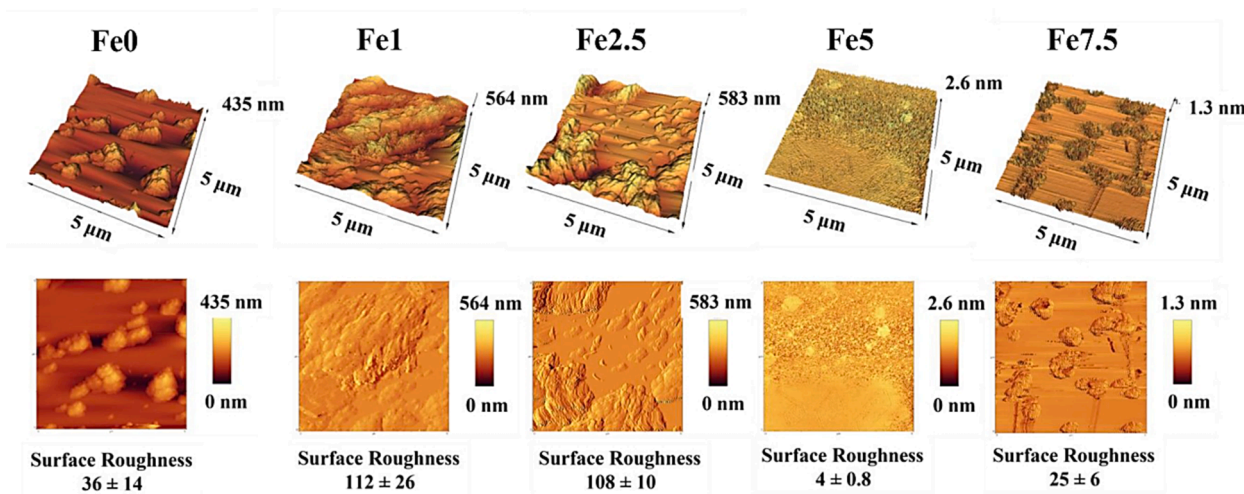


Fig. 7. AFM micrographs of the Fe₂O₃ free and Fe₂O₃-containing MBGs.

N₂ adsorption/desorption analysis

The BET/BJH results of the prepared samples are shown in Fig. 8. According to Brunauer–Deming–Deming–Teller theory (BDDT) classification, the shape of the hysteresis loop of the MBGs is related to category IV and closely attributed to the H4 class of mesoporous particles. This class designates particles with hollow spheres of irregular and broad size and/or ordered mesoporous particles [30]. The details of mesoporous characteristics of the MBGs are presented in Table 4, indicating the mesoporous range (2–50 nm) of materials.

VSM

The magnetic hysteresis (M-H) loops of the MBGs are presented in Fig. 9. The values of magnetization saturation (*M_s*) of the samples were 0.021, 0.083, 0.161, 0.180, and 0.187 emu/g for the Fe-free, 1, 2.5, 5, and 7.5 mol% Fe₂O₃-containing MBGs, respectively.

Table 4

The mesoporous characteristics of the synthesized Fe₂O₃ free and Fe₂O₃ doped MBGs.

Sample	<i>S</i> _{BET} (m ² /g)	Total pore volume (cm ³ /g)
Fe0	60	0.32
Fe1	95	0.84
Fe2.5	195	1.22
Fe5	306	0.99
Fe7.5	270	1.00

Ion release and pH variations

The release profile of ions from the MBGs into SBF is illustrated in Fig. 10. The calculated kinetics of the ions released estimated from the slope of the curves are represented in Supplementary Tables S1–S5. According to the data, the highest release rate values of Fe³⁺ ions are related to the first 24 h of incubation. The pH changes in the glass-

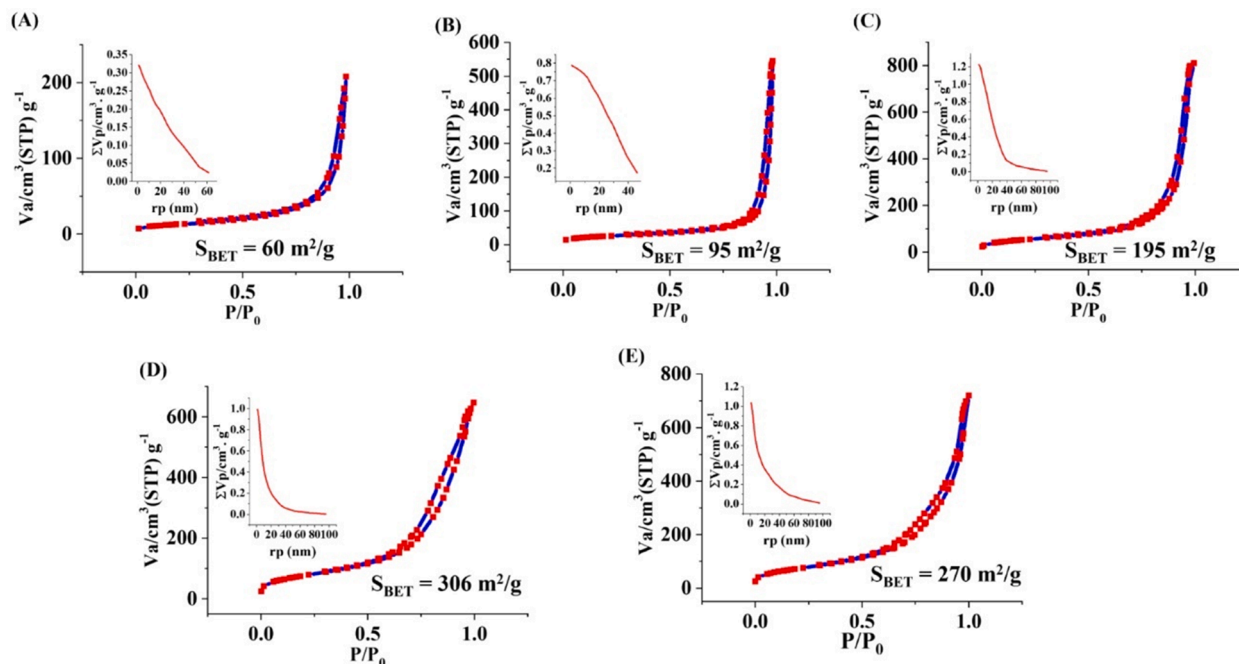


Fig. 8. N₂ adsorption-desorption isotherms, specific surface area by BET and pore size distributions by BJH method of 0% (A), 1% (B), 2.5% (C), 5% (D) and 7.5% (E) Fe₂O₃ doped MBGs.

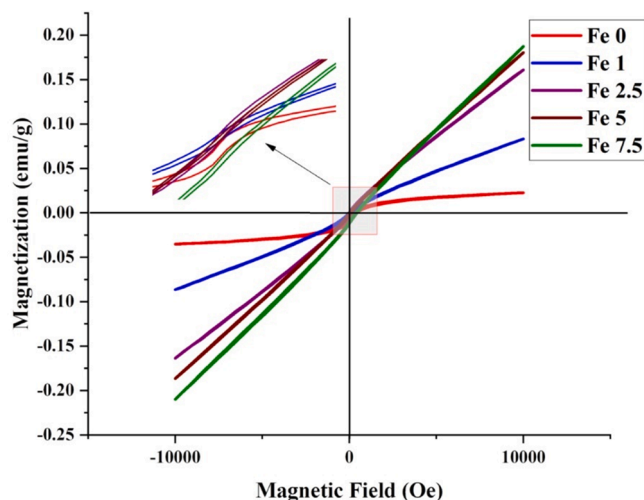


Fig. 9. Magnetic hysteresis loops of the Fe₂O₃ free and Fe₂O₃-containing MBGs.

containing SBF were recorded for 7 days. As shown in Fig. 11, a sharp increase in the pH (from 7.42 to 8.5) is seen during the first 100 h of post-incubation.

Electro-Fenton properties

Cyclic voltammetry (CV) analysis

The CV scan of the coated MBGs in both O₂- and N₂-saturated electrolytes is represented in Fig. 12. As shown, the reduction peak assigned as reduction of O₂ and subsequent generation of H₂O₂ is only observed in the CV curves of the MBGs incorporating 5 and 7.5 mol% of Fe₂O₃ at a cathodic potential higher than -0.2 V (vs. Ag/AgCl) in O₂-saturated solution. It is clearly visible that the reduction peak is wholly disappeared in N₂ gas purging conditions.

Electrochemical impedance spectroscopy (EIS)

Fig. 13 illustrates the EIS profile of the working electrode coated with Fe₂O₃-doped MBGs in O₂-saturated electrolytes. For all the samples, one semicircle is observed in Nyquist plots. This semicircle could be attributed to different kinds of pore geometry. An equivalent circuit, including the electrolyte resistance (R_s), charge transfer resistance (R_{ct}), and constant phase element (CPE) is seen in Figs. 12 and 13. The R_s, R_{ct}, and CPE values of five different working electrodes from Nyquist plots are summarized in Table 5. Moreover, the rate constant (K⁰) values of the samples are represented in Table 5. The K⁰ of electrodes coated with the MBGs were 6.25 × 10⁻¹⁰, 4.47 × 10⁻⁹, 4.55 × 10⁻⁹, 7.57 × 10⁻⁹, 2.40492 × 10⁻⁸ for the un-doped, 1, 2.5, 5, and 7.5 mol% Fe₂O₃-containing samples, respectively.

Discussion

In recent years, glasses and glass-ceramics have attracted much

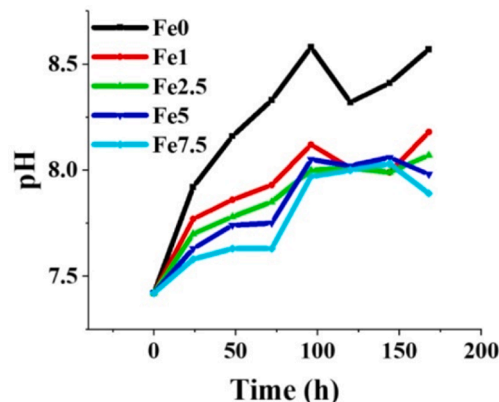


Fig. 11. The pH variations during the incubation time of Fe₂O₃ free and Fe₂O₃-containing MBGs in SBF.

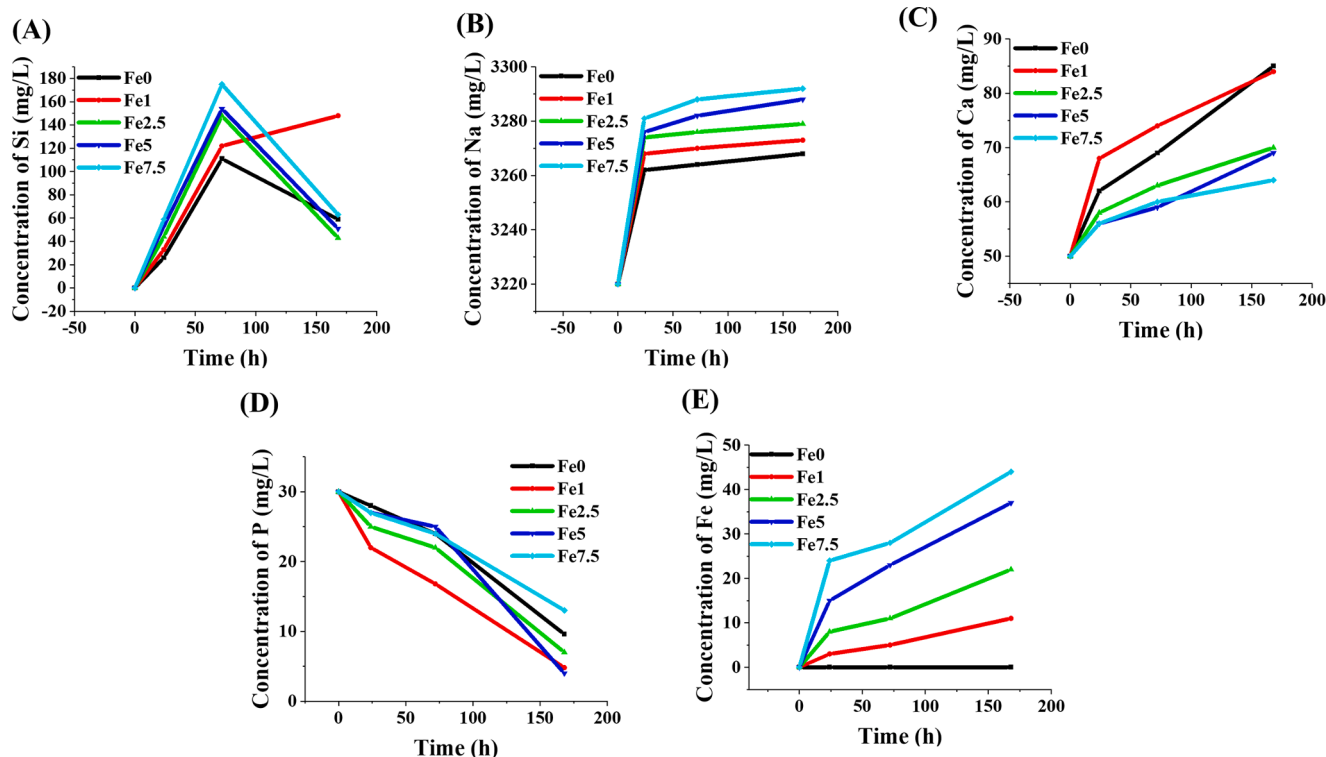


Fig. 10. The release of various ions from the Fe₂O₃ free and Fe₂O₃-containing MBGs into the SBF release medium during 7 days of incubation.

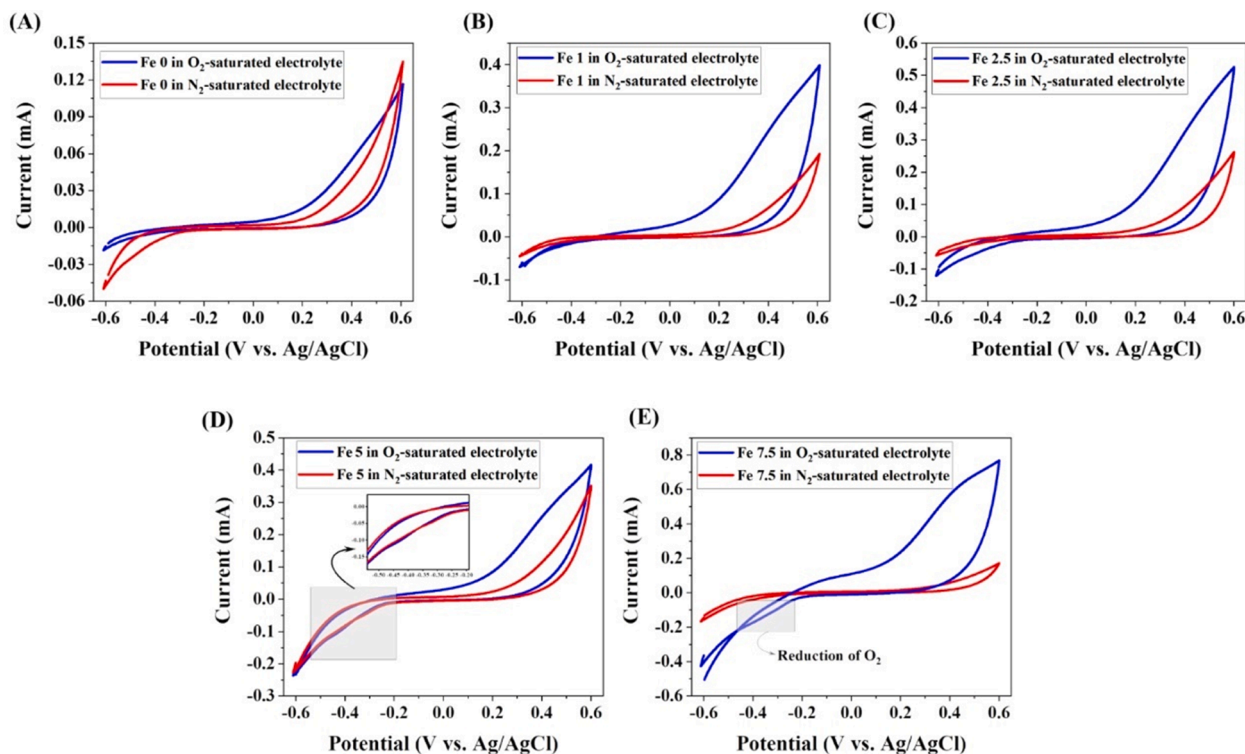


Fig. 12. Cyclic voltammetry analyses of the Fe₂O₃ free (A), 1% (B), 2.5% (C), 5% (D) and 7.5% (E) Fe₂O₃-containing MBGs.


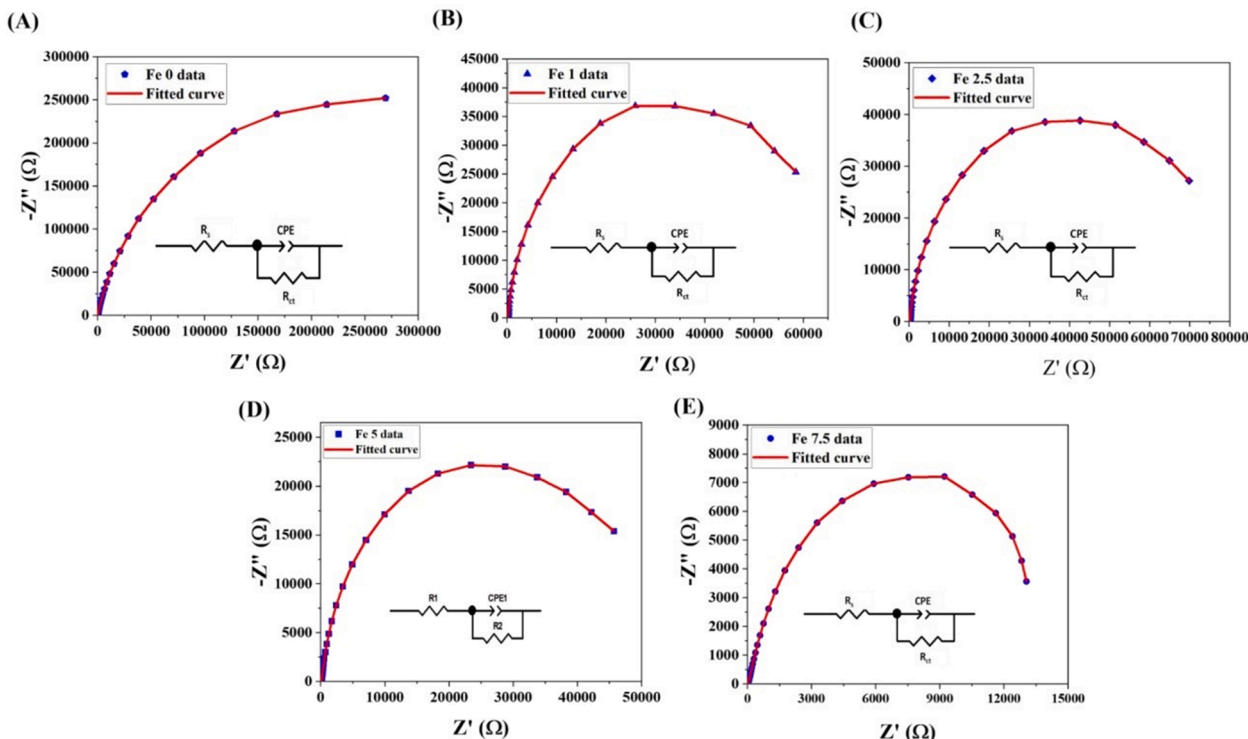


Fig. 13. Nyquist plots and EIS equivalent circuit fitting of the Fe₂O₃ free (A), 1% (B), 2.5% (C), 5% (D) and 7.5% (E) Fe₂O₃-containing MBGs.

attention in cancer treatment due to their great functional versatility and outstanding features, including excellent biocompatibility, the ability to load anticancer drugs and chemicals, and the possibility of producing radioactive glasses [11,12]. Furthermore, adding anticancer elements to the glass structure is a fairly simple and feasible approach with

satisfactory outcomes in battling against cancer cells. Fe and iron oxides are well-known anticancer substances, which can generate ROS in tumor cells through the reduction of H₂O₂ to free radicals ([•]OH) [31]. In the current study, we synthesized a group of sol-gel-derived MBGs based on 45S5 Bioglass formulation in which various concentrations (0, 1, 2.5, 5,

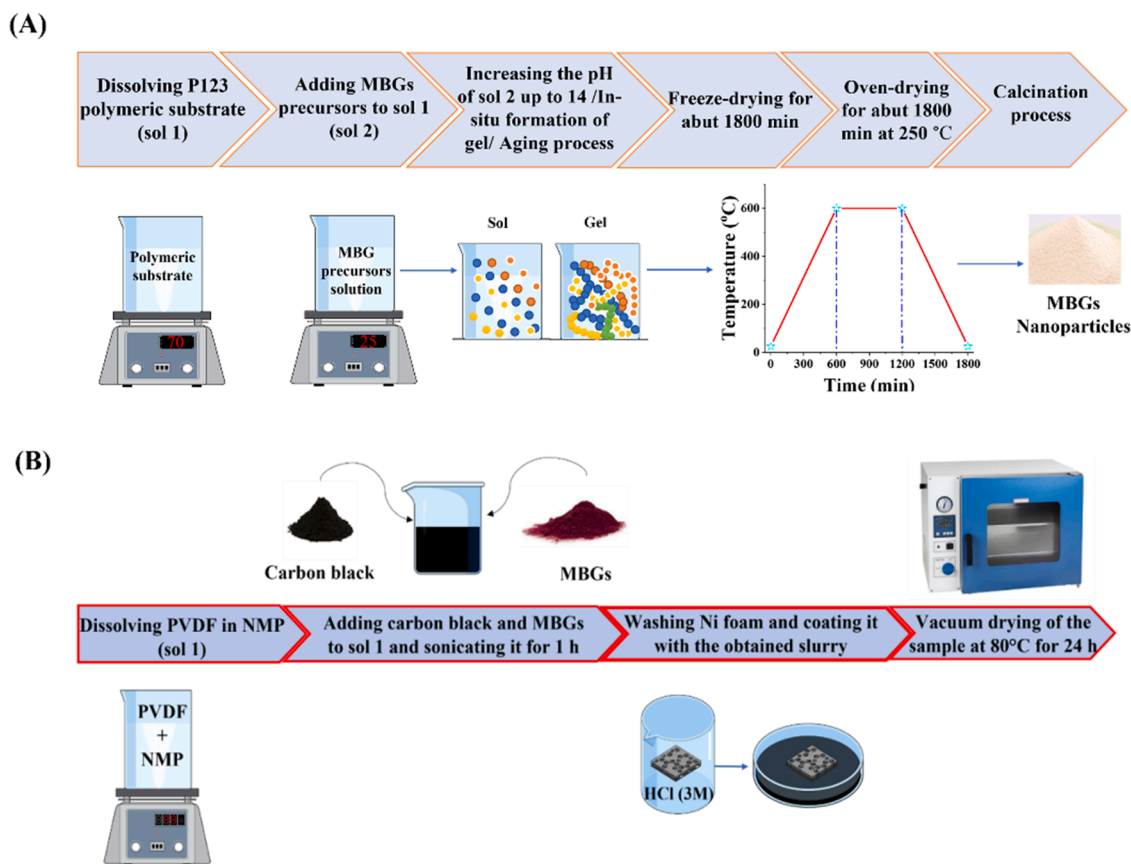








Scheme 1. A pictorial illustration of the steps involved in the synthesis process (A) and working electrode preparation process (B).

Table 5

The EIS equivalent circuit fitting data (R_s , CPE, and R_{ct}) and calculated rate constants of electro-Fenton reaction (k^0).

Sample	R_s (Ohm)	CPE ($\times 10^{-5}$)	R_{ct} (Ohm)	k^0
Fe0	65.62	1.73	7.09×10^5	6.25×10^{-10}
Fe1	55.55	6.57	9.92×10^4	4.47×10^{-9}
Fe2.5	62.19	5.17	9.74×10^4	4.55×10^{-9}
Fe5	66.58	8.06	5.86×10^4	7.57×10^{-9}
Fe7.5	26.36	18.17	1.84×10^4	2.40×10^{-8}

and 7.5 mol%) of Fe_2O_3 were incorporated in order to obtain anticancer Fe_2O_3 -containing glasses. As reported elsewhere [32], the P-O-Fe and Si-O-Fe linkages could be formed in the glass structure by adding Fe_2O_3 as a modifier oxide. Fe_2O_3 ($Fe/O = 1.5$) can trigger the reduction reactions (R1-R8) reported below. Regarding the reactions, the standard electrochemical reduction potential of Fe_2O_3 (hematite) is higher than other Fe-based oxides including Fe_3O_4 (magnetite) and FeO (wüstite).



The DTA analysis (Fig. 1) indicated that the incorporation of Fe_2O_3 to the MBGs network can reduce the glass transition temperature (from 713 to 659 °C), which can be associated with an increasing number of non-bridging oxygens (NBOs) in the glass network and subsequent decrease of crystallization energy [33]. The different peak positions seen in DTA graphs could also be related to the anti-polarization effect of Fe^{3+} ions and the decrease of glass network coherency [32]. The particle size analysis (Table 2) indicates that the addition of Fe_2O_3 significantly hinders the particle growth (size decrease from 110 to 11 nm), which is in line with other reported experiments on different glass compositions [28]. It should be mentioned that the net negative surface charge of the particles (Table 2) (about -30 mV) could be beneficial for enhancing the biological performance of the MBGs [29].


The XRD results (Fig. 3) suggested that the crystallization rates of the synthesized MBGs was depending on the Fe_2O_3 concentration. The rate constant of phase transformation increased along with higher concentrations of Fe_2O_3 , which may be attributed to the weakening of the structural bonds as a result of the effect of adding a transition metal [34]. Compared to the 3-day SBF-incubated glasses, the Rietveld refinement data showed an increase in the lattice constant of HAp ($a = b$ from 9.418 to 9.443 Å, c from 6.881 to 6.904 Å) of the 7-day SBF-immersed samples during the phase transformation of the glass to HAp. This increase could be related to the elevated levels of released ions (Si^{4+} , Na^+ , and Fe^{3+}) from the MBG particles at day 7 and entrance to the HAp structure [30]. The FTIR results (Fig. 4A) revealed that the intensity and peak positions of the P-O and Si-O-Si bands changed depending on Fe_2O_3 content. The formation of P-O-Fe and Si-O-Fe bonds, which occurs randomly, may lead to the disordering of glass structure (higher than its Fe-free pristine form) as well as enhanced cross-link density of the glass [35], resulting in the observed changes in

the position and the intensity of FTIR bands. The structural bonds of the HAp/HCA were also observed in Fig. 4B, indicating the bioactivity of the synthesized MBGs.


The SEM micrographs (Fig. 5) also verified the formation of the HCA layer onto the SBF-incubated MBGs after 7 days. The TEM micrographs (Fig. 6) revealed that the presence of Fe₂O₃ may decrease the particles size of the MBGs from 50 to 100 nm to below 10 nm. This decrease, also observed in the DLS data, could be attributed to the Fe₂O₃ impact on increasing the repulsion force between the glass particles [36]. The AFM data (Fig. 7) revealed that the dopant would enhance the surface roughness from 36 to 112 nm [37]. Therefore, this suggests that the dopant amount in the glass matrix can also have an effect on surface topography and, hence, play a role in modulating the initial interaction of the glass in the biological solution or bio-fluids. The data of the N₂ adsorption/desorption analysis (Fig. 8) revealed the well-ordered porous structure of the MBGs. This state can be related to the templating action and subsequent burning out of Pluronic P123 during the heat-treatment process. The BET data indicated a significant increase in S_{BET} of Fe-doped samples (from 60 to 306 m²/g), which is in line with previous studies [20] and also makes Fe₂O₃-containing MBGs suitable for drug delivery applications [38]. The synthesized MBGs possess a certain magnetization saturation (Fig. 9), ranging from 0.021 to 0.187 emu/g, which might be probably attributed to the formation of the ferrite phase (XFe₂O₄) due to the transformation of glass to spinel structure [39]. The formation of spinel structure (AB₂O₄) in which A site occupied with divalent cations and B occupied with trivalent cations in the random forms could enhance the magnetic properties [40]. However, these phases did not observe in the XRD patterns due to the instrumental detection limitations.

This micromagnetic behavior in all Fe-doped MBGs, which becomes more evident as the Fe₂O₃ content increases, reflects the presence of long-range (Ferri)magnetic interactions among the Fe ions that have been incorporated in the glass network [41]. In fact, two types of interactions exist in glassy systems containing Fe₂O₃ as network modifiers, i.e., dipole-dipole and superexchange-type interactions [42]. Overall, the values of magnetization saturation assessed in the present work (<0.2 emu/g) are comparable with those reported for different Fe-doped MBG systems (Fe₂O₃ < 10 mol%) by other authors [43,44].

The ICP results (Fig. 10) showed that incorporation of Fe₂O₃ had no adverse effects on the release profile of ions from the glass into the surrounding medium (SBF). Apparently, an increasing Fe₂O₃ content overall induces less significant increments of pH in the solution. Sequestration of phosphate ions, which is typically related to the formation of a HAp layer on the biomaterial surface, can be seen for all compositions (Fig. 10D), in perfect agreement with the results of *in vitro* bioactivity tests. In addition, a sustained release was monitored for Fe in case of the Fe₂O₃-containing MBGs over 7 days, which is in favor of cancer treatment strategies. The indirect electro-oxidation method, i.e., the EF approach, was considered to investigate the *in-situ* production of H₂O₂ and Fe²⁺ in a two-electron oxygen reduction reaction (ORR). For evaluating the EF activity of Fe₂O₃-containing 45S5 MBGs, we employed the CV and the EIS analyses in the 0.1 M O₂- and N₂-saturated Na₂SO₄ solution. In the mentioned tests, the reduction (cathodic) peak is regarded as one of the most important indicators of EF activity in the coated samples. In this study, the cathodic peak is attributed to the reduction of O₂ into H₂O₂ (R9):




The Fe^{X+} ions released from the MBGs (Fig. 10F) and the Fenton's reaction occurred as follows (R10):




In Fenton's reaction, free radicals (•OH) are generated at sufficient levels for inducing cancer cell death. It is noted that the formation of free radicals is also feasible in another approach such as Haber-Weiss

reaction, as follows (R11):



In addition, according to the following reaction (R12), the released Fe^{X+} ions from the MBGs can be regenerated continuously during the process of the EF reaction. Potential changes during this reaction also may be a critical factor in killing cancer cells.



We further used the EIS test for determining the kinetics of the EF activities in Fe-doped MBG powders. The EIS is a powerful method for the assessment of EF kinetics in different electrodes [45]. Moreover, the various equivalent circuits were used for the physical evaluation of diverse reactions in the EF reaction as well as the clarification of electrolyte-electrode interference. In the Nyquist plots (Fig. 13), one semicircle is observed in all the samples. This semicircle could be attributed to the presence of different kinds of pore geometry in the samples, which was also observed in BET data. It is claimed that the observation of only one semicircle in the EIS curve may be associated with the open superficial morphology that inhibits the pore contribution on the impedance spectra [46].

Another criterion for evaluating the EF reaction is its standard rate constant (K⁰), which is calculated from the following equation (Eq. (2)):

$$K^0 = \frac{RT}{n^2 F^2 R_c A C_{O_2}} \quad (2)$$

Where R is the gas ideal constant (8.314 J/mol·K), T is the absolute temperature (298 K), n is the mol number during two-electron reduction of O₂, F is the Faraday's constant (96,485 C/mol), A is the area of the working electrode (0.5 cm²), and C_{O₂} is the bulk concentration of dissolved oxygen (3 × 10⁻⁷ mol/cm³).

The obtained data based on Eq. (2) are summarized in Table 5. According to the information, the EF kinetics of the MBGs containing 7.5 mol% Fe₂O₃ were 3.18, 5.28, 5.38, and 38.44 times higher than the doped samples with 5, 2.5, 1, and 0 mol% Fe₂O₃, respectively. Regarding the EIS data, which are in good agreement with the CV results, the EF properties of the MBGs are enhanced by increasing the dopant amount. As a result, it can be concluded that the MBGs incorporating 7.5 mol% of Fe₂O₃ have superior EF activities compared to other electrodes, proofing a concept for further *in vitro* and *in vivo* studies.

Conclusions

A series of Fe-doped MBGs were successfully synthesized based on 45S5 bioglass formulation through the sol-gel process in the presence of the Pluronic P123 template for potential use in cancer treatment. We supposed that these compositions can activate the Fenton's reaction in cancer cells through generating free radicals (•OH). The obtained results indicated that adding Fe₂O₃ to the glass may result in a slight decrease in bioactivity *in vitro*. The synthesized Fe-doped MBGs showed a particle size between 11 and 86 nm, surface charge value of 27–30 mV, S_{BET} of 95–306 m²/g, and Ms of 0.08 to 0.2 emu/g. The Fe₂O₃ incorporation into the glass network could alter the kinetics of phase transformation of glass to HAp as well as the ion release kinetics. The electrochemical investigation, including the CV and the EIS, confirmed the high potential of the Fe-doped MBGs in activating the Fenton's reaction. Starting from these highly-promising obtained results, further *in vivo* animal studies seem essential in order to conclude the actual potential of Fe-doped MBGs in cancer therapy strategies.

Funding

This study was kindly funded by Mashhad University of Medical Sciences through research grant number 4000105.

CRedit authorship contribution statement

Farzad Kermani: Investigation, Writing – original draft. **Arghavan Vojdani-Saghir:** Investigation, Writing – original draft. **Sahar Mollazadeh Beidokhti:** Validation, Writing – review & editing. **Simin Nazarnezhad:** Investigation, Writing – original draft. **Zahra Mollaei:** Formal analysis. **Sepideh Hamzehlou:** Writing – review & editing. **Ahmed El-Fiqi:** Conceptualization, Validation, Writing – review & editing. **Francesco Baino:** Validation, Writing – review & editing. **Saeid Kargoazar:** Funding acquisition, Project administration, Resources, Supervision, Writing – review & editing.

Declaration of Competing Interest

The authors have no conflict to declare.

Supplementary materials

Supplementary material associated with this article can be found, in the online version, at doi:[10.1016/j.tranon.2022.101397](https://doi.org/10.1016/j.tranon.2022.101397).

Reference

- [1] L.B. Kennedy, A.K.S. Salama, A review of cancer immunotherapy toxicity, *CA Cancer J. Clin.* 70 (2) (2020) 86–104.
- [2] K. Esfahani, et al., A review of cancer immunotherapy: from the past, to the present, to the future, *Curr. Oncol.* 27 (Suppl 2) (2020) S87–S97.
- [3] Y.H. Xie, Y.X. Chen, J.Y. Fang, Comprehensive review of targeted therapy for colorectal cancer, *Signal Transduct. Target Ther.* 5 (1) (2020) 22.
- [4] Y. Hou, W. Wang, P. Bartolo, A concise review on the role of selenium for bone cancer applications, *Bone* 149 (2021), 115974.
- [5] M. Martinez-Carmona, et al., Lectin-conjugated pH-responsive mesoporous silica nanoparticles for targeted bone cancer treatment, *Acta Biomater.* 65 (2018) 393–404.
- [6] S.I. Schmitz, et al., Superior biocompatibility and comparable osteoinductive properties: sodium-reduced fluoride-containing bioactive glass belonging to the CaO-MgO-SiO₂ system as a promising alternative to 45S5 bioactive glass, *Bioact. Mater.* 5 (1) (2020) 55–65.
- [7] A. Houaoui, et al., Dissolution, bioactivity and osteogenic properties of composites based on polymer and silicate or borosilicate bioactive glass, *Mater. Sci. Eng. C Mater. Biol. Appl.* 107 (2020), 110340.
- [8] J. Mesquita-Guimaraes, et al., Cell adhesion evaluation of laser-sintered HAp and 45S5 bioactive glass coatings on micro-textured zirconia surfaces using MC3T3-E1 osteoblast-like cells, *Mater. Sci. Eng. C Mater. Biol. Appl.* 109 (2020), 110492.
- [9] F. Baino, S. Hamzehlou, S. Kargoazar, Bioactive glasses: where are we and where are we going? *J. Funct. Biomater.* 9 (1) (2018) 25.
- [10] S. Kargoazar, et al., Mesoporous bioactive glasses (MBGs) in cancer therapy: full of hope and promise, *Mater. Lett.* 251 (2019) 241–246.
- [11] M. Miola, et al., Glass-ceramics for cancer treatment: so close, or yet so far? *Acta Biomater.* 83 (2019) 55–70.
- [12] F. Baino, et al., Biomedical radioactive glasses for brachytherapy, *Materials (Basel)* 14 (5) (2021) 1131.
- [13] S. Hooshmand, et al., Mesoporous silica nanoparticles and mesoporous bioactive glasses for wound management: from skin regeneration to cancer therapy, *Materials (Basel)* 14 (12) (2021) 3337.
- [14] S. Kargoazar, et al., Copper-containing bioactive glasses and glass-ceramics: from tissue regeneration to cancer therapeutic strategies, *Mater. Sci. Eng. C* 121 (2021), 111741.
- [15] S.S. Danewalia, K. Singh, Bioactive glasses and glass-ceramics for hyperthermia treatment of cancer: state-of-art, challenges, and future perspectives, *Mater. Today Bio.* 10 (2021), 100100.
- [16] E. El-Meliogy, et al., Novel Fe₂O₃-doped glass /chitosan scaffolds for bone tissue replacement, *Ceram. Int.* 44 (8) (2018) 9140–9151.
- [17] S. Arabyazdi, et al., Synthesis and characterization of CaO-P₂O₅-SiO₂-Li₂O-Fe₂O₃ bioactive glasses: the effect of Li₂O-Fe₂O₃ content on the structure and in-vitro bioactivity, *J. Non Cryst. Solids* 503-504 (2019) 139–150.
- [18] V. Ramalingam, et al., Wet chemical mediated hematite α -Fe₂O₃ nanoparticles synthesis: preparation, characterization and anticancer activity against human metastatic ovarian cancer, *J. Alloys Compd.* (2020) 834.
- [19] X.-Q. Wang, et al., Free radicals for cancer theranostics, *Biomaterials* 266 (2021), 120474.
- [20] S. Zhang, et al., Mechanism of heterogeneous fenton reaction kinetics enhancement under nanoscale spatial confinement, *Environ. Sci. Technol.* 54 (17) (2020) 10868–10875.
- [21] X. Meng, et al., Fenton reaction-based nanomedicine in cancer chemodynamic and synergistic therapy, *Appl. Mater. Today* 21 (2020).
- [22] A. El-Fiqi, H.-W. Kim, Iron ions-releasing mesoporous bioactive glass ultrasmall nanoparticles designed as ferroptosis-based bone cancer nanotherapeutics: ultrasonic-coupled sol-gel synthesis, properties and iron ions release, *Mater. Lett.* 294 (2021).
- [23] ; Available from: O.V. Mazurin, A.I. Priven, SciGlass - Glass Information System - Glass Database - Glass 374 Properties, ITC, Inc., Newton, MA, USA, 2017 <http://www.sciglass.info/>.
- [24] N. Doebelin, R. Kleeberg, Profex: a graphical user interface for the rietveld refinement program BGMN, *J. Appl. Crystallogr.* 48 (Pt 5) (2015) 1573–1580.
- [25] Z. Mollaei, et al., In silico study and experimental evaluation of the solution combustion synthesized manganese oxide (MnO₂) nanoparticles, *Ceram. Int.* (2021).
- [26] T. Kokubo, H. Takadama, How useful is SBF in predicting *in vivo* bone bioactivity? *Biomaterials* 27 (15) (2006) 2907–2915.
- [27] K. Zheng, et al., Aging time and temperature effects on the structure and bioactivity of gel-derived 45S5 glass-ceramics, *J. Am. Ceram. Soc.* 98 (1) (2015) 30–38.
- [28] F. Kermani, et al., Strontium- and cobalt-doped multicomponent mesoporous bioactive glasses (MBGs) for potential use in bone tissue engineering applications, *Materials (Basel)* 13 (6) (2020).
- [29] F. Kermani, et al., Improved osteogenesis and angiogenesis of theranostic ions doped calcium phosphates (CaPs) by a simple surface treatment process: a state-of-the-art study, *Mater. Sci. Eng. C Mater. Biol. Appl.* 124 (2021), 112082.
- [30] F. Kermani, et al., Solution combustion synthesis (SCS) of theranostic ions doped biphasic calcium phosphates; kinetic of ions release in simulated body fluid (SBF) and reactive oxygen species (ROS) generation, *Mater. Sci. Eng. C Mater. Biol. Appl.* 118 (2021), 111533.
- [31] Y. Zhang, et al., Construction of tellurium-doped mesoporous bioactive glass nanoparticles for bone cancer therapy by promoting ROS-mediated apoptosis and antibacterial activity, *J. Colloid Interface Sci.* 610 (2022) 719–730.
- [32] M.M.E. Shakkofa, E.A. Mahdy, H.A. Abo-Mosallam, Thermo-magnetic properties of Fe₂O₃-doped lithium zinc silicate glass-ceramics for magnetic applications, *Ceram. Int.* 47 (18) (2021) 25467–25474.
- [33] I.W. Donald, et al., The influence of Fe₂O₃ and B₂O₃ additions on the thermal properties, crystallization kinetics and durability of a sodium aluminum phosphate glass, *J. Non Cryst. Solids* 352 (28–29) (2006) 2993–3001.
- [34] A. Yazdanpanah, F. Moztarzadeh, Synthesis and characterization of Barium-Iron containing magnetic bioactive glasses: the effect of magnetic component on structure and *in vitro* bioactivity, *Colloids Surf. B* 176 (2019) 27–37.
- [35] M. Zhao, et al., Structural origin of CaO-MgO-Al₂O₃-SiO₂-Fe₂O₃ glass crystallization: iron-containing clusters, *J. Non. Cryst. Solids* (2020) 547.
- [36] E.M. Moreno, et al., Preparation of narrow size distribution superparamagnetic γ -Fe₂O₃ nanoparticles in a sol-gel transparent SiO₂ matrix, *Langmuir* 18 (12) (2002) 4972–4978.
- [37] S. Kargoazar, et al., Functionalization and surface modifications of bioactive glasses (BGs): tailoring of the biological response working on the outermost surface layer, *Materials (Basel)* 12 (22) (2019).
- [38] Y. Zhang, et al., The effect of iron incorporation on the *in vitro* bioactivity and drug release of mesoporous bioactive glasses, *Ceram. Int.* 39 (6) (2013) 6591–6598.
- [39] S.A.M. Abdel-Hameed, F.H. Margha, Preparation, crystallization behavior and magnetic properties of nanoparticles magnetic glass-ceramics in the systems Fe₂O₃ CoO MnO₂, Fe₂O₃ NiO MoO₃ and Fe₂O₃ CoO V₂O₅, *J. Non Cryst. Solids* 358 (4) (2012) 832–838.
- [40] V. Sandu, et al., Effect of Cr₂O₃ on the magnetic properties of magnetite-based glass-ceramics obtained by controlled crystallization of Fe-containing aluminoborosilicate glass, *J. Eur. Ceram. Soc.* 37 (9) (2017) 3089–3099.
- [41] C. Hurd, Varieties of magnetic order in solids, *Contemp. Phys.* 23 (5) (1982) 469–493.
- [42] T. Komatsu, N. Soga, ESR and Mössbauer studies of crystallization process of sodium iron silicate glass, *J. Chem. Phys.* 72 (3) (1980) 1781–1785.
- [43] C. Wu, et al., Multifunctional magnetic mesoporous bioactive glass scaffolds with a hierarchical pore structure, *Acta Biomater.* 7 (10) (2011) 3563–3572.
- [44] F. Baino, et al., Fe-doped sol-gel glasses and glass-ceramics for magnetic hyperthermia, *Materials (Basel)* 11 (1) (2018) 173.
- [45] B.Y. Chang, S.M. Park, Electrochemical impedance spectroscopy, *Annu. Rev. Anal. Chem. (Palo Alto Calif.)* 3 (2010) 207–229.
- [46] D.A. Harrington, The rate-determining step in electrochemical impedance spectroscopy, *J. Electroanal. Chem.* 737 (2015) 30–36.