


 Cite this: *RSC Adv.*, 2020, 10, 21876

# The utilization of Fe-doped g-C<sub>3</sub>N<sub>4</sub> in a heterogeneous photo-Fenton-like catalytic system: the effect of different parameters and a system mechanism investigation†

 Wei Luo,<sup>a</sup> Wenyu Huang,<sup>\*ab</sup> Xiaoqing Feng,<sup>a</sup> Ying Huang,<sup>a</sup> Xiongwei Song,<sup>a</sup> Hongfei Lin,<sup>b</sup> Shuangfei Wang<sup>bc</sup> and Gilles Mailhot<sup>d</sup>

In this study, a series of Fe-doped g-C<sub>3</sub>N<sub>4</sub> (Fe-C<sub>3</sub>N<sub>4</sub>) samples was synthesized and characterized via X-ray powder diffraction (XRD), scanning electron microscopy (SEM), Fourier transform infrared (FTIR) spectroscopy, X-ray photoelectron spectroscopy (XPS), UV-vis diffuse reflection spectroscopy (UV-vis DRS), and photoluminescence (PL) spectroscopy. The photocatalytic activity of the synthesized Fe-C<sub>3</sub>N<sub>4</sub> was investigated toward methylene blue (MB) degradation with hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>) assistance. The results showed that the Fe-C<sub>3</sub>N<sub>4</sub> heterogeneous photo-Fenton-like system showed excellent catalytic performance when the pH value was varied from 3.0 to 9.0. Evaluating the effects of various inorganic anions in the Fe-C<sub>3</sub>N<sub>4</sub> heterogeneous photo-Fenton-like system, HCO<sub>3</sub><sup>-</sup> showed a dual effect on MB degradation, and Cl<sup>-</sup> and NO<sub>3</sub><sup>-</sup> showed an inhibitory effect on MB degradation. Evaluating the effects of inorganic cations, Al<sup>3+</sup>, Mg<sup>2+</sup>, and Ca<sup>2+</sup> strongly inhibited MB degradation. Recycling experiments demonstrated that Fe-C<sub>3</sub>N<sub>4</sub> possesses good reusability and stability. Quenching experiments were carried out, and it was found that hydroxyl radicals (·OH) were the primary active species in the system. Besides, nine intermediates were identified via LC/MS, and a possible MB degradation pathway in the system was proposed. This study could promote the application of this Fe-C<sub>3</sub>N<sub>4</sub> heterogeneous photo-Fenton-like system in realistic dye wastewater.

Received 2nd February 2020

Accepted 18th May 2020

DOI: 10.1039/d0ra00993h

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

Nowadays, advanced oxidation processes (AOPs) are commonly recognized as potential alternative technologies for the treatment of refractory organic pollutants because of their simplicity, high efficiency, and easy handling.<sup>1–5</sup> Among the various available AOPs, the visible-light-induced heterogeneous photo-Fenton-like process is considered an effective method for pollutant treatment. Compared with the traditional Fenton and photo-Fenton processes in homogeneous systems, it has shown many advantages, such as the efficient mineralization of organic pollutants, lower cost, good reusability, excellent chemical stability, and only precipitating small amounts of

iron.<sup>6</sup> However, the strict pH operating range (acidic or near-neutral conditions), high levels of iron leaching (>2 ppm), smaller number of iron active sites, and low cycling efficiency of Fe<sup>3+</sup>/Fe<sup>2+</sup> have limited the application of this process.<sup>7,8</sup> Therefore, exploring a highly efficient and low-cost catalyst for use in this system is essential.

Polymeric graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) as a visible-light-driven photocatalyst has been applied widely in water splitting, organic degradation, and the conversion of CO<sub>2</sub>.<sup>9–11</sup> However, rapid charge recombination has limited its application in AOPs.<sup>12,13</sup> To overcome this drawback, external element doping and copolymerization approaches have been taken into account and proved to be applicable.<sup>14–17</sup> Fe is an environmentally friendly and earth-abundant element. It has been extensively investigated with the aim of improving the photocatalytic performance of g-C<sub>3</sub>N<sub>4</sub> via element doping. Meanwhile, it was certified in previous studies that the photocatalytic activity of g-C<sub>3</sub>N<sub>4</sub> towards dye degradation could be remarkably improved via Fe doping, and Fe can exist in Fe-C<sub>3</sub>N<sub>4</sub> in the form of Fe-N ligands.<sup>18–21</sup> Also, photo-induced electrons from Fe-C<sub>3</sub>N<sub>4</sub> can reduce Fe<sup>3+</sup> to Fe<sup>2+</sup> under visible light illumination.<sup>22</sup> Hence, Fe-C<sub>3</sub>N<sub>4</sub> can work as an efficient catalyst in a heterogeneous photo-Fenton-like system. It has already been reported that Fe-

<sup>a</sup>College of Resources, Environment and Materials, Guangxi University, Nanning 530004, P. R. China. E-mail: [huangwenyu@gxu.edu.cn](mailto:huangwenyu@gxu.edu.cn)

<sup>b</sup>Guangxi Bossco Environmental Protection Technology Co., Ltd, Nanning, 530007, China

<sup>c</sup>Guangxi Key Laboratory of Clean Pulp & Papermaking and Pollution Control, Guangxi University, Nanning 530004, China

<sup>d</sup>Université Clermont Auvergne, CNRS, SIGMA Clermont, Institut de Chimie de Clermont-Ferrand, F-63000 Clermont-Ferrand, France

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra00993h



C<sub>3</sub>N<sub>4</sub> is an active catalyst for the removal of organic pollutants in a photo-Fenton system. However, previous studies have focused on the preparation and optimization of Fe–C<sub>3</sub>N<sub>4</sub> or coupled Fe–C<sub>3</sub>N<sub>4</sub> materials.<sup>23–25</sup> The influence of reaction parameters, especially involving various inorganic ions in natural water, on the activity and degradation pathway of a specific contaminant (MB) in a Fe–C<sub>3</sub>N<sub>4</sub> based photo-Fenton system have not been systematically studied.

In this study, Fe–C<sub>3</sub>N<sub>4</sub> was reported as an efficient photo-Fenton-like photocatalyst for MB degradation under simulated sunlight. Various Fe–C<sub>3</sub>N<sub>4</sub> catalysts with different Fe doping amounts were synthesized and characterized. The effects of essential parameters, including the amount of Fe doping, H<sub>2</sub>O<sub>2</sub> concentration, catalyst dosage, pH, MB concentration, the presence of naturally occurring inorganic ions (Cl<sup>−</sup>, NO<sub>3</sub><sup>−</sup>, HCO<sub>3</sub><sup>−</sup>, Al<sup>3+</sup>, Mg<sup>2+</sup>, and Ca<sup>2+</sup>) and the stability of Fe–C<sub>3</sub>N<sub>4</sub>, were investigated. In addition, scavenging tests were conducted to identify the active species for MB degradation in this catalytic process and, coupled with the intermediates observed *via* LC-MS, a possible degradation pathway for MB was proposed.

## 2. Experimental

### 2.1 Materials

The chemicals used were of commercially available analytical grade and were used as purchased without further purification. Melamine, ferric nitrate (Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O<sub>2</sub>), hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>, 30% w/w), sodium hydroxide (NaOH), hydrochloric acid (HCl), tertiary butanol (TBA), *p*-benzoquinone, sodium chloride (NaCl), sodium bicarbonate (NaHCO<sub>3</sub>), sodium nitrate (NaNO<sub>3</sub>), calcium chloride (CaCl<sub>2</sub>, P96.0%), magnesium chloride (MgCl<sub>2</sub>, P98.0%), aluminum chloride (AlCl<sub>3</sub>, P97.0%), potassium iodide (KI), and methylene blue (MB) were supplied by Nanning Lantian Experiment Equipment Co., Ltd (Nanning, China).

### 2.2 Synthesis of Fe–C<sub>3</sub>N<sub>4</sub>

The Fe–C<sub>3</sub>N<sub>4</sub> catalyst was synthesized according to a method previously reported.<sup>26,27</sup> Typically, 6 g of melamine was dispersed in 30 mL of deionized water under magnetic stirring. Then, different dosages of ferric nitrate (0.03, 0.06, 0.12, and 0.3 g) were added. The mixture was heated to 100 °C to remove water. The obtained solid product was milled and put into a 25 mL crucible, placed into a muffle furnace, and heated to 520 °C, where it was maintained for 2 h. Finally, yellow powder of Fe–C<sub>3</sub>N<sub>4</sub> was obtained. The products were labeled *x* wt% Fe–C<sub>3</sub>N<sub>4</sub>, where *x* was the mass percent of ferric nitrate to melamine. Pristine g-C<sub>3</sub>N<sub>4</sub> was synthesized *via* heating melamine directly under the same conditions without ferric nitrate.

### 2.3 Characterization of the catalyst

XRD with a 40 kV operating voltage and 300 mA current (DX-2700A) was applied to determine the crystal structure of g-C<sub>3</sub>N<sub>4</sub> and *x* wt% Fe–C<sub>3</sub>N<sub>4</sub>. The morphologies of all the catalysts were characterized *via* S-3400N scanning electron microscopy. The functional groups and chemical states of C, N, and Fe on

the catalyst surface were analyzed using a Nicolet iS 50 Fourier transform infrared spectrometer and ESCALAB 250XI+ X-ray photoelectron spectrometer. UV-vis absorption spectra were investigated *via* UV-2501 PC apparatus to determine the light adsorption region of the catalysts. Photoluminescence data were obtained using a ZLX-PL-I fluorescence spectrometer to evaluate the changes in charge carrier recombination in the prepared catalysts.

### 2.4 Experimental procedures

MB was chosen as the model compound to evaluate the efficiency of the heterogeneous photo-Fenton-like system. Investigations into the degradation of MB were conducted in a 250 mL quartz reactor at room temperature under magnetic stirring. MB solutions of different concentrations (20, 30, and 40 mg L<sup>−1</sup>) were prepared. During each experiment, 200 mL of MB was placed in the reactor. The initial pH of the MB solution was either not adjusted (initial pH of 6.86) or it was adjusted with 1 M NaOH and HCl solutions. To achieve adsorption equilibrium, Fe–C<sub>3</sub>N<sub>4</sub> or g-C<sub>3</sub>N<sub>4</sub> was added into MB solution under constant stirring for 30 min in the dark. After that, H<sub>2</sub>O<sub>2</sub> was added, and the suspension was exposed to a 150 W xenon lamp (Fig. S1†). At a given time, about 5 mL of the suspension was removed. The suspension was filtered with a 0.22 μm filter immediately. To investigate the influence of inorganic ions on MB degradation, different concentrations of NaCl, NaNO<sub>3</sub>, NaHCO<sub>3</sub>, CaCl<sub>2</sub>, MgCl<sub>2</sub>, and AlCl<sub>3</sub> were added. To carry out recycling experiments, Fe–C<sub>3</sub>N<sub>4</sub> was removed from solution *via* centrifugation. Then, Fe–C<sub>3</sub>N<sub>4</sub> was washed, dried, and applied in the next operation without purification.

### 2.5 Analytical methods

The absorbance of the MB solution was obtained using a 722N Vis spectrophotometer at the wavelength of 665 nm. The removal efficiency of MB was calculated *via* eqn (1), where *C*<sub>0</sub> and *C* are the initial concentration of MB and the concentration of MB after irradiation for a given time, respectively.

$$\text{Degradation efficiency (\%)} = \frac{C_0 - C}{C_0} \times 100 \quad (1)$$

Kinetics analysis of MB degradation was done using the pseudo-first-order rate model in eqn (2), where *k* is the pseudo-first-order rate constant.

$$\ln\left(\frac{C_0}{C}\right) = kt + \text{constant} \quad (2)$$

The reactive species were investigated *via* trapping experiments. For this, 2 mM TBA, 2 mM *p*-benzoquinone, and 2 mM KI were used as quenchers of ·OH, ·O<sub>2</sub><sup>−</sup>, and h<sup>+</sup>, respectively. Liquid chromatography coupled with tandem mass spectrometry (LC/MS, AGILENT 6460, America) was applied to analyze the reaction intermediates formed during MB degradation. The related testing parameters are referred to in a previous report.<sup>28</sup>

### 3. Results and discussion

#### 3.1 Characterization of g-C<sub>3</sub>N<sub>4</sub> and Fe-C<sub>3</sub>N<sub>4</sub>

The morphologies and structures of g-C<sub>3</sub>N<sub>4</sub> and *x*% Fe-C<sub>3</sub>N<sub>4</sub> were observed *via* SEM (Fig. S2†). The results revealed that all prepared samples had a typical layered structure. The crystal phase structures of g-C<sub>3</sub>N<sub>4</sub> and *x* wt% Fe-C<sub>3</sub>N<sub>4</sub> were investigated *via* XRD, as displayed in Fig. 1(a). Two typical peaks were observed obviously in the XRD patterns of all catalysts. The weak peaks at 13.2° and 27.4° are the (100) and (002) facet diffraction peaks of g-C<sub>3</sub>N<sub>4</sub>, respectively.<sup>29</sup> With an increase in the amount of Fe doping, the diffraction peak intensity of the (002) facet gradually weakened. This phenomenon indicated the inhibitory effects of Fe species on polymeric condensation and host-guest interactions.<sup>27</sup> Furthermore, other characteristic Fe species peaks were not found, which may be caused by the limited amount of doped iron. Therefore, Fe was probably chemically coordinated to the g-C<sub>3</sub>N<sub>4</sub> structure in the form of Fe-N bonds.<sup>30</sup>

The chemical compositions and structures of pristine g-C<sub>3</sub>N<sub>4</sub> and *x* wt% Fe-C<sub>3</sub>N<sub>4</sub> samples were investigated *via* FT-IR spectroscopy. As shown in Fig. 1(b), all materials exhibited characteristic peaks near 3000–3300, 1200–1700, 892, and 806 cm<sup>-1</sup>. Pristine g-C<sub>3</sub>N<sub>4</sub> and *x* wt% Fe-C<sub>3</sub>N<sub>4</sub> samples had similar characteristic peaks. This result indicated that Fe-C<sub>3</sub>N<sub>4</sub> and pristine g-C<sub>3</sub>N<sub>4</sub> had the same structure. The broad peak between 3000 and 3300 cm<sup>-1</sup> was indicative of terminal N-H stretching vibrations. The peak from 1200 to 1700 cm<sup>-1</sup> was due to the characteristic breathing modes of tri-*s*-triazine rings. The peak at 892 cm<sup>-1</sup> was assigned to the cross-linked deformation mode of N-H. Additionally, the peak at 806 cm<sup>-1</sup> was due to tri-*s*-triazine ring breathing vibrations.<sup>31,32</sup>

To analyze the elemental compositions and surface states of *x* wt% Fe-C<sub>3</sub>N<sub>4</sub>, an XPS investigation of 5 wt% Fe-C<sub>3</sub>N<sub>4</sub> was carried out. As shown in Fig. 2(a), four elements were present in the XPS survey spectrum of 5 wt% Fe-C<sub>3</sub>N<sub>4</sub>: C, N, O, and Fe. This result was the same as the EDS analysis, showing that Fe was successfully doped into the structure of 5 wt% Fe-C<sub>3</sub>N<sub>4</sub> (Fig. S3†). The O signal was ascribed to O<sub>2</sub> or H<sub>2</sub>O adsorbed on the surface of 5 wt% Fe-C<sub>3</sub>N<sub>4</sub>.<sup>33</sup> The Fe signal was weak because of the low amount of Fe doping. The C 1s XPS spectrum could be deconvoluted into two peaks with binding energies of 283.7 and

287.3 eV, as shown in Fig. 2(b). The peak at 283.7 eV is the characteristic peak of graphitic carbon (C=C), and the peak at 287.3 eV is ascribed to sp<sup>2</sup> bonded carbon (N-C=C).<sup>3,34</sup> Fig. 2(c) shows that the N 1s XPS spectrum could be deconvoluted into three peaks with binding energies of 397.9, 399.1, and 400.4 eV. The main peak at 397.9 eV is due to sp<sup>2</sup>-bonded N atoms in the triazine rings. The peak at 399.1 eV is attributed to the presence of N-(C)<sub>3</sub> or H-N-(C)<sub>2</sub>. The weaker peak at 400.4 eV is ascribed to -NH<sub>2</sub> or =NH groups.<sup>35</sup> As seen in Fig. 2(d), the O 1s spectrum exhibits one characteristic peak at 531.39 eV, which was ascribed to surface adsorbed water in Fe-C<sub>3</sub>N<sub>4</sub>. Fe-O-Fe and Fe-OH were not found in Fe-C<sub>3</sub>N<sub>4</sub> due to the absence of the characteristic diffraction peak of Fe-O-Fe and Fe-OH at 529.8 eV.<sup>24</sup> Fe 2p<sub>3/2</sub> XPS spectrum of 5% Fe-C<sub>3</sub>N<sub>4</sub> shows a peak centered at 710.4 eV, as shown in Fig. 2(e). The binding energy peak of Fe<sup>3+</sup> is in the range from 710.3 to 711.8 eV. Thus, the primary Fe state on the surface of Fe-C<sub>3</sub>N<sub>4</sub> was Fe<sup>3+</sup>.<sup>23,27,36</sup> Meanwhile, the binding energy of Fe species stabilized in the g-C<sub>3</sub>N<sub>4</sub> structure through Fe-N bonds was close to 710.4 eV.<sup>20,37</sup> Therefore, Fe had been successfully doped into g-C<sub>3</sub>N<sub>4</sub> and Fe<sup>3+</sup> was connected to N atoms *via* Fe-N(III) coordinate bonds.

To estimate the optical properties of all the samples, UV-vis DRS studies were conducted. Fig. 3(a) shows the UV-vis DRS spectra of g-C<sub>3</sub>N<sub>4</sub> and *x* wt% Fe-C<sub>3</sub>N<sub>4</sub>. The band gap energy (*E<sub>g</sub>*) values of the prepared samples were obtained according to Tauc plots,<sup>38</sup> as shown in Fig. 3(b). The *E<sub>g</sub>* values of g-C<sub>3</sub>N<sub>4</sub>, 0.5 wt% Fe-C<sub>3</sub>N<sub>4</sub>, 1 wt% Fe-C<sub>3</sub>N<sub>4</sub>, 2 wt% Fe-C<sub>3</sub>N<sub>4</sub>, and 5 wt% Fe-C<sub>3</sub>N<sub>4</sub> were 2.51, 2.46, 2.44, 2.40, and 2.38 eV, respectively. Light absorbance by all samples was observed to occur in the range of 250–800 nm. As the amount of iron doping increases, the light absorption range gradually increases. This phenomenon indicated that Fe doping could effectively enhance the light-harvesting abilities of g-C<sub>3</sub>N<sub>4</sub>. Pristine g-C<sub>3</sub>N<sub>4</sub> showed an apparent absorption edge at approximately 456 nm. With an increase in the Fe doping, the adsorption edge of Fe-C<sub>3</sub>N<sub>4</sub> displayed an obvious redshift from 456 to 477 nm. This result was caused by the formation of impurity energy levels due to Fe doping.<sup>26</sup>

The transfer and separation efficiencies of photogenerated charge carriers in g-C<sub>3</sub>N<sub>4</sub> and Fe-C<sub>3</sub>N<sub>4</sub> were investigated *via* photoluminescence (PL) measurements. As shown in Fig. 3(c), all samples showed a broad emission peak centered at

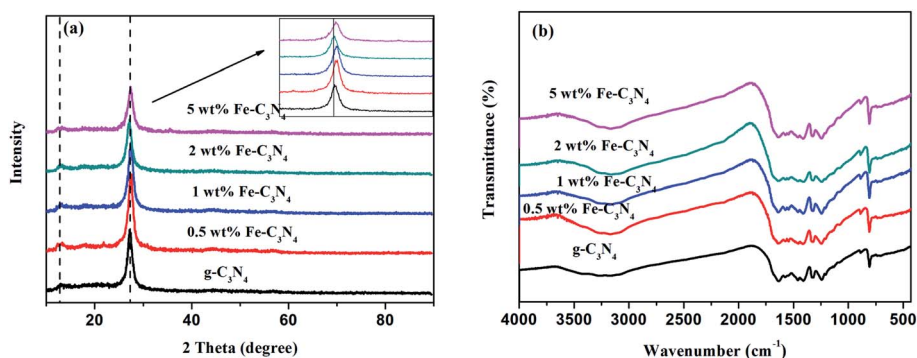


Fig. 1 XRD patterns (a) and FT-IR spectra (b) of g-C<sub>3</sub>N<sub>4</sub> and Fe-C<sub>3</sub>N<sub>4</sub> samples.

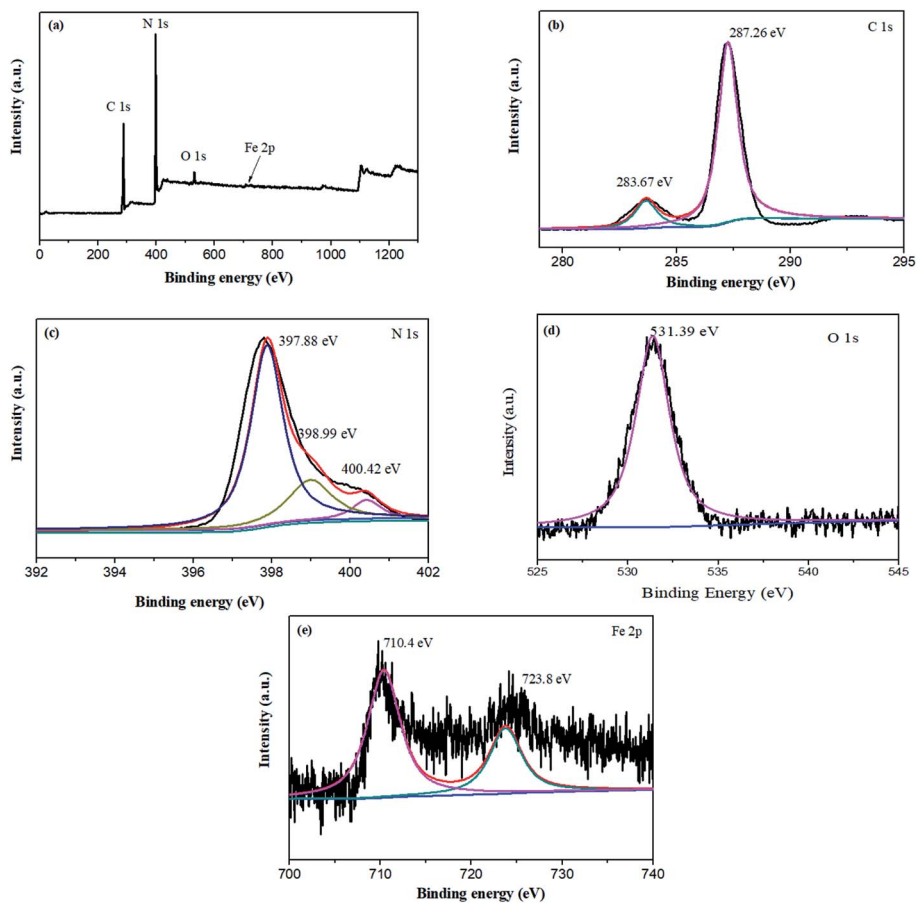


Fig. 2 XPS spectra of the 5 wt% Fe-C<sub>3</sub>N<sub>4</sub> sample: (a) survey scan, (b) C 1s, (c) N 1s, (d) O 1s, and (e) Fe 2p.

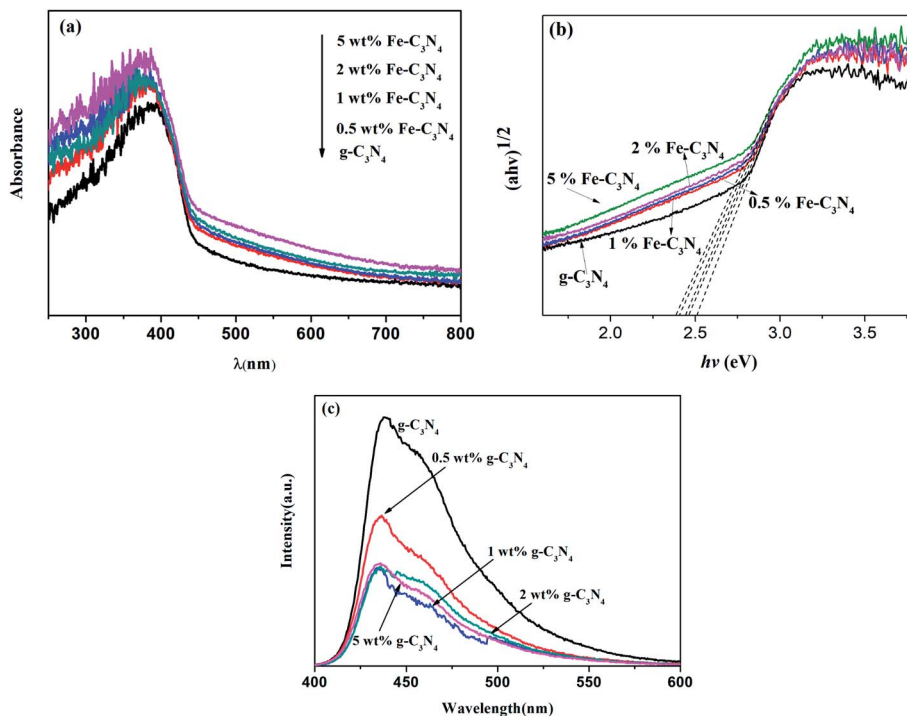


Fig. 3 UV-vis diffuse reflectance spectra (a), Tauc plots (b), and photoluminescence emission spectra (c) of g-C<sub>3</sub>N<sub>4</sub> and Fe-C<sub>3</sub>N<sub>4</sub> samples.

approximately 438 nm. This result was due to the characteristic band-band PL phenomenon involving the photoexcited charge carriers in  $g\text{-C}_3\text{N}_4$ . The peak intensities of  $\text{Fe-C}_3\text{N}_4$  were far weaker than that of pristine  $g\text{-C}_3\text{N}_4$ , obeying the order:  $g\text{-C}_3\text{N}_4 > 0.5\% \text{ Fe-C}_3\text{N}_4 > 5\% \text{ Fe-C}_3\text{N}_4 > 1\% \text{ Fe-C}_3\text{N}_4 \approx 2\% \text{ Fe-C}_3\text{N}_4$ . The separation and transport efficiencies of photoexcited carriers were enhanced by Fe doping. This result suggested that Fe doping sites in the catalyst could trap photogenerated electrons and reduce the recombination of photogenerated electron-hole pairs.<sup>27</sup> However, when the doping content of Fe is excessive, electron-hole recombination centers may be generated to suppress the separation of photogenerated charges.<sup>39</sup>

### 3.2 Catalytic performance of Fe-doped $g\text{-C}_3\text{N}_4$

It was expected that  $\text{Fe-C}_3\text{N}_4$  would show good performance for the removal of organic molecules in the photo-Fenton-like system. Cationic MB was chosen as a model pollutant for evaluating the catalytic activities of the synthesized materials. Experiments involving MB oxidation were conducted without pH control (initial pH = 6.86) and the results are shown in Fig. 4(a). The degradation efficiencies toward MB of  $\text{H}_2\text{O}_2$  in the dark,  $\text{H}_2\text{O}_2$  under simulated sunlight irradiation,  $\text{Fe-C}_3\text{N}_4$  in the dark,  $\text{Fe-C}_3\text{N}_4$  under irradiation, and  $\text{Fe-C}_3\text{N}_4$  assisting  $\text{H}_2\text{O}_2$  in the dark were 5.9%, 45.3%, 4.7%, 42.8%, and 35.8%, respectively. The degradation efficiency toward MB of the  $g\text{-C}_3\text{N}_4$ ,  $\text{H}_2\text{O}_2$ , and simulated sunlight irradiation system was 71.6%. The  $\text{Fe-C}_3\text{N}_4$  heterogeneous photo-Fenton-like system displayed excellent performance towards MB degradation compared to other reaction systems, and the degradation efficiency reached 85.9%. From the results, it was inferred that a synergetic effect was involved between  $\text{Fe-C}_3\text{N}_4$  and  $\text{H}_2\text{O}_2$  under simulated sunlight irradiation. The high MB removal efficiency in the  $\text{Fe-C}_3\text{N}_4$  heterogeneous photo-Fenton-like system may have arisen from the following: (1) the photocatalytic efficiency of  $g\text{-C}_3\text{N}_4$  was improved by Fe doping; (2) the photo-generated electrons of  $\text{Fe-C}_3\text{N}_4$  were captured by  $\text{H}_2\text{O}_2$ , and the separation of photo-generated electrons and holes was enhanced; and (3)  $\text{H}_2\text{O}_2$  was activated to generate  $\cdot\text{OH}$  by photo-generated electrons and the  $\text{Fe}^{3+}/\text{Fe}^{2+}$  cycle under light irradiation.

### 3.3 Effects of reagent doses and pH on the degradation of MB

The effect of the amount of Fe doping on MB degradation was investigated in the range of 0.5–5 wt%, and the results are shown in Fig. 4(b). From the results, increasing the amount of Fe doping had a promoting effect on the degradation of MB. With an increase in the amount of Fe doping from 0.5 wt% to 5 wt%, the MB degradation efficiency increased from 75% to 95%. This result demonstrated that the amount of Fe doping plays a major role in the degradation of MB, and that Fe-N bonds in the catalyst can activate  $\text{H}_2\text{O}_2$  to produce hydroxyl radicals. As the content of  $\text{Fe}^{3+}$  doping increased, more  $\cdot\text{OH}$  was generated in the system for the degradation of MB.

The effect of  $\text{H}_2\text{O}_2$  concentration was investigated in the range of 25 to 200 mM, as shown in Fig. 4(c). The MB

degradation performance was enhanced upon increasing the concentration of  $\text{H}_2\text{O}_2$ . The degradation efficiency increased from 79.2% to 97.1% when the concentration of  $\text{H}_2\text{O}_2$  increased from 25 to 200 mM. This result may be attributed to an increase in the amount of  $\cdot\text{OH}$  produced by  $\text{Fe-C}_3\text{N}_4$  and  $\text{H}_2\text{O}_2$  under simulated sunlight irradiation. However, the degradation efficiency showed little change when the dosage of  $\text{H}_2\text{O}_2$  was increased from 100 to 200 mM. Therefore, there was no requirement to continue increasing the concentration of  $\text{H}_2\text{O}_2$  further.

To investigate the influence of the dosage of  $\text{Fe-C}_3\text{N}_4$ , five different values were tested, as shown in Fig. 4(d). An increase in the  $\text{Fe-C}_3\text{N}_4$  dosage from 0.25 to 2  $\text{g L}^{-1}$  had a promoting effect on the degradation of MB. The degradation efficiency increased significantly from 62.99% to 96.95% within 30 minutes. The number of active sites in the  $\text{Fe-C}_3\text{N}_4$  heterogeneous photo-Fenton-like system affected the degradation rate of MB, and the degradation rate was limited at a low  $\text{Fe-C}_3\text{N}_4$  dosage by reason of a lack of active sites. However, with an increase in the  $\text{Fe-C}_3\text{N}_4$  dosage from 2 to 4  $\text{g L}^{-1}$ , the MB degradation curves showed very similar profiles across 90 minutes. The MB photocatalytic degradation performance was determined by the number of active sites on the catalyst and the penetration of simulated solar irradiation. Upon increasing the dosage of  $\text{Fe-C}_3\text{N}_4$ , the number of active sites is increased and more photoelectrons are generated, resulting in more  $\cdot\text{OH}$  being produced from  $\text{H}_2\text{O}_2$ . However, light reflectance and shielding effects can occur at excess  $\text{Fe-C}_3\text{N}_4$  dosages. Therefore, the degradation efficiency of MB showed no noticeable change with an increase of  $\text{Fe-C}_3\text{N}_4$  from 2 to 4  $\text{g L}^{-1}$ .

The effect of pH within the range of 3–9 on MB degradation in the  $\text{Fe-C}_3\text{N}_4$  heterogeneous photo-Fenton-like system was investigated. As shown in Fig. 4(e), the catalyst remains highly active towards MB degradation over a broad initial pH range, from 3 to 9. When the pH was increased from 3 to 9, the efficiency of MB degradation decreased slightly. Interestingly, in the first 30 min, the heterogeneous photo-Fenton-like system degradation efficiencies at pH = 3, 5, 7, and 9 were 97%, 91%, 85%, and 79%, respectively. This phenomenon was attributed to the formation of different Fe-N ligands in the system. Under acidic conditions, the produced Fe-N ligands were more conducive to the activation of  $\text{H}_2\text{O}_2$  compared to the ligands formed under alkaline conditions. Besides,  $\text{H}_2\text{O}_2$  can be consumed and decomposed to  $\text{H}_2\text{O}$  and  $\text{O}_2$  under alkaline conditions. In general, after 90 min, the MB decolorization rates of all samples were more than 90% as the pH rose from 3 to 9. Hence, the  $\text{Fe-C}_3\text{N}_4$  heterogeneous photo-Fenton-like system showed a wide pH operating range compared to conventional Fenton systems.

The effect of the initial MB concentration on degradation was examined in the range of 20 to 40  $\text{mg L}^{-1}$ . As shown in Fig. 4(f), the MB degradation efficiency within 90 min reached almost 100% at all increasing MB concentrations from 20 to 40  $\text{mg L}^{-1}$ . However, in the first 30 min, the degradation efficiency decreased from 96.7% to 53.9% as the MB concentration was increased from 20 to 40  $\text{mg L}^{-1}$ . This result was attributed to the number of active species. With an increase in the initial

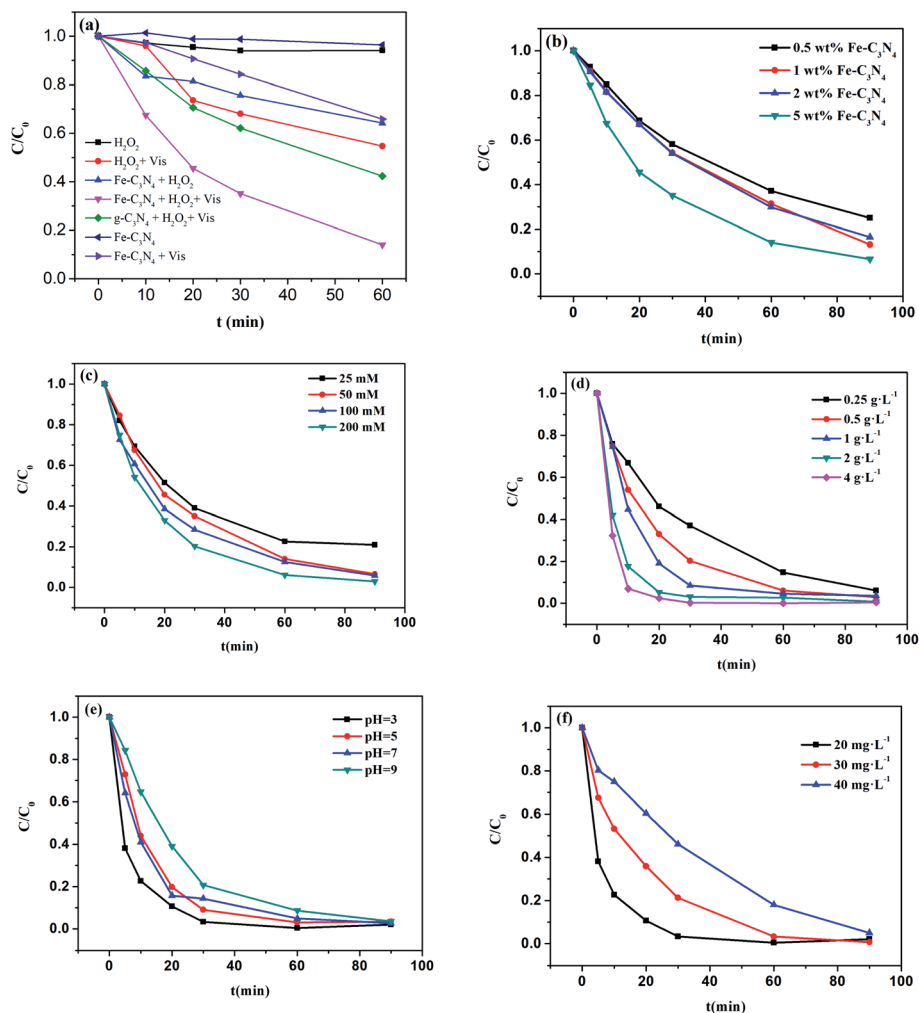


Fig. 4 The decolorization of MB in different systems (a), the effect of the amount of Fe doping (b), the effect of  $\text{H}_2\text{O}_2$  concentration (c), the effect of catalyst dosage (d), the effect of pH (e), and the effect of the MB initial concentration (f). Experimental conditions: (a)  $[\text{MB}] = 20 \text{ mg L}^{-1}$ ,  $[5 \text{ wt\% Fe-C}_3\text{N}_4] = 0.5 \text{ g L}^{-1}$ ,  $[\text{H}_2\text{O}_2] = 50 \text{ mM}$ ,  $\text{pH} = 6.86$ ; (b)  $[\text{MB}] = 20 \text{ mg L}^{-1}$ ,  $[\text{Fe-C}_3\text{N}_4] = 0.5 \text{ g L}^{-1}$ ,  $[\text{H}_2\text{O}_2] = 50 \text{ mM}$ ,  $\text{pH} = 6.86$ ; (c)  $[\text{MB}] = 20 \text{ mg L}^{-1}$ ,  $[5 \text{ wt\% Fe-C}_3\text{N}_4] = 0.5 \text{ g L}^{-1}$ ,  $\text{pH} = 6.86$ ; (d)  $[\text{MB}] = 20 \text{ mg L}^{-1}$ ,  $[\text{H}_2\text{O}_2] = 200 \text{ mM}$ ,  $\text{pH} = 6.86$ ; (e)  $[\text{MB}] = 20 \text{ mg L}^{-1}$ ,  $[5 \text{ wt\% Fe-C}_3\text{N}_4] = 2 \text{ g L}^{-1}$ ,  $[\text{H}_2\text{O}_2] = 200 \text{ mM}$ ; and (f)  $[5 \text{ wt\% Fe-C}_3\text{N}_4] = 2 \text{ g L}^{-1}$ ,  $[\text{H}_2\text{O}_2] = 200 \text{ mM}$ ,  $\text{pH} = 3$ .

MB concentration, more active species were required for the degradation of MB. However, the number of active species in the system theoretically remained constant at a fixed Fe-C<sub>3</sub>N<sub>4</sub> dosage, H<sub>2</sub>O<sub>2</sub> concentration, and light intensity. Thus, the number of active species was inadequate for higher MB concentrations.

### 3.4 Effects of inorganic ions on the degradation of MB

Various inorganic ions may co-exist with dye wastewater. Thus, examining the effects of co-existing ions on MB degradation is very important and beneficial for a realistic dye treatment process. Previous studies have confirmed that the presence of some inorganic ions in the photocatalytic system can affect the degradation of MB.<sup>40–43</sup> To investigate the effects of various co-existing inorganic ions on MB degradation, the photocatalytic degradation of MB was conducted with six typical inorganic ions: nitrate ( $\text{NO}_3^-$ ), chloride ( $\text{Cl}^-$ ), bicarbonate ( $\text{HCO}_3^-$ ),

aluminum ( $\text{Al}^{3+}$ ), magnesium ( $\text{Mg}^{2+}$ ), and calcium ( $\text{Ca}^{2+}$ ). Considering that natural water does not contain buffer solution, and that the introduction of buffer solution will make the system more complicated, the influence of inorganic ions was not investigated in buffer solution.

The effect of  $\text{Cl}^-$  on the degradation of MB in the Fe-C<sub>3</sub>N<sub>4</sub> heterogeneous photo-Fenton-like system was investigated at different  $\text{Cl}^-$  concentrations from 0 to 100 mM. Fig. 5(a) shows that the efficient degradation of MB was inhibited by  $\text{Cl}^-$ . Adding different concentrations of  $\text{Cl}^-$  obviously decreased the  $k$  value of the MB degradation rate (Fig. 5(a) and Table S1†). The  $k$  value of the MB degradation rate decreased from  $0.0302$  to  $0.0187 \text{ min}^{-1}$  upon increasing the concentration of  $\text{Cl}^-$  from 0 to 100 mM. This phenomenon could be attributed to the reaction of  $\cdot\text{OH}$  with  $\text{Cl}^-$ , which generated  $\text{ClOH}^{\cdot-}$  (eqn (3)), whose reactivity is not as high as  $\cdot\text{OH}$ . Under these circumstances,  $\text{Cl}^-$  act as an  $\cdot\text{OH}$  scavenger, inhibiting MB degradation.<sup>43</sup>

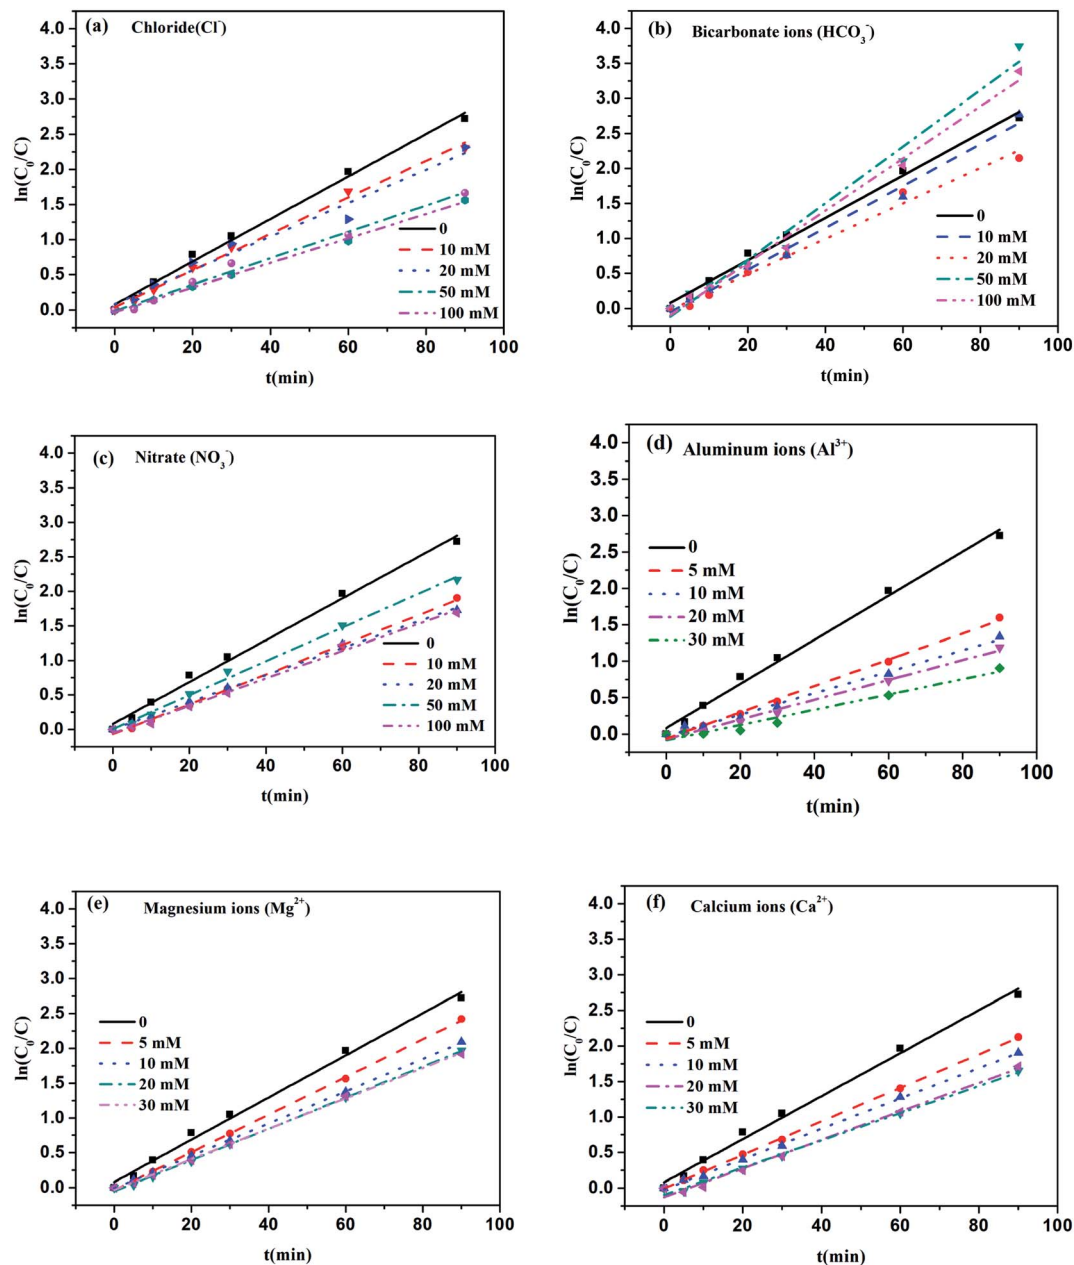










Fig. 5 Effects of inorganic anions and cations on MB degradation under simulated solar light irradiation. Experimental conditions: [MB] = 20 mg L<sup>-1</sup>; [5 wt% Fe-C<sub>3</sub>N<sub>4</sub>] = 0.5 g L<sup>-1</sup>; no pH adjustment (original pH = 6.86); [Cl<sup>-</sup>] (a), [HCO<sub>3</sub><sup>-</sup>] (b), and [NO<sub>3</sub><sup>-</sup>] (c) = 10, 20, 50, and 100 mM; [Al<sup>3+</sup>] (d), [Mg<sup>2+</sup>] (e), and [Ca<sup>2+</sup>] (f) = 5, 10, 20, and 30 mM.

Fig. 5(b) shows the effect of HCO<sub>3</sub><sup>-</sup> on MB degradation in the Fe-C<sub>3</sub>N<sub>4</sub> heterogeneous photo-Fenton-like system. With an increase in the HCO<sub>3</sub><sup>-</sup> concentration from 0 to 20 mM, the *k* value of the MB degradation rate decreased from 0.0303 to 0.0299 min<sup>-1</sup> (Table S1†). However, the *k* value improved with a further increase in the HCO<sub>3</sub><sup>-</sup> concentration. It has been found that HCO<sub>3</sub><sup>-</sup> could react with <sup>•</sup>OH to produce the carbonate radical (CO<sub>3</sub><sup>-•</sup>) (eqn (4)). Meanwhile, the ionization reactions of carbonic acid to reach equilibration can occur (eqn (5)–(8)),<sup>43</sup> and the concentration of HCO<sub>3</sub><sup>-</sup> could influence the pH of the reaction system. Therefore, the effect of different HCO<sub>3</sub><sup>-</sup> concentrations on the degradation of MB can be

explained based on the following reasons: (1) at a low HCO<sub>3</sub><sup>-</sup> concentration (10 and 20 mM), HCO<sub>3</sub><sup>-</sup> mostly plays the role of being an <sup>•</sup>OH scavenger, and the produced CO<sub>3</sub><sup>-•</sup> is not involved in the degradation of MB. The degradation rate of MB decreased due to <sup>•</sup>OH scavenging; (2) at a high HCO<sub>3</sub><sup>-</sup> concentration (50 and 100 mM), the degradation rate increased because abundant CO<sub>3</sub><sup>-•</sup> was produced and participated in MB degradation. Besides, with an increase in the HCO<sub>3</sub><sup>-</sup> concentration, the pH of the reaction system changed from neutral to alkaline, which could result in negatively charged Fe-C<sub>3</sub>N<sub>4</sub>, so more MB molecules could be contacted and degraded.

As for  $\text{NO}_3^-$ , Fig. 5(c) shows how the MB degradation rate  $k$  value varies at different concentrations from 0 to 100 mM.  $\text{NO}_3^-$  showed an inhibitory effect on the Fe- $\text{C}_3\text{N}_4$  heterogeneous photo-Fenton system. With an increase in the  $\text{NO}_3^-$  concentration from 0 to 20 mM, the  $k$  value of the MB degradation rate decreased from 0.0303 to 0.0195  $\text{min}^{-1}$  (Table S1†). This result might be attributed to a reaction between  $\cdot\text{OH}$  and  $\text{NO}_3^-$ .  $\cdot\text{OH}$  could react with  $\text{NO}_3^-$  to produce the nitrate radical ( $\text{NO}_3^{\cdot-}$ ) (eqn (9)), whose redox ability is weaker than  $\cdot\text{OH}$ .<sup>43</sup> However, when the  $\text{NO}_3^-$  concentration was further increased from 20 to 50 mM, the  $k$  value of the MB degradation rate increased from 0.0195 to 0.0245  $\text{min}^{-1}$ . When the concentration of  $\text{NO}_3^-$  was more than 20 mM, the  $k$  value of MB degradation was improved. This phenomenon might be due to the formation of  $\cdot\text{OH}$  under simulated solar irradiation (eqn (10)).<sup>43</sup> Interestingly, upon further increasing the  $\text{NO}_3^-$  concentration to 100 mM, the  $k$  value of MB degradation rate decreased to 0.0198  $\text{min}^{-1}$ . When the concentration of  $\text{NO}_3^-$  was further increased, more  $\cdot\text{OH}$  was consumed by  $\text{NO}_3^-$  rather than being produced. Therefore, the MB removal efficiency was irregularly inhibited by  $\text{NO}_3^-$ .

The influence of inorganic cations on the degradation of MB in the Fe- $\text{C}_3\text{N}_4$  heterogeneous photo-Fenton system was investigated at various concentrations from 0 to 30 mM. Inorganic cations, including  $\text{Al}^{3+}$ ,  $\text{Mg}^{2+}$ , and  $\text{Ca}^{2+}$ , exhibited an inhibitory effect on the degradation of MB, as shown in Fig. 5(d–f) and Table S2.† Among the three kinds of cations,  $\text{Al}^{3+}$  ions showed the strongest negative effect on the  $k$  value of the MB degradation rate; the  $k$  value decreased from 0.0303 to 0.0105  $\text{min}^{-1}$  upon increasing the concentration of  $\text{Al}^{3+}$  from 5 to 30 mM. Compared with  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$ , the  $k$  value decreased 2.88-fold with 30 mM  $\text{Al}^{3+}$  addition. This result could be explained based on  $\text{Al}^{3+}$ ,  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  being absorbed onto the Fe- $\text{C}_3\text{N}_4$  surface. At the same time, the accompanying shielding effect, reduction in the number of active sites, and reduced penetration of light irradiation caused the low photocatalytic efficiency.<sup>42,44–47</sup>



### 3.5 Stability of the Fe- $\text{C}_3\text{N}_4$ catalyst

Focusing on the practical application of the Fe- $\text{C}_3\text{N}_4$  heterogeneous photo-Fenton-like system, the stability of the catalyst was

examined. As shown in the results in Fig. 6(a), the MB degradation efficiency was still more than 90% within 90 min after three cycles. The residual amount of iron ions in solution after the reaction was measured *via* atomic absorption spectrophotometry (AA-700, Shimadzu International Trading Co., Ltd.), and the concentration of iron ion was 0.4781  $\text{mg L}^{-1}$ . The concentration of leached Fe was lower than the drinking water limitations in the EU and US (<2 ppm).<sup>8,23,48</sup> Also, XRD results from used Fe- $\text{C}_3\text{N}_4$  showed that the XRD pattern of Fe- $\text{C}_3\text{N}_4$  had not obviously changed, as shown in Fig. 6(b). These results demonstrated that Fe- $\text{C}_3\text{N}_4$  has good reusability and stability.

### 3.6 Degradation mechanism of the Fe- $\text{C}_3\text{N}_4$ heterogeneous photo-Fenton-like system

It was considered that MB molecules were broken up and degraded into smaller molecules in the Fe- $\text{C}_3\text{N}_4$  heterogeneous photo-Fenton-like system. To demonstrate this hypothesis, UV-vis absorption spectra were obtained, as shown in Fig. 7(a). The results showed the MB spectral absorption variations with irradiation time. Two main absorbance peaks were observed at 665 and 290 nm. The peak at 665 nm was attributed to the chromophore ( $-\text{C}=\text{S}$ ) of MB, and the peak at 290 nm was attributed to the unsaturated conjugated aromatic rings.<sup>28,49,50</sup> It was evident that the adsorption peaks at 665 and 290 nm decreased significantly with irradiation time, suggesting that the conjugate structure of MB was destroyed and the aromatic rings of MB were degraded in the system. Besides, as the reaction time increased, the position of the maximum absorbance peak at 665 nm did not shift. Related research has shown that blue-shifting of the MB peak at 665 nm is related to the occurrence of *N*-demethylation intermediates of MB.<sup>28</sup> Thus, we inferred that the initial step of MB degradation in the Fe- $\text{C}_3\text{N}_4$  heterogeneous photo-Fenton system might not involve *N*-demethylation. To investigate the reactive MB degradation species in the system, quenching experiments involving TBA, KI and 1,4-benzoquinone were conducted.<sup>51</sup> As shown in Fig. 7(b), in the first 30 min, the MB degradation efficiency decreased from 96.7% to 93.2%, 86.1%, and 75.3% after adding 1,4-benzoquinone, KI, and TBA, respectively. It was found that 1,4-benzoquinone had little effect on MB removal in this system, and TBA showed a significant inhibitory effect on MB degradation. This result implies the fact that  $\cdot\text{OH}$  is a primary active species in the system. When 1,4-benzoquinone was added to the reaction system, the degradation efficiency of MB was mildly affected, but it did not decrease within 30 min and was nearly similar to the performance of the control experiment. This result demonstrated that  $\text{O}_2^{\cdot-}$  was rarely or not at all formed in this reaction system. However, the MB degradation efficiency was enhanced when 1,4-benzoquinone was added into the catalytic system in the first 20 min. This phenomenon may be due to the activation of  $\text{H}_2\text{O}_2$  by 1,4-benzoquinone. Several literature studies have reported that peroxydisulfate and  $\text{H}_2\text{O}_2$  can be activated by organic quinones. For instance, Zhou *et al.* found that peroxymonosulfate could be activated by benzoquinone.<sup>52</sup> Fang *et al.* reported that 1,4-benzoquinone, 2-methyl-1,4-benzoquinone, and 2-chloro-1,4-benzoquinone could



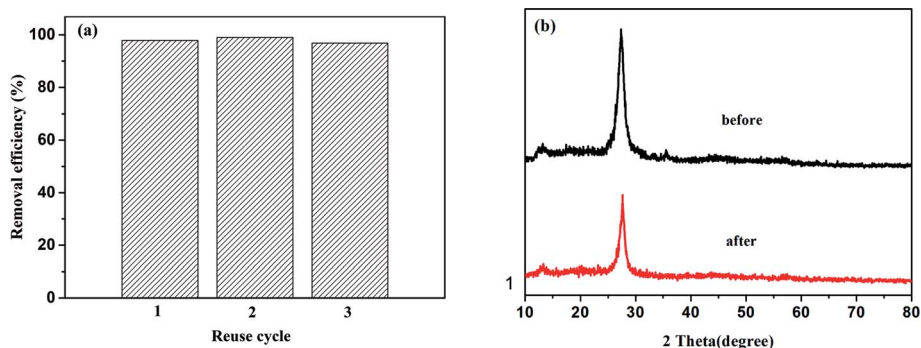


Fig. 6 The degradation efficiency of MB during recycling experiments (a) and XRD survey scans of Fe-C<sub>3</sub>N<sub>4</sub> before and after the decolorization of MB in the Fe-C<sub>3</sub>N<sub>4</sub> heterogenous photo-Fenton-like system (b). Experimental conditions: (a) and (b) [MB] = 20 mg L<sup>-1</sup>, [5 wt% Fe-C<sub>3</sub>N<sub>4</sub>] = 2 g L<sup>-1</sup>, [H<sub>2</sub>O<sub>2</sub>] = 200 mM, pH = 3.

enhance the 2,4,4'-trichlorobiphenyl degradation efficiency when using peroxydisulfate.<sup>53</sup> Zhu *et al.* reported that halogenated quinones could activate H<sub>2</sub>O<sub>2</sub> to produce  $\cdot\text{OH}$ .<sup>54</sup> Besides, Chen *et al.* investigated the degradation of tetracycline using H<sub>2</sub>O<sub>2</sub> alone, and a similar phenomenon was found: the tetracycline degradation efficiency was enhanced in the first 45 min when benzoquinone was added into the catalytic system.<sup>55</sup>

For degradation pathway analysis, the intermediate products resulting from MB degradation over 60 min were analyzed *via* LC-MS. According to the results, nine primary intermediate product ions at *m/z* values of 305.16, 301.17, 143.09, 135.12, 130.16, 109.10, 95.09, 93.04, and 75.03 were detected at different retention times, which probably correspond to C<sub>16</sub>H<sub>23</sub>N<sub>3</sub>SO, C<sub>16</sub>H<sub>19</sub>N<sub>3</sub>SO, C<sub>6</sub>H<sub>6</sub>O<sub>4</sub>, C<sub>7</sub>H<sub>5</sub>NS, C<sub>6</sub>H<sub>13</sub>NO<sub>2</sub>, C<sub>6</sub>H<sub>7</sub>NO, C<sub>6</sub>H<sub>6</sub>O, C<sub>6</sub>H<sub>7</sub>N, and C<sub>2</sub>H<sub>2</sub>O<sub>3</sub>, respectively (Table S3<sup>†</sup>). It has been confirmed that the benzene ring of MB could be hydroxylated by  $\cdot\text{OH}$  in previous work.<sup>28,56,57</sup> However, we did not observe the corresponding intense fragments in this study. Thus,  $\cdot\text{OH}$  may play a role in aromatic ring-opening and oxidation. Meanwhile, based on intermediates from previous work,<sup>58-65</sup> the possible pathway of MB degradation in the Fe-C<sub>3</sub>N<sub>4</sub> heterogenous photo-Fenton-like system is proposed in Fig. S4.<sup>†</sup> Cl in the MB molecule was firstly ionized, and after that C-N<sup>+</sup>=C and C-S<sup>+</sup>-C were

destroyed. Then, the -N=(CH<sub>3</sub>)<sub>2</sub> groups were also degraded, inducing the breakup of the aromatic rings. In the process, intermediates such as DL-norleucine, phenol, and benzothiadiazole were produced, which were partly further mineralized to carbon dioxide, water, and inorganic anions (SO<sub>4</sub><sup>2-</sup>, NH<sub>4</sub><sup>+</sup>, and NO<sub>3</sub><sup>-</sup>).

The XPS results showed that Fe(III)-N was the main active site for the photo-Fenton-like reaction. By combining the XPS results and previous work,<sup>23,66,67</sup> we propose a possible mechanism in this catalytic system (Fig. 8). There are two pathways for generating  $\cdot\text{OH}$  (eqn 11-13): (1) Fe-C<sub>3</sub>N<sub>4</sub> was excited to generate electrons and holes under simulated sunlight. Fe(III)-N accepted electrons and transformed to Fe(II)-N. Fe(II)-N and H<sub>2</sub>O<sub>2</sub> combined to generate Fe(III)-N and  $\cdot\text{OH}$  *via* electron transfer. At the same time, a series of chain reactions was initiated, including the formation of redox cycles of  $\cdot\text{OH}$  and Fe(III)/Fe(II); (2) H<sub>2</sub>O<sub>2</sub> decomposed to  $\cdot\text{OH}$  under simulated sunlight and was activated by photogenerated electrons from Fe-C<sub>3</sub>N<sub>4</sub>. Theoretically, the VB of g-C<sub>3</sub>N<sub>4</sub> is at +1.57 V and the redox potential of  $\cdot\text{OH}/\text{OH}^-$  is +1.99 V. Thus,  $\cdot\text{OH}$  cannot be generated from VB holes in g-C<sub>3</sub>N<sub>4</sub>. In the Fe-C<sub>3</sub>N<sub>4</sub> heterogenous photo-Fenton-like system, MB was absorbed on the surface of Fe-C<sub>3</sub>N<sub>4</sub> firstly. Then, MB was attacked by  $\cdot\text{OH}$  and

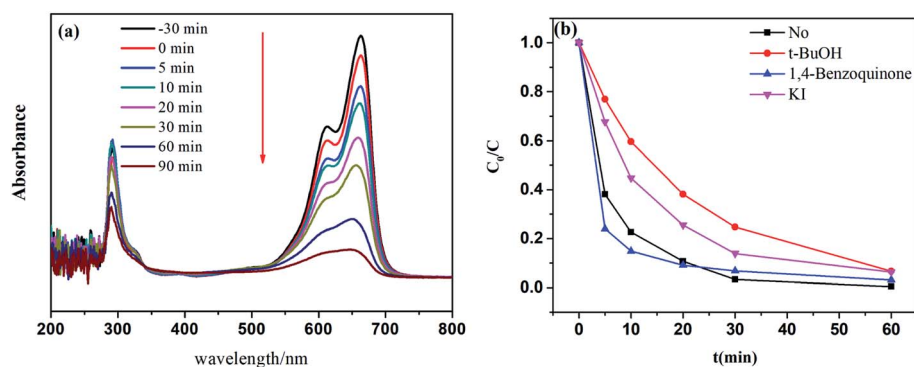


Fig. 7 The temporal evolution of UV-vis spectra during the decolorization of MB in the Fe-C<sub>3</sub>N<sub>4</sub> heterogenous photo-Fenton-like system (a) and influence of radical scavengers on the decolorization of MB (b). Experimental conditions: (a) [MB] = 20 mg L<sup>-1</sup>, [5 wt% Fe-C<sub>3</sub>N<sub>4</sub>] = 0.5 g L<sup>-1</sup>, [H<sub>2</sub>O<sub>2</sub>] = 50 mM, pH = 3; (b) [MB] = 20 mg L<sup>-1</sup>, [5 wt% Fe-C<sub>3</sub>N<sub>4</sub>] = 2 g L<sup>-1</sup>, [H<sub>2</sub>O<sub>2</sub>] = 200 mM, [t-BuOH] = 2 mM, [1,4-benzoquinone] = 2 mM, [KI] = 2 mM, pH = 3.




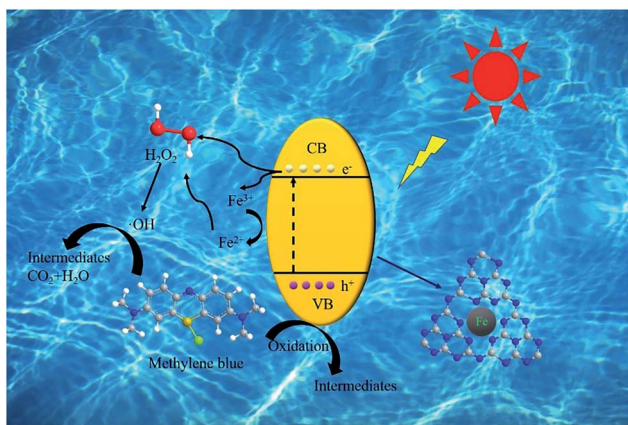


Fig. 8 A schematic diagram of the Fe-C<sub>3</sub>N<sub>4</sub> catalyzed heterogeneous photo-Fenton-like reaction.

transformed into small organic molecules, inorganic ions, CO<sub>2</sub>, and H<sub>2</sub>O.



## 4. Conclusions

In this study, Fe-C<sub>3</sub>N<sub>4</sub> was fabricated and applied in a heterogeneous photo-Fenton-like system. Fe-C<sub>3</sub>N<sub>4</sub> exhibited superb performance for the degradation of MB in the pH range of 3–9. The effects of various inorganic ions on the degradation of MB were studied; Cl<sup>-</sup> and NO<sub>3</sub><sup>-</sup> inhibited the degradation of MB and HCO<sub>3</sub><sup>-</sup> exhibited a dual effect. The presence of cations (Al<sup>3+</sup>, Mg<sup>2+</sup>, and Ca<sup>2+</sup>) inhibits the degradation of MB, and the order of the inhibitory effect was: Al<sup>3+</sup> > Ca<sup>2+</sup> > Mg<sup>2+</sup>. Catalyst cycling experiments illustrated that Fe-C<sub>3</sub>N<sub>4</sub> was highly stable, showing the consistently high degradation of MB. According to quenching experiments, the dominant active species was ·OH. In short, this photo-assisted heterogeneous Fenton-like process showed the highly efficient removal of MB while overcoming common issues that occur in conventional Fenton systems.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This study was funded by the National Natural Science Foundation of China (grant number 21367003), Guangxi Major Project Science and Technology (grant number AA17129001), and Guangxi Key Laboratory of Clean Pulp & Papermaking and Pollution Control Open Foundation (grant number KF201724).

## References

- 1 D. B. Miklos, C. Remy, M. Jekel, K. G. Linden, J. E. Drewes and U. Hübner, *Water Res.*, 2018, **139**, 118–131.
- 2 T. Guo, K. Wang, G. Zhang and X. Wu, *Appl. Surf. Sci.*, 2019, **469**, 331–339.
- 3 Z. Xiong, Z. Wang, M. Muthu and Y. Zhang, *J. Hazard. Mater.*, 2019, **373**, 565–571.
- 4 S. Yang, P. Wu, J. Liu, M. Chen, Z. Ahmed and N. Zhu, *Chem. Eng. J.*, 2018, **350**, 484–495.
- 5 J. Liu, P. Wu, S. Yang, S. Rehman, Z. Ahmed, N. Zhu, Z. Dang and Z. Liu, *Appl. Catal., B*, 2020, **261**, 118232.
- 6 C. Cai, Z. Zhang, J. Liu, N. Shan, H. Zhang and D. D. Dionysiou, *Appl. Catal., B*, 2016, **182**, 456–468.
- 7 X. Y. Li, Y. H. Pi, L. Q. Wu, Q. B. Xia, J. L. Wu, Z. Li and J. Xiao, *Appl. Catal., B*, 2017, **202**, 653–663.
- 8 X. Li, X. Liu, L. Xu, Y. Wen, J. Ma and Z. Wu, *Appl. Catal., B*, 2015, **165**, 79–86.
- 9 J. Fu, J. Yu, C. Jiang and B. Cheng, *Adv. Energy Mater.*, 2018, **8**, 1701503.
- 10 Z. Sun, H. Wang, Z. Wu and L. Wang, *Catal. Today*, 2018, **300**, 160–172.
- 11 X. Zhang, X. Zhang, J. Li, J. Sun, J. Bian, J. Wang, Y. Qu, R. Yan, C. Qin and L. Jing, *Appl. Catal., B*, 2018, **237**, 50–58.
- 12 A. Nikokavoura and C. Trapalis, *Appl. Surf. Sci.*, 2018, **430**, 18–52.
- 13 Y. Yu, W. Yan, X. Wang, P. Li, W. Gao, H. Zou, S. Wu and K. Ding, *Adv. Mater.*, 2018, **30**, 1705060.
- 14 X. Ma, Y. Lv, J. Xu, Y. Liu, R. Zhang and Y. Zhu, *J. Phys. Chem. C*, 2012, **116**, 23485–23493.
- 15 J. Jiang, S. Cao, C. Hu and C. Chen, *Chin. J. Catal.*, 2017, **38**, 1981–1989.
- 16 W. Yan, L. Yan and C. Jing, *Appl. Catal., B*, 2019, **244**, 475–485.
- 17 Y. Wang, S. Zhao, Y. Zhang, W. Chen, S. Yuan, Y. Zhou and Z. Huang, *Appl. Surf. Sci.*, 2019, **463**, 1–8.
- 18 S. Hu, L. Ma, J. You, F. Li, Z. Fan, G. Lu, D. Liu and J. Gui, *Appl. Surf. Sci.*, 2014, **311**, 164–171.
- 19 Q. Liu, T. Chen, Y. Guo, Z. Zhang and X. Fang, *Appl. Catal., B*, 2017, **205**, 173–181.
- 20 J. Gao, Y. Wang, S. Zhou, W. Lin and Y. Kong, *ChemCatChem*, 2017, **9**, 1708–1715.
- 21 W. D. Oh, V. W. C. Chang, Z.-T. Hu, R. Goei and T. T. Lim, *Chem. Eng. J.*, 2017, **323**, 260–269.
- 22 X. Chen, J. Zhang, X. Fu, M. Antonietti and X. Wang, *J. Am. Chem. Soc.*, 2009, **131**, 11658–11659.
- 23 J. Ma, Q. Yang, Y. Wen and W. Liu, *Appl. Catal., B*, 2017, **201**, 232–240.
- 24 X. Qian, Y. Wu, M. Kan, M. Fang, D. Yue, J. Zeng and Y. Zhao, *Appl. Catal., B*, 2018, **237**, 513–520.
- 25 X. Li, Y. Pi, L. Wu, Q. Xia, J. Wu, Z. Li and J. Xiao, *Appl. Catal., B*, 2017, **202**, 653–663.
- 26 X. Song, H. Tao, L. Chen and Y. Sun, *Mater. Lett.*, 2014, **116**, 265–267.
- 27 S. Hu, R. Jin, G. Lu, D. Liu and J. Gui, *RSC Adv.*, 2014, **4**, 24863–24869.

- 28 Y. Liu, W. Jin, Y. Zhao, G. Zhang and W. Zhang, *Appl. Catal., B*, 2017, **206**, 642–652.
- 29 S. Yan, Z. Li and Z. Zou, *Langmuir*, 2009, **25**, 10397–10401.
- 30 H. Li, C. Shan and B. Pan, *Environ. Sci. Technol.*, 2018, **52**, 2197–2205.
- 31 K. Wang, Q. Li, B. Liu, B. Cheng, W. Ho and J. Yu, *Appl. Catal., B*, 2015, **176–177**, 44–52.
- 32 Y. Cui, Z. Ding, P. Liu, M. Antonietti, X. Fu and X. Wang, *Phys. Chem. Chem. Phys.*, 2012, **14**, 1455–1462.
- 33 S. Hu, X. Chen, Q. Li, F. Li, Z. Fan, H. Wang, Y. Wang, B. Zheng and G. Wu, *Appl. Catal., B*, 2017, **201**, 58–69.
- 34 X. Du, X. Yi, P. Wang, J. Deng and C.-c. Wang, *Chin. J. Catal.*, 2019, **40**, 70–79.
- 35 A. Mirzaei, Z. Chen, F. Haghghat and L. Yerushalmi, *Appl. Catal., B*, 2019, **242**, 337–348.
- 36 M. Chen, P. Wu, L. Yu, S. Liu, B. Ruan, H. Hu, N. Zhu and Z. Lin, *J. Environ. Manag.*, 2017, **192**, 31–38.
- 37 X. Wang, X. Chen, A. Thomas, X. Fu and M. Antonietti, *Adv. Mater.*, 2009, **21**, 1609–1612.
- 38 T. Guo, K. Wang, G. Zhang and X. Wu, *Appl. Surf. Sci.*, 2019, **469**, 331–339.
- 39 W. J. Ong, L. L. Tan, Y. H. Ng, S.-T. Yong and S. P. Chai, *Chem. Rev.*, 2016, **116**, 7159–7329.
- 40 C. Guillard, H. Lachheb, A. Houas, M. Ksibi, E. Elaloui and J.-M. Herrmann, *J. Photochem. Photobiol. Chem.*, 2003, **158**, 27–36.
- 41 A. G. Rincón and C. Pulgarin, *Appl. Catal., B*, 2004, **51**, 283–302.
- 42 I. K. Konstantinou and T. A. Albanis, *Appl. Catal., B*, 2004, **49**, 1–14.
- 43 C. Hu, J. C. Yu, Z. Hao and P. K. Wong, *Appl. Catal., B*, 2003, **46**, 35–47.
- 44 X. Gao, X. Zhang, Y. Wang, S. Peng, B. Yue and C. Fan, *Chem. Eng. J.*, 2015, **273**, 156–165.
- 45 S. Liu, P. Wu, M. Chen, L. Yu, C. Kang, N. Zhu and Z. Dang, *Environ. Pollut.*, 2017, **228**, 277–286.
- 46 C. Liu, P. Wu, Y. Zhu and L. Tran, *Chemosphere*, 2016, **144**, 1026–1032.
- 47 L. Chen, P. Wu, M. Chen, X. Lai, Z. Ahmed, N. Zhu, Z. Dang, Y. Bi and T. Liu, *Appl. Clay Sci.*, 2018, **159**, 74–82.
- 48 X. J. Yang, X. M. Xu, J. Xu and Y.-f. Han, *J. Am. Chem. Soc.*, 2013, **135**, 16058–16061.
- 49 Y. Li and F. S. Zhang, *Chem. Eng. J.*, 2010, **158**, 148–153.
- 50 B. Zhou, X. Zhao, H. Liu, J. Qu and C. P. Huang, *Appl. Catal., B*, 2010, **99**, 214–221.
- 51 J. Wang, Y. Xia, H. Zhao, G. Wang, L. Xiang, J. Xu and S. Komarneni, *Appl. Catal., B*, 2017, **206**, 406–416.
- 52 Y. Zhou, J. Jiang, Y. Gao, J. Ma, S. Y. Pang, J. Li, X. T. Lu and L. P. Yuan, *Environ. Sci. Technol.*, 2015, **49**, 12941–12950.
- 53 G. Fang, J. Gao, D. D. Dionysiou, C. Liu and D. Zhou, *Environ. Sci. Technol.*, 2013, **47**, 4605–4611.
- 54 B. Z. Zhu, H. T. Zhao, B. Kalyanaraman and B. Frei, *Free Radic. Biol. Med.*, 2002, **32**, 465–473.
- 55 Y. Y. Chen, Y. L. Ma, J. Yang, L. Q. Wang, J. M. Lv and C. J. Ren, *Chem. Eng. J.*, 2017, **307**, 15–23.
- 56 L. C. A. Oliveira, M. Gonçalves, M. C. Guerreiro, T. C. Ramalho, J. D. Fabris, M. C. Pereira and K. Sapag, *Appl. Catal., A*, 2007, **316**, 117–124.
- 57 H. A. Bicalho, J. L. Lopez, I. Binatti, P. F. R. Batista, J. D. Ardisson, R. R. Resende and E. Lorençon, *Mol. Catal.*, 2017, **435**, 156–165.
- 58 S. Xia, L. Zhang, G. Pan, P. Qian and Z. Ni, *Phys. Chem. Chem. Phys.*, 2015, **17**, 5345–5351.
- 59 M. A. Rauf, M. A. Meetani, A. Khaleel and A. Ahmed, *Chem. Eng. J.*, 2010, **157**, 373–378.
- 60 A. Houas, H. Lachheb, M. Ksibi, E. Elaloui, C. Guillard and J.-M. Herrmann, *Appl. Catal., B*, 2001, **31**, 145–157.
- 61 H. Huang, D. Y. C. Leung, P. C. W. Kwong, J. Xiong and L. Zhang, *Catal. Today*, 2013, **201**, 189–194.
- 62 A. Xu, X. Li, H. Xiong and G. Yin, *Chemosphere*, 2011, **82**, 1190–1195.
- 63 P. V. Bakre, P. S. Volvoikar, A. A. Vernekar and S. G. Tilve, *J. Colloid Interface Sci.*, 2016, **474**, 58–67.
- 64 K. Yu, S. Yang, C. Liu, H. Chen, H. Li, C. Sun and S. A. Boyd, *Environ. Sci. Technol.*, 2012, **46**, 7318–7326.
- 65 Q. Wang, S. L. Tian and P. Ning, *Ind. Eng. Chem. Res.*, 2014, **53**, 643–649.
- 66 J. Hu, P. Zhang, W. An, L. Liu, Y. Liang and W. Cui, *Appl. Catal., B*, 2019, **245**, 130–142.
- 67 X. Qian, Y. Wu, M. Kan, M. Fang, D. Yue, J. Zeng and Y. Zhao, *Appl. Catal., B*, 2018, **237**, 513–520.