

Supporting Information

Separation of Saturated Fatty Acids and Fatty Acid Methyl Esters with Epoxy Nanofiltration  
Membranes

Chad M. Gilmer, Christina Zvokel, Alexandra Vick and Ned B. Bowden

Department of Chemistry

*University of Iowa, Iowa City, IA, 52242*

[ned-bowden@uiowa.edu](mailto:ned-bowden@uiowa.edu)

## Table of Contents

	Page
Permeation of fatty acids through an epoxy membrane in a diffusion apparatus.	S-3-5
Permeation of fatty acid methyl esters through an epoxy membrane in a diffusion apparatus.	S-5-6
$^1\text{H}$ NMR and $^{13}\text{C}$ NMR spectrums of methyl undecylenate.	S-6-7
AFM images of a spin-coated epoxy membrane	S-7-8
Permeation of FAMES through membranes A-2 and A-2 $^{13}\text{C}_3$ in a pressure apparatus.	S-8-9
Permeation of $\text{C}_{10}$ - $\text{C}_{18}$ even chain length FAMES through membrane A-2 in a pressure apparatus.	S-10

**Permeation of fatty acids through an epoxy membrane in a diffusion apparatus.**



**Fig S1.** Diffusion apparatus used to monitor the flux of FAs and FAMES through the epoxy membrane.

**Table S1.** Initial screening of the permeation of model fatty acids through epoxy membranes.

Molecules	Membrane	Relative Flux	Normalized Flux (mol/cm <sup>2</sup> *h) <sup>a</sup>
Butyric Acid	A-1	5.84	2.83 x 10 <sup>-6</sup>
Undecylenic Acid		1.75	8.49 x 10 <sup>-7</sup>
Stearic Acid		1	4.85 x 10 <sup>-7</sup>
Butyric Acid	A-2	7.02	9.90 x 10 <sup>-7</sup>
Undecylenic Acid		3.01	4.24 x 10 <sup>-7</sup>
Stearic Acid		1.00	1.41 x 10 <sup>-7</sup>
Butyric Acid	A-3	21.4	4.24 x 10 <sup>-7</sup>
Undecylenic Acid		4.29	8.49 x 10 <sup>-8</sup>
Stearic Acid		1.00	1.98 x 10 <sup>-8</sup>

<sup>a</sup>All flux values carry a ± 4.24% relative error.

**Table S2.** Permeation of model fatty acids through epoxy membranes fabricated with epoxides 1 and 3.

Molecule	Membrane	Relative Flux	Normalized Flux (mol/cm <sup>2</sup> *h) <sup>a</sup>
Butyric acid	A-1 <sup>3</sup> 3 <sup>1</sup>	7.97	1.41 x 10 <sup>-6</sup>
Undecylenic acid		3.20	5.66 x 10 <sup>-7</sup>
Stearic acid		1.00	1.77 x 10 <sup>-7</sup>
Butyric acid	A-1 <sup>1</sup> 3 <sup>1</sup>	16.6	1.41 x 10 <sup>-6</sup>
Undecylenic acid		4.99	4.24 x 10 <sup>-7</sup>
Stearic acid		1.00	8.49 x 10 <sup>-8</sup>
Butyric acid	A-1 <sup>1</sup> 3 <sup>3</sup>	22.5	8.49 x 10 <sup>-7</sup>
Undecylenic acid		7.51	2.83 x 10 <sup>-7</sup>
Stearic acid		1.00	3.77 x 10 <sup>-8</sup>

<sup>a</sup>All flux values carry a ± 4.24% relative error.

**Table S3.** Permeation of model fatty acids through epoxy membranes fabricated with epoxides 2 and 3.

Molecule	Membrane	Relative Flux	Normalized Flux (mol/cm <sup>2</sup> *h) <sup>a</sup>
Butyric acid	A-2 <sup>3</sup> 3 <sup>1</sup>	30.0	8.49 x 10 <sup>-7</sup>
Undecylenic acid		4.98	1.41 x 10 <sup>-7</sup>
Stearic acid		1.00	2.83 x 10 <sup>-8</sup>
Butyric acid	A-2 <sup>1</sup> 3 <sup>1</sup>	20.0	8.49 x 10 <sup>-7</sup>
Undecylenic acid		3.33	1.41 x 10 <sup>-7</sup>
Stearic acid		1.00	4.24 x 10 <sup>-8</sup>
Butyric acid	A-2 <sup>1</sup> 3 <sup>3</sup>	60.2	8.49 x 10 <sup>-7</sup>
Undecylenic acid		8.01	1.13 x 10 <sup>-7</sup>
Stearic acid		1.00	1.41 x 10 <sup>-8</sup>

<sup>a</sup>All flux values carry a ± 4.24% relative error.

**Table S4.** Permeation of model fatty acids through epoxy membranes fabricated with epoxides 1 and 2.

Molecule	Membrane	Relative Flux	Normalized Flux (mol/cm <sup>2</sup> *h) <sup>a</sup>
Butyric acid	A-1 <sup>1</sup> 2 <sup>3</sup>	6.67	2.83 x 10 <sup>-6</sup>
Undecylenic acid		3.00	1.27 x 10 <sup>-6</sup>
Stearic acid		1.00	4.24 x 10 <sup>-7</sup>
Butyric acid	A-1 <sup>1</sup> 2 <sup>1</sup>	4.99	4.24 x 10 <sup>-6</sup>
Undecylenic acid		1.67	1.41 x 10 <sup>-6</sup>
Stearic acid		1.00	8.49 x 10 <sup>-7</sup>
Butyric acid	A-1 <sup>3</sup> 2 <sup>1</sup>	6.67	3.77 x 10 <sup>-6</sup>
Undecylenic acid		3.00	1.70 x 10 <sup>-6</sup>
Stearic acid		1.00	5.66 x 10 <sup>-7</sup>

<sup>a</sup>All flux values carry a ± 4.24% relative error.

**Permeation of fatty acid methyl esters (FAMES) through a membrane in a diffusion apparatus.**

**Table S5.** Permeation of saturated FAMES through membrane A-2<sup>1</sup>3<sup>3</sup>


Molecule	Relative Flux	Normalized Flux (mol/cm <sup>2</sup> *h) <sup>a</sup>
Methyl butyrate (C <sub>4</sub> )	100	9.90 x 10 <sup>-8</sup>
Methyl hexanoate (C <sub>6</sub> )	57.1	5.66 x 10 <sup>-8</sup>
Methyl octanoate (C <sub>8</sub> )	28.6	2.83 x 10 <sup>-8</sup>
Methyl decanoate (C <sub>10</sub> )	14.3	1.41 x 10 <sup>-8</sup>
Methyl laurate (C <sub>12</sub> )	8.58	8.49 x 10 <sup>-9</sup>
Methyl myristate (C <sub>14</sub> )	4.28	4.24 x 10 <sup>-9</sup>
Methyl palmitate (C <sub>16</sub> )	2.86	2.83 x 10 <sup>-9</sup>
Methyl stearate (C <sub>18</sub> )	1.00	9.90 x 10 <sup>-10</sup>


<sup>a</sup>All flux values carry a ± 4.24% relative error.

**Table S6.** Permeation of saturated FAMES through membrane A-1<sup>13</sup>

Molecule	Relative Flux	Normalized Flux (mol/cm <sup>2</sup> *h) <sup>a</sup>
Methyl butyrate (C <sub>4</sub> )	49.8	1.41 x 10 <sup>-7</sup>
Methyl hexanoate (C <sub>6</sub> )	28.3	8.49 x 10 <sup>-8</sup>
Methyl octanoate (C <sub>8</sub> )	18.9	5.66 x 10 <sup>-8</sup>
Methyl decanoate (C <sub>10</sub> )	10.0	2.83 x 10 <sup>-8</sup>
Methyl laurate (C <sub>12</sub> )	4.70	1.41 x 10 <sup>-8</sup>
Methyl myristate (C <sub>14</sub> )	3.50	9.90 x 10 <sup>-9</sup>
Methyl palmitate (C <sub>16</sub> )	1.89	5.66 x 10 <sup>-9</sup>
Methyl stearate (C <sub>18</sub> )	1.00	2.83 x 10 <sup>-9</sup>


<sup>a</sup>All flux values carry a ± 4.24% relative error.

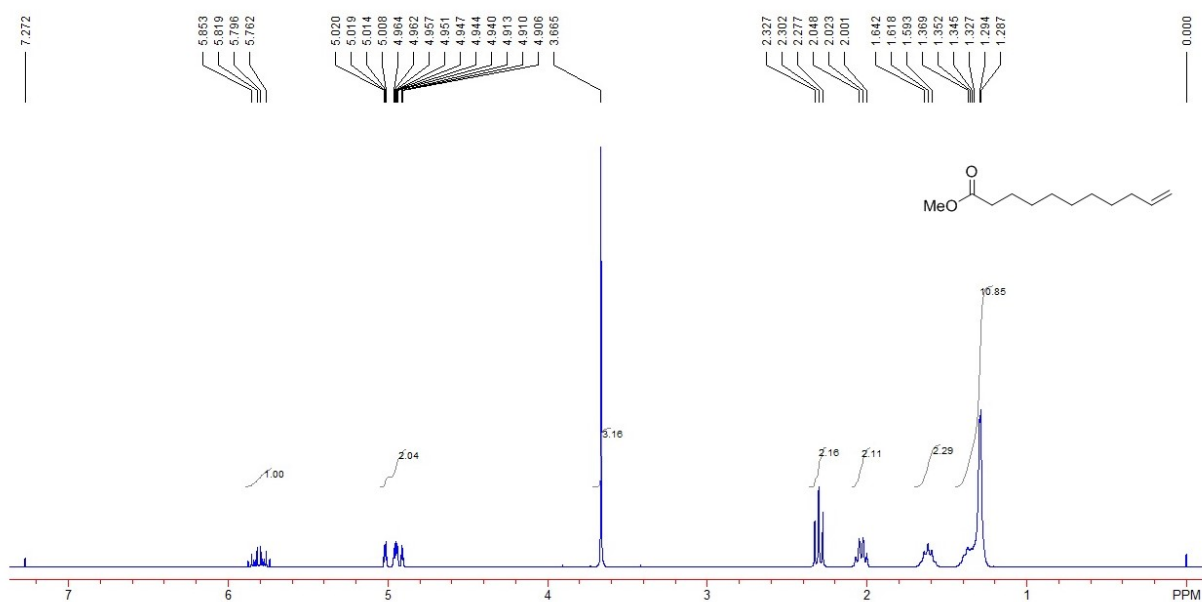**<sup>1</sup>H NMR and <sup>13</sup>C NMR spectrums of methyl undecylenate.****Figure S2.** <sup>1</sup>H NMR spectrum of methyl undecylenate in CDCl<sub>3</sub>.

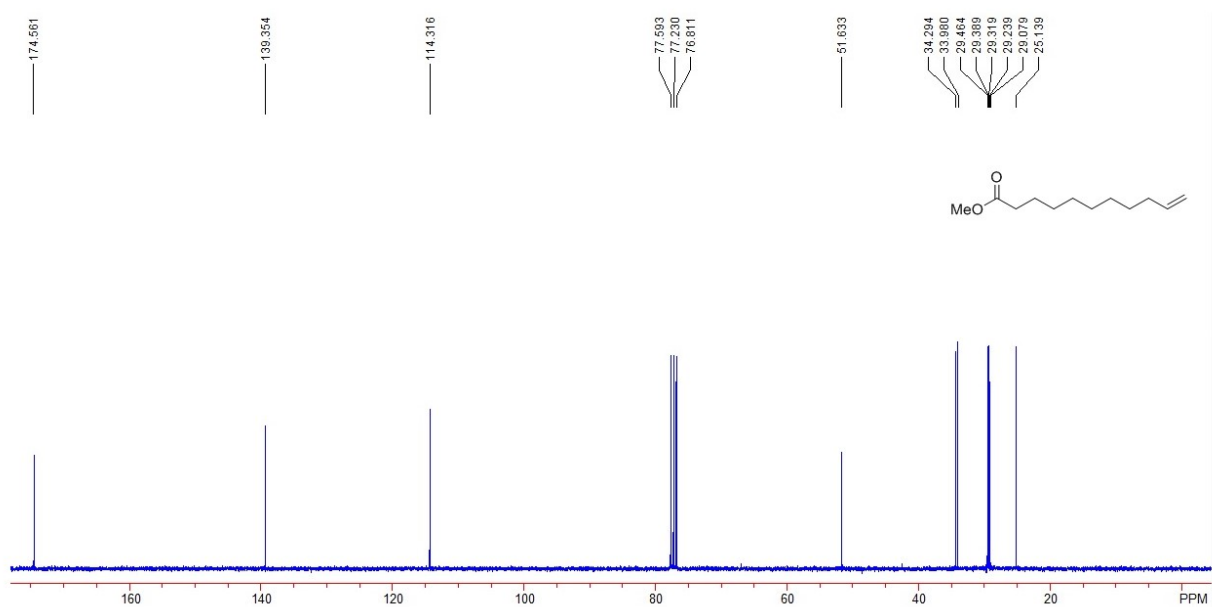


**Figure S3.**  $^{13}\text{C}$  NMR spectrum of methyl undecylenate in  $\text{CDCl}_3$ .

**AFM images of spin-coated epoxy membrane A-2.**

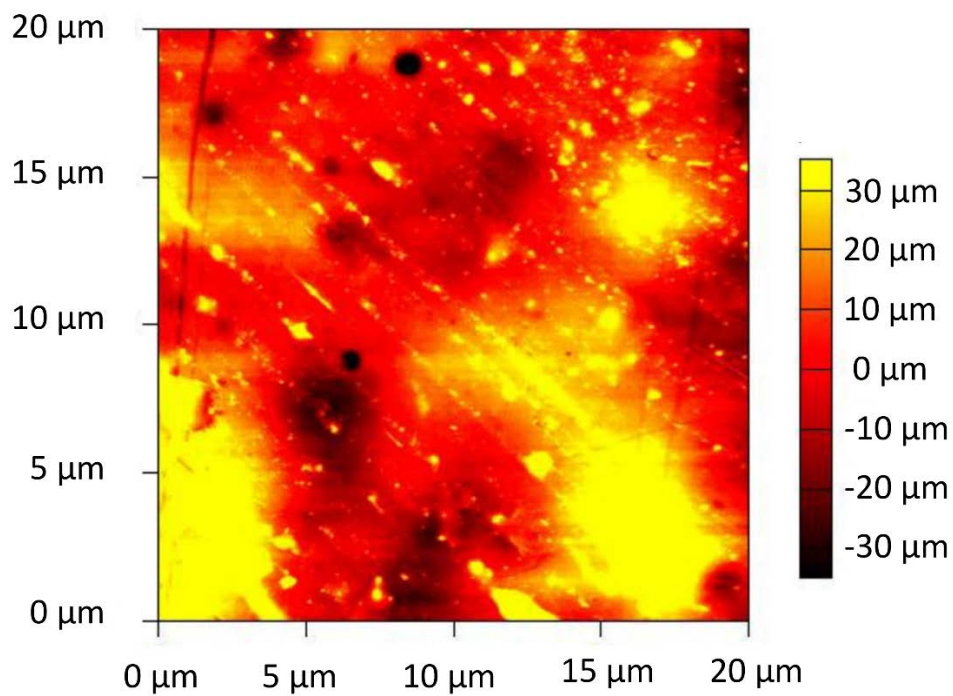


**Figure S4.** 2D AFM image showing the changes in height on the surface of a spin-coated epoxy membrane A-2.

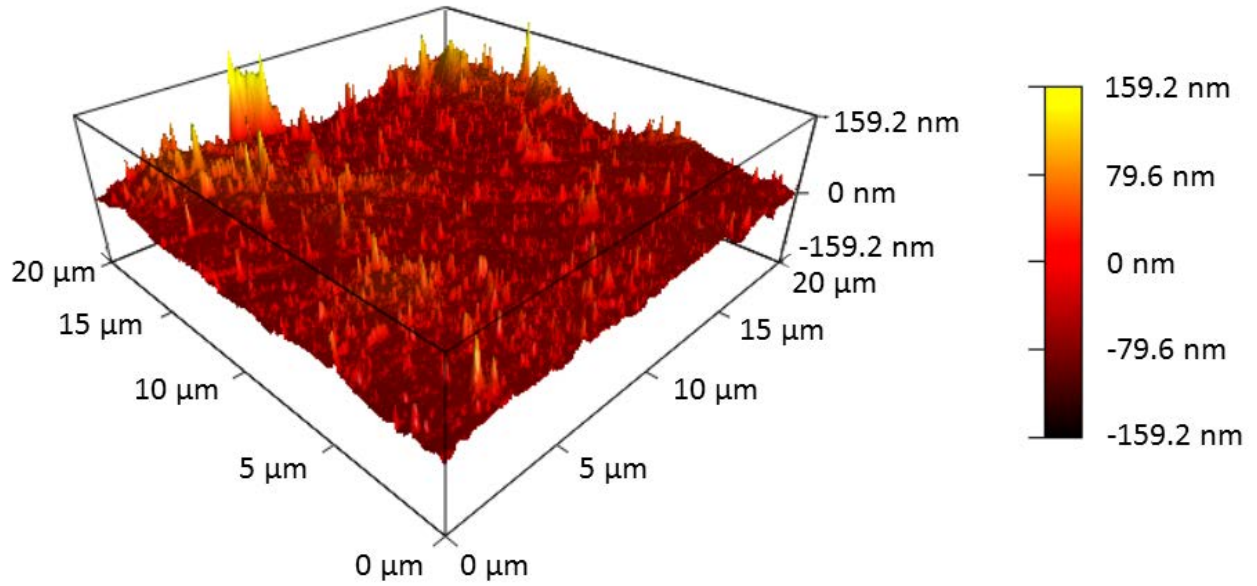

**Figure S5.** 3D AFM image showing the changes in height on the surface of a spin-coated epoxy membrane.

**Permeation of methyl undecylenate and methyl stearate through membrane A-2 in a pressure apparatus.**

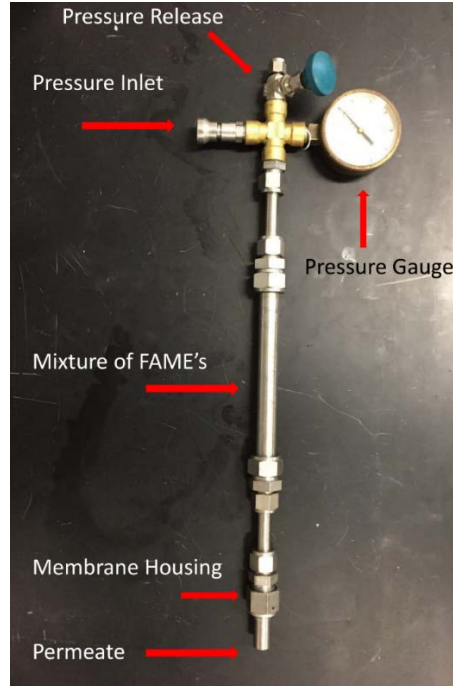

**Figure S6.** Dead end-filtration apparatus for high pressure experiments



**Table S7.** Composition of FAMEs collected in the pressure experiment with membrane A-2.

	Mass of FAMEs (mg)	Methyl Undecylenate (mol%)	Methyl Stearate (mol %)
Initial <sup>a</sup>	1,860	49.9	50.1
Fraction 1	38.0	67.9	32.1
Fraction 2	42.3	68.5	31.5
Fraction 3	44.3	67.7	32.3
Fraction 4	85.1	70.0	30.0
Fraction 5 <sup>b</sup>	60.7	62.2	37.8
Total Permeate	270	67.4	32.6
Retention	1,480	45.5	54.5

<sup>a</sup>Initial composition was determined by removing a 1 mL sample of the initial mixture and analyzing via <sup>1</sup>H NMR spectroscopy.

<sup>b</sup>Fraction 5 is the sample that was on the permeate side of the dead-end filtration and did not go into the vial. This sample was collected by washing the end of the metal apparatus with DCM and removing DCM to obtain the FAMEs.

**Table S8.** Composition of FAME's collected in the pressure experiment with membrane A-2<sup>133</sup>.

	Mass of FAME's and FAEE (mg)	Methyl Hexanoate (mol%)	Methyl Undecylenate (mol%)	Ethyl Stearate <sup>d</sup> (mol%)
Initial <sup>a</sup>	2,380	32.8	33.1	34.1
Fraction 1	12.0	17.7 <sup>c</sup>	62.1	20.2
Fraction 2 <sup>b</sup>	53.6	30.6 <sup>c</sup>	52.5	16.8
Retention	2,110	32.3	32.2	35.4

<sup>a</sup>Initial composition was determined by removing a 1 mL sample of the initial mixture and analyzing via <sup>1</sup>H NMR spectroscopy.

<sup>b</sup>Fraction 2 is the sample that was on the permeate side of the dead-end filtration and did not go into the vial. This sample was collected by washing the end of the metal apparatus with DCM and removing DCM to obtain the FAMEs.

<sup>c</sup>Due to the low boiling point of methyl hexanoate, it had evaporated from the permeate side before analysis could be completed.

<sup>d</sup>Ethyl stearate was used in this experiment because it has a unique peak in the <sup>1</sup>H NMR spectrum that so it can be distinguished from the other two FAMEs being used.

**Permeation of a multicomponent mixture of FAMES through epoxy membrane A-2 in a pressure apparatus.**

**Table S9.** Composition of FAMES collected in the pressure experiment with membrane A-2.

	Mass of FAMES (mg)	Methyl Decanoate (mol%)	Methyl Laurate (mol %)	Methyl Myristate (mol%)	Methyl Palmitate (mol%)	Methyl Stearate (mol%)
Initial	4,510	23.2	20.6	19.7	19.6	16.8
Fraction 1	46.1	31.0	21.5	18.9	15.5	13.0
Fraction 2	10.2	31.8	21.6	17.6	16.3	12.7
Fraction 3	53.7	31.1	23.2	18.5	15.2	12.0
Fraction 4	91.8	30.9	24.1	18.5	15.4	11.0
Fraction 5 <sup>b</sup>	85.5	27.7	24.9	19.0	16.5	11.9
Total Permeate	287	30.3	23.4	18.6	15.8	11.9
Retention	3,920	22.1	22.0	19.7	20.1	16.1

<sup>a</sup> Initial composition was determined by removing a 1 mL sample of the initial mixture and analyzing via gas chromatography-mass spectrometry (GC-MS).

<sup>b</sup>Fraction 5 is the sample that was on the permeate side of the dead-end filtration and did not go into the vial. This sample was collected by washing the end of the metal apparatus with DCM and removing DCM to obtain the FAMES.